INCH-POUND

A-A-52408A
14 April 2023
SUPERSEDING
A-A-52408
31 August 1993

COMMERCIAL ITEM DESCRIPTION

PRESERVATIVE COATING, RUBBER: FOR RUBBER SURFACES

The General Services Administration has authorized the use of this commercial item description by all federal agencies as a replacement for MIL-P-11520F, which is cancelled.

1. SCOPE. This commercial item description (CID) covers preservative coating for the protection of natural or synthetic rubber items such as tires, track pads, bogey wheels, gaskets, hoses and others. Its purpose is to eliminate deterioration due to oxidation, ultraviolet light and ozone. The material can be used where solvent vapor is not a hazard. The preservative is suitable where storage temperatures may be below 32°F. It is intended for spray, brush or dip application. The preservative coating is also referred to herein as "preservative."

2. SALIENT CHARACTERISTICS.

2.1 Materials. The preservative shall conform to the physical properties and performance requirements specified herein. The use of recovered material made in compliance with regulatory requirements is acceptable providing that all requirements of this CID are met (see section 3, titled Regulatory Requirements). Hazardous materials shall be handled in accordance with 29 CFR Chapter XVII.

2.2 Toxicity. The preservative shall contain no substances of known toxicity, and shall conform to rule 442 of the South Coast Air Quality Management District (see Salient Characteristics (SC)).

2.3 Homogeneity. The preservative shall remain in a completely homogenous state. The homogeneity shall be verified by visual examination of container contents upon opening an as received, non-agitated container for separation of ingredients.

Beneficial comments, recommendations, additions, deletions, clarifications, and any other data that may improve this document should be sent to U.S. Army Ground Vehicle Systems Center, ATTN: FCDD-GVS-SAT, MS #268, 6501 E. 11 Mile Road, Detroit Arsenal, MI 48397-5000 or emailed to usarmy.detroit.devcom-gvsc.mbx.standardization@army.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST online database at https://assist.dla.mil/.

FSC 8030

Distribution Statement A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:08Z
Check the source to verify that this is the current version before use.

2.4 Viscosity. The viscosity shall be such that the preservative shall pass through a number 4 Ford cup in not more than 60 seconds when tested in accordance with American Society for Testing and Materials (ASTM) D1200.

2.5 Dry time. Applied preservative shall be dry to the touch in no more than 60 minutes; when touched with clean white laboratory filter paper for no less than 5 seconds. The paper shall show no indication of wetting or discoloration.

2.6 Accelerated storage. The preservative shall be free from gelation, hard caking, separation, or other visible signs of deterioration or nonconformance after storage for 28 days in typical storage containers at both 120° ± 5°F and 20° ± 5°F. The preservative shall then conform to paragraph 2.2 through 2.5.

2.7 Discoloration. The discoloration of the natural or synthetic rubber products treated with the preservative shall be kept to a minimum.

2.8 Ozone resistance. Five preserved test specimens in accordance with ASTM D1149 Method B, Procedure B1 shall be free of cracks and crazing when examined under 7-power magnification after 25% elongation and exposure to an air and ozone mixture of 50 ± 5 parts ozone per one hundred million (pphm) of air by volume for 200 ± 1 hours, or 100 ± 10 pphm of ozone for 100 ± 1 hours, at 104 ± 2°F in accordance with ASTM D1149 Method B, Procedure B1.

2.9 Penetration and retention of preservative. The average minimum increase in weight for five preserved test specimens shall be at least 2% of the weight of the five test specimens prior to preservation, when weighed 24 ± 1 hour after preservation to the nearest 0.0001 gram. Test specimens shall be 3 x 1 inches.

2.10 Unit container sizes. The preservative shall be available in the following unit container sizes: pints, gallons, 5 gallon pails, and 55 gallon drums (see paragraph 6.2 and 6.3).

2.11 Material safety data sheet (MSDS). A MSDS shall be prepared in accordance with the latest revision of FED-STD-313 (see paragraphs 6.2 and 6.5).

2.12 Identification and markings. Each unit container (see paragraph 2.10) shall be marked in accordance with MIL-STD-129.

2.13 Test specimens. Test specimens shall conform to the composition shown in Table I. Rubber test specimens shall be cured into sheets per ASTM D3182 under a minimum pressure of 500 psi at a temperature of 307°F for 30 minutes. Unless otherwise specified (see paragraph 6.2), test specimens shall be thoroughly cleaned of all contaminants and preservative applied by hand brushing until completely treated or saturated.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:08Z
Check the source to verify that this is the current version before use.

Table I. Rubber test specimen composition.

Material	Parts by weight
SBR 1500	100.0
HAF Type Carbon Black (N330)	50.0
Zinc Oxide	3.0
Stearic Acid	1.5
Highly Aromatic Process Oil	7.0
Akrowax 5084 /1	1.5
Santoflex 6PPD /2	3.5
Sulfur	2.0
Tertiary-Butyl Benzothiazole Sulfenamide (TBBS)	1.25

/1 Or equivalent microcrystalline paraffin wax
/2 Or chemical abstracts service (CAS) equivalent

3. REGULATORY REQUIREMENTS. The offeror/contractor is encouraged to use recovered materials to the maximum extent practicable, in accordance with Public Law 94-580.

4. PRODUCT CONFORMANCE PROVISIONS

4.1 Responsibility for inspection. The contractor is responsible for the performance of all inspections (examinations and tests).

4.2 Product conformance. The products provided shall meet the salient characteristics of this commercial item description, conform to the producer's own drawings, specifications, standards, and quality assurance practices, and be the same product offered for sale in the commercial marketplace. The government reserves the right to require proof of such conformance.

5. PACKAGING. Preservation, packing, and marking shall be as specified in the contract or order (see paragraph 6.2).

5.1 Additional labeling and marking. When applicable, all unit containers shall be marked with necessary personnel hazard precautions and necessary equipment to be used, e.g., breathing apparatus, rubber gloves. If special spraying equipment is required to apply the preservative, it shall be marked on all unit containers. Hazardous materials shall be marked in accordance with MIL-STD-129.

6. NOTES.

6.1. Source of documents.

6.1.1 Government specifications and standards. Copies of MIL-STD-129, Marking for Shipment and Storage; and FED-STD-313, Material Safety Data, Transportation Data and Disposal Data for Hazardous Materials Furnished to Government Activities, are available from https://quicksearch.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:08Z
Check the source to verify that this is the current version before use.


6.1.2 Other Government documents, drawings and publications. Copies of Title 29, Chapter XVII, "Occupational Safety and Health Administration," are available from https://www.ecfr.gov, copies of "Rule 442 of the South Coast Air Quality Management District" are available from http://www.aqmd.gov, while copies of "Public Law 94-580" are available from https://www.govinfo.gov.

6.1.3 Non-government publications. Copies of ASTM D1149 "Standard Test Methods for Rubber Deterioration - Cracking in an Ozone Controlled Environment," ASTM D1200 "Standard Test Method for Viscosity by Ford Viscosity Cup," and ASTM D3182 "Standard Practice for Rubber - Materials, Equipment, and Procedures for Mixing Standard Compounds and Preparing Standard Vulcanized Sheets" are available from https://www.astm.org.

6.2 Ordering data. Acquisition documents should specify the following:

a. Title, number and date of this commercial item description
b. Issue of ASSIST to be cited in the solicitation, and if required, the specific issue of individual documents referenced.
c. Unit container size and PIN
d. Identify activities requiring copies of completed MSDS and specify when the MSDS will be inspected.
e. Whether test specimens should not be cleaned.
f. Whether the application of preservative on test specimens is other than as specified.
g. Packaging, packing and marking required.

6.3 Part or identification number (PIN). The PIN to be used for preservative acquired to this CID is as follows:

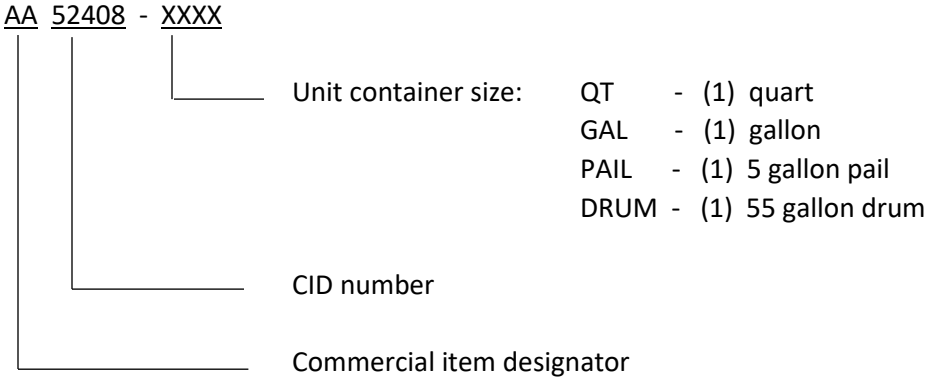

6.4 Cross-reference data. Preservative conforming to this CID is substitutable/interchangeable with preservative conforming to MIL-P-11520F.

6.5 MSDS. The contracting officer should identify those activities requiring copies of the completed MSDS prepared in accordance with FED-STD-313. Additional pertinent Government mailing addresses for submission of data are listed in paragraph 5.5 of FED-STD-313.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:08Z
Check the source to verify that this is the current version before use.

6.6 Changes from previous issue. The margins of this CID are marked with vertical lines to indicate where changes from the previous issues were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the previous issue.

MILITARY INTERESTS:

CIVIL AGENCY COORDINATION ACTIVITY:
GSA - FSS

Custodian:
Army - AT

Preparing Activity:
Army - AT

(Project 8030-2022-009)

Review Activities:
Army - AR, CR4, GL, MR, SM
Navy - AS, MC, OS, SH

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:08Z
Check the source to verify that this is the current version before use.