INCH-POUND

A-A-50370
31 May 89

COMMERCIAL ITEM DESCRIPTION

GLOVES, CLOTH, VINYL DIPPED

This Commercial Item Description is authorized for use in preference to MIL-G-82253.

1. SALIENT CHARACTERISTICS

1.1 Design and construction. The gloves shall be manufactured from jersey or interlock knit fabric, 100% cotton, back side lightly napped, natural color, constructed from a two piece cut and sew process, coated with a two part poly vinyl dip. All seams shall be to the inside of the glove. Seam allowances shall be 1/8 inch minimum. The base dip shall impart a smooth finish. The final dip shall contain particles of powdered vinyl resin and shall impart a roughened texture. The color of the finished glove shall be black.

1.1.1 Type I. The Type I glove has a grown-on gauntlet. The base dip shall impart a smooth finish the complete length of the glove. The final dip shall extend up from the fingertips to 1 1/2 to 2 1/2 inches above thumb crotch.

1.1.2 Type II. The Type II glove has a wristlet, made of a tubular knit. The base dip shall impart a smooth finish to approximately 1 1/2 inches above wristlet seam. The final dip shall extend up from the fingertips to 1 1/2 to 2 1/2 inches above thumb crotch.

1.2 Sizes.

1.2.1 Type I. Medium and large.

1.2.2 Type II. One size only.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Officer in Charge, Navy Clothing and Textile Research Facility, 21 Strathmore Road, Natick, MA 01760-2490 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

ASMC N/A FSC 8415

DISTRIBUTION STATEMENT A. Approved for public release, distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026l0-26T08:41Z
Check the source to verify that this is the currentversion before use.

1.3 Measurements. The gloves shall be of the following minimum dimensions in inches:

	Type I		Type II
	Medium	Large	
A. Overall length	12	12	10 1/4
B. Palm width	4 3/4	5 1/4	5
C. Width of opening	6	6	-
D. Width of wristlet	-	-	3 1/2
E. Length of wristlet	-	-	2 1/2

Measurements are taken at the following locations (see Figures 1 and 2):
A. Overall length - Top edge to tip of second finger.
B. Palm width - At thumb crotch from folded edge to folded edge.
C. Width of opening - Across the top edge, folded edge to folded edge.
D. Width of wristlet - Approximately 1 inch from top edge, folded edge to folded edge.
E. Length of wristlet - Top edge of wristlet to bottom edge at seam.

1.4 Patterns. The patterns for cutting the gloves shall be furnished by the contractor, and shall be of the proper proportions to provide gloves conforming to the finished measurements specified in 1.3.

1.5 Pairing. The gloves shall be paired by any commercially accepted method.

1.6 Labeling.

1.6.1 Contract #, NSN, and size label. In addition to any commercial markings, each glove shall be legibly stamped with the size (Type I only), contract name and contract number.

1.6.2 Instruction label. The instruction label shall contain the information listed below, positioned on the outside back of the right hand glove.

DO NOT USE FOR ELECTRICAL WORK, CBR PROTECTION,
OR FOR ROCKET FUEL OPERATIONS

1.6.3 Instruction sheet. A white paper instruction sheet containing the information listed below shall be inserted inside one glove of each pair:

GLOVES, CLOTH, VINYL DIPPED

This general purpose glove is intended for wear under cold/wet operating conditions or where protection from solvents, jet fuels, oils, low concentrations of acids and other chemicals is required. It is not to be used for electrical work, CBR protection, or for rocket fuel operations. For added protection against cold/wet conditions, use a wool liner insert. To prolong life of the gloves, rinse with water or wash with soap solution, especially after contact with chemical or oils.

Source: https://assist.dla.mil -- Downloaded: 202610-26T08:41Z
Check the source to verify that this is the current version before use.

1.7 Approved Styles. The following styles meet the requirements of this description:

	Type I	Type II
Edmont	Style 12-212	Style 12-202
Ansell		Style 1630

Other manufacturers may submit their styles to the procuring activity for evaluation by the Specification Preparing Activity and ultimate inclusion in this document if approved.

1.7 Workmanship. The gloves shall be uniform in quality and shall be free from irregularities or defects which adversely affect performance, reliability, or durability.

1.8 Product demonstration model. During the solicitation phase, interested firms (including the manufacturer of the above approved styles) shall provide the Procuring Agency with four product demonstration models (two pairs) of the item they propose to furnish for evaluation. Two samples shall be used for performance testing. The remaining two samples provided by the successful offerer shall be tagged and sealed. One shall be retained by the Procuring Agency and the other furnished the assigned Quality Assurance Representative for use as a reference in performing the examination in paragraph 2.2 and the scoring of defects in design, material and workmanship not otherwise classified herein.

2. QUALITY ASSURANCE

2.1 Certification. When requested by the Contracting Officer, the contractor shall certify, and maintain substantiating evidence, that the product offered meets the salient characteristics of this Commercial Item Description, and that the product conforms to the producer's own drawings, specifications, standards, and quality assurance practices. The Government reserves the right to require proof of such conformance prior to first delivery and thereafter as may be otherwise provided for under the provisions of the contract.

2.2 Examination of the fabric support shell. Examination of the completely assembled knit fabric support shells shall be made prior to dipping. The defects found shall be classified as below. The sample unit shall be one support shell. The lot size shall be expressed in units of one support shell. The inspection level shall be level II of MIL-STD-105. The acceptable quality level shall be 2.5 major defects and 6.5 (major and minor defects combined) defects per hundred units.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:41Z
Check the source to verify that this is the current version before use.

Defects	Classification Major	Minor
I. MATERIAL DEFECTS AND WORKMANSHIP DAMAGES		
A. Any hole, cut, tear, run, drop stitch, needle chew, misknit or mend	X	
B. Any loose knitting, causing sleaziness		X
C. Pulled or snagged yarn		X
D. Base fabric (interlock or jersey knit) not brushed or napped as specified	X	
II. CLEANNESS		
A. Thread ends not trimmed or loose threads not removed		X
B. Surplus seam allowance material not trimmed off, trimmed unevenly or trimmed to less than 1/8 inch in width		X
III. CUTTING		
A. Any part not cut in accordance with approved styles/product demonstration models	X	
VI. SEAMS AND STITCHING		
A. Seam puckered, twisted, pleated or any part of glove caught in an unrelated operation	X	
B. Any open seam, loose stitch tension or seam, stitch type and stitches/inch not in accordance with the approved style/product demonstration model		X

2.3 Examination of the end item. The gloves shall be inspected in accordance with MIL-STD-105. The defects found during the examination of the end item shall be classified as below. The applicable inspection levels and acceptable quality levels (AQL's) shall be as indicated in 2.3.1. The lot size shall be expressed in terms of one finished glove. The sample unit shall be one finished glove, and the selection shall be by pairs. Defects for pairing shall be classified as a single defect.

Source: https://assist.dla.mil -- Downloaded: 202610-26T08:41Z
Check the source to verify that this is the current version before use.

Defects	Classification Major	Minor
I. PAIRING		
A. Mispaired, e.g., two left or two right gloves	X	
II. CLEANNESS		
A. Any permanent spot or stain on outside		X
III. DESIGN AND ASSEMBLY		
A. Not cut or fabricated in accordance with the approved styles/product demonstration model	X	
IV. COATED FABRIC		
A. Any hole, cut, tear, abrasion, or area of no coating exposing base fabric	X	
B. Any evidence of delamination		X
C. Evidence of strike through of the coating on the inside of gloves affecting comfort or function		X
D. Any brittle area which when bent results in a crack	X	
E. Any area of excessive coating		X
F. Any pitted area		
1. Base fabric not exposed	X	
2. Base fabric exposed	X	
G. Rough final coat omitted	X	
H. Any tackiness; blister	X	
I. Any imbedded foreign matter:		
1. affecting serviceability; or when removed exposes base fabric or leaves hole	X	
2. affecting appearance		X
V. WORKMANSHIP		
A. Any evidence that seams in support shell were not properly aligned with those on dipping form		X

Source: https://assist.dla.mil -- Downloaded: 202640-26T08:41Z
Check the source to verify that this is the currentversion before use.

Defects	Classification Major	Minor
VI. LABEL (MARKING)		
A. Omitted, incorrect; incomplete or illegible	X	
VII. GENERAL		
A. Any defect not otherwise classified herein but at variance with the approved style/product demonstration model		X
VIII. DIMENSIONS		
A. Less than minimum specified	X	

2.3.1 Inspection levels and AQL's. The inspection levels and the acceptable quality levels (AQL's), expressed in defects per 100 units for visual and dimensional examination, shall be as follows:

	AQL's	Inspection level
Major	2.5	II
Total (Major and Minor combined)	6.5	II

2.4 Performance testing. Each lot of the end item shall be tested for fuel resistance and porosity. The sample unit shall be one pair of gloves. The lot size shall be expressed in units of one glove each, and the selection made in pairs. The inspection level shall be S-1. Any failure encountered in the porosity or fuel resistance test shall cause rejection of the lot.

2.4.1 Resistance to fuel. The coated fabric shall show no evidence of cracking, softening, flaking, or separation of coating from fabric after immersion in fuel. A 3X3 inches specimen cut from the rough portion of the glove shall be immersed in a solution of 70% isooctane and 30% toluol for 15 minutes. The specimen shall dry at room temperature for 4 hours. When dry, the specimen shall be folded in half and rolled with a roller of approximately 10 pounds in weight. The specimen shall be folded again in half, perpendicular to the direction of the first fold, and rolled again in the same manner. One determination shall be made per sample unit and the results reported as "pass" or "fail".

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:41Z
Check the source to verify that this is the current version before use.

2.4.2 Porosity. The porosity test apparatus shall be similar to that shown in Figure 3. The opening of the glove shall be pulled over the shank of the test apparatus and clamped firmly in place by tightening the ring against the base plate. Compressed air shall be fed into the glove in sufficient quantity to fill out the glove and to provide a slight additional pressure. The inflated glove shall be immersed in water for 1 minute observation of porosity as indicated by air bubbles. No visible bubbles shall be permiitted within the 1 minute period. One determination shall be made per sample and the results reported as "pass" or "fail".

3. PACKAGING, PACKING, AND MARKING

3.1 Packaging, packing and marking. Eight (8) pairs of gloves shall be bundled and securely tied. Forty-eight (48) pairs of gloves shall be packed in a fiberboard shipping container assembled and closed conforming to type CF, class domestic, variety DW, grade 200, size 2A of MIL-B-17757. The fiberboard for the box liner shall conform to type CF, class domestic of MIL-B-17757. Marking shall be in accordance with MIL-STD-129.

3.2 Palletization. Gloves packed as specified shall be palletized on a 4-way entry pallet in accordance with load type 1A of MIL-STD-147. Each prepared load shall be bonded in accordance with bonding means C, K, and L or O or P. Pallet pattern shall be in accordance with the appendix of MIL-STD-147.

The pallet shall be 4-way, Type IV; Type V, Class 1, Size 2; or Type VIII, fabricated from wood group I, II, III or IV, Grade A of NN-P-71, or 4-way Style 1, Size A, Type I, Class 1 fabricated from wood groups specified of MIL-P-15011. Interlocking of loads shall be effected by reversing the pattern of each course. If the container is of a size which does not conform to any of the patterns specified in MIL-STD-147, the pallet pattern used shall be approved by the contracting officer.

4. NOTES

4.1 Intended use. This Commercial Item Description covers vinyl dipped gloves to be used in handling low concentration of chemicals, in cold/wet weather, or during jet fueling operations.

4.2 Ordering data.

a. Title, number, and date of this document.
b. Types and sizes required (see 1.1 and 1.2)
c. When palletization is required (see 3.2).

Custodians:
Navy - NU
Air Firce - 99

Review Activities:
Navy - SH
Air Force - 11

User Activities:
Navy - YD, AS, MC, OS

Preparing Activity:
Navy - NU

Project Number:
8415-0709

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:41Z
Check the source to verify that this is the current version before use.

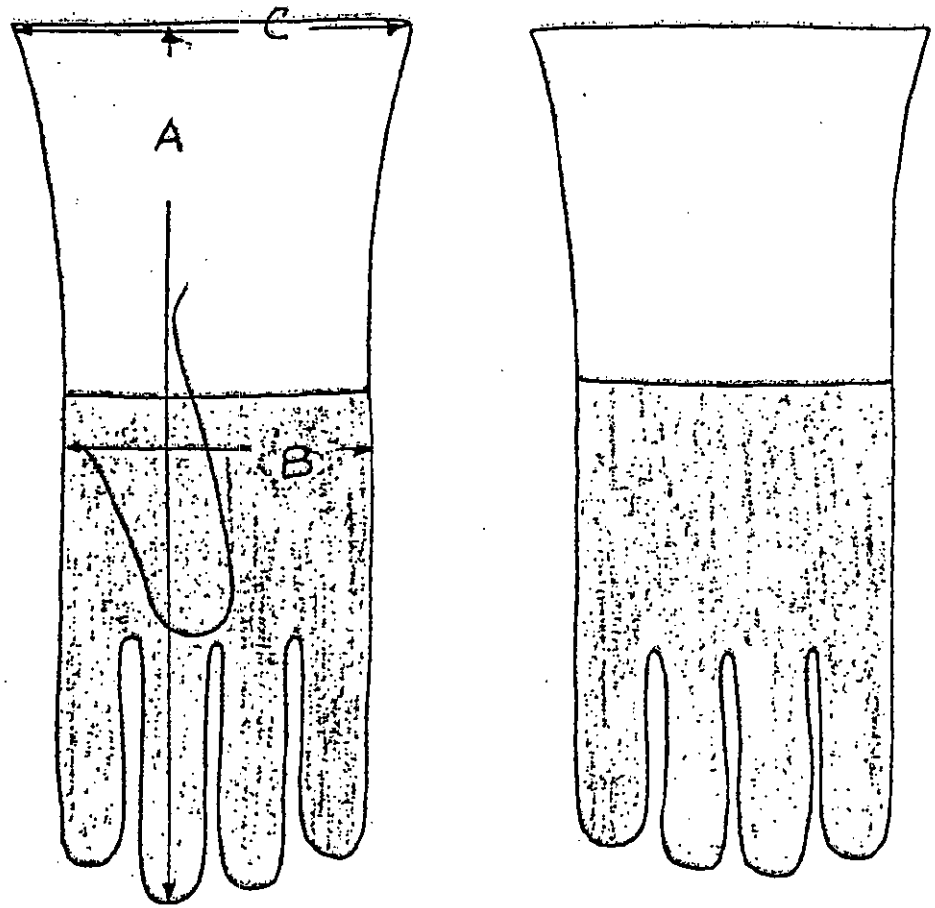


Figure 1 - GLOVES, CLOTH, VINYL DIPPED
TYPE I - GAUNTLET STYLE

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:41Z
Check the source to verify that this is the current version before use.

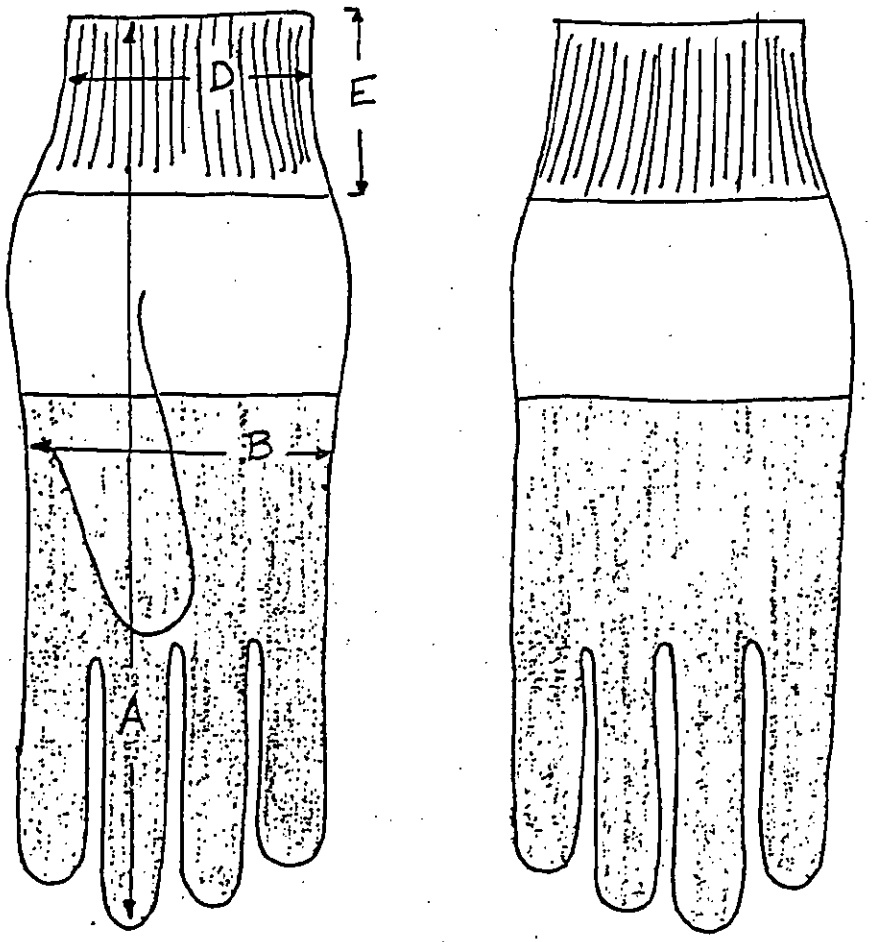


Figure 2 - GLOVES, CLOTH, VINYL DIPPED
TYPE II - WRISTLET STYLE

Source: https://assist.dla.mil -- Downloaded: 2026-04-26 08:41Z
Check the source to verify that this is the current version before use.

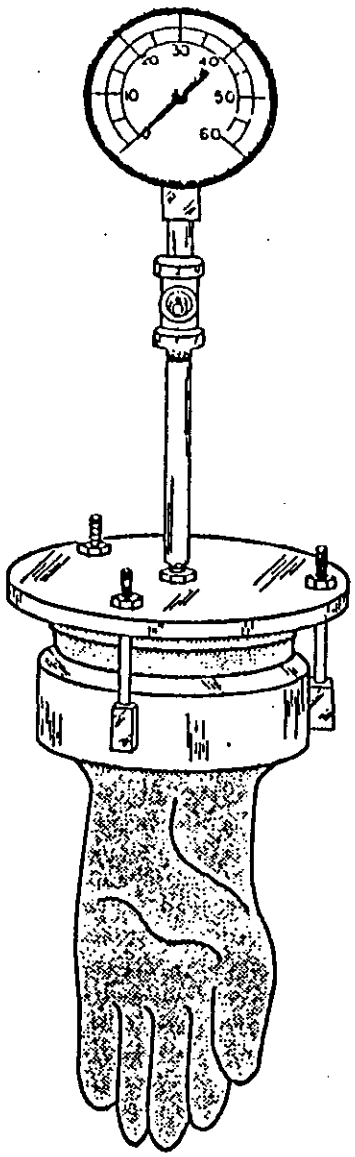


Figure 3 - APPARATUS FOR POROSITY TEST

☆U.S. GOVERNMENT PRINTING OFFICE: 1989 - 604-033/13375

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:41Z
Check the source to verify that this is the current version before use.