INCH-POUND
MIL-D-85306A(AS)
7 November 1991
SUPERSEDING
MIL-D-85306(AS)
29 June 1981

MILITARY SPECIFICATION

DELAY COMPOSITION, T-10

This specification is approved for use by the Naval Air Systems Command, Department of the Navy, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for the manufacture, acceptance, and delivery of one type of delay composition designated T-10 (see 6.1).

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATIONS

FEDERAL

PPP-B-601	Boxes, Wood, Cleated-Plywood
PPP-B-621	Boxes, Wood, Nailed and Lock-Corner
PPP-C-96	Cans, Metal, 28 Gauge and Lighter

Beneficial comments, (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commanding Officer, Naval Air Engineering Center, Systems Engineering and Standardization Department (SESD) Code 53, Lakehurst, NJ 08733-5100, by using the Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 1377

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

MILITARY

MIL-B-550	Barium Chromate
MIL-C-10464	Cans, Hermetic Sealing, Metal, Light Gage, Tear-Strip Type
MIL-P-22264	Powder, Ignition, Gasless, A-1A
MIL-P-46994	Pellets/Granules, Boron/Potassium Nitrate
MIL-B-51092	Boron, Amorphous, Powder
MIL-B-82647	Bag, Conductive Plastic, Heat-Sealable, Flexible

STANDARDS

MILITARY

MIL-STD-105	Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	Marking for Shipment and Storage
MIL-STD-1167	Ammunition Data Card
MIL-STD-1168	Ammunition Lot Numbering

(Unless otherwise indicated, copies of federal and military specifications, standards, and handbooks are available from the Standardization Documents Order Desk, Building 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues are those cited in the solicitation.

DRAWINGS

NAVAL SEA SYSTEMS COMMAND (CAGE Code 10001)

423038	Replacement Sample Powder Tank, Mk 1 and Mods
LD 480089	Test Element and Output Charge Holder
1826685	Delay Body
1826687	Test Element No. 3, Loading Procedures
1826740	Output Charge Holder, Loading Procedures

(Application for copies should be addressed to Commanding Officer, Naval Ordnance Station (Code 802), Louisville, KY 40214-5001.)

PUBLICATIONS

NAVAL AIR SYSTEMS COMMAND (CAGE Code 30003)

AD 1014	Operating Procedures for Pyrotechnic Delay Timing Apparatus

(Application for copies should be addressed to Commanding Officer, Naval Ordnance Station, Data Control Branch (Code 3720), Indian Head, MD 20640-5000.)

CODE OF FEDERAL REGULATIONS

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

(Application for copies should be addressed to the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402-0001.)

2.2 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the documents cited in the solicitation (see 6.2).

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

ASTM C516 Standard Specification for Vermiculite Loose Fill Thermal Insulation

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103-1187.)

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents. These documents also may be available in or through libraries or other informational services.

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Material. The material shall be a homogeneous mixture of boron and barium chromate.

3.1.1 Boron. The boron used in the T-10 delay composition shall conform to the requirements specified in MIL-B-51092.

3.1.2 Barium chromate. The barium chromate used in the T-10 delay composition shall conform to MIL-B-550, grade A.

3.2 Composition. The composition of the material shall consist of a mixture of boron and barium chromate in such ratio that the T-10 delay composition meets the requirements specified herein. Figure 1 establishes the approximate burntime for a given ratio of ingredients.

3.3 Burntime at room temperature. When tested as specified in 4.4.2, the average burntime shall be as specified by the acquiring activity (see 6.2).

3.4 Coefficient of variation at room temperature. When determined as specified in 4.4.2.4, the coefficient of variation of the burntime shall not exceed 5.0 percent.

3.5 Low temperature burntime. When tested as specified in 4.4.3, the average burntime shall not increase more than 25.0 percent.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

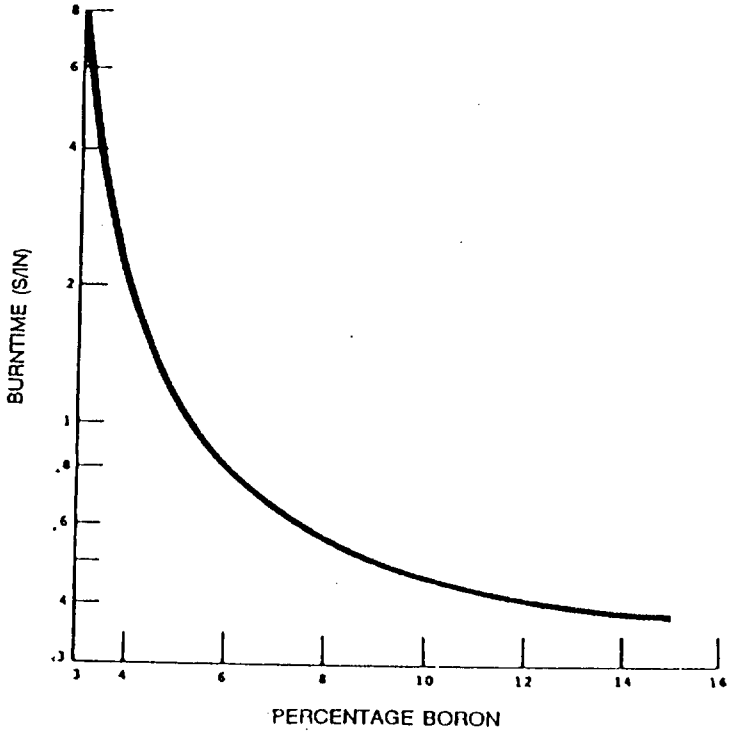


FIGURE 1. T-10 delay composition burning characteristics.

3.6 Coefficient of variation at low temperature. When determined as specified in 4.4.3, the coefficient of variation of the burntime shall not exceed 5.0 percent.

3.7 Burn effectiveness. When ignited by the ignition powder, tested as specified in 4.4.2 and 4.4.3, the delay column shall burn through.

3.8 Burntime after shipment or storage. The burntime, determined after shipment or storage of not less than 12 months, in accordance with 4.4.2.5, shall not differ by more than 3.0 percent from the 24 ± 2° C (75 ± 3.6° F) burntime determined at the time of original manufacture.

3.9 Alternate burntime after storage method. This requirement may be used in lieu of burntime after storage requirement in 3.8. Prior to production of any end-item lot using T-10 delay mix stored for not less than 12 months and regardless of age or previous testing of the delay mix, a preproduction sample of end-items shall be ballistically tested in accordance with the end-item specification and 4.4.2.6. Delay time requirements of the end-item shall be met at all specified temperatures in order for the delay mix to be accepted for use in a production lot. An end-item is defined as a complete explosive assembly representative of assemblies intended for delivery. Testing per this requirement shall not effect acceptance tests or requirements of the end-item lot and shall not commit the Government to acceptance of an end-item lot.

3.10 Toxicological product formulations. The material shall have no adverse effect on the health of personnel when used for its intended purpose in accordance with the Material Safety Data Sheets (MSDS). Questions pertinent to this effect shall be referred by the acquiring activity to the appropriate departmental medical service who will act as an advisor to the contracting agency.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

3.10.1 Material Safety Data Sheets (MSDS). The acquiring activity shall be provided an MSDS at the time of contract award. The MSDS shall be prepared in accordance with the requirements of 29 CFR 1910.1200(g), Hazard Communication, and included with each shipment. OSHA Form 174 MSDS or a more effective contractor developed MSDS format may be used.

3.11 Workmanship. The delay composition shall be a homogeneous powder and free from foreign matter.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in this specification where such inspections are deemed necessary to ensure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items shall meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of the manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to accept defective material.

4.1.2 Test inspection equipment and facilities. The manufacturer shall furnish and maintain all necessary test equipment facilities and personnel for performing all tests. The test equipment shall be of sufficient accuracy and quality to permit performance of the required tests.

4.1.3 Test conditions. Unless otherwise specified, all inspections shall be performed in accordance with the applicable paragraph herein.

4.2. Toxicological product formulations. The contractor shall have the toxicological product formulations and associated information available to the acquiring activity to evaluate the safety of material for the proposed use (see 3.10, 6.3, and 6.9).

4.3 Quality conformance inspection. The quality conformance inspection shall consist of the examination in 4.3.3 and the tests specified in table I. The tests shall be performed by the contractor or his representative in the presence of the Government inspector to ensure conformance to 3.3 through 3.7.

4.3.1 Lot. A lot of T-10 delay composition shall consist either of a manufacturer's batch which has been mixed as a unit from the ingredients or of a blend of one or more such batches (see 6.8).

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

TABLE I. Quality conformance inspection.

Inspection	Requirement paragraph	Test paragraph
Burntime at room temperature	3.3	4.4.2
Coefficient of variation at room temperature	3.4	4.4.2
Burntime at low temperature	3.5	4.4.3
Coefficient of variation at low temperature	3.6	4.4.3
Burn effectiveness	3.7	4.4.2 and 4.4.3
Burntime after shipment or storage	3.8	4.4.2.5
Workmanship	3.11	-

4.3.2 Sampling. Sampling of the T-10 delay composition for test purposes shall be done after the last mixing operation and screening of the dried powder. Each lot (see 4.3.1) to be tested shall be divided into 20 equal parts, and 20 delay bodies shall be loaded so that each delay body contains a representative sample from each of the 20 parts without duplication (see 4.4.2). A second representative pooled sample of the delay composition shall be selected and a sufficient quantity to load a minimum of 10 test elements according to 4.4.2.1 for the low temperature functioning test (4.4.3). All sampling before test loading or loading in delay assemblies shall be done in areas having relative humidity controlled below 60 percent. The samples shall be stored in hermetically sealed containers and correctly labeled to show the following information:

a. Name of item
b. Sample weight
c. Lot number of T-10 composition
d. Manufacturer
e. Date of manufacture

The lot shall be rejected if any specimen fails to meet the requirement specified in 3.7. If any specimen fails to meet the requirements specified in 3.3 through 3.6, the lot may be remixed and resubmitted for acceptance.

4.3.3 Packaging inspection. An examination shall be made to determine if the preservation, packing, and marking comply with the requirements of section 5 of this specification. The sample unit shall be one shipping container fully prepared for delivery. Each sample unit shall be examined for the defects listed in table II. The lot size shall be the number of shipping containers in the lot. The examination shall be in accordance with MIL-STD-105, inspection level S-2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

TABLE II. Packaging inspection.

Examination	Defect
Material	Not material required.
Construction	Not style, class, or type specified. Closure not as specified.
Marking	Warning labels or marking missing, omitted, illegible, incorrect, incomplete. Not in accordance with contract requirements.

4.4 Test procedures.

4.4.1 Ingredient testing. All ingredients shall be tested in accordance with the applicable specifications and in accordance with section 3.

4.4.2 Room-temperature functioning test. The test shall be conducted on the basis of each lot as specified in 4.3.1. The sample for the room temperature test shall consist of 20 test elements as specified in 4.4.2.1. The lot shall be divided into 20 equal parts, and 20 delay bodies shall be loaded so that each delay body contains a representative sample from each of the 20 parts without duplication.

4.4.2.1 Loading of the test element. The delay body shown on Drawing 1826685 shall be loaded in accordance with Drawing 1826687, with the exception that increments D1 through D6 shall consist of T-10 delay powder pressed at 40,000 ± 500 pounds per square inch (psi). The tools required for loading are specified on LD 480089. The ignition increment P shall consist of approximately 160 milligrams (mg) of A-1A ignition powder conforming to MIL-P-22264 or 160 mg of composition consisting of 80 percent A-1A ignition powder (MIL-P-22264) and 20 percent $BKNO_3$ ignition powder conforming to MIL-P-46994, type VII, class 3, and shall be adjusted to be within the drawing limits (0.060 ± 0.002 inch) for increment length when pressed at 40,000 ± 500 psi. Each increment may be measured volumetrically by means of a scoop of such size as to give six approximately equal increments. After the last increment, D6, is pressed, the loading funnel cap shall be loosened and tightened again. The D6 increment shall be repressed to improve compaction and to minimize the danger of loss of powder by fallout. The surface of the delay column shall be flush with the end of the delay element in which it is contained. Excess powder may be removed by sliding the end of the test element over a hard cloth. The output charge holder containing the P_2 charge shall be loaded in accordance with Drawing 1826740.

4.4.2.2 Timing of test elements. Suggested directions for mounting components into the delay holder and assembling the test adapter are given in AD 1014. The temperature of the test elements for room temperature firing shall be within 24 ± 4° C (75 ± 7° F). The test adapters shall be conditioned continuously for at least 4 hours at the required temperature before firing. The test adapters shall be fired within 2 minutes after removal from the temperature conditioning unit.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

4.4.2.3 Procedure for operating test apparatus. It is suggested that AD 1014 be used for operating instructions of the test apparatus.

4.4.2.4 Computation of burning time and percent coefficient of variation. Compute the burning time ($\bar{X}$) which is the average time of the observations obtained in 4.4.2.2. Compute the standard deviation (S) of the time observations. The symbols and the method of computation shall be governed by 6.3. Compute the percent coefficient of variation by dividing (100) x (S) by $\bar{X}$. Disposition of the lot shall be governed by 3.4 and 3.6. Where lot rejection is on the basis of the percent coefficient of variation, or by 3.6, the lot may be remixed and resubmitted for acceptance under all provisions of 4.4.

4.4.2.5 Testing after shipment or 12-months storage. After shipment or storage of not less than 12 months, retest the lot in accordance with 4.4.2 and 4.4.3.

4.4.2.6 Alternate burntime after storage method. Size of the preproduction sample shall be 15 units. The samples shall be divided for ballistic test at each temperature for which ballistic requirements are specified in the end-item specification. If the sample cannot be evenly divided for each test temperature, apply the odd unit to the highest test temperature.

4.4.3 Low-temperature functioning test. Sampling shall be conducted after the last mixing operation. Select and prepare a representative pooled sample of delay mixture from the lot in accordance with 4.4.2 by preparing 10 test elements as provided by 4.4.2.1. Determine the burning time at low temperature by the procedures of 4.4.2.2 and 4.4.2.4 with the exception that the conditioning temperature shall be -54 $\pm$ 2° C (-65 $\pm$ 3.6° F). Determine the average burning time according to 4.4.2.4. Compute the percentage change in burning time on the basis of change from the burning time determined under 4.4.2.4 at room temperature (24 $\pm$ 4° C) (75 $\pm$ 7° F). The lot is acceptable if the increase in burntime is less than 25.0 percent as required by 3.5 and meets the requirements of 3.6 and 3.7.

5. PACKAGING

5.1 Preservation.

5.1.1 Unit packaging. Place approximately 1,200 grams of T-10 delay composition into a double bag of 4-mil conductive plastic formed by inserting a 6- by 12-inch bag into another. The plastic bags shall conform to MIL-B-82647. Twist the top of the bag tightly, fold over once, and secure with two No. 84 rubber bands.

5.1.2 Intermediate packaging. Place two double conductive bags in a metal ammunition can conforming to Drawing 423038. Expanded vermiculite conforming to ASTM C516 shall be used inside the intermediate container to ensure a tight pack. The net weight per can shall not be greater than 5 pounds of T-10 delay composition.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

5.1.2.1 Intermediate packaging, alternate No. 1. Place two double conductive bags in a can conforming to MIL-C-10464. Expanded vermiculite material conforming to ASTM C516 shall be used to fill voids inside the intermediate container to ensure a tight pack prior to sealing in accordance with conventional canning techniques. This can is hermetically sealed. The net weight per can shall be not greater than 2,500 grams or 5 pounds of T-10 delay composition.

5.1.2.2 Intermediate packaging, alternate No. 2. Place two double conductive bags in a 1-gallon capacity, friction-top container conforming to PPP-C-96, type V, class 2. The cover shall be fixed by crimping at four or more points. Expanded vermiculite conforming to ASTM C516 shall be used inside the intermediate container to ensure a tight pack. The net weight per container shall be not greater than 2,500 grams or 5 pounds of T-10 delay composition.

5.2 Packing. The packaged T-10 delay composition shall be packed in a domestic type, wood cleated plywood box conforming to PPP-B-601 or in a class 1, style 2, 2-1/2, 3, or 4 nailed wooden box conforming to PPP-B-621. Containers conforming to PPP-B-621 shall be lined with a material which will not cause nor produce a static electric discharge. Vermiculite conforming to ASTM C516 shall be used within the shipping box to provide separation of the intermediate containers and to ensure a tight pack. The gross weight of a shipping container shall be not greater than 50 pounds.

5.3 Marking. In addition to any special markings required by contract or purchase order, unit packages, intermediate packages, and shipping containers shall be marked in accordance with the requirements of MIL-STD-129. In addition, the label on each container shall contain the following information:

a. T-10 delay composition
b. Name of manufacturer
c. Date of manufacture
d. Lot number in accordance with MIL-STD-1168
e. Burntime at room temperature

5.4 Data cards. Data cards, in accordance with MIL-STD-1167, shall be retained by the contractor for each lot and made available for inspection by the contracting officer's representative. Each data card shall contain the following information:

T-10 delay composition

Manufacturer
Manufacturer's lot No.
Original lot weight
Container net weight
Burntime (average):
  a. 24 ± 4° C (75 ± 7° F)
  b. -54 ± 2° C (-65 ± 3.6° F)
Standard deviation
  a. 24 ± 4° C (75 ± 7° F)
  b. -54 ± 2° C (-65 ± 3.6° F)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

Boron

Manufacturer
Manufacturer's lot No.

Barium chromate

Manufacturer
Manufacturer's lot No.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. T-10 delay composition is intended for use as a delay time determining element in ignition devices such as fuze explosive trains and cartridge actuated devices. The mixture burns essentially with no gas evolution; however, venting or expansion chamber pressure relief is desirable to relieve pressure generated by primary ignition elements. Application of this composition is restricted to hermetically sealed assemblies.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of the specification.

b. Issue of DODISS to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.1.1 and 2.2).

c. Quantity.

d. Burntime at room temperature (see 3.3).

e. Preservation and packing requirements (see section 5).

f. Special marking (see 5.3).

g. That the safety precaution requirements of the "Contractor's Safety Manual for Ammunition and Explosives," DOD 4145.26M are applicable. NOTE: When this specification is used as part of the description of work to be accomplished by a Government activity, the safety precaution requirements of "Ammunition and Explosives Ashore," OP 5 are applicable.

6.3 Consideration of data requirements. The following data requirements should be considered when this specification is applied on a contract. The applicable Data Item Descriptions (DID's) should be reviewed in conjunction with the specific acquisition to ensure that only essential data are requested/provided and that the DID's are tailored to reflect the requirements of the specific application. To ensure correct contractural application of the data requirements, a Contract Data Requirements List (DD Form 1423) must be prepared to obtain the data, except where DOD FAR Supplement 27.475-1 exempts the requirement for a DD Form 1423.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

Reference Paragraph	DID Number	DID Title	Suggested Tailoring
4.2	DI-NDTI-80809A	Test/inspection reports	---

The above DID's were those cleared as of the date of this specification. The current issue of DOD 5010.12-L, Acquisition Management Systems and Data Requirements Control List (AMSDL), must be researched to ensure that only current, cleared DID's are cited on the DD Form 1423.

6.4 Computation of sample mean and standard deviation.

6.4.1 Sample mean ($\bar{X}$).

$$\bar{X} = \sum X/N$$

where

$\sum X$ = sum of individual measurements
N = number of measurements

6.4.2 Sample standard deviation (S).

$$S = \sqrt{\frac{N(\sum x^2) - (\sum x)^2}{N(N-1)}}$$

where

$(\sum X^2)$ = sum of the square of each individual measurement
$(\sum X)^2$ = sum of individual measurements squared

6.5 OSHA recommendation. The Occupational Safety and Health Administration (OSHA) recommends that the worker exposure to hexavalent chromium be controlled or eliminated. Barium chromate is an inferred carcinogen.

6.6 Advisory procedures for formulation.

6.6.1 Pilot mixture. Since the particle size distribution and chemical purity of the boron and barium chromate will vary from lot to lot, the burntime of delay compositions made from different ingredient lots may vary. A pilot mixture technique is therefore necessary to define the composition-burntime curve for the new components. A composition on the curve within the range of burntime of interest should be prepared and its burntime determined according to 4.4.2. These data are used to construct a parallel curve to that shown on figure 1 from which the composition for any desired burntime may be determined.

6.6.2 Processing pilot mixtures and production batches. Dry the barium chromate ingredient at 88 ± 6° C (190 ± 11° F) for 16 hours minimum. Before mixing, screen the barium chromate ingredient through a U.S. Standard Sieve No. 30. Several mixing methods may be attempted.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

6.6.2.1 Wet mixing in a muller-type blender. Preblend the dried and weighed ingredients for 15 minutes on a remotely operated jar rolling mill. Charge the preblended ingredients into a Lancaster mixer or equivalent. Add ethyl alcohol (MIL-E-463, grade 1) to the powder in sufficient quantity to form a viscous paste, after determining this amount experimentally with a small quantity of the powder. Approximately 20 mL alcohol per 100 grams of mix has been found to be satisfactory. During mixing, turn the mixer on and off by remote control and keep the mixer completely isolated. Stop the mixer every 15 minutes to scrape down the sides and muller with a conductive spatula. Continue mixing until damp clumps of powder will crumble easily under pressure. Maximum mixing time will be 1.5 hours. Do not continue mixing until powder reaches an apparently dry state.

6.6.2.2 Wet mixing with a fluid shear mixer. Place the dried and weighed barium chromate into a suitable size mix bowl. Add ethyl alcohol per MIL-E-463, grade 1, in the amount of 100 mL alcohol per 100 grams of mixture. Using a fluid shear mixer such as the Eppenbach Homo-Mixer, mix ethyl alcohol and barium chromate for 60 minutes to break up particle agglomerates. Stop mixer and add preweighed boron ingredient. Mix remotely for 10 minutes, stop mixer, and scrape bowl sides toward center of bowl with conductive spatula. Mix remotely for 10 or more minutes and stop mixer.

6.6.2.3 Drying after wet mixing. Dry wet mixture at 60 $\pm$ 6° C (140 $\pm$ 11° F) for 16 hours minimum. Screen through a U.S. Standard Sieve No. 30. A final drying at 80 $\pm$ 3° C (176 $\pm$ 5.4° F) for 144 hours serves to preage the mixture and renders it more stable.

6.6.2.4 Judging mixing effectiveness and completeness. The completeness of the mixing operation can be measured by means of the quality assurance provisions and test requirements. The T-10 delay composition may be considered homogeneous if it meets the requirements of 3.3 through 3.7.

6.7 T-10 properties. After T-10 delay composition has been properly mixed, it is possible for the fuel and oxidants to segregate under conditions of storage and transportation. Segregation appears to occur near the surface when a delay composition is subjected to prolonged agitation, particularly during shipment by rail. The surface layer is then nonhomogeneous and not representative of the composition of the lot.

6.8 Batch. A batch is defined as that quantity of material which has been manufactured by some unit chemical process and subjected to some physical mixing operation intended to make the final product substantially uniform.

6.9 Material safety data sheets. Contracting officers will identify those activities requiring copies of MSDSs. Additional Government mailing information is contained in Appendix B of FED-STD-313. In order to obtain the MSDS, FAR clause 52.223-3 must be in the contract.

6.10 Toxicological product formulations. Material safety data sheet requirements are applicable and should be specified in the contract as required by DOD FAR 23.303.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

6.11 Subject term (key word) listing.

Barium chromate
Boron
Burntime
Coefficient of variation

6.12 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

Preparing activity:
Navy - AS
(Project 1377-ND76)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER	2. DOCUMENT DATE (YYMMDD)
	MIL-D-85306A(AS)	7 November 1991

3. DOCUMENT TITLE: DELAY COMPOSITION, T-10

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER		
a. NAME (Last, First, Middle Initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) (1) Commercial (2) AUTOVON (If applicable)	7. DATE SUBMITTED (YYMMDD)

8. PREPARING ACTIVITY		
a. NAME Commanding Officer NAEC (SESD) Code 53	b. TELEPHONE (Include Area Code) (1) Commercial: (908) 323-1116 (2) AUTOVON: 624-1116	
c. ADDRESS (Include Zip Code) Lakehurst, NJ 08733-5100	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 AUTOVON 289-2340	

DD Form 1426, OCT 89 — Previous editions are obsolete. — 198/290

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:38Z
Check the source to verify that this is the current version before use.