GG-R-60c
April 9, 1965

SUPERSEDING
Int. Fed. Spec. GG-R-0060b (GSA-FSS)
March 22, 1963

FEDERAL SPECIFICATION

RAZORS, SAFETY; AND BLADES, RAZOR

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers the requirements for hoe-shaped safety razors and safety razor blades used for shaving the human skin

1.2 Classification.

1.2.1 *Types and classes of razors.* The safety razors covered by this specification shall be of the following types and classes, as specified (see 6.1):

Type I—One shaving side razor.
Class 1—For style 1, single edge blades (figs 1 and 5).
Type II—Two shaving sides razor.
Class 2—Nonseparable, nonadjustable, for styles 2 and 3 double edge blades (figs 2, 3, and 6).
Class 3—Separable for styles 2 and 3 double edge blades (figs. 2, 3, and 7).
Class 4—Nonseparable, adjustable, for styles 2 and 3 double edge blades (figs. 2, 3, and 8).
Type III—Ejector, one shaving side razor.
Class 5—For style 4, injector blades (figs 4 and 9).

1.2.2 *Style of blades.* The safety razor blades covered by this specification shall be of the following styles, as specified (see 6 1)

Style 1—Single edge blade (fig. 1).
Style 2—Double edge, regular blade (fig. 2).
Style 3—Double edge, thin blade (fig. 3)
Style 4—Injector blade (fig. 4).

1.2.3 *Grade.* Razor blades covered by this specification shall be of the following grades, as specified (see 6.1).

Grade A—Carbon steel blades, untreated edges.
Grade B—Carbon steel blades, treated edges.
Grade C—Stainless steel blades, treated edges.

1.2.4 *Treatment.* When specified, the grade and style of razor blades shall be furnished with the following treatments, as specified (see 6.1).

Treatment A—Silicone fluid coating, for grade B, style 3 razor blade.
Treatment B—Polytetrafluoroethylene sintered coating for grade C, styles 1, 3, and 4 razor blades.

2. APPLICABLE SPECIFICATIONS AND STANDARDS

2.1 The following specifications and standards, of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

Federal Specifications:

UU-P-553—Paper, Wrapping, Tissue.
PPP-B-566—Boxes, Folding, Paperboard.
PPP-B-585—Boxes, Wood, Wirebound.
PPP-B-591—Boxes, Fiberboard, Wood-Cleated.
PPP-B-601—Boxes, Wood, Cleated-Plywood.
PPP-B-621—Boxes, Wood, Nailed and Lock-Corner.
PPP-B-636—Box, Fiberboard.
PPP-B-665—Boxes: Paperboard, Metal Stayed (Including Stay Material).
PPP-B-676—Boxes, Set-Up, Paperboard.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

Federal Standards:

Fed. Std. No 102—Preservation, Packaging, and Packing Levels.
Fed. Std. No. 123—Marking for Domestic Shipment (Civilian Agencies)

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington, D C. 20402

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D C, Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, Los Angeles, and Seattle, Wash.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies)

Military Specification:

MIL-L-10547—Liners, Case, and Sheet, Overwrap, Water-Vaporproof or Waterproof, Flexible

Military Standards:

MIL-STD-105—Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129—Marking for Shipment and Storage.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer)

3. REQUIREMENTS

3.1 **Illustrations.** The illustrations shown herein are for the purpose of identification and are not intended to preclude the purchase of razors and blades which are otherwise in accordance with the requirements of this specification, however, the dimensions and tolerances shown on the blade alignment pattern and blade illustrations are requirements of this specification.

3.2 **Preproduction sample approval.** When specified (see 6.1) before production is commenced, a sample of the item shall be submitted or made available to the contracting officer or his authorized representative for examination and approval in accordance with 4.2. Approval of the preproduction sample authorizes commencement of production but does not relieve the supplier of responsibility for compliance with the detailed provisions of this specification The preproduction sample shall be manufactured in the same facilities to be used for the manufacture of the production item

3.3 **Material.**

3 3.1 *Handle.* The razor handle shall be of metal, plastic, or both metal and plastic, unless otherwise specified (see 6 1).

3 3 2 *Cap and guard.* The cap and guard shall be of metal.

3.3.3 *Corrosion-resistance.* All components of the razor shall be either inherently corrosion-resistant or plated so as to be corrosion-resistant. They shall withstand submersion in water for 24 hours without deterioration (see 4.4.1.1 hot water test)

3.4 **Razors.**

3.4.1 *General requirements*

3 4.1.1 *Design and construction.* The safety razors covered by this specification shall be of a hoe-shape design and when assembled with the blade shall be evenly balanced. The handle shall provide a comfortable finger grip that is fabricated in a manner to prevent slipping or twisting. The handle shall be not less than 2-1/2 nor more than 5 inches in length and not less than 3/8-inch in diameter or 3/8- by 3/8-inch measured on the largest cross-section. Except for type II, class 4 adjustable razor (see 3 4 2 2 3), the weight of the razor completely assembled, without blade, shall not ex-

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

ceed 2-1/2 ounces. The razor design shall provide for proper positioning of the blade for satisfactory shaving. Adjacent to where the blade cuts the whiskers, the razor shall be provided with a guard with continuous edge, to smoothen and tighten the skin in advance of the cutting edge of the blade Openings shall be provided in the razor adjacent to the cutting edge of the assembled blade to receive lather and whiskers removed from the shaved area, and thus prevent clogging of the cutting edge Threads, if used, shall be free running and provide for clamping of the blade in the razor so that it will not loosen when shaving Hinges, if used, or any other parts which might affect the assembly, disassembly, or operation of the razor in normal use, shall be designed for durability, ease of operation, and for maintaining the proper position of the blade during use All components of the razor shall be smoothly finished, and serrated or knurled surfaces, if used, shall not present any sharp edges or burrs The guard shall be parallel to the blade within 0 006 inch when tested as described in 4.4.1 2.

3.4.1.2 *Marking* Each razor shall be marked in a legible and permanent manner with manufacturer's name or trademark of such known character that the source of manufacture can be readily identified

3 4 2 *Detail requirements for razors*

3.4.2.1 *Type I.* Type I, class 1 razors (fig. 5a) shall have one shaving side, be nonseparable, and provide for readily changing the blades without disassembling the razor. The razor shall have two edge stops in accordance with figure 5b for alignment of style 1 (figs 1 and 10) single edge razor blades with metal backing strip.

3.4.2.2 *Type II.* Type II razors shall have two shaving sides and accommodate both style 2, regular double edge blades, and style 3, thin double edge blades. The blade alignment pattern shall be of the bar, pin, or end located style, in accordance with figure 6b

3 4.2.2.1 *Class* 2. Type II, class 2 razors (fig 6a) shall be nonseparable, nonadjustable, and provide for readily changing the blades without disassembling the razor.

3 4.2.2 2 *Class* 3. Type II, class 3 razors (fig. 7) shall provide for blade changing by disassembling the razor into its three parts (1) the cap, (2) the guard, and (3) the handle The blade alignment pattern for type II, class 3 razors shall be the same as for type II, class 2 razors (see fig 6b).

3.4.2 2 3 *Class* 4. Type II, class 4 razors (fig. 8) shall be nonseparable, have adjustment for blade setting, and provide for readily changing the blades without disassembling the razor The weight of the adjustable razor completely assembled without blade shall not exceed 3-1/4 ounces. The razor design shall provide for proper positioning and adjustment of the blade exposure for satisfactory shaving The blade alignment pattern for type II, class 4 razors shall be the same as for type II, class 2 razors (see fig. 6b).

3.4.2.3 *Type III* Type III, class 5 razors (fig 9a), shall be of the ejector type in which the used blade is propelled from the razor head by the new blade when it is positioned in the razor, the injector blade dispenser is used to aid in the blade-changing operation. The razor shall have two edge stops in accordance with figure 9b for alignment of style 4 injector blades The handle may be either shape shown on figure 9a, or other design meeting the requirements of 3 4 1.1.

3.5 Blades.

3.5 1 *General requirements.*

3 5 1 1 *Steel.* Razor blades shall be manufactured from virgin stainless steel or carbon steel, as specified (see 1.2.3 and 6.1). Stainless steel shall have a carbon content of not less than 0 06 percent and no more than 1.05 percent, and a chromium content of not less than 12 50 percent. Carbon steel shall have a carbon content of not less than

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

1.15 percent nor more than 1.36 percent. The blades shall show a uniform, well spheroidized cementite structure, with carbide particles of uniform size and distribution, free from laminations and nonmetallic inclusions

3 5.1.2 *Hardness.* The hardness of the blades, tested at the edge of the blade adjacent to the beveled cutting edges, shall be not less than 560 DPHN for stainless steel blades, nor more than 920 DPHN for carbon steel blades on the Vickers hardness tester, using a pyramidal diamond 2-1/2 or 3 kilogram load for blades thinner than 0 0068 inch in thickness, and a 5 kilogram load for blades greater than 0.0068 inch in thickness; or with 15 kilogram load it shall be not less than 89 3 nor more than 93 on the Rockwell N superficial scale.

3 5 1.3 *Treatment.* When treatment "A" is specified (see 1 2.4 and 6.1), grade B, style 3, blades (see 1.2.2 and 1.2.3) shall be treated through an intricate process of applying a fine silicone fluid coating When treatment "B" is specified (see 1 2 4 and 6 1), the beveled edges of grade C (see 1.2 3) blades shall be treated through an intricate process of applying polytetrafluoroethylene coating. The method of applying treatment "A" or "B" shall be according to industry's standard practice.

3.5.1.4 *Marking.* Each blade, except style 4 injector blades, and each blade dispenser shall be marked in a plain and permanent manner with the manufacturer's name or trademark of such known character that the source of manufacturer can be readily identified.

3.5.1 5 *Cutting edges.* The included angle of each cutting edge shall be not less than 15° nor more than 25°. Both sides of the blade at the cutting edge(s) shall be honed. The final honing bevels shall be either hollow or flat, smooth and continuous throughout the length of each edge and be of 0 0008-inch minimum width to eliminate from the cutting edge(s) the marks made by grinding and rough honing operations when viewed under a magnification of 100 diameters. The grinding, rough honing, and final honing bevels shall be separate, distinct, and running parallel to the edge of the blade. Stainless steel blades shall be stropped and polished before coating. When viewed under a magnification of 100 diameters, the cutting edge(s) shall be free from bent edges, jagged edges, honed edge gouged out, one side not honed, and bent over edges at end of blade. Blades shall average not more than three nicks (at 100-diameter magnification) per blade edge of a size no larger than one-hundredth of one millimeter (mm.) and shall not in any case be closer than 1/4 inch apart. (See 3.5 1.6 for definition of a nick).

3.5.1 6 *Nicks.* For the purpose of this specification, a nick is defined as a chipped out, broken out, indented, bent out, semicircular projection, or any similar gap, indentation, or projection, having a dimension greater than one-hundredth of one mm.

Note Any nick one-hundredth of one mm. or smaller, or any nick appearing in the chamfered or curved portion at the ends of the cutting edge shall not be counted This paragraph is not to be interpreted that serrated or unhoned cutting edges are permissible.

3 5.1.7 *Straightness and parallelism of cutting edge(s).* When checked on top of the cutting edge along the full length of the blade, each cutting edge shall be straight to within 0 0015 inch. The two cutting edges of style 2 and 3 double edge blades shall be straight and parallel to within 0.003 inch so that when measured at the two ends and at least three intermediate positions there shall not be a variation in excess of 0.003 inch in the maximum and minimum perpendicular measurements between the two cutting edges In no event shall the minimum or maximum dimensions exceed those specified in figures 11 and 12.

3 5.1.8 *Protection from corrosion.* The finished surface of each blade, including the

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

beveled cutting edges, shall be coated with a protective film that will prevent corrosion. The protective film shall not have any ingredient which will cause skin irritation (see 6.2) To provide greater corrosion-resisting qualities on blades other than stainless steel, when specified, for dispenser use grades A and B, double edge blades (styles 2 and 3) shall be coated with lacquer on both flat sides (see 6.1).

3.5 1.9 *Design.* Each style of blade shall be designed to fit the type of razor specified, without excessive or insufficient blade exposure, and shall have sharp edges for satisfactory shaving.

3.5.2 *Detail requirements of blades*

3.5 2.1 *Style* 1 *blades.* Style 1 single edge blades shall be in accordance with the dimensions and tolerances shown in figure 10 Each blade shall be provided with a securely attached metal backing strip Style 1 blades shall fit type I razors.

3.5.2.2 *Style* 2. Style 2 double edge regular blades shall be in accordance with the dimensions and tolerances shown in figure 11. Style 2 blades shall fit type II razors Style 2 blades shall meet the flexibility test in 4.4.2.2.

3.5 2.3 *Style* 3 Style 3 double edge thin blades shall be in accordance with the dimensions and tolerances shown in figure 11 except that the thickness of the blade shall be in accordance with figure 12. Style 3 blades shall fit type II razors Style 3 blades shall meet the flexibility tests in 4 4 2.3

3.5.2 4 *Style* 4. Style 4 injector blades shall have one cutting edge and shall be in accordance with the dimensions and tolerances shown in figure 13. Style 4 blades shall fit type III ejector razors

3.6 Cases. When specified (see 6 1), one safety razor and one package of blades containing not less than two blades shall be furnished in a case. The case shall be designed to prevent the razor from contacting the package of blades and shall be provided with a cover which can be conveniently opened and closed. Unless otherwise specified (see 6 1), the case shall be made of metal, plastic or paperboard or a combination thereof.

3.6.1 *Metal case* Metal cases shall withstand the load test described in 4.4.3.1. Metal cases not inherently corrosion-resistant shall be either made corrosion-resistant by metallic plating, or covered outside with a water-resistant nonmetallic curable covering securely bonded with the metal The inside surface of the cases shall be suitably coated, treated, plated, or covered.

3.6 2 *Plastic cases* Plastic cases shall withstand the load test described in 4 4.3.1

3.6 3 *Paperboard cases.* Paperboard cases shall be of such material that will not crush or break in shipment and handling, and shall withstand the load test described in 4 4 3 1.

3.7 Workmanship. The finished razor, blades, and cases shall conform to the quality and grade of product established by this specification. The occurrence of defects shall not exceed the applicable acceptable quality level (AQL)

4. SAMPLING, INSPECTION, AND TEST PROCEDURES

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements

4.2 Preproduction sample inspection. When a preproduction sample is required, inspection shall be made of the end item for

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

conformance with all provisions of this specification (see 3 2).

4.3 **Sampling for inspection and acceptance.** Sampling for inspection and acceptance shall be performed in accordance with the provisions set forth in MIL-STD-105, except where otherwise indicated herein

4 3.1 *Inspection of materials and components.* In accordance with 4 1, the supplier is responsible for insuring that materials and components used are manufactured, tested and inspected in accordance with the requirements of referenced subsidiary specifications and standards to the extent specified, or, if none, in accordance with this specification

4.3.2 *Inspection of the end product* A lot shall consist of all razors of the same type and class, or razor with a package of blades in a case of the same kind, or of all blades of the same grade, style and treatment submitted for inspection at one time. The sample unit for this inspection shall be one razor, razor with blades in case, or razor blade

4 3.2.1 *Visual examination.* Visual examination shall be made for the classification of defects set forth in table I The inspection level for razors and razors in cases shall be level II with an AQL of 2 5 for major defects and 6 5 for total defects expressed in terms of defects per hundred units. The inspection level for razor blades shall be S-2 with an AQL of 1 5 for major defects and 4 0 for total defects expressed in terms of defects per hundred units

TABLE I *Classification of defects*

Examine	Defect	Classification	
		Major	Minor
(Razors)			
Design and construction	Wrong type or class	X	
	Cap and guard missing or not made of metal	X	
	Openings adjacent to cutting edge missing		X
	Threads and hinges (when applicable) not free running or easy to operate		X
Type I, class 1	Edge stops missing	X	
Type II, classes 2, 3, and 4	Not as specified	X	
Type III, class 5	Not as specified	X	
Workmanship	Any component missing	X	
	Any component damaged, affecting serviceability	X	
	Burrs or sharp edges		X
Marking	Missing, incorrect, illegible, incomplete		X
(Razor with blades in case)	Cover does not conveniently open and close		X
	Razor in contact with package of blades		X
	Less than 2 blades in package		X
(Razor blades)			
Design	Wrong style	X	
	Not as specified	X	
Grade and treatment	Not as specified	X	
Quality, finish, and workmanship	Hone marks not eliminated from cutting edge, edges not honed, edge serrated, chipped jagged, etc , edge bent, blades not oiled, blades broken or cracked	X	
Marking	Missing, incorrect, illegible, incomplete		X

4 3 2 2 *Dimensional examination* Examination shall be made of the end product to determine compliance with dimensional requirements specified herein Any dimension

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

not within the established requirements shall be classified a defect. The inspection level shall be S-2 with an AQL of 1.5 expressed in terms of defects per hundred units

4 3.2.3 *Testing of the end product.* Tests shall be performed on razors, razor blades, and razor cases as specified in 4.4 as applicable. The inspection level shall be S-2 with an AQL of 1.5 expressed in terms of defects per hundred units.

4.3.3 *Certificate of compliance.* When treatment A and B razor blades are required as specified in the contract or purchase order, the contractor shall submit a certificate of compliance to the contracting officer certifying that the treatment meets the requirements specified in 3.5.1.3. The Government reserves the right to perform tests as necessary to determine that the treatment has been satisfactorily applied.

4.3.4 *Examination of preparation for delivery.* An examination shall be made of packaging, packing, and marking to determine compliance with requirements of section 5. Defects shall be scored as specified in table II. The sample unit shall be one shipping container fully prepared for delivery. The lot shall be the number of containers offered for delivery at one time. The inspection level shall be S-2 and the AQL 4.0 expressed in terms of defects per hundred units.

TABLE II *Examination of preparation for delivery*

Examine	Defect
Markings (exterior and interior)	Omitted, incorrect, illegible, of improper size, location, sequence, or method of application.
Materials	Any component missing or damaged.
Workmanship	Inadequate application of components, such as incomplete closure of container flaps, case liner; loose strapping, inadequate stapling, or improper taping
	Bulging or distortion of containers.
Contents exterior and interior container)	Number per container is more or less than required.

4.4 Tests.

4 4.1 *Razors.*

4 4 1.1 *Hot water and corrosion-resistant test* Each sample razor shall be submerged for 30 minutes in water having a temperature of 160° ± 30°F. after which the water shall be allowed to cool to room temperature. Sample razors shall remain submerged in the water for 24 hours and then be examined to determine compliance with 3 3.3. Sample razors showing evidence of corrosion, pitting, scumming, deformation, or other defects shall be considered as nonconforming, except that aluminum or aluminum alloy components of the razors, when applicable, shall not exhibit any corrosion products that cannot be wiped off with a clean cloth restoring the finish to a condition showing no deterioration when visually examined

4 4 1.2 *Parallelism of blade and razor guard* Employing a new blade or a blank blade known to be flat, straight, and true, check the parallelism of the razor by (1) inserting the blade in the razor, (2) true the razor up in either V-blocks or a fixture by leveling the razor by dial indicator gaging the blade on top of both ends of the cutting edge, (3) relocate the dial indicator anvil to obtain a reading on the top of the guard, (4) move the dial indicator gage across the top edge of the guard and the difference between the minimum and maximum readings shall not exceed 0.006 inch to determine compliance with 3 4 1.1, (5) on type II, two shaving sides razors, the tests shall be conducted on both shaving sides of the razor

4 4.2 *Blades*

4.4.2.1 *Hardness test.* Conformance with the requirements of 3.5.1.2, hardness of blades, shall be determined by means of a suitable hardness testing machine Hardness shall be tested as close to the cutting edge as is feasible and hardness readings shall be taken at two or more places per edge. In the event that the Rockwell N superficial scale hardness readings are taken,

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

it is recommended that an auxiliary anvil having a Rockwell C hardness of 63 (Rockwell N-91 5) be placed on top of the regular hardness testing machine anvil. The purpose of the auxiliary anvil is to overcome "anvil effect" when testing blades within a 89 3 to 93 Rockwell N superficial scale reading (with 15 kg. load). Blades not falling within the hardness ranges specified shall be considered as nonconforming.

4.4 2.2 *Flexibility test for style 2 blades.* Style 2 double edge, regular blades shall be flexibility-tested by bending around a smooth steel bar 1-3/4 inches in diameter without cracking or breaking when flexed along the long axis of the blade, and around a smooth steel bar 1-1/2 inches in diameter without cracking or breaking when flexed along the short axis (see 3.5 2 2).

4.4 2.3 *Flexibility test for style 3 blades* Style 3 double edge thin blades shall be flexibility-tested by bending around a smooth steel bar 1-1/2 inches in diameter without cracking or breaking when flexed along the long axis of the blade, and around a smooth steel bar 1-1/4 inches in diameter without cracking or breaking when flexed along the short axis (see 3 5 2 3).

4.4 2.4 *Microscopic examination* Oil, grease, protective film, and lint shall be removed from the cutting edges of the blade by any suitable means which will not damage the blade edge The blade edge shall then be placed in the microscopic field and adequately illuminated for clear vision The size of the nicks in the blade edge shall be measured by a field micrometer eye piece with one-hundredth mm graduations, in a one-hundred power microscope Nicks greater than one-hundredth of one mm in any direction shall be counted and the number of nicks in the sample blade edges shall be divided by the number of blade edges examined If the average number of nicks per blade edge is greater than 3, the lot represented by the sample shall be rejected (see 3 5 1 5 and 3 5.1 6)

4.4 2.5 *Final honing angle.* The final honing angle of the blade edge(s) shall be measured by a suitable method, preferably by means of a microscope and rectilinear beam of light from a source movable in a plane perpendicular to the blade bevel. Blades with the honing angle of the cutting edges not within the range of 11 to 25 degrees shall be considered as nonconforming (see 3.5.1.5).

4 4.2.6 *Load test for blade dispensers.* A ten-pound weight shall be gently applied on each surface of blade dispensers and injector dispensers for blades except for the key injector surface of injector type blade dispensers. Dispensers which break, or become otherwise defective shall be considered as nonconforming (see 5 1 1.1.3 and 5.1.1.1.4).

4.4 3 *Razor cases.*

4.4.3.1 *Load test.* Safety razor cases as described in 3.6.1 (metal) 3 6.2 (plastic) and 3.6 3 (paperboard) shall not permanently deform, crack, or break when tested as follows: An empty case shall be placed upon a flat surface, with cover uppermost, closed, and a weight of 50 pounds placed gently upon the cover, distributed over the whole top case area, and allowed to remain for 30 minutes Permanent deformation, cracking, or breakage shall be cause for rejection.

5 PREPARATION FOR DELIVERY

For civil agency procurement, the definitions and application of levels of packaging and packing shall be in accordance with Fed. Std No 102.

5.1 **Packaging.** Razor blades, or razors shall be packaged level A, B, or C as specified (see 6 1 and 6.2).

5 1.1 *Level A or B*

5 1.1.1 *Blades.* Blades shall be so packaged that no cutting edge will contact any surface of the packaging material Blades shall be packaged in accordance with table III, according to the pack designation specified (see 6.1)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

5.1 1.1.1 *Unit containers.* Unit containers shall be the same for levels A, B, and C

5.1.1 1 2 *Paperboard containers.* Style 1 blades that are designated in table III to be packaged in paperboard containers shall first have each individual blade sheathed in a folded sheet of high finish, grease-resistant 0 013-inch minimum thickness paperboard, and each sheathed blade shall be completely wrapped in a snug-fitting paper wrapper. Styles 2 and 3, blades that are designated in table III to be packaged in paperboard containers shall first have each blade wrapped individually in at least two paper wrappers. The blades shall be sealed either individually or collectively from dust, dirt, and other foreign material. The paperboard container may be wrapped in commercial type cellophane paper

5.1 1.1.3 *Dispensers.* Styles 2 and 3 blades that are designated in table III to be packed in dispensers may be wrapped individually. Blades may be separated with paper strips or other material to afford ease in ejecting each blade. The blades shall be placed in a dispenser made of plastic, metal, or a combination of metal and plastic. The dispenser shall afford ease and safety to the operator as each blade is dispensed. The dispenser shall be so designed as to afford ease in hooking the razor blade onto the razor head aligning pins or bar The dispenser shall hold the applicable number of blades as specified in table III and provide storage for an equal number of used blades. The dispenser shall automatically position the blades so that as each blade is dispensed the next new blade will be in position for ejection. The dispenser shall be so designed as to prevent the ejection of more than one blade at a time. The dispenser shall withstand the application of a ten-pound weight on any surface without damage

5.1.1.1 4 *Injector dispensers.* Style 4 injector blades (see table III) in injector dispensers shall not be wrapped individually The blades shall be placed in a metal or combination of metal and plastic injector dispenser. The dispenser shall afford ease and safety to the operator when injecting the new blade into the razor head The ejector shall be so designed that after release of the locking pressure of the blade to the razor head, longitudinal pressure against the new blade shall propel it into operating position after ejecting the old blade from the razor The injector dispenser shall be so designed as to prevent the ejection of more than one blade at a time Except for the injector key surface, the dispenser shall withstand the application of a 10-pound weight on any surface without damage

TABLE III. *Packaging of blades*

Pack designation	Blades per pack	Blade				Blade container			For razor	
		Style	Fig. No.	Cutting edges		Paper board	Dispenser	Injector dispenser	Type	Class
				One	Two					
1	5	1	10	X	—	X	—	—	I	1
2	10	1	10	X	—	X	—	—	I	1
3	5	2	11	—	X	X	—	—	II	2-3-4
4	20	2	11	—	X	—	X	—	II	2-3-4
5	5	3	12	—	X	X	—	—	II	2-3-4
6	4	3	12	—	X	X	—	—	II	2-3-4
7	10	3	12	—	X	—	X	—	II	2-3-4
8	20	3	12	—	X	—	X	—	II	2-3-
9	25	3	12	—	X	—	X	—	II	2-3-4
10	20	4	13	X	—	—	—	X	III	5
11	7	4	13	X	—	—	—	X	III	5

Note The letter "X" denotes commercially available pack

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

5 1.1 1 5 *Intermediate and shipping container quantities.* Quantities of razor blades, razors, and/or razor and blades in case, in intermediate packages and shipping containers shall be in conformance with table IV

5.1.1 1.6 *Intermediate container for blades* The intermediate container shall be the same for levels A, B, or C The quantity of packages shown in table IV, packaged in accordance with 5.1.1.1.2, 5.1.1.1.3 or 5 1.1.1.4 shall be packaged in a carton of appropriate size constructed in accordance with PPP-B-566, or PPP-B-676. Each carton shall be adequately secured to prevent accidental opening

TABLE IV. *Intermediate packaging and packing quantities*

Item	Intermediate container (carton)	Shipping container
Double edge blades packaged in paperboard containers	20 packages of blades (this carton is the unit of issue)	50 intermediate packages
Double edge blades in dispensers	20 dispensers (this carton is the unit of issue)	50 intermediate packages
Single edge blades in paperboard packages	20 packages of blades (this carton is the unit of issue)	50 intermediate packages
Razors in single cartons	50 cartoned razors	20 intermediate packages 1,000 cartoned razors)
Razors and blades in case	6 cases	20 intermediate packages (120 cased razors)

5 1.1 2 *Razors.*

5 1,1.2 1 *Unit container* Each razor of type I, II, or III shall be disassembled, where possible, and wrapped as a unit in tissue paper conforming to type I, grade A, class 2 of UU-P-553, unless otherwise specified in the contract or order (see 6 1) Each wrapped razor shall be placed in a carton in accordance with 5 1.1.1.6. When specified, each razor, along with one package of blades packaged in accordance with table III, shall be placed in a case in accordance with 3 6

5 1.1 2.2 *Intermediate container for razors, cartoned or cased* Intermediate containers shall be the same for levels A, B, or C The number of razors, cartoned or cased in the intermediate container shall be as shown in table IV The carton shall be of appropriate size and constructed in accordance with PPP-B-566, PPP-B-676, or alternately nontest fiberboard in accordance with PPP-B-636, or a paperboard metal stayed container in accordance with PPP-B-665.

5 1 2 *Level C* Razors and razor blades shall be packaged in accordance with the industries practice

5.2 Packing. Razor blades or razors shall be packed level A, B, or C as specified (see 6 1)

5 2 1 *Level A* The quantity of razor blades, and/or razors, cartoned or cased as specified, as shown in table IV, packaged as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container conforming to style RSC, V3c or V3s of PPP-B-636. Each fiberboard container shall be waterproofed with a case liner or tape, as specified in the appendix of PPP-B-636 Closure, waterproofing by means of tape, and reinforcing with flat steel strapping or tape banding shall be in accordance with the appendix of the container specification

5.2.2 *Level B* The quantity of razor blades, and/or razors, cartoned or cased as specified, as shown in table IV, packaged as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container conforming to style RSC, type CF or SF, class domestic, variety optional, grade 275 of PPP-B-636 Closure shall be in accordance with the appendix of the container specification

5 2 3 *Level C.* Razors and razor blades, packaged as specified in 5 1, shall be packed in a manner to insure carrier acceptance and safe delivery at destination at the lowest transportation rate for such supplies Con-

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

tainers shall be in accordance with rules and regulations of carriers applicable to the mode of transportation.

5.3 Marking.

5.3.1 *Civil agencies.* In addition to any special marking required by the contract or order, interior packages and shipping containers shall be marked in accordance with Fed. Std. No. 123.

5.3.2 *Military requirements.* In addition to any special marking required by the contract or order, interior packages and shipping containers shall be marked in accordance with MIL-STD-129.

6. NOTES

6.1 **Ordering data.** Purchasers should exercise any desired options offered herein and procurement documents should specify the following:

(*a*) Title, number, and date of this specification.
(*b*) Type and class of razor required (see 1.2.1).
(*c*) Style of blades required (see 1.2.2).
(*d*) Grade of blades required (see 1.2.3).
(*e*) When treatment "A" or "B" is required (see 1.2.4).
(*f*) When each razor with one package of blades for each razor are to be furnished in a case (see 3.6).
(*g*) Razor handle material, if not contractor's option (see 3.3.1).
(*h*) If lacquer coating is required on both flat sides of double edge blades, grades A and B, styles 2 and 3 (see 3.5.1.8).
(*i*) The pack designation for packaging of blades (see 5.1 1.1 and table III).
(*j*) Razor case material required (see 3.6).
(*k*) Selection of applicable levels of packaging and packing (see 5.1 and 5.2)

6.2 **Military requirements.** Questions pertaining to the possible adverse effect of the protective films used in conformance with 3.5.1.8 should be referred by the procuring activity to the appropriate Departmental Medical Service who will act as an advisor to the procuring agency.

6.3 **Civil agency procurement** When level B packaging is specified for civil agency procurement, the requirements of 5.1.1 shall apply.

6.3 Transportation descriptions and minimum weights applicable to this commodity are:

Rail:

Razors, other than electric.
Carload minimum weight 20,000 pounds, subject to Rule 34, Uniform Freight Classification.

Motor:

Razors, safety.
Truckload minimum weight 20,000 pounds subject to Rule 115, National Motor Freight Classification.

Rail:

Razor blades.
Carload minimum weight 20,000 pounds, subject to Rule 34, Uniform Freight Classification.

Motor:

Razor blades.
Truckload minimum weight 20,000 pounds, subject to Rule 115, National Motor Freight Classification

MILITARY INTEREST:

Army—GL, MD
Navy—S&A
Air Force—MAA (Code 67)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

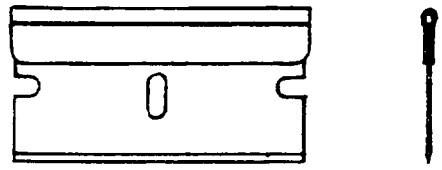


FIGURE 1. Style 1, single edge blade for type I razor (see fig. 10 for details)

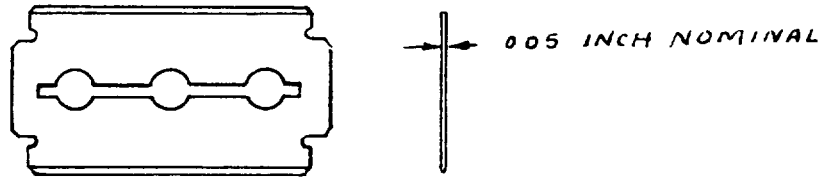


FIGURE 2. Style 2, double edge, regular blade for type II razors (see fig. 11 for details)

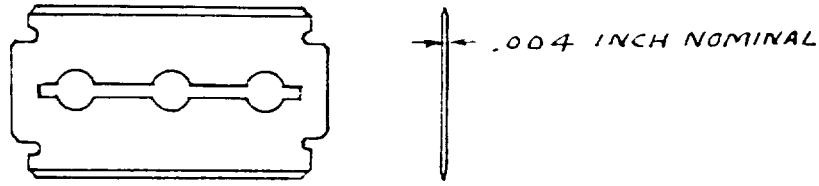


FIGURE 3 Style 3, double edge thin blade, for type II razors (see fig. 11 and 12 for details)




FIGURE 4. Style 4 injector blade for type III razors (see fig 13 for details)

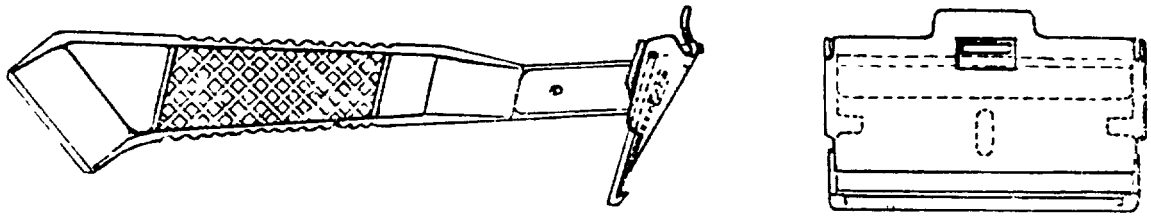


FIGURE 5a Type I, class 1, razor with one shaving side, for style 1, single edge blades

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

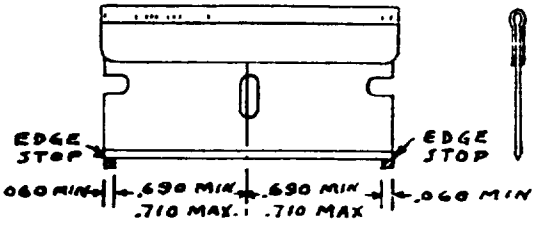


FIGURE 5b. Blade alignment pattern for type I, class 1 razor, for style 1, single edge blades




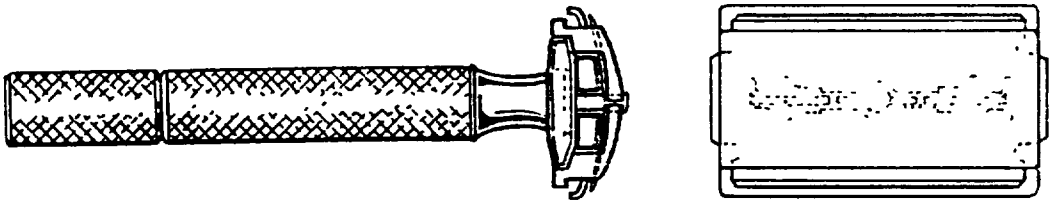


FIGURE 6a. Type II, class 2, nonseparable, nonadjustable razor with two shaving sides, for styles 2 and 3 double edge blades

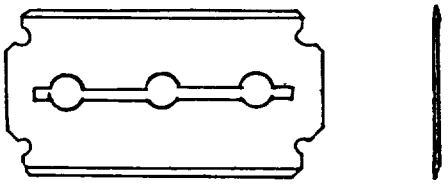


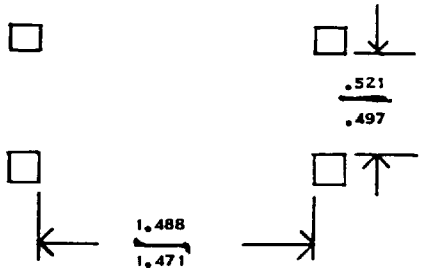

End Located Style Blade Alignment Pattern

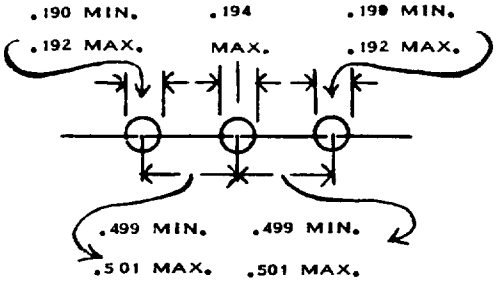

Pin Style Blade Alignment Pattern

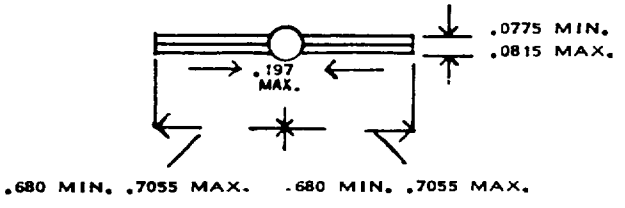

Bar Style Blade Alignment Pattern

FIGURE 6b. Blade alignment pattern for type II, classes 2 and 3 razors, for styles 2 and 3 double edge blades

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

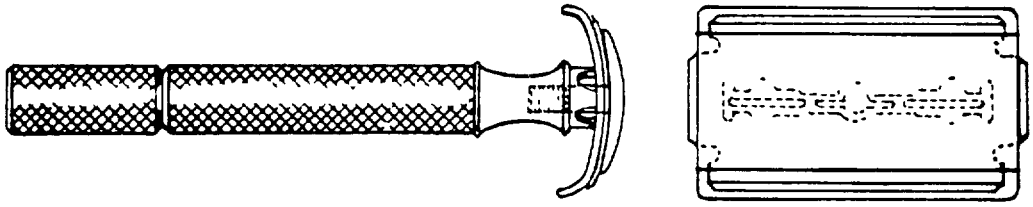


FIGURE 7. Type II, class 3 separable razor with two shaving sides for styles 2 and 3 double edge blades

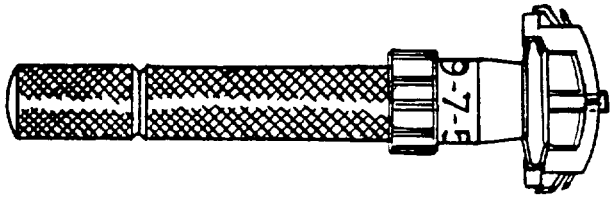


FIGURE 8 Type II, class 4 nonseparable, adjustable razor with two shaving sides, for styles 2 and 3 double edge blades

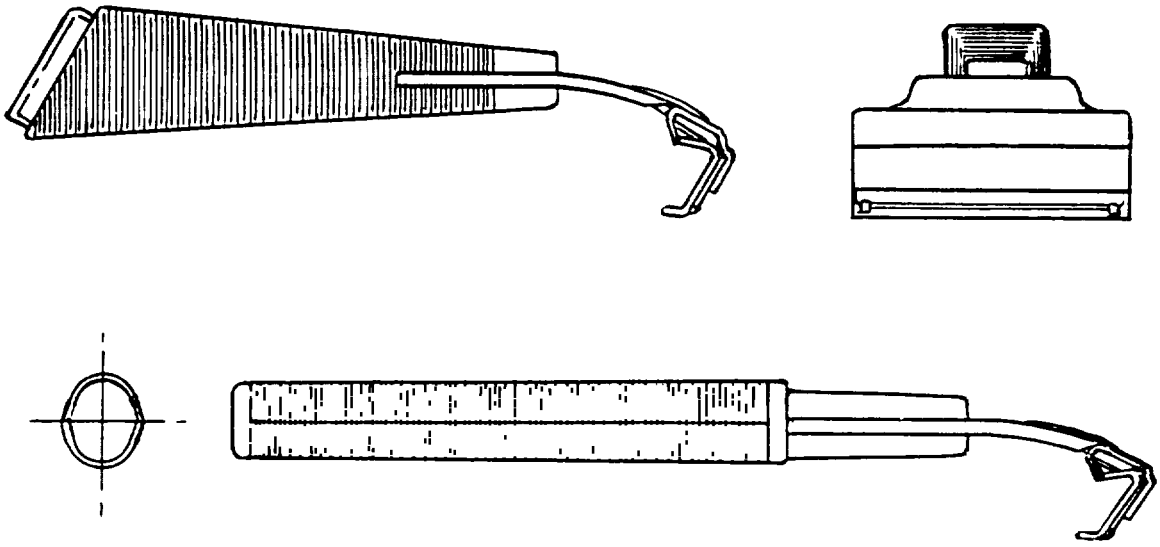


FIGURE 9a Type III, class 5 ejector razor for style 4 injector blades, (either handle design acceptable, see 3.4.1.1 and 3.4.2.3)




FIGURE 9b Blade alignment pattern for type III, class 5, ejector razors for style 4 injector blades

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.


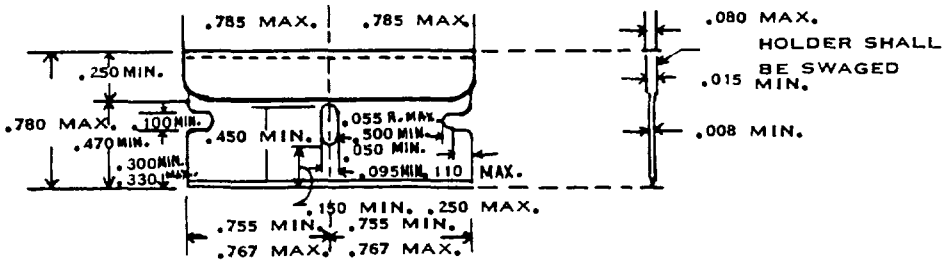


FIGURE 10 Style 1, single edge blade for type I razors

Note Blade shall fit Pin style, Bar style, and End located style blade alignment patterns for Type II razors Design of slot not restrictive except that at those points which control fit and clearance of blade the dimensions shall

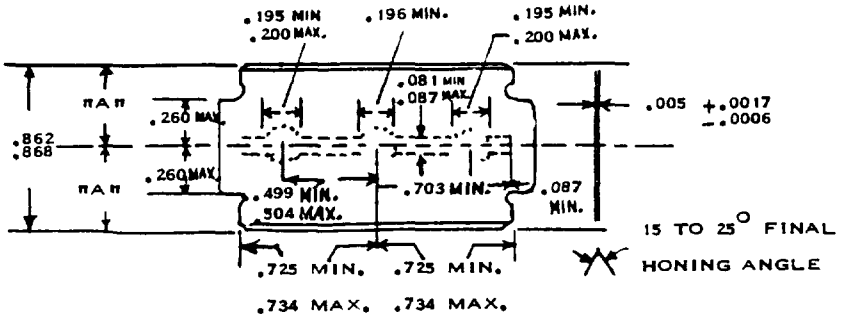


be as shown.

One half width dimension "A" shall not vary from opposite dimension "A" by more than .0025 to .004 inch

FIGURE 11. Style 2, double edge regular blade for type II razors

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.

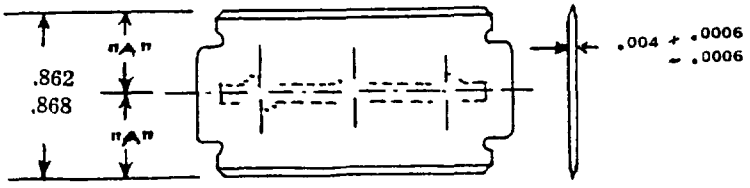

One half width dimension "A" shall not vary from opposite dimension "A" by more than 0025 to 004 inch.

FIGURE 12 Style 3, double edge thin blade for type II razors

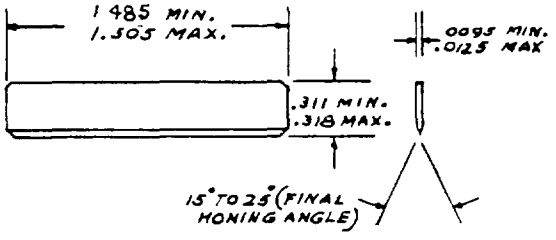


FIGURE 13. Style 4, injector blade

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:48Z
Check the source to verify that this is the current version before use.