The documentation and process conversion measures necessary to comply with this document shall be completed by 27 November 2020.

INCH-POUND
MIL-PRF-19500/357P
27 August 2020
SUPERSEDING
MIL-PRF-19500/357N
20 May 2015

PERFORMANCE SPECIFICATION SHEET

TRANSISTOR, PNP, RADIATION HARDENED, SILICON, AMPLIFIER, TYPES 2N3634 THROUGH 2N3637, JAN, JANTX, JANTXV, JANS, JANHC AND JANKC

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-PRF-19500.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for PNP, silicon, radiation hardened, low-power amplifier, and switching transistors. Four levels of product assurance are provided for each encapsulated device (JAN, JANTX, JANTXV, and JANS) and two levels of product assurance are provided for unencapsulated die (JANHC and JANKC).

1.2 Package outlines and die topography. The device package for the encapsulated device type are as follows: TO-5 and TO-39 in accordance with figure 1, surface mount version in accordance with figure 2. The dimensions and topography for JANHC and JANKC unencapsulated die are as follows: “A” version die in accordance with figure 3, “B” version die in accordance with figure 4, and “C” version die in accordance with figure 5.

* 1.3 Maximum ratings. Unless otherwise specified T_A = +25°C.

Types	P_T (1) T_A = +25°C	P_T (2) T_C = +25°C	P_T (3) T_{SP} = +25°C	$R_{\theta JA}$ (4)	$R_{\theta JC}$ (4)	$R_{\theta JSP}$ (4)	I_C	T_J and T_{STG}	V_{CBO}	V_{CEO}	V_{EBO}
	W	W	W	°C/W	°C/W	°C/W	A dc	°C	V dc	V dc	V dc
2N3634, 2N3634L	1	5	N/A	175	35	N/A	1	-65 to +200	-140	-140	-5
2N3634UB and UBN	0.5	N/A	1.5	325	N/A	90	1		-140	-140	-5
2N3635, 2N3635L	1	5	N/A	175	35	N/A	1		-140	-140	-5
2N3635UB and UBN	0.5	N/A	1.5	325	N/A	90	1		-140	-140	-5
2N3636, 2N3636L	1	5	N/A	175	35	N/A	1		-175	-175	-5
2N3636UB and UBN	0.5	N/A	1.5	325	N/A	90	1		-175	-175	-5
2N3637, 2N3637L	1	5	N/A	175	35	N/A	1		-175	-175	-5
2N3637UB and UBN	0.5	N/A	1.5	325	N/A	90	1		-175	-175	-5

(1) See figure 6 and figure 7.
(2) See figure 8.
(3) See figure 9.
(4) See figures 10, 11, and 12.

Comments, suggestions, or questions on this document should be addressed to DLA Land and Maritime, ATTN: VAC, P.O. Box 3990, Columbus, OH 43218-3990, or emailed to Semiconductor@dla.mil . Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil .

AMSC N/A

FSC 5961

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

* 1.4 Primary electrical characteristics. Unless otherwise specified, T_A = +25°C.

Types	h_{FE} at V_{CE} = 10 V dc (1)							$\lvert h_{fe} \rvert$		C_{obo}
	h_{FE1} I_C = 0.1 mA dc	h_{FE2} I_C = 1.0 mA dc	h_{FE3} I_C = 10 mA dc	h_{FE4} I_C = 50 mA dc		h_{FE5} I_C = 150 mA dc		V_{CE} = -30 V dc I_C = 30 mA dc f = 100 Mhz		V_{CB} = -20 V dc I_E = 0 100 Khz ≤ f ≤ 1 Mhz
	Min	Min	Min	Min	Max	Min	Max	Min	Max	Max
2N3634, 2N3634L	25	45	50	50	150	30		1.5	8.0	10
2N3634UB and UBN	25	45	50	50	150	30		1.5	8.0	10
2N3635, 2N3635L	55	90	100	100	300	60		2.0	8.5	10
2N3635UB and UBN	55	90	100	100	300	60		2.0	8.5	10
2N3636, 2N3636L	25	45	50	50	150	30		1.5	8.0	10
2N3636UB and UBN	25	45	50	50	150	30		1.5	8.0	10
2N3637, 2N3637L	55	90	100	100	300	60		2.0	8.5	10
2N3637UB and UBN	55	90	100	100	300	60		2.0	8.5	10

	$V_{CE(sat)1}$ I_C = -10 mA dc (1) I_B = -1 mA dc	$V_{CE(sat)2}$ I_C = -50 mA dc (1) I_B = -5 mA dc	$V_{BE(sat)1}$ I_C = -10 mA dc (1) I_B = -1 mA dc	$V_{BE(sat)2}$ I_C = -50 mA dc (1) I_B = -5 mA dc	Switching parameters			
					t_d	t_r	t_s	t_f
	V dc	V dc	V dc	V dc	ns	ns	ns	ns
Minimum				0.65				
Maximum	0.3	0.6	0.8	0.90	100	100	500	150

(1) Pulsed (see 4.5.1).

1.5 Part or Identifying Number (PIN). The PIN is in accordance with MIL-PRF-19500, and as specified herein. See 6.5 for PIN construction example and 6.6 for a list of available PINs.

1.5.1 JAN certification mark and quality level for encapsulated devices. The quality level designators for encapsulated devices that are applicable for this specification sheet from the lowest to the highest level are as follows: “JAN”, “JANTX”, “JANTXV” and "JANS".

1.5.2 JAN certification mark and quality level for unencapsulated devices (die). The quality level designators for unencapsulated devices (die) that are applicable for this specification sheet from the lowest to the highest level are as follows: "JANHC" and "JANKC".

1.5.3 Radiation hardness assurance (RHA) designator. The RHA levels that are applicable for this specification sheet from lowest to highest are as follows: "M", "D", "P", "L", "R", "F", "G", and "H".

1.5.4 Device type. The designation system for the device types of transistors covered by this specification sheet are as follows.

1.5.4.1 First number and first letter symbols. The transistors of this specification sheet use the first number and letter symbols "2N".

1.5.4.2 Second number symbols. The second number symbols for the transistors covered by this specification sheet are as follows: "3634", "3635", “3636”, and "3637".


1.5.4.3 Suffix symbols. The suffix letter "L" is used on devices that are packaged in the TO-5 package of figure 1 that have a long lead length: 1.500 inches (38.10 mm) minimum and 1.750 inches (44.45 mm) maximum. Devices with standard length leads (see figure 1, TO-39) use no suffix. The suffix letters “UB” or “UBN” are used on devices that are packaged in the surface mount package of figure 2. The “UBN” suffix has an isolated metal lid where the “UB” suffix does not.

1.5.5 Die identifiers for unencapsulated devices (manufacturers and critical interface identifiers). The manufacturer die identifiers that are applicable for this specification sheet are "A", “B”, and "C" and are in figures 3, 4, and 5 respectively.

* 1.5.6 Lead finish. The lead finishes applicable to this specification sheet are listed on QPDSIS-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

Ltr	Dimensions				
	Inches		Millimeters		Notes
	Min	Max	Min	Max	
CD	.305	.335	7.75	8.51	
CH	.240	.260	6.10	6.60	
HD	.335	.370	8.51	9.40	
LC	.200 TYP		5.08 TYP		7
LD	.016	.021	0.41	0.53	6
LL	See notes 7, 9, and 10				
LU	.016	.019	0.41	0.48	7
L_1		.050		1.27	7
L_2	.250		6.35		7
P	.100		2.54		5
Q		.050		1.27	
r		.010		0.254	8
TL	.029	.045	0.74	1.14	4
TW	.028	.034	0.71	0.86	3
α	45° TP		45° TP		6
Term 1	Emitter				
Term 2	Base				
Term 3	Collector				

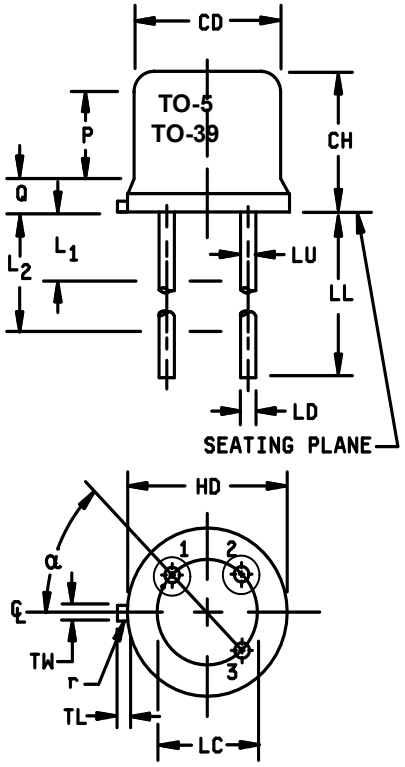

NOTES:

1. Dimensions are in inches.
2. Millimeters are given for general information only.
3. Beyond r maximum, TW must be held to a minimum length of .021 inch (0.53 mm).
4. TL measured from maximum HD.
5. CD shall not vary more than ±.010 inch (0.25 mm) in zone P. This zone is controlled for automatic handling.
6. Leads at gauge plane .054 - .055 inch (1.37 - 1.40 mm) below seating plane shall be within .007 inch (0.18 mm) radius of true position (TP) at a maximum material condition (MMC) relative to the tab at MMC. The device may be measured by direct methods or by gauge and gauging procedure.
7. LU applies between L_1 and L_2. LD applies between L_2 and L minimum. Diameter is uncontrolled in L_1 and beyond LL minimum.
8. r (radius) applies to both inside corners of tab.
9. For transistor types 2N3634 through 2N3637, LL is .500 inch (12.70 mm) minimum, and .750 inch (19.05 mm) maximum (TO-39).
10. For transistor types 2N3634L through 2N3637L, LL is 1.500 inches (38.10 mm) minimum, and 1.750 inches (44.45 mm) maximum (TO-5).
11. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

FIGURE 1. Physical dimensions (TO-5 and TO-39).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

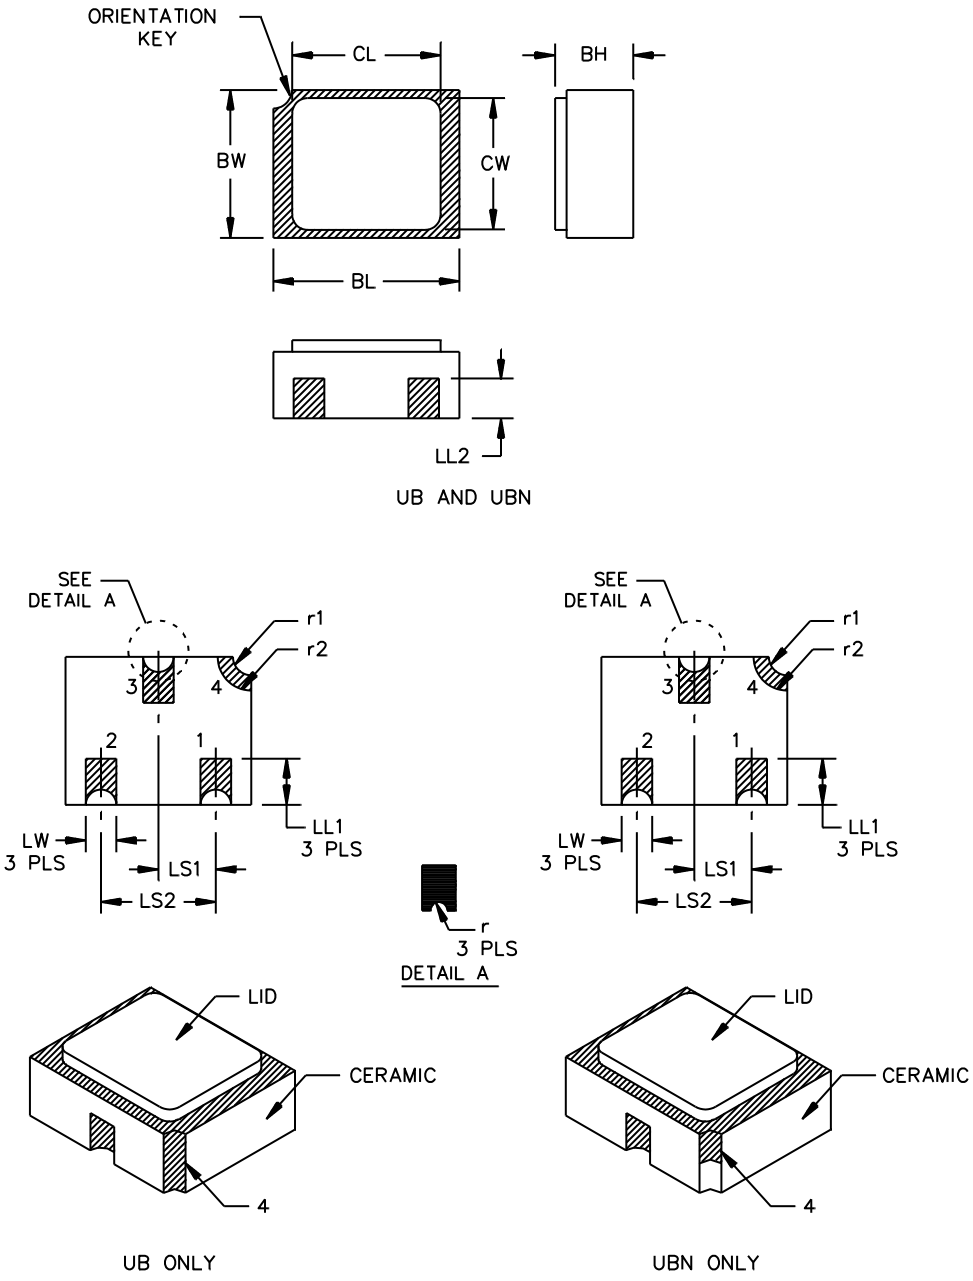


FIGURE 2. Physical dimensions, surface mount 2N3634UB through 2N3637UB (UB and UBN version).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.


Symbol	Dimensions				Note
	Inches		Millimeters		
	Min	Max	Min	Max	
BH	.046	.056	1.17	1.42	
BL	.115	.128	2.92	3.25	
BW	.085	.108	2.16	2.74	
CL		.128		3.25	
CW		.108		2.74	
LL1	.022	.038	0.56	0.97	
LL2	.017	.035	0.43	0.89	

Symbol	Dimensions				Note
	Inches		Millimeters		
	Min	Max	Min	Max	
LS_1	.036	.040	0.91	1.02	
LS_2	.071	.079	1.80	2.01	
LW	.016	.024	0.41	0.61	
r		.008		.203	
r1		.012		.305	
r2		.022		.559	

NOTES:
1. Dimensions are in inches.
2. Millimeters are given for general information only.
3. Hatched areas on package denote metallized areas.
4. Lid material: Kovar.
5. UB only: Pad 1 = Base, Pad 2 = Emitter, Pad 3 = Collector, Pad 4 = Shielding connected to the metal lid.
6. UBN only: Pad 1 = Base, Pad 2 = Emitter, Pad 3 = Collector, Isolated lid with three pads only.
7. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

FIGURE 2. Physical dimensions, surface mount 2N3634UB through 2N3637UB (UB and UBN version).


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

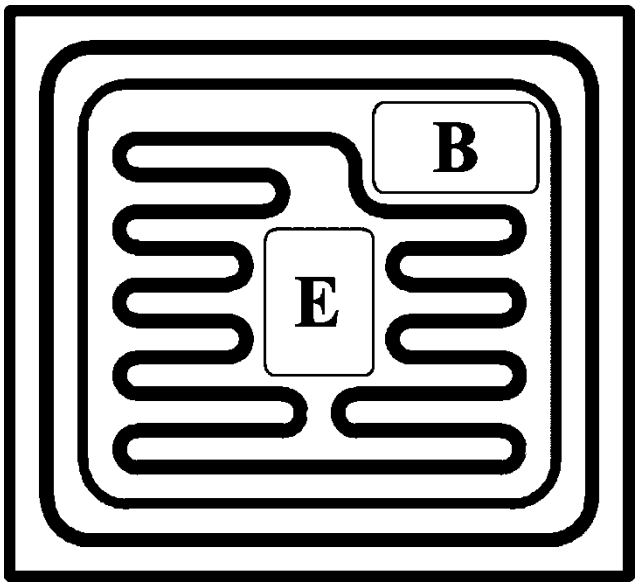

1. Chip size.....…024 x .026 inch ±.002 inch (0.61 x 0.66 mm ±0.051mm).
2. Chip thickness.....…010 ±.0015 inch nominal (0.254 ±0.038 mm).
3. Top metal.....Aluminum 15,000Å minimum, 18,000Å nominal.
4. Back metal.....Gold 3,500Å minimum, 5,000Å nominal.
5. Backside.....…Collector.
6. Bonding pad .....B = .004 x .006 inch, (0.102 mm x 0.152 mm).
   E = .004 x .0055 inch. (0.102 mm x 0.140 mm).
7. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

FIGURE 3. JANHCA and JANKCA die dimensions.


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

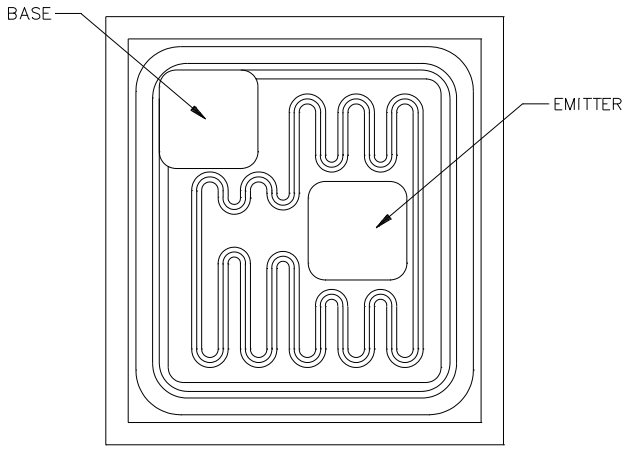

1. Chip size.....….024 x .0259 inch nominal (0.61 x 0.66 mm).
2. Chip thickness.....….0079 inch nominal (0.21mm).
3. Top metal.....Aluminum 20,000Å nominal.
4. Back metal.....12K Gold.
5. Backside. .....Collector.
6. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

FIGURE 4. JANHCB and JANKCB die dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

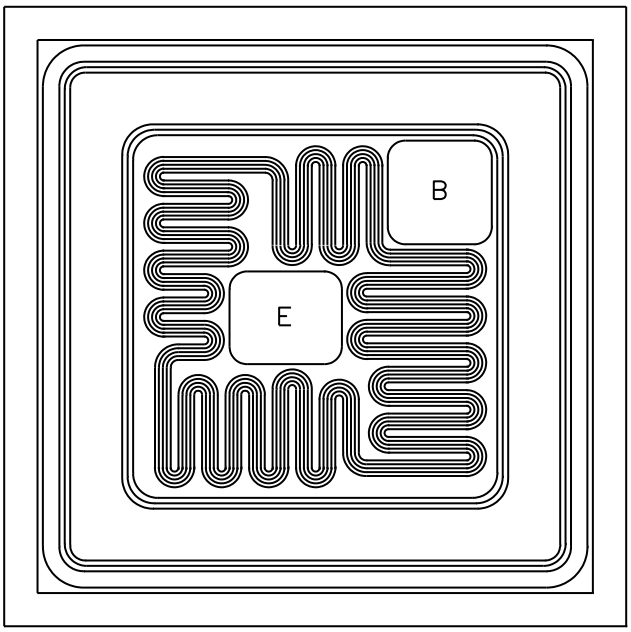

1. Chip size.....….0.027 x 0.027 inch nominal (0.686 x 0.686 mm).
2. Chip thickness.....….0.008 inch nominal (0.203mm).
3. Top metal.....Aluminum, 24,500Å nominal.
4. Back metal.....Gold, 6,500Å nominal.
5. Backside. .....….Collector.
6. Bonding Pad…….Base = 0.0045 x 0.0045 inch nominal (0.114 x 0.114 mm)
   Emitter = 0.004 x 0.005 inch nominal (0.102 x 0.127 mm)
7. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

FIGURE 5. JANHCC and JANKCC die dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-750 - Test Methods for Semiconductor Devices.

(Copies of these documents are available online at https://quicksearch.dla.mil.)

2.3 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

* 3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturers list QML-19500 before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500 and as follows.

$R_{\theta JSP(AM)}$ ..... Thermal resistance junction to solder pads (adhesive mount to PCB).
$R_{\theta JSP(IS)}$..... Thermal resistance junction to solder pads (infinite sink mount to PCB).

3.4 Interface and physical dimensions. The interface and physical dimensions shall be as specified in MIL-PRF-19500 and on figure 1, figure 2, figure 3, figure 4, and figure 5.

3.4.1 Lead finish. Lead finish shall be solderable in accordance with MIL-PRF-19500, MIL-STD-750, and herein. Where a choice of lead finish is desired, it shall be specified in the acquisition document (see 6.2).

3.5 Radiation hardness assurance (RHA). Radiation hardness assurance requirements, PIN designators, and test levels shall be as defined in MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I.

3.7 Electrical test requirements. The electrical test requirements shall be as specified in table I herein.

3.8 Marking. Marking shall be in accordance with MIL-PRF-19500. The radiation hardened designator M, D, P, L, R, F, G, or H shall immediately precede (or replace) the device "2N" identifier (depending upon degree of abbreviation required).

3.9 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3).

c. Conformance inspection (see 4.4 and tables I and II).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.2.1 JANHC and JANKC qualification. JANHC and JANKC qualification inspection shall be in accordance with MIL-PRF-19500.

4.2.2 Group E qualification. Group E inspection shall be performed for qualification or requalification only. In case qualification was awarded to a prior revision of the specification sheet that did not request the performance of table III tests, the tests specified in table III herein that were not performed in the prior revision shall be performed on the first inspection lot to this revision to maintain qualification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

4.3 Screening.

* 4.3.1 Screening of encapsulated devices (JANTX, JANTXV, and JANS levels only). Screening shall be in accordance with table E-IV of MIL-PRF-19500, and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen	Measurement	
	JANS level	JANTX and JANTXV levels
(1) 3c	Thermal impedance, method 3131 of MIL-STD-750 (see 4.3.4).	Thermal impedance, method 3131 of MIL-STD-750 (see 4.3.4).
9	I_{CBO2} and h_{FE5}	Not applicable
10	24 hours minimum.	24 hours minimum.
11	I_{CBO2} and h_{FE5} ΔI_{CBO2} = 100 percent of initial value or 10 nA dc, whichever is greater; Δh_{FE5} = ±15 percent of initial value.	I_{CBO2} and h_{FE5}
12	See 4.3.3, 240 hours minimum.	See 4.3.3.
13	Subgroups 2 and 3 of table I herein; ΔI_{CBO2} = 100 percent of initial value or 10 nA dc, whichever is greater. Δh_{FE5} = ±15 percent of initial value.	Subgroup 2 of table I herein; ΔI_{CBO2} = 100 percent of initial value or 10 nA dc, whichever is greater. Δh_{FE5} = ±15 percent of initial value.

(1) Shall be performed anytime after temperature cycling, screen 3a; JANTX and JANTXV levels do not need to be repeated in screening requirements.

4.3.2 Screening of unencapsulated die (JANHC and JANKC). Screening of JANHC and JANKC unencapsulated die shall be in accordance with appendix G of MIL-PRF-19500. The burn-in duration for JANKC level shall follow the JANS requirements; the JANHC level shall follow the JANTX requirements of table E-IV of MIL-PRF-19500.

* 4.3.3 Power burn-in conditions. Power burn-in conditions are as follows: V_{CB} = -10 - -30 V dc. Power shall be applied to achieve T_J = +135°C minimum using a minimum P_D = 75 percent of P_T maximum rated as defined in 1.3. With approval of the qualifying activity and preparing activity, alternate burn-in criteria (hours, bias conditions, T_J, and mounting conditions) may be used for JANTX and JANTXV quality levels. A justification demonstrating equivalence is required. In addition, the manufacturing site's burn-in data and performance history will be essential criteria for burn-in modification approval.

* 4.3.4 Thermal impedance ($Z_{\theta JX}$ measurements). The $Z_{\theta JX}$ measurements shall be performed in accordance with method 3131 of MIL-STD-750 using the guidelines in that method for determining I_M, I_H, t_H, t_{MD} (and V_C where appropriate). (See figure 10, figure 11, and figure 12.) See table III, group E, subgroup 4 herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500 and as specified herein. If alternate screening is being performed in accordance with MIL-PRF-19500, a sample of screened devices shall be submitted to and pass the requirements of table I, group A, subgroup 1, subgroup 2 inspection only.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with table E-V of MIL-PRF-19500 and table I herein.

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-VIA (JANS) of MIL-PRF-19500 and 4.4.2.1 herein. Delta requirements shall be in accordance with 4.5.4 herein. See 4.4.2.2 for JAN, JANTX, and JANTXV group B testing. Delta requirements for JAN, JANTX, and JANTXV shall be after each step in 4.4.2.2 and shall be in accordance with 4.5.4 herein.

4.4.2.1 Group B inspection, table E-VIA (JANS) of MIL-PRF-19500.

	Subgroup	Method	Condition
*	B4	1037	V_{CB} = -10 - -30 V dc; 2,000 cycles. No heat sink or forced-air cooling on devices shall be permitted.
*	B5	1027	V_{CB} = -10 V dc; $P_D \geq$ 100 percent of maximum rated P_T (see 1.3). (NOTE: If a failure occurs, resubmission shall be at the test conditions of the original sample.) Option 1: 96 hours minimum, sample size in accordance with table E-VIa of MIL-PRF-19500 adjust T_A or P_D to achieve T_J = +275°C minimum. Option 2: 216 hours minimum, sample size = 45, c = 0; adjust T_A or P_D to achieve T_J = +225°C minimum.

4.4.2.2 Group B inspection, table E-VIb (JAN, JANTX, and JANTXV) of MIL-PRF-19500. Separate samples may be used for each step. In the event of a lot failure, the resubmission requirements of MIL-PRF-19500 shall apply. In addition, all catastrophic failures during CI shall be analyzed to the extent possible to identify root cause and corrective action. Whenever a failure is identified as wafer lot and /or wafer processing related, the entire wafer lot and related devices assembled from the wafer lot shall be rejected unless an appropriate determined corrective action to eliminate the failures mode has been implemented and the devices from the wafer lot are screened to eliminate the failure mode.

	Step	Method	Condition
*	1	1026	Steady-state life: 1,000 hours minimum, V_{CB} = -10 V dc, power shall be applied to achieve T_J = +150°C minimum using a minimum of P_D = 75 percent of maximum rated P_T as defined in 1.3. n = 45 devices, c = 0. The sample size may be increased and the test time decreased as long as the devices are stressed for a total of 45,000 device hours minimum, and the actual time of test is at least 340 hours.
	2	1048	Blocking life, T_A = +150°C, V_{CB} = 80 percent of rated voltage, 48 hours minimum. n = 45 devices, c = 0.
	3	1032	High-temperature life (non-operating), t = 340 hours, T_A = +200°C. n = 22, c = 0.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

4.4.2.3 Group B sample selection. Samples selected from group B inspection shall meet all of the following requirements:

a. For JAN, JANTX, and JANTXV samples shall be selected randomly from a minimum of three wafers (or from each wafer in the lot) from each wafer lot. For JANS, samples shall be selected from each inspection lot. See MIL-PRF-19500.

b. Shall be chosen from an inspection lot that has been submitted to and passed table I, subgroup 2, conformance inspection. When the final lead finish is solder or any plating prone to oxidation at high temperature, the samples for life test (subgroups B4 and B5 for JANS, and group B for JAN, JANTX, and JANTXV) may be pulled prior to the application of final lead finish.

4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the test and conditions specified for subgroup testing in table E-VII of MIL-PRF-19500, and in 4.4.3.1 (JANS) and 4.4.3.2 (JAN, JANTX, and JANTXV) herein for group C testing. Delta requirements only apply to subgroup C6 and shall be in accordance with 4.5.4 herein.

4.4.3.1 Group C inspection (JANS), table E-VII of MIL-PRF-19500.

	Subgroup	Method	Condition
	C2	2036	Test condition E; (not applicable for UB and UBN devices).
	C5	3131	$R_{\theta JA}$ and $R_{\theta JC}$ only, as applicable (see 1.3) and in accordance with thermal impedance curves.
*	C6	1026	Test condition B, 1,000 hours at V_{CB} = -10 V dc; power shall be applied to achieve T_J = +150°C minimum and a minimum of P_D = 75 percent of maximum rated P_T as defined in 1.3. n = 45, c = 0. The sample size may be increased and the test time decreased as long as the devices are stressed for a total of 45,000 device hours minimum, and the actual time of test is at least 340 hours.

4.4.3.2 Group C inspection (JAN, JANTX, and JANTXV), table E-VII of MIL-PRF-19500.

Subgroup	Method	Condition
C2	2036	Test condition E; not applicable for UB and UBN devices.
C5	3131	$R_{\theta JA}$ and $R_{\theta JC}$ only, (see 1.3 and 4.3.4) and in accordance with thermal impedance curves.
C6		Not applicable.

4.4.3.3 Group C sample selection. Samples for subgroups in group C shall be chosen at random from any inspection lot containing the intended package type and lead finish procured to the same specification which is submitted to and passes table I tests herein for conformance inspection. When the final lead finish is solder or any plating prone to oxidation at high temperature, the samples for C6 life test may be pulled prior to the application of final lead finish. Testing of a subgroup using a single device type enclosed in the intended package type shall be considered as complying with the requirements for that subgroup.

4.4.4 Group D inspection. Conformance inspection for hardness assured JANS and JANTXV types shall include the group D tests specified in table II herein. These tests shall be performed as required in accordance with MIL-PRF-19500 and method 1019 of MIL-STD-750, for total ionizing dose or method 1017 of MIL-STD-750 for neutron fluence as applicable (see 6.2 herein), except group D, subgroup 2 may be performed separate from other subgroups. Alternate package options may also be substituted for the testing provided there is no adverse effect to the fluence profile.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

4.4.5 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in appendix E, table E-IX of MIL-PRF-19500 and as specified herein. Electrical measurements (end-points) shall be in accordance with subgroup 2 of table I and 4.5.4 herein.

4.5 Method of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows.

4.5.1 Pulse measurements. Conditions for pulse measurement shall be as specified in section 4 of MIL-STD-750.

4.5.2 Input capacitance. This test shall be conducted in accordance with method 3240 of MIL-STD-750, except the output capacitor shall be omitted.

4.5.3 Noise figure. Noise figure shall be measured using a model 310B Quan Tech Laboratories test set, or equivalent. Conditions shall be as specified in table I herein.

* 4.5.4 Delta requirements. Delta requirements shall be as specified below:

Step	Inspection	MIL-STD-750		Symbol	Limit	Unit
		Method	Conditions			
1	Collector-base cutoff current	3036	Bias condition D, V_{CB} = -100 V dc	ΔI_{CB02} (1)	100 percent of initial value or ±20 nA dc, whichever is greater.	
2	Forward current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -150 mA dc; pulsed see 4.5.1	Δh_{FE5} (1)	±25 percent change from initial reading.	

(1) Devices which exceed the table I limits for this test shall not be accepted.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 1 2/						
Visual and mechanical inspection 3/	2071					
Solderability 3/ 4/	2026	n = 15 leads, c = 0				
Resistance to solvents 3/ 4/ 5/	1022	n = 15 devices, c = 0				
* Salt atmosphere (corrosion)	1041	n = 6 devices, c = 0 (For laser marked devices only)				
Temp cycling 3/ 4/	1051	Test condition C, 25 cycles. n = 22 devices, c = 0				
Hermetic seal 4/ Fine leak Gross leak	1071	n = 22 devices, c = 0				
Electrical measurements 4/		Table I, subgroup 2				
* Decap internal visual (design verification) 4/	2075	n = 4 device, c = 0				
Subgroup 2						
Thermal impedance	3131	See 4.3.4	$Z_{\theta JX}$			°C/W
Collector to base, cutoff current	3036	Bias condition D				
2N3634, 2N3634L, UB, UBN		V_{CB} = -140 V dc	I_{CBO1}		-10	µA dc
2N3635, 2N3635L, UB, UBN		V_{CB} = -140 V dc	I_{CBO1}		-10	µA dc
2N3636, 2N3636L, UB, UBN		V_{CB} = -175 V dc	I_{CBO1}		-10	µA dc
2N3637, 2N3637L, UB, UBN		V_{CB} = -175 V dc	I_{CBO1}		-10	µA dc
Emitter to base, cutoff current	3061	Bias condition D, V_{EB} = -5 V dc	I_{EBO1}		-10	µA dc
Breakdown voltage, collector to emitter	3011	Bias condition D, I_C = -10 mA dc pulsed (see 4.5.1)	$V_{(BR)CEO}$			
2N3634, 2N3634L, UB, UBN 2N3635, 2N3635L, UB, UBN				-140		V dc
2N3636, 2N3636L, UB, UBN 2N3637, 2N3637L, UB, UBN				-175		V dc

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 2 - Continued						
Collector to base cutoff current	3036	Bias condition D, V_{CB} = -100 V dc	I_{CBO2}		-100	nA dc
Emitter to base cutoff current	3061	Bias condition D, V_{EB} = 3 V dc	I_{EBO2}		50	nA dc
Collector to emitter cutoff current	3041	Bias condition D, V_{CE} = -100 V dc	I_{CEO}		-10	µA dc
Forward-current transfer ratio	3076	V_{CE} = -10 V dc, I_C = -0.1 mA dc pulsed (see 4.5.1)	h_{FE1}			
2N3634, 2N3634L, UB, UBN 2N3636, 2N3636L, UB, UBN				25		
2N3635, 2N3635L, UB, UBN 2N3637, 2N3637L, UB, UBN				55		
Forward-current transfer ratio	3076	V_{CE} = -10 V dc, I_C = -1.0 mA dc pulsed (see 4.5.1)	h_{FE2}			
2N3634, 2N3634L, UB, UBN 2N3636, 2N3636L, UB, UBN				45		
2N3635, 2N3635L, UB, UBN 2N3637, 2N3637L, UB, UBN				90		
Forward-current transfer ratio	3076	V_{CE} = -10 V dc, I_C = -10 mA dc pulsed (see 4.5.1)	h_{FE3}			
2N3634, 2N3634L, UB, UBN 2N3636, 2N3636L, UB, UBN				50		
2N3635, 2N3635L, UB, UBN 2N3637, 2N3637L, UB, UBN				100		
Forward-current transfer ratio	3076	V_{CE} = -10 V dc, I_C = -50 mA dc pulsed (see 4.5.1)	h_{FE4}			
2N3634, 2N3634L, UB, UBN 2N3636, 2N3636L, UB, UBN				50	150	
2N3635, 2N3635L, UB, UBN 2N3637, 2N3637L, UB, UBN				100	300	
Forward-current transfer ratio	3076	V_{CE} = -10 V dc, I_C = -150 mA dc pulsed (see 4.5.1)	h_{FE5}			
2N3634, 2N3634L, UB, UBN 2N3636, 2N3636L, UB, UBN				30		
2N3635, 2N3635L, UB, UBN 2N3637, 2N3637L, UB, UBN				60		

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 2 - Continued						
Collector to emitter voltage (saturated)	3071	I_C = -10 mA dc, I_B = -1 mA dc pulsed (see 4.5.1)	$V_{CE(sat)1}$		-0.3	V dc
Collector to emitter voltage (saturated)	3071	I_C = -50 mA dc, I_B = -5 mA dc pulsed (see 4.5.1)	$V_{CE(sat)2}$		-0.6	V dc
Base-emitter voltage (saturated)	3066	Test condition A; I_C = -10 mA dc, I_B = -1.0 mA dc pulsed (see 4.5.1)	$V_{BE(sat)1}$		-0.8	V dc
Base-emitter voltage (saturated)	3066	Test condition A; I_C = -50 mA dc, I_B = -5 mA dc pulsed (see 4.5.1)	$V_{BE(sat)2}$	-0.65	-0.90	V dc
Subgroup 3						
High temperature operation:		T_A = +150°C				
Collector to base cutoff current	3036	Bias condition D, V_{CB} = -100 V dc	I_{CBO3}		-10	µA dc
Low-temperature operation:		T_A = -55°C				
Forward-current transfer ratio	3076	V_{CE} = -10 V dc, I_C = -50 mA dc	h_{FE6}			
2N3634, 2N3634L, UB, UBN 2N3636, 2N3636L, UB, UBN				25		
2N3635, 2N3635L, UB, UBN 2N3637, 2N3637L, UB, UBN				50		
Subgroup 4						
Small-signal short-circuit forward-current transfer ratio	3306	V_{CE} = -30 V dc, I_C = -30 mA dc, f = 100 MHz	$\|h_{fe}\|$			
2N3634, 2N3634L, UB, UBN 2N3636, 2N3636L, UB, UBN				1.5	8.0	
2N3635, 2N3635L, UB, UBN 2N3637, 2N3637L, UB, UBN				2.0	8.5	
Small-signal short-circuit forward current transfer ratio	3206	V_{CE} = -10 V dc, I_C = -10 mA dc, f = 1 kHz	h_{fe}			
2N3634, 2N3634L, UB, UBN 2N3636, 2N3636L, UB, UBN				40	160	
2N3635, 2N3635L, UB, UBN 2N3637, 2N3637L, UB, UBN				80	320	

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 4 - Continued						
Small-signal short-circuit input impedance	3201	V_{CE} = -10 V dc, I_C = -10 mA dc, f = 1 kHz	h_{ie}			
2N3634, 2N3634L, UB, UBN 2N3636, 2N3636L, UB, UBN				100	600	Ω
2N3635, 2N3635L, UB, UBN 2N3637, 2N3637L, UB, UBN				200	1,200	Ω
Small signal open circuit reverse voltage transfer ratio	3211	V_{CE} = -10 V dc, I_C = -10 mA dc, f = 1 kHz	h_{re}		$3x10^{-4}$	
Small signal open circuit output admittance	3216	V_{CE} = -10 V dc, I_C = -10 mA dc, f = 1 kHz	h_{oe}		200	µs
Open circuit output capacitance	3236	V_{CB} = -20 V dc, I_E = 0, 100 kHz ≤ f ≤ 1 MHz	C_{obo}		10	pF
Input capacitance (output open circuited)	3240	V_{EB} = 1 V dc, I_C = 0, 100 kHz ≤ f ≤ 1 MHz	C_{ibo}		75	pF
Noise figure	3246	V_{CE} = -10 V dc, I_C = -0.5 mA dc, R_G = 1 kΩ (see 4.5.3) f = 100 Hz f = 10 kHz f = 1 kHz	NF		 5 3 3	 dB dB dB
Pulse response	3251	Test condition A				
Switching parameters						
Pulse delay time		See figure 13	t_d		100	ns
Pulse rise time		See figure 13	t_r		100	ns
Pulse storage time		See figure 13	t_s		500	ns
Pulse fall time		See figure 13	t_f		150	ns
t_{off}		t_s & t_f	t_{off}		600	ns

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 5						
Safe operating area (continuous dc) TO-39	3051	T_C = + 25°C, t = 1s, 1 cycle (see figures 14 and 15)				
Test 1						
2N3634, 2N3634L 2N3635, 2N3635L		V_{CE} = -100 V dc, I_C = -30 mA dc				
2N3636, 2N3636L 2N3637, 2N3637L		V_{CE} = -130 V dc, I_C = -20 mA dc				
Test 2		V_{CE} = -50 V dc, I_C = -95 mA dc				
Test 3		V_{CE} = -5 V dc, I_C = -1 A dc				
Safe operating area (continuous dc) UB	3051	T_C = + 25°C, t = 100 ms, 1 cycle (see figures 16 and 17)				
Test 1						
2N3634UB, 2N3635UB, 2N3634UBN, 2N3635UBN		V_{CE} = -85 V dc, I_C = -30 mA dc				
2N3636UB, 2N3637UB 2N3636UBN, 2N3637UBN		V_{CE} = -125 V dc, I_C = -20 mA dc				
Test 2		V_{CE} = -50 V dc, I_C = -50 mA dc				
Test 3		V_{CE} = -5 V dc, I_C = -500 mA dc				
End-point electrical measurements		Subgroup 2 of table I.				
Subgroups 6 and 7						
Not applicable						

1/ For sampling plan see MIL-PRF-19500.
2/ For resubmission of failed table I, subgroup 1, double the sample size of the failed test or sequence of tests. A failure in table I, subgroup 1 shall not require retest of the entire subgroup. Only the failed test shall be rerun upon submission.
3/ Separate samples may be used.
4/ Not required for JANS devices.
5/ Not required for laser marked devices.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

TABLE II. Group D inspection.

Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limit		Unit
	Method	Conditions		Min	Max	
Subgroup 1 4/						
Neutron irradiation	1017	Neutron exposure V_{CES} = 0 V				
Collector to base, cutoff current	3036	Bias condition D				
2N3634, 2N3634L, UB, UBN		V_{CB} = -140 V dc	I_{CBO1}		-20	µA dc
2N3635, 2N3635L, UB, UBN		V_{CB} = -140 V dc	I_{CBO1}		-20	µA dc
2N3636, 2N3636L, UB, UBN		V_{CB} = -175 V dc	I_{CBO1}		-20	µA dc
2N3637, 2N3637L, UB, UBN		V_{CB} = -175 V dc	I_{CBO1}		-20	µA dc
Emitter to base, cutoff current	3061	Bias condition D, V_{EB} = -5 V dc	I_{EBO1}		-20	µA dc
Breakdown voltage, collector to emitter	3011	Bias condition D, I_C = -10 mA dc pulsed (see 4.5.1)	$V_{(BR)CEO}$			
2N3634, 2N3634L, UB, UBN 2N3635, 2N3635L, UB, UBN				-140		V dc
2N3636, 2N3636L, UB, UBN 2N3637, 2N3637L, UB, UBN				-175		V dc
Collector to base cutoff current	3036	Bias condition D, V_{CB} = -100 V dc	I_{CBO2}		-200	nA dc
Emitter to base cutoff current	3061	Bias condition D, V_{EB} = 3 V dc	I_{EBO2}		100	nA dc
Collector to emitter cutoff current	3041	Bias condition D, V_{CE} = -100 V dc	I_{CEO}		-20	µA dc
Forward-current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -0.1 mA dc	[h_{FE1}] 5/			
2N3634, 2N3636 2N3635, 2N3637				[12.5] [27.5]		
Forward-current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -1.0 mA dc	[h_{FE2}] 5/			
2N3634, 2N3636 2N3635, 2N3637				[22.5] [45]		
Forward-current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -10 mA dc	[h_{FE3}] 5/			
2N3634, 2N3636 2N3635, 2N3637				[25] [50]		
Forward-current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -50 mA dc	[h_{FE4}] 5/			
2N3634, 2N3636 2N3635, 2N3637				[25] [50]	150 300	

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

TABLE II. Group D inspection - Continued.

Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limit		Unit
	Method	Conditions		Min	Max	
Subgroup 1 - Continued.						
Forward-current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -150 mA dc	[h_{FE5}] 5/			
2N3634, 2N3636 2N3635, 2N3637				[15] [30]		
Collector-emitter saturation voltage	3071	I_C = -10 mA dc; I_B = -1.0 mA dc	$V_{CE(sat)1}$		-.35	V dc
Collector-emitter saturation voltage	3071	I_C = -50 mA dc; I_B = -5.0 mA dc	$V_{CE(sat)2}$		-.69	V dc
Base-emitter voltage (saturated)	3066	Test condition A; I_C = -10 mA dc, I_B = -1.0 mA dc pulsed (see 4.5.1)	$V_{BE(sat)1}$		-.92	V dc
Base-emitter voltage (saturated)	3066	Test condition A; I_C = -50 mA dc, I_B = -5 mA dc pulsed (see 4.5.1)	$V_{BE(sat)2}$	-.65	-1.04	V dc
Subgroup 2						
Total dose irradiation	1019	Gamma exposure				
2N3634, 2N3636 2N3635, 2N3637		V_{CES} = -112 V V_{CES} = -140 V				
Collector to base, cutoff current	3036	Bias condition D				
2N3634, 2N3634L, UB, UBN		V_{CB} = -140 V dc	I_{CBO1}		-20	µA dc
2N3635, 2N3635L, UB, UBN		V_{CB} = -140 V dc	I_{CBO1}		-20	µA dc
2N3636, 2N3636L, UB, UBN		V_{CB} = -175 V dc	I_{CBO1}		-20	µA dc
2N3637, 2N3637L, UB, UBN		V_{CB} = -175 V dc	I_{CBO1}		-20	µA dc
Emitter to base, cutoff current	3061	Bias condition D, V_{EB} = 5 V dc	I_{EBO1}		20	µA dc
Breakdown voltage, collector to emitter	3011	Bias condition D, I_C = -10 mA dc pulsed (see 4.5.1)	$V_{(BR)CEO}$			
2N3634, 2N3634L, UB, UBN 2N3635, 2N3635L, UB, UBN				-140		V dc
2N3636, 2N3636L, UB, UBN 2N3637, 2N3637L, UB, UBN				-175		V dc
Collector to base cutoff current	3036	Bias condition D, V_{CB} = -100 V dc	I_{CBO2}		-200	nA dc
Emitter to base cutoff current	3061	Bias condition D, V_{EB} = 3 V dc	I_{EBO2}		100	nA dc
Collector to emitter cutoff current	3041	Bias condition D, V_{CE} = -100 V dc	I_{CEO}		-20	µA dc

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

TABLE II. Group D inspection - Continued.

Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limit		Unit
	Method	Conditions		Min	Max	
Subgroup 2 - Continued.						
Forward-current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -0.1 mA dc	[h_{FE1}] 5/			
2N3634, 2N3636 2N3635, 2N3637				[12.5] [27.5]		
Forward-current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -1.0 mA dc	[h_{FE2}] 5/			
2N3634, 2N3636 2N3635, 2N3637				[22.5] [45]		
Forward-current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -10 mA dc	[h_{FE3}] 5/			
2N3634, 2N3636 2N3635, 2N3637				[25] [50]		
Forward-current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -50 mA dc	[h_{FE4}] 5/			
2N3634, 2N3636 2N3635, 2N3637				[25] [50]	150 300	
Forward-current transfer ratio	3076	V_{CE} = -10 V dc; I_C = -150 mA dc	[h_{FE5}] 5/			
2N3634, 2N3636 2N3635, 2N3637				[15] [30]		
Collector-emitter saturation voltage	3071	I_C = -10 mA dc; I_B = -1.0 mA dc;	$V_{CE(sat)1}$		-.35	V dc
Collector-emitter saturation voltage	3071	I_C = -50 mA dc; I_B = -5.0 mA dc;	$V_{CE(sat)2}$		-.69	V dc
Base-emitter voltage (saturated)	3066	Test condition A; I_C = -10 mA dc, I_B = -1.0 mA dc pulsed (see 4.5.1)	$V_{BE(sat)1}$		-.92	V dc
Base-emitter voltage (saturated)	3066	Test condition A; I_C = -50 mA dc, I_B = -5 mA dc pulsed (see 4.5.1)	$V_{BE(sat)2}$	.65	-1.04	V dc


1/ Tests to be performed on all devices receiving radiation exposure.
2/ For sampling plan, see MIL-PRF-19500.
3/ Electrical characteristics apply to device types unless otherwise noted.
4/ Subgroup 1 is an optional test and must be specified on the contract when required.
5/ See method 1019 of MIL-STD-750 for how to determine [h_{FR}] by first calculating the delta (1/h_{FE}) from the pre- and post-radiation h_{FE}. Notice the [h_{FE}] is not the same as h_{FE} and cannot be measured directly. The [h_{FE}] value can never exceed the pre-radiation minimum h_{FE} that it is based upon.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

TABLE III. Group E inspection (all quality levels) - for qualification only.

Inspection	MIL-STD-750		Qualification
	Method	Conditions	
Subgroup 1			45 devices c = 0
Temperature cycling (air to air)	1051	Test condition C, 500 cycles	
Hermetic seal	1071		
Fine leak Gross leak			
Electrical measurements		See table I, subgroup 2 and 4.5.4 herein.	
Subgroup 2			45 devices c = 0
Intermittent life	1037	V_{CB} = -10 V dc, 6,000 cycles. Adjust device current, or power, to achieve a minimum ΔT_J of +100°C.	
Electrical measurements		See table I of subgroup 2 and 4.5.4 herein.	
Subgroup 4			15 devices, c = 0
Thermal resistance	3131	$R_{\theta JSP}$ can be calculated but shall be measured once in the same package with a similar die size to confirm calculations (may apply to multiple specification sheets).	
Thermal impedance curves		See MIL-PRF-19500, table E-IX, group E, subgroup 4.	Sample size N/A
Subgroup 5			
Not applicable			
Subgroup 8			45 devices c = 0
Reverse stability	1033	Condition B.	

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

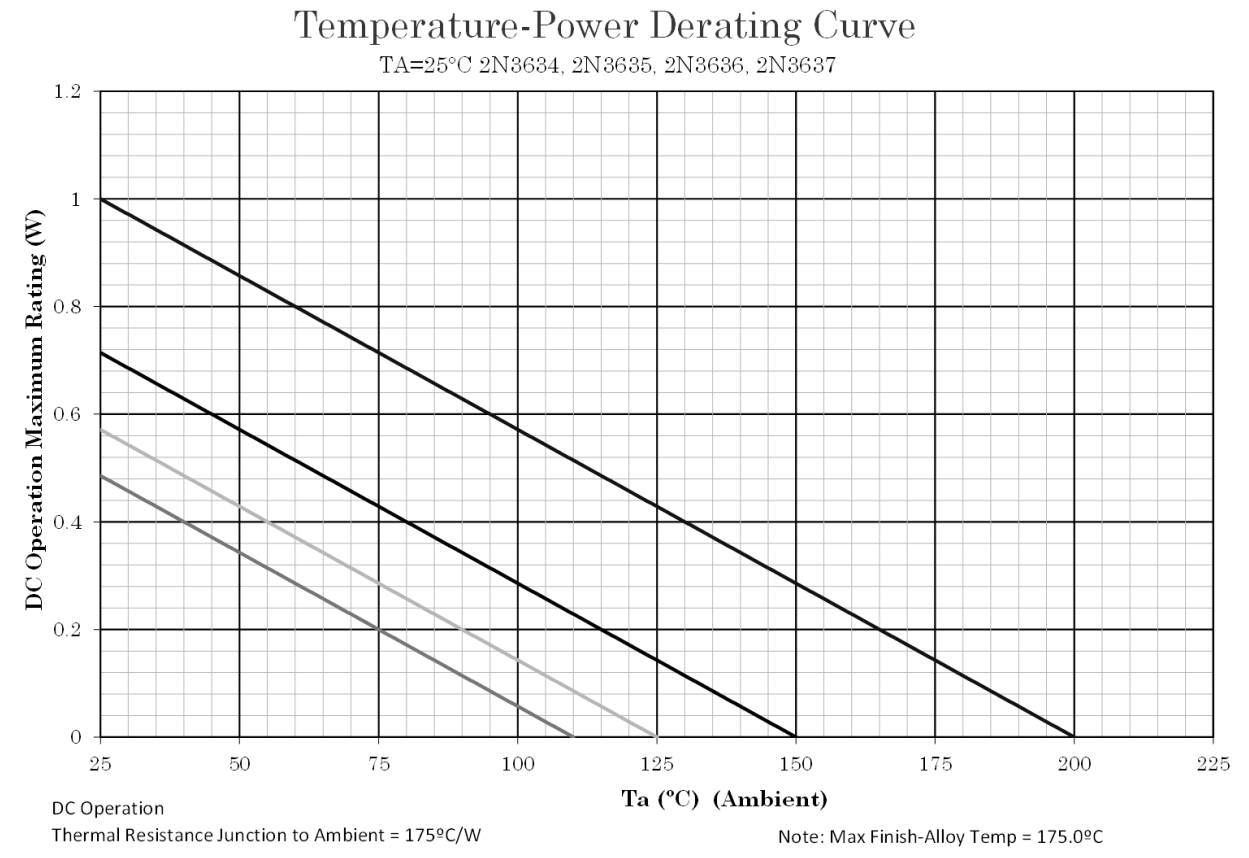


NOTES:

1. This is the true inverse of the worst case thermal resistance value. All devices are capable of operating at ≤ T_J specified on this curve. Any parallel line to this curve will intersect the appropriate power for the desired maximum T_J allowed.
2. Derate design curve constrained by the maximum junction temperature (T_J ≤ 200°C) and power rating specified. (See 1.3 herein.)
3. Derate design curve chosen at T_J ≤ 150°C, where the maximum temperature of electrical test is performed.
4. Derate design curve chosen at T_J ≤ 125°C, and 110°C to show power rating where most users want to limit T_J in their application.

FIGURE 6. Temperature-power derating for ($R_{\theta JA}$), base case mount (TO-5 and TO-39).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

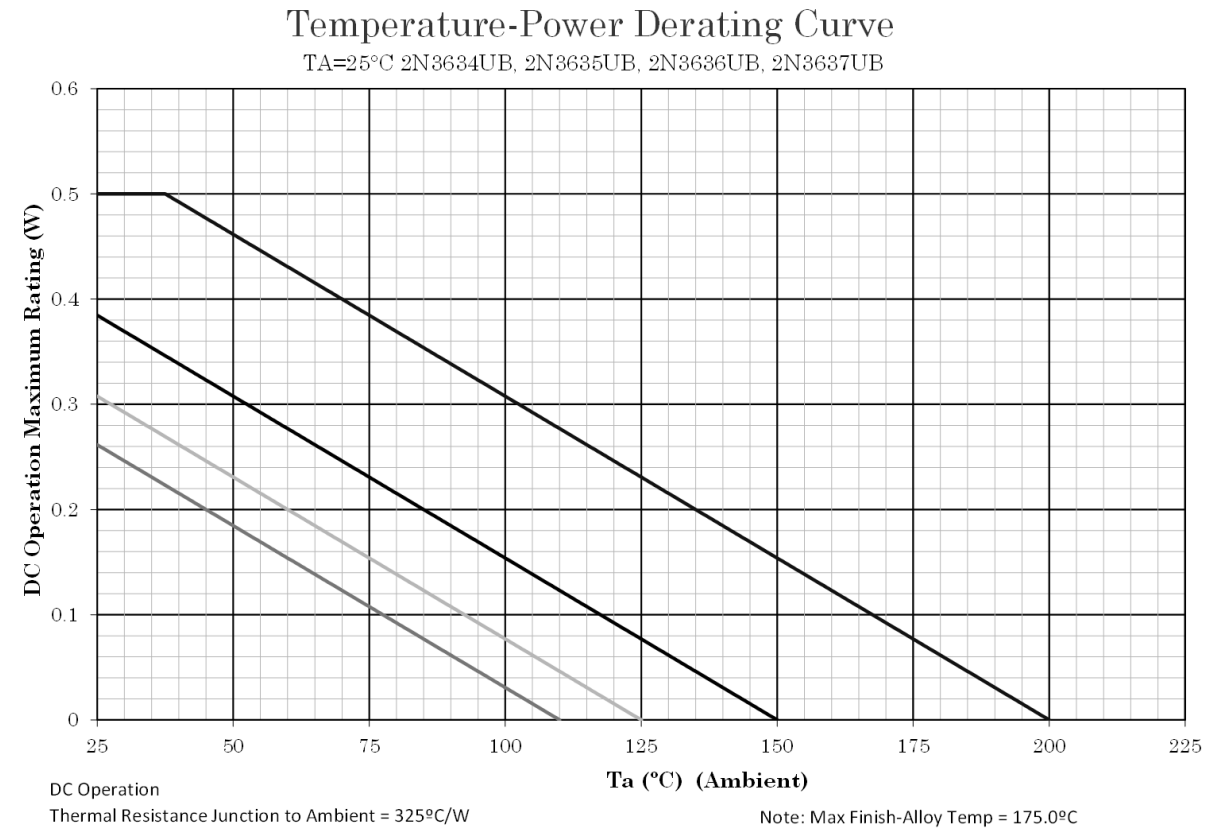


NOTES:

1. This is the true inverse of the worst case thermal resistance value. All devices are capable of operating at $\leq T_J$ specified on this curve. Any parallel line to this curve will intersect the appropriate power for the desired maximum T_J allowed.
2. Derate design curve constrained by the maximum junction temperature ($T_J \leq 200°C$) and power rating specified. (See 1.3 herein.)
3. Derate design curve chosen at $T_J \leq 150°C$, where the maximum temperature of electrical test is performed.
4. Derate design curve chosen at $T_J \leq 125°C$, and 110°C to show power rating where most users want to limit T_J in their application.

FIGURE 7. Temperature-power derating for ($R_{\theta JA}$) (UB AND UBN).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

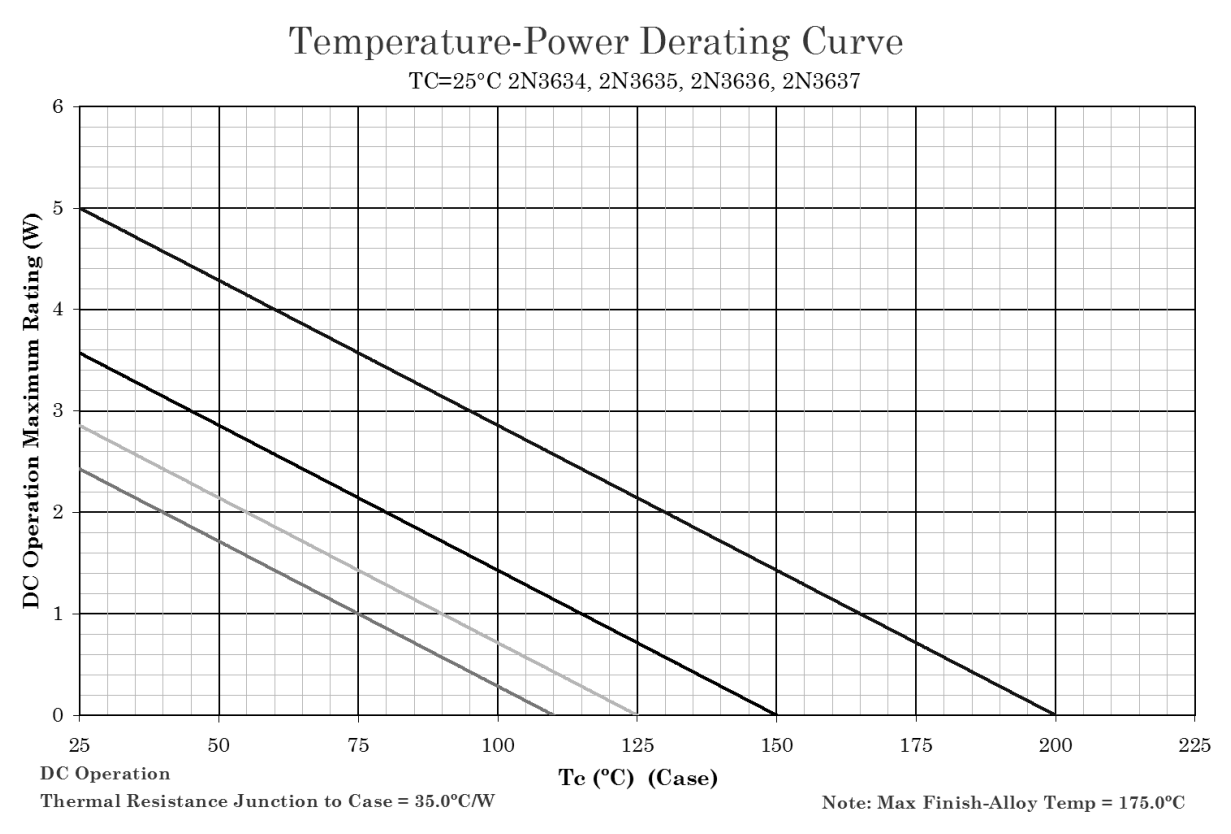


NOTES:

1. This is the true inverse of the worst case thermal resistance value. All devices are capable of operating at $\leq T_J$ specified on this curve. Any parallel line to this curve will intersect the appropriate power for the desired maximum T_J allowed.
2. Derate design curve constrained by the maximum junction temperature ($T_J \leq 200°C$) and power rating specified. (See 1.3 herein.)
3. Derate design curve chosen at $T_J \leq 150°C$, where the maximum temperature of electrical test is performed.
4. Derate design curve chosen at $T_J \leq 125°C$, and 110°C to show power rating where most users want to limit T_J in their application.

FIGURE 8. Temperature-power derating for ($R_{\theta JC}$), base case mount (TO-5 and TO-39 Kovar).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

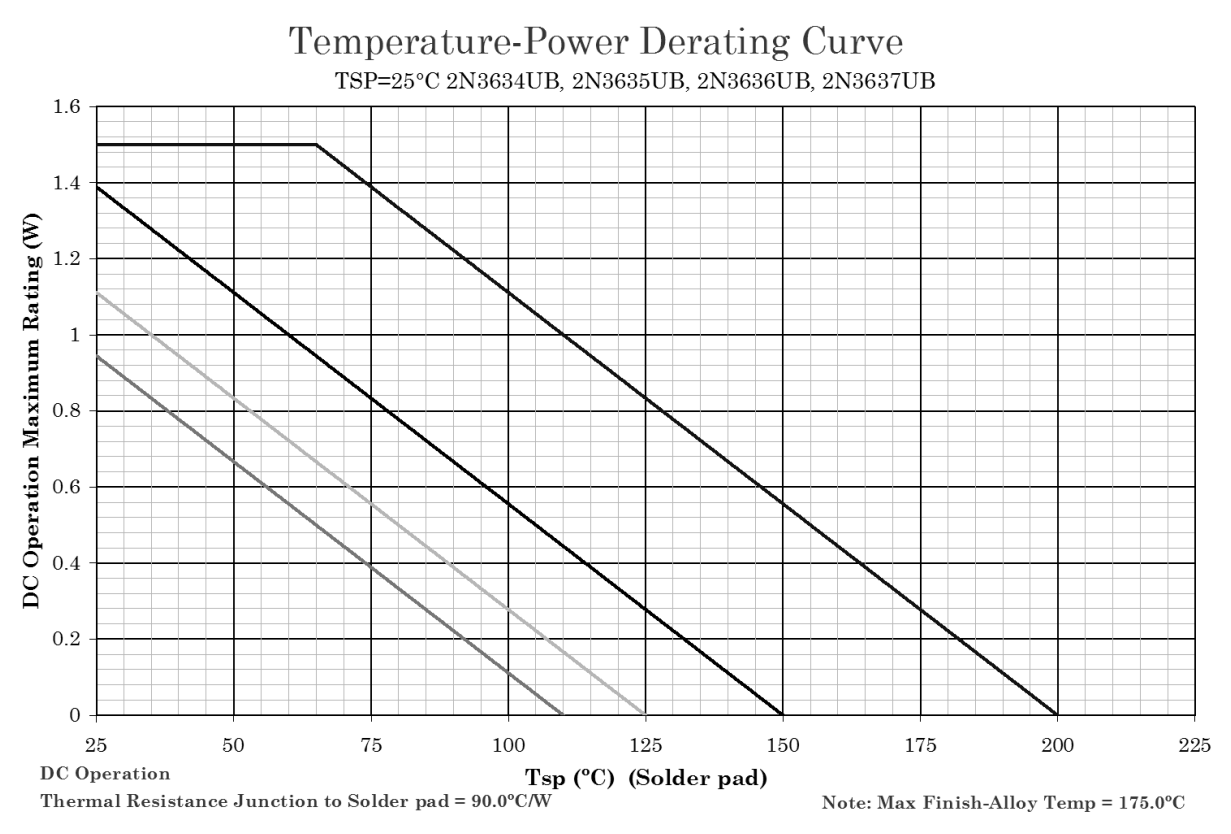


NOTES:

1. This is the true inverse of the worst case thermal resistance value. All devices are capable of operating at ≤ T_J specified on this curve. Any parallel line to this curve will intersect the appropriate power for the desired maximum T_J allowed.
2. Derate design curve constrained by the maximum junction temperature (T_J ≤ 200°C) and power rating specified. (See 1.3 herein.)
3. Derate design curve chosen at T_J ≤ 150°C, where the maximum temperature of electrical test is performed.
4. Derate design curve chosen at T_J ≤ 125°C, and 110°C to show power rating where most users want to limit T_J in their application.

FIGURE 9. Temperature-power derating for ($R_{\theta JSP}$), base case mount (UB AND UBN).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

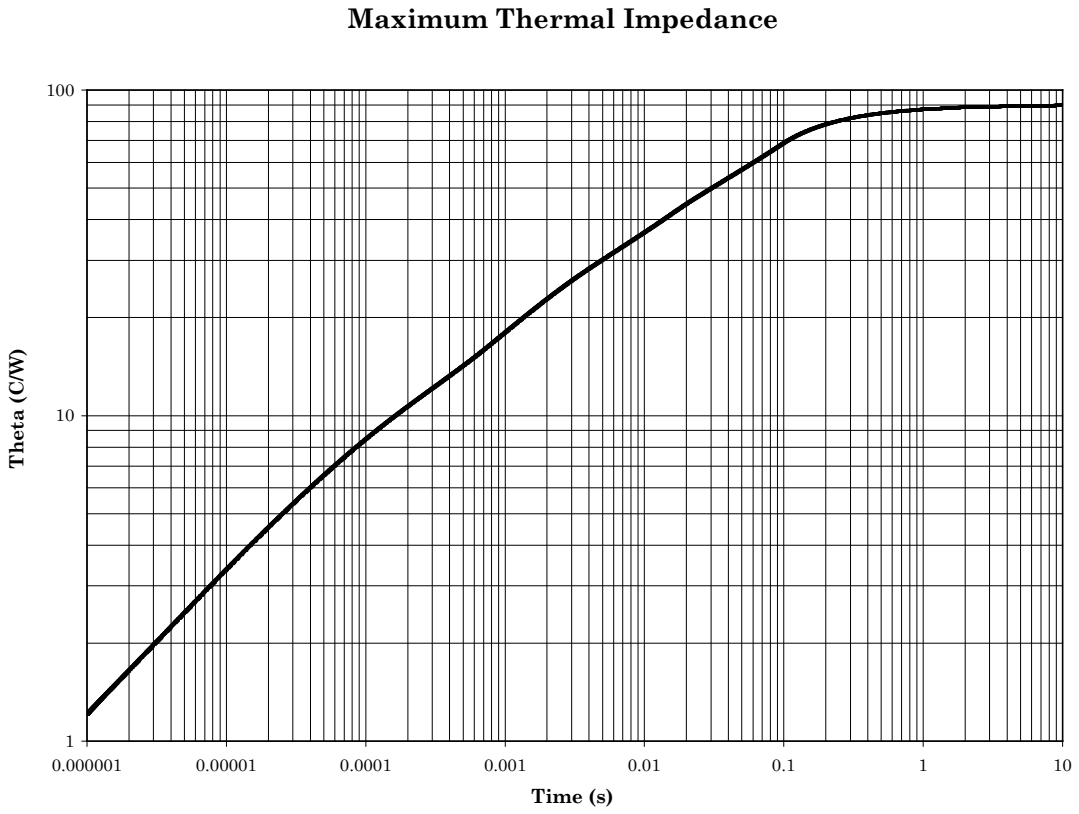


T_{SP} = +25°C, thermal resistance $R_{\theta JSP}$ = 90°C/W (solder mounted to heavy copper clad PCB).

FIGURE 10. Thermal impedance graph ($R_{\theta JSP}$) for 2N3634UB through 2N3637UB (UB AND UBN).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

Maximum Thermal Impedance

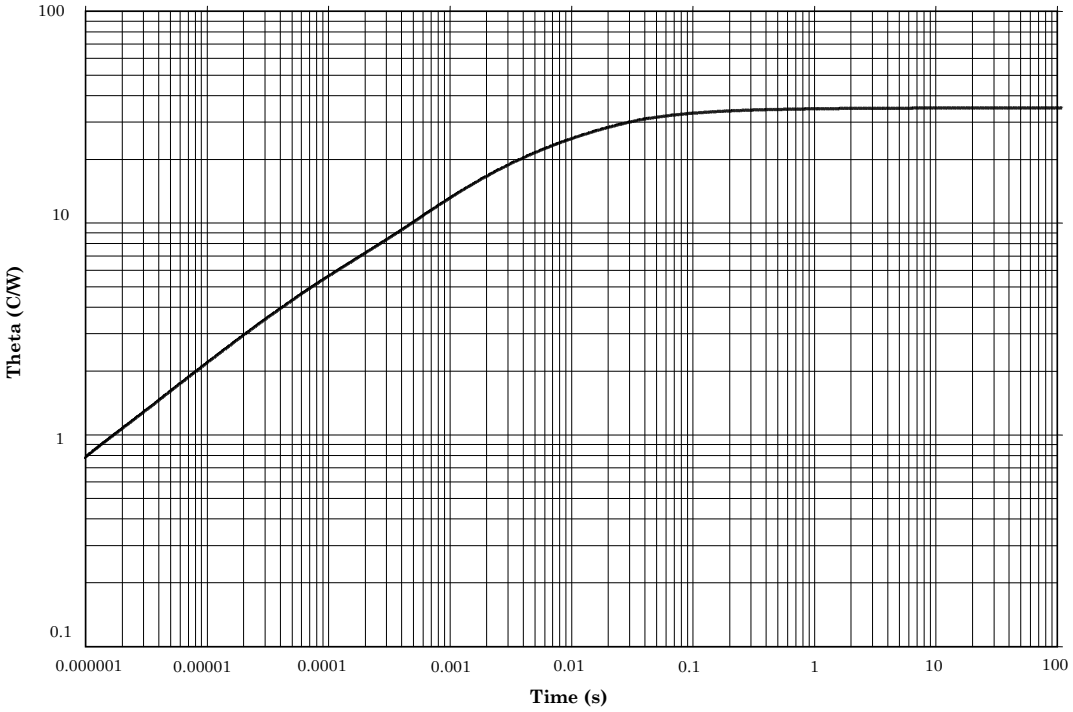


T_C = +25°C, thermal resistance $R_{\theta JC}$ = 35°C/W (ambient case mount).

FIGURE 11. Thermal impedance graph ($R_{\theta JC}$) for 2N3634 through 2N3637 and 2N3634L through 2N3637L (TO-5 and TO-39 Kovar).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.


Maximum Thermal Impedance

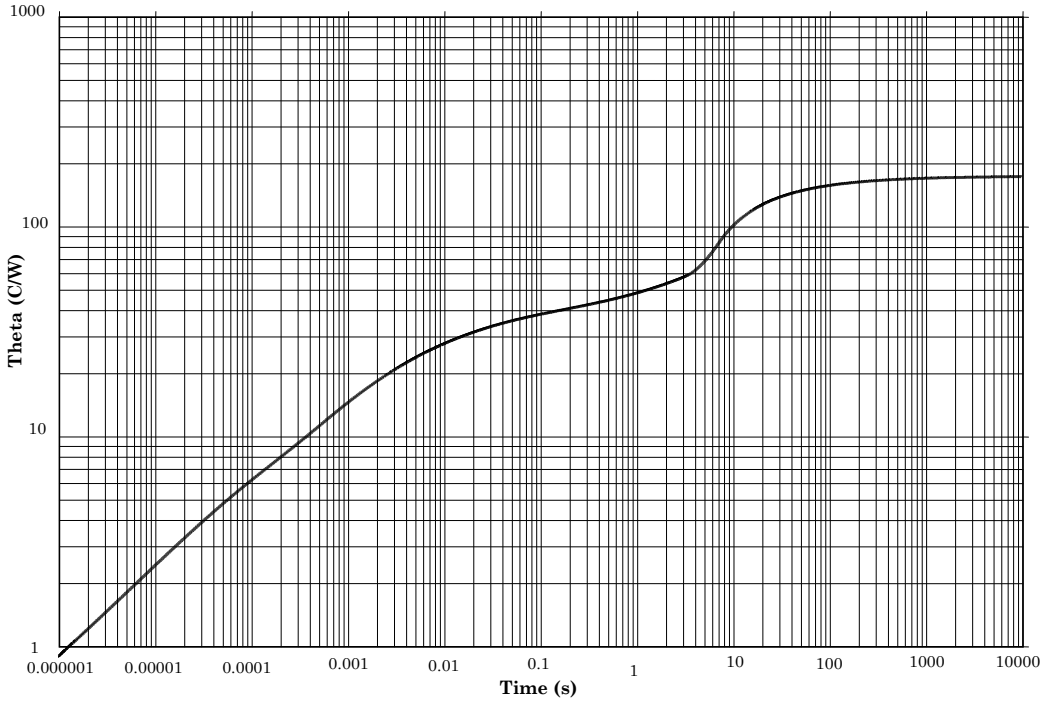


T_A = +25°C, thermal resistance $R_{\theta JA}$ = 175°C/W (ambient free air cooled).

FIGURE 12. Thermal impedance graph ($R_{\theta JA}$) for 2N3634 through 2N3637 and 2N3634L through 2N3637L (TO-5 and TO-39).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

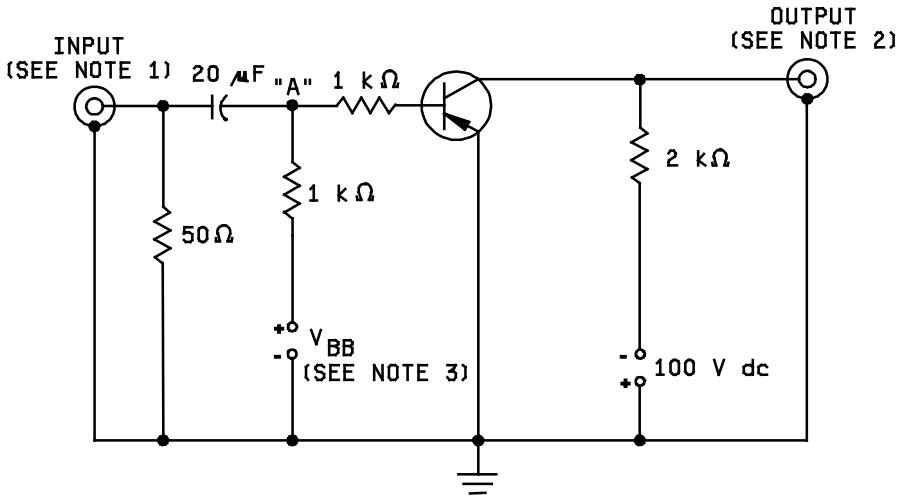

TEST CIRCUIT

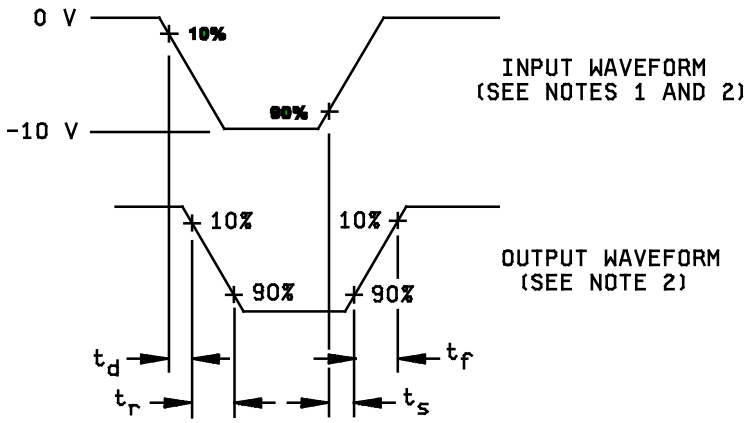


NOTES:

1. The input waveform is supplied by a pulse generator with the following characteristics: $t_r \leq 15$ ns, $t_f \leq 15$ ns, $Z_{OUT} = 50\ \Omega$, PW = 20 µs, duty cycle ≤ 2 percent.
2. Output waveforms are monitored on an oscilloscope with the following characteristics: $t_r \leq 15$ ns, $R_{in} \geq 10\ M\Omega$, $C_{in} \leq 11.5$ pF.
3. V_{BB} = 4.0 V dc for t_{on}, 4.1 V dc for t_{off} at point "A".
4. Resistors shall be noninductive types.
5. The dc power supplies may require additional by-passing in order to minimize ringing.

FIGURE 13. Pulse response test circuit.


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

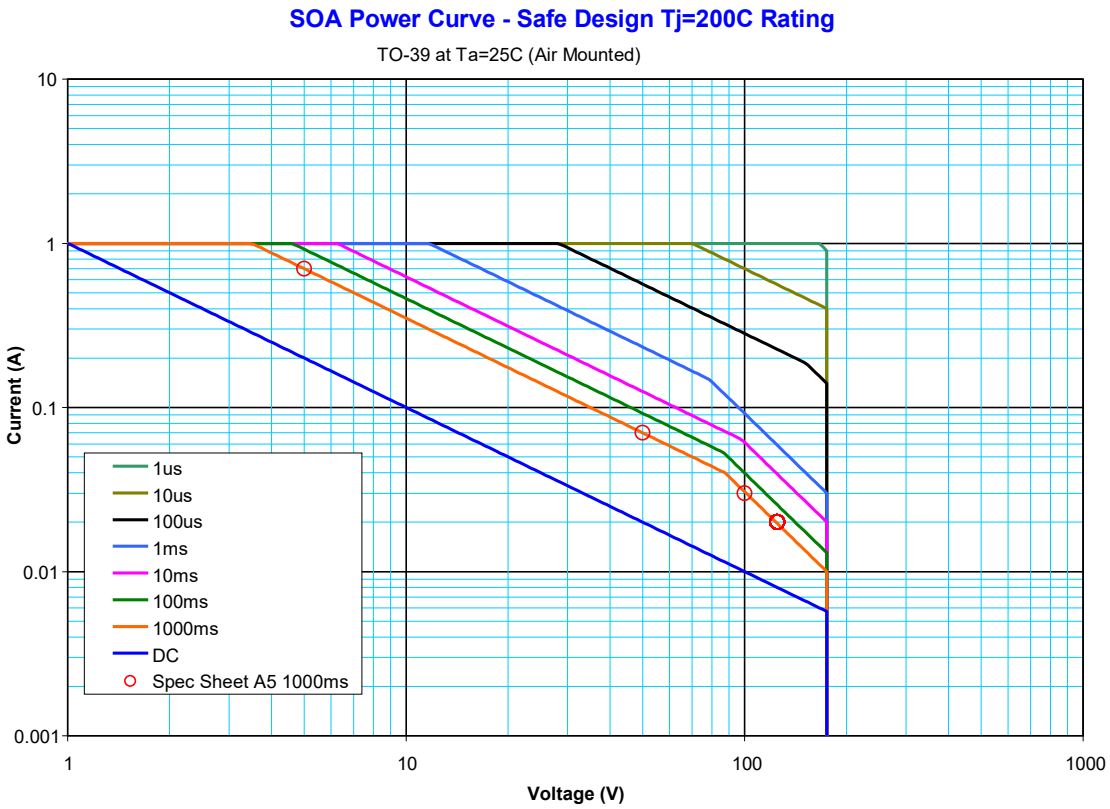

2N3637 T_A = +25°C. A5 limits at 1,000 ms.
V_{CE} = 5V at 0.7A,
V_{CE} = 50V at 0.07A,
V_{CE} = 100V at 0.03A,
V_{CE} = 125V at 0.02A.

FIGURE 14. Maximum safe operating area graph (continuous dc).


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

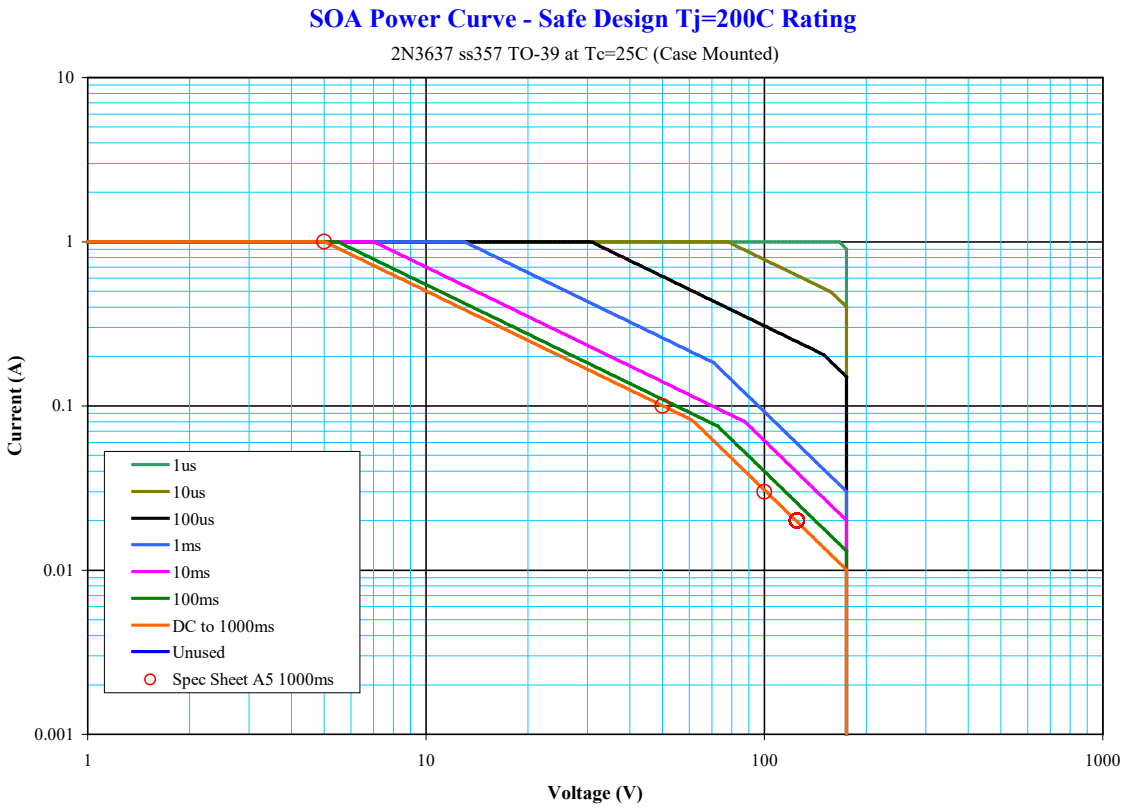

2N3637 T_C = +25°C. A5 limits at 1,000 ms.
V_{CE} = 5V at 1A,
V_{CE} = 50V at 0.095A,
V_{CE} = 100V at 0.03A,
V_{CE} = 130V at 0.02A.

FIGURE 15. Maximum safe operating area graph (continuous dc).


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

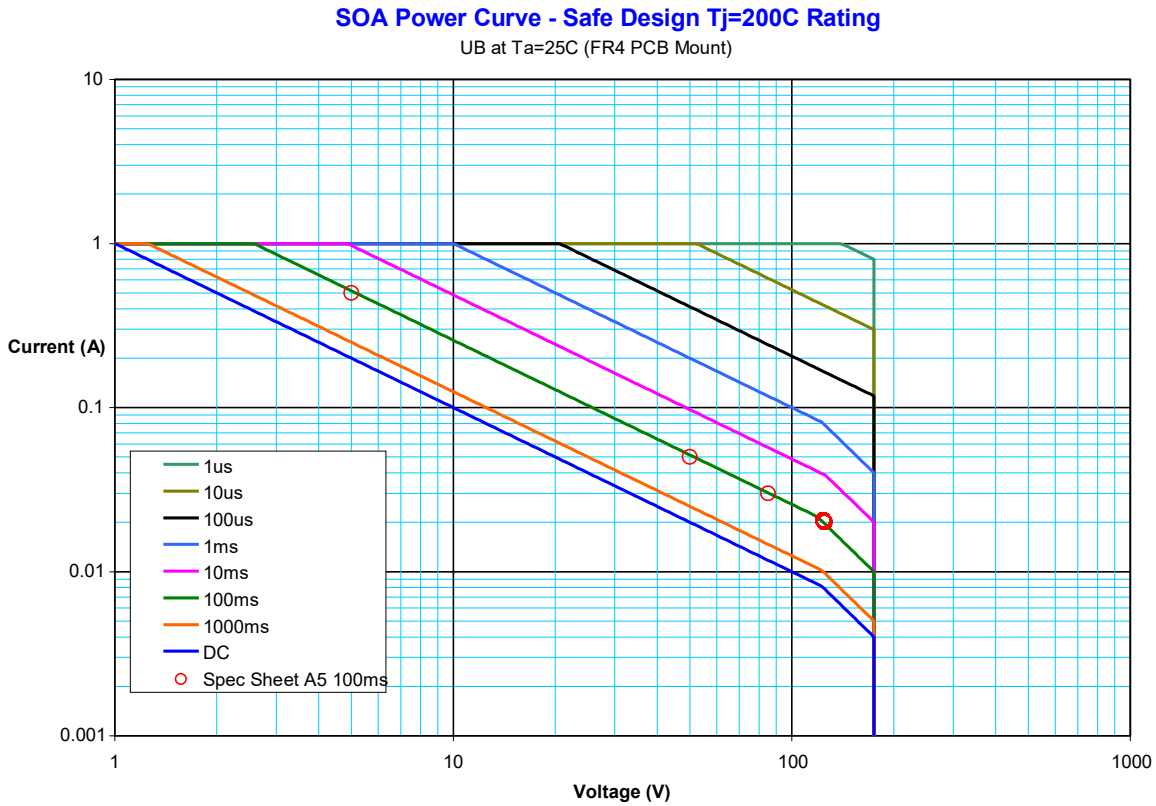

2N3637UB T_A = +25°C. A5 limits at 100 ms.
V_{CE} = 5V at 0.5A,
V_{CE} = 50V at 0.05A,
V_{CE} = 85V at 0.03A,
V_{CE} = 125V at 0.02A.

FIGURE 16. Maximum safe operating area graph for UB AND UBN (continuous dc).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

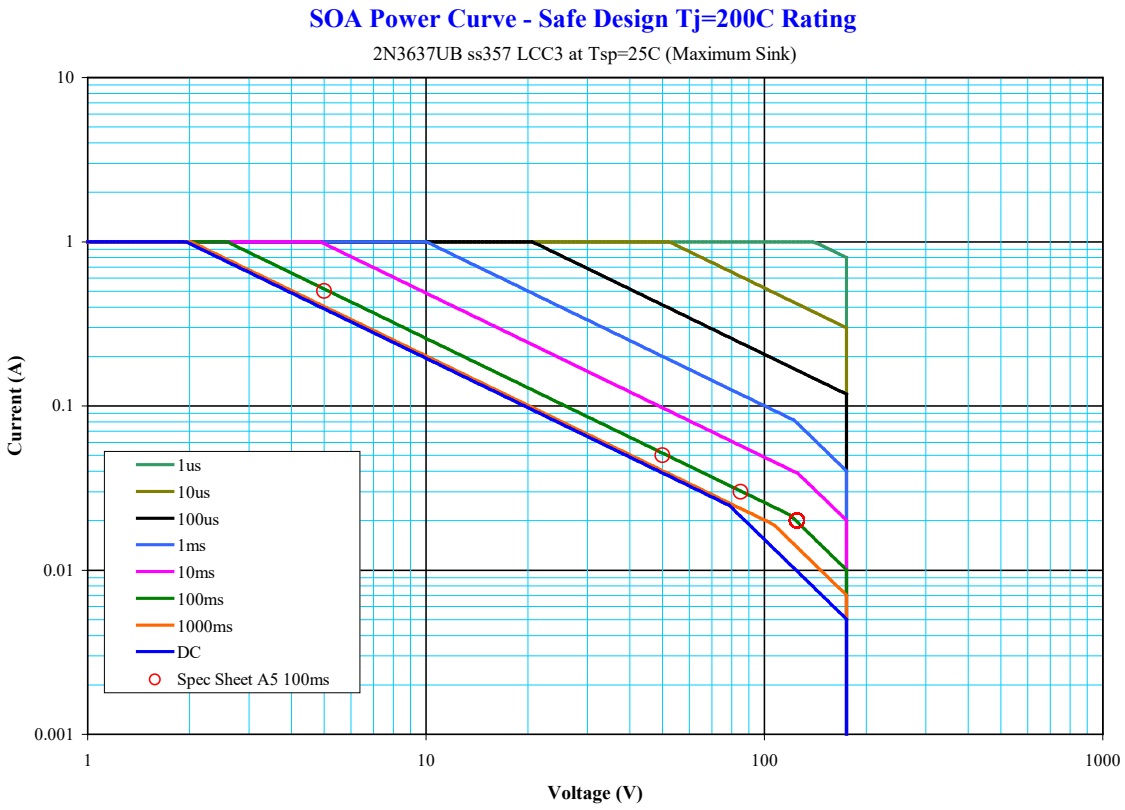

2N3637UB T_{SP} = +25°C. A5 limits at 100 ms.
V_{CE} = 5V at 0.5A,
V_{CE} = 50V at 0.05A,
V_{CE} = 85V at 0.03A,
V_{CE} = 125V at 0.02A.

FIGURE 17. Maximum safe operating area graph for UB AND UBN (continuous dc).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the Military Service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory. The notes specified in MIL-PRF-19500 are applicable to this specification.)

6.1 Intended use. Semiconductors conforming to this specification are intended for original equipment design applications and logistic support of existing equipment.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Packaging requirements (see 5.1).

c. Lead finish (see 3.4.1).

d. The complete Part or Identifying Number (PIN), see 1.5 and 6.6.

e. For die acquisition, the JANHC or JANKC letter version shall be specified (see figures 3, 4, and 5).

f. Surface mount designation if applicable.

g. For acquisition of RHA designed devices, table II, subgroup 1 testing of group D is optional. If subgroup 1 testing is desired, it must be specified in the contract.


6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List (QML-19500) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from DLA Land and Maritime, ATTN: VQE, P.O. Box 3990, Columbus, OH 43218-3990 or e-mail vqe.chief@dla.mil. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://assist.dla.mil.

6.4 Supersession information. Devices covered by this specification supersede the manufacturers' and users' Part or Identifying Number (PIN). The term Part or Identifying Number (PIN) is equivalent to the term part number which was previously used in this specification. This information in no way implies that manufacturers' PINs are suitable as a substitute for the military PIN.


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

6.5 PIN construction example.

6.5.1 PIN construction example for encapsulated devices. The PINs for encapsulated devices are construction using the following form.

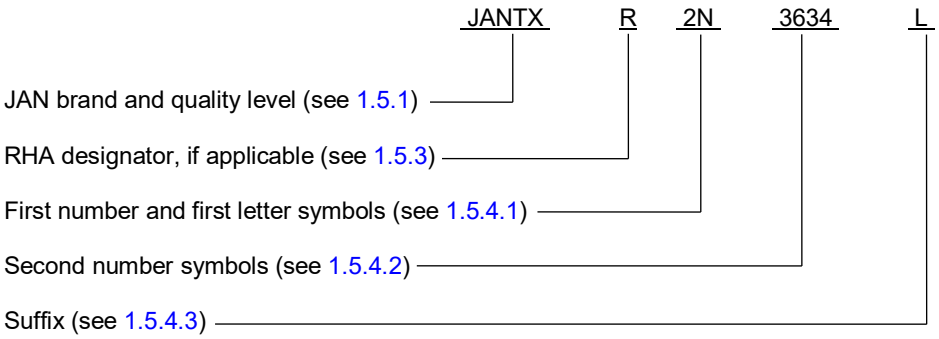

6.5.2 Un-encapsulated devices. The PINs for un-encapsulated devices are constructed using the following form.

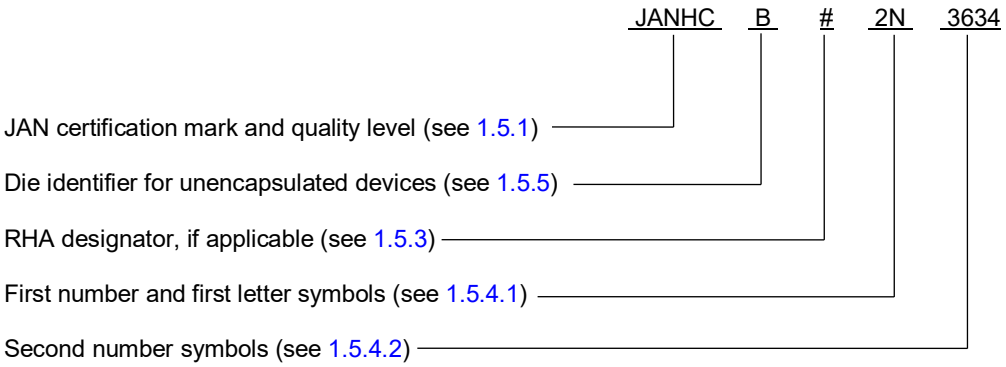

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

6.6 List of PINs.

6.6.1 List of PINs for encapsulated devices. The following is a list of possible PINs for encapsulated devices available on this specification sheet.

PINs for devices of the base quality level	PINs for devices of the "TX" quality level	PINs for devices of the "TXV" quality level (1)	PINs for devices of the "S" quality level (1)
JAN2N3634	JANTX2N3634	JANTXV#2N3634	JANS#2N3634
JAN2N3634L	JANTX2N3634L	JANTXV#2N3634L	JANS#2N3634L
JAN2N3634UB	JANTX2N3634UB	JANTXV#2N3634UB	JANS#2N3634UB
JAN2N3634UBN	JANTX2N3634UBN	JANTXV#2N3634UBN	JANS#2N3634UBN
JAN2N3635	JANTX2N3635	JANTXV#2N3635	JANS#2N3635
JAN2N3635L	JANTX2N3635L	JANTXV#2N3635L	JANS#2N3635L
JAN2N3635UB	JANTX2N3635UB	JANTXV#2N3635UB	JANS#2N3635UB
JAN2N3635UBN	JANTX2N3635UBN	JANTXV#2N3635UBN	JANS#2N3635UBN
JAN2N3636	JANTX2N3636	JANTXV#2N3636	JANS#2N3636
JAN2N3636L	JANTX2N3636L	JANTXV#2N3636L	JANS#2N3636L
JAN2N3636UB	JANTX2N3636UB	JANTXV#2N3636UB	JANS#2N3636UB
JAN2N3636UBN	JANTX2N3636UBN	JANTXV#2N3636UBN	JANS#2N3636UBN
JAN2N3637	JANTX2N3637	JANTXV#2N3637	JANS#2N3637
JAN2N3637L	JANTX2N3637L	JANTXV#2N3637L	JANS#2N3637L
JAN2N3637UB	JANTX2N3637UB	JANTXV#2N3637UB	JANS#2N3637UB
JAN2N3637UBN	JANTX2N3637UBN	JANTXV#2N3637UBN	JANS#2N3637UBN

(1) The number sign (#) represent one of eight RHA designators available (M, D, P, L, R, F, G, or H) if desired. Remove for no RHA.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.

6.6.2 List of PINs for unencapsulated devices. The following is a list of possible PINs available on this specification sheet. The qualified JANHC and JANKC suppliers with the applicable letter version (example JANHCA2N3634) will be identified on the QML.

JANHC and JANKC ordering information (1)			
PIN	Manufacturer		
	43611	31471	34156
2N3634	JANHCA#2N3634 JANKCA#2N3634	JANHCB#2N3634 JANKCB#2N3634	JANHCC#2N3634 JANKCC#2N3634
2N3635	JANHCA#2N3635 JANKCA#2N3635	JANHCB#2N3635 JANKCB#2N3635	JANHCC#2N3635 JANKCC#2N3635
2N3636	JANHCA#2N3636 JANKCA#2N3636	JANHCB#2N3636 JANKCB#2N3636	JANHCC#2N3636 JANKCC#2N3636
2N3637	JANHCA#2N3637 JANKCA#2N3637	JANHCB#2N3637 JANKCB#2N3637	JANHCC#2N3637 JANKCC#2N3637

(1) The number sign (#) represent one of eight RHA designators available (M, D, P, L, R, F, G, or H) if desired. Remove for no RHA.

6.7 Changes from previous issue. The margins of this specification are marked with asterisks to indicate where changes from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

Custodians:
Army - CR
Navy - EC
Air Force - 85
NASA - NA
DLA - CC

Review activities:
Army - AR, MI, SM
Navy - AS, MC, SH
Air Force - 19, 71

Preparing activity:
DLA - CC

(Project 5961-2020-065)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:48Z
Check the source to verify that this is the current version before use.