JJ-G-451c
MAY 25, 1960
SUPERSEDING
Int. Fed. Spec. JJ–G–00451b(GSA–FSS)
February 25, 1960 and
Fed. Spec. JJ–G–451a
June 28, 1955

FEDERAL SPECIFICATION

GLOVES, CLOTH, LEATHER PALM

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope.—This specification covers men's and women's cotton gloves with leather palms and having a gauntlet or knitted wristlet.

1.2 Classification.

1.2.1 *Types and classes.*—The gloves shall be of the following types and classes as specified (see 6.1):

Type I.—Gauntlet.
Class 1.—Men's ("M" size).

Type II.—Knitted wristlet.
Class 1.—Men's ("M" size).
Class 2.—Women's ("W" size).

2. APPLICABLE SPECIFICATIONS AND STANDARDS

2.1 The following specifications and standards, of the issues in effect on date of invitation for bids, form a part of this specification:

Federal Specifications:

V–T–276—Thread, Cotton.
KK–L–311—Leather; Methods of Sampling and Testing.
UU–T–111 — Tape, Paper, Gummed (Sealing and Securing).
CCC–T–191—Textile Test Methods.
DDD–B–331—Binding; Cotton, Bias-Cut.
PPP–B–566 — Boxes, Folding, Paperboard.
PPP–B–591—Boxes, Fiberboard, Wood-Cleated.
PPP–B–601—Boxes, Wood, Cleated-Plywood.
PPP–B–621—Boxes, Wood, Nailed and Lock-Corner.
PPP–B–636—Box, Fiberboard.
PPP–B–676—Boxes, Set-Up, Paperboard.

Federal Standards:

Fed. Std. No. 102—Preservation, Packaging and Packing Levels.
Fed. Std. No. 123—Marking for Domestic Shipment (Civilian Agencies).
Fed. Std. No. 751—Stitches, seams and Stitching.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications, Standards, and Handbooks and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington 25, D. C.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, Los Angeles, Seattle, and Washington, D. C.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

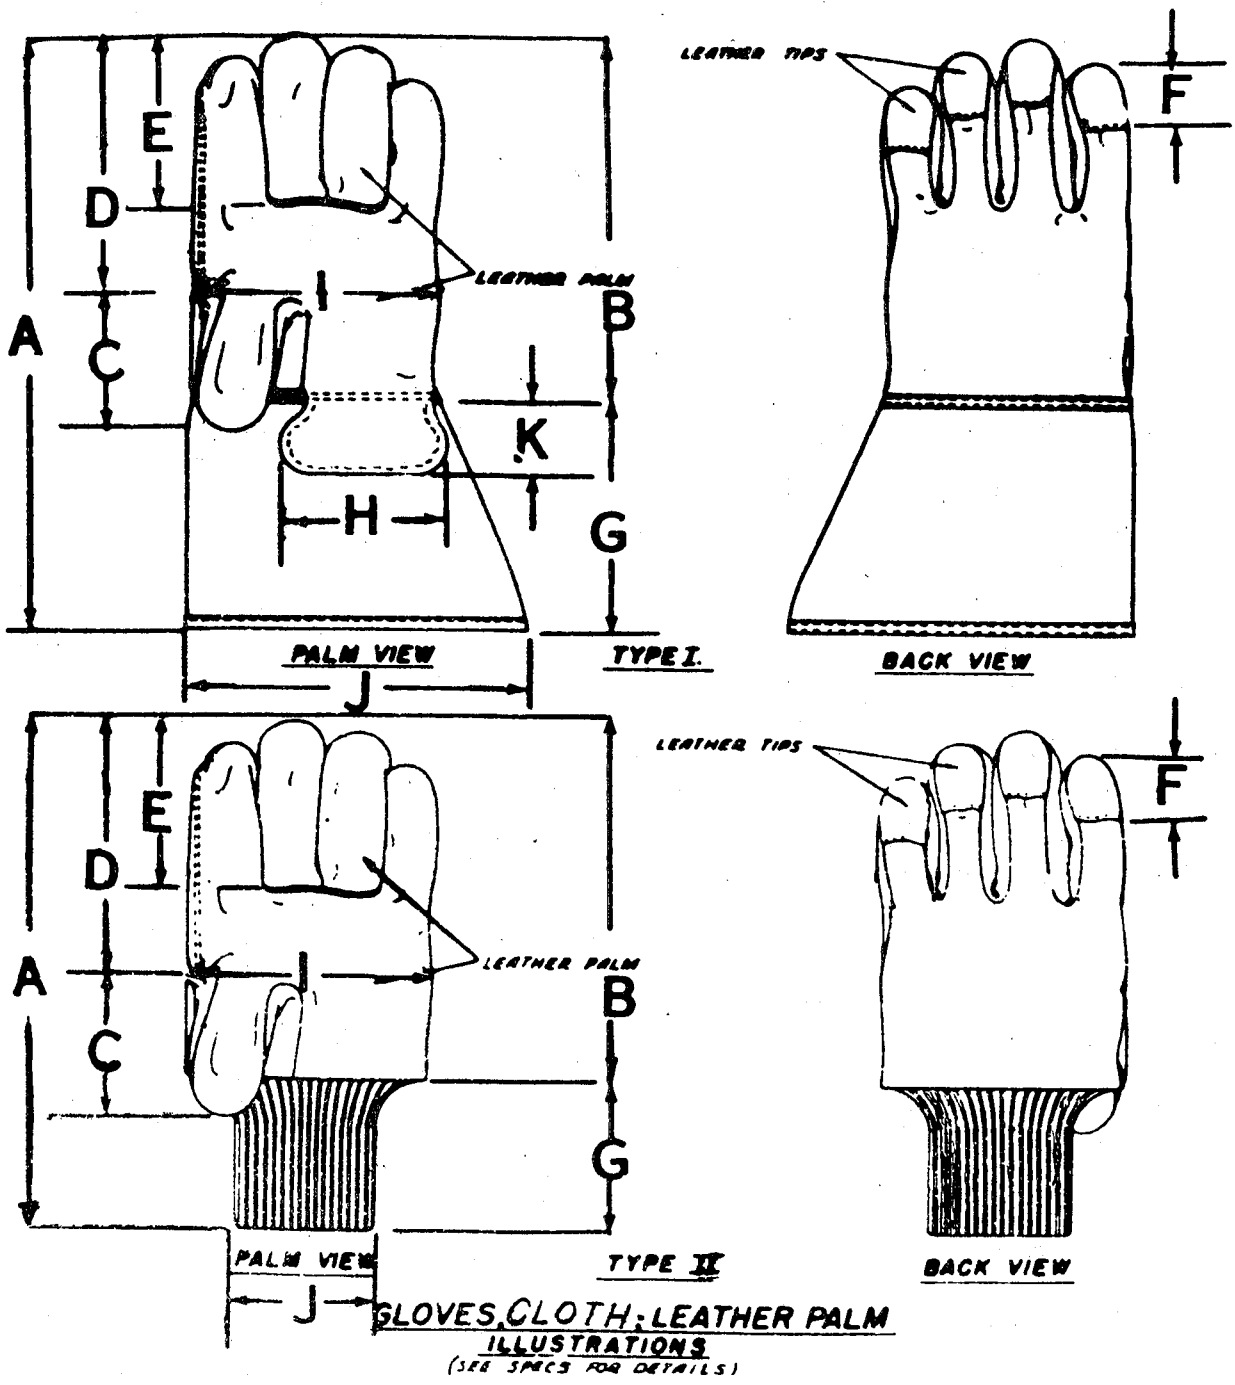


FIG. 1

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications, Standards, and Handbooks from established distribution points in their agencies.)

Military Specifications:

MIL–B–10377—Box, Wood, Cleated, Veneer, Paper Overlaid.

MIL–L–10547 — Liners, Case, Waterproof.

Military Standards:

MIL–STD–105 — Sampling Procedures and Tables for Inspection by Attributes.

MIL–STD–129 — Marking for Shipment and Storage.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

3. REQUIREMENTS

3.1 Sample.—Samples are furnished solely for guidance and information to contractors (see 6.3). Variation from this specification may appear in the sample in which case this specification shall govern.

3.2 Preproduction sample.—When specified, before production is commenced the contractor shall submit a finished pair of gloves to the contracting officer for approval. (See 6.2.)

3.3 Materials.

Delete ... sentence + substitute as in alteration

3.3.1 *Leather.*—The leather shall be flesh-split cowhide or horsehide. It shall be pliable, free from flesh cuts and suitable for use in gloves. Middle splits, hard, stiff, or loose, spongy leather will not be acceptable.

3.3.1.1 *Tannage.* — The leather shall be fully chrome tanned.

3.3.1.2 *Welting.*—The welting shall be a continuous flexible split leather of the same quality as used for the body of glove. The thickness of the welt shall be not less than 1½ nor more than 2 ounces. The finished welt on outside of glove shall measure not less than 1/16 nor more than 3/16 inch wide from the closing seam.

3.3.1.3 *Color.*—The color of all leather components shall be yellow, light (pearl) gray, or brown. All leather components used in each pair of gloves shall be of the same color.

3.3.1.4 *Physical and chemical requirements.*—The leather shall conform to the requirements of table I when tested as specified in 4.3.1.1. The thickness of the leather in each type and class of gloves shall be as shown in table I when measured by a Woburn or similar standard leather gage.

TABLE I.—*Physical and chemical requirements, leather*

Characteristics	Requirement	
	Minimum	Maximum
Thickness (ounces)[1]		
Palm and back finger tips; men's	3	3½
Palm and back finger tips; women's	2½	3
Tensile strength (pounds per square inch)	2100	---
Tongue tearing strength (pounds) (Load required to continue a tear in the leather)	10	---
Chromic oxide (percent) (moisture and chloroform extract free basis)	3.5	---
Chloroform extract (percent)	10	20.0
Ash (moisture free basis) (percent)	---	8.0
Acidity (the Ph value shall be not less than)	3.5	---

[1]An ounce is equivalent in thickness to 1/64 (0.0156) inch.

3.3.1.5 *Flexibility after soaking.* — The leather shall not be permanently affected nor be increased in flex stiffness by more than

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

100 percent, after being soaked in distilled water at room temperature and allowed to air dry, when tested as specified in 4.3.1.1.1.

3.3.2 *Canton flannel.*—The flannel for the back of the gloves shall be made from cleaned, unbleached cotton yarns. The fabric shall be cotton twill fabric, napped on the back (filling flush side), and shall conform to the minimum requirements of table II when tested as specified in 4.3.1.1.

3.3.3 *Flannel lining.*—The flannel lining for the inner palm, fingers and thumb of types I and II gloves shall be a napped cotton flannel, weighing not less than 6 ounces per square yard, with a breaking strength of not less than 70 pounds in the warp and not less than 15 pounds in the filling when tested as specified in 4.3.1.1.

3.3.4 *Knitted cotton tubing for wristlet (type II gloves).*—The tubing for the wristlet shall be made of a true 1 by 1 rib-knit, seamless cotton tubing. The tubing for class 1 wristlets shall weigh not less than 9 nor more than 12 yards per pound, having a width not less than 3 inches and a minimum of 16 wales and 20 courses per inch. The tubing for class 2 wristlets shall weigh not less than 12 nor more than 14 yards per pound, having a width not less than 2¼ inches and a minimum of 14 wales and 20 courses per inch (see 4.3.1.1).

3.3.5 *Laminated fabric for gauntlet (type I glove).*—The finished fabric shall be composed of two thicknesses of cotton fabric securely laminated together. The face fabric shall be a cotton twill or drill weighing not less than five ounces per square yard and the back fabric shall be a cotton plain weave weighing not less than 2.5 ounces per square yard. The finished fabric shall contain not less than 14 ounces per square yard of natural rubber, synthetic rubber or synthetic resin. The total weight of the finished fabric shall be not less than 21.5 ounces per square yard.

3.3.6 *Thread.*—All thread for stitching and seaming shall be ticket No. 20, 4-ply, unbleached cotton thread with the exception that thread for stitching the binding shall be ticket No. 30, 4-ply. The thread shall conform to type IA1 of Federal Specification V–T–276.

3.3.7 *Binding.*—The cotton binding for the top and bottom edges of the gauntlet for type I gloves shall be bleached and conform to type I of Federal Specification DDD–B–331. The binding shall be bias-cut and not less than 1 inch wide.

3.4 **Design.**—The gloves shall be a gunn cut pattern, leather palm with canton flannel back. Type I shall have a gauntlet and type II shall have a knitted wristlet (see figure 1).

3.4.1 *Patterns.*—The dies or patterns for cutting all parts of the gloves shall be furnished by the contractor and shall be of the proper proportions to provide good fitting gloves conforming to finished measurements in table IV.

3.5 **Stitches, seams and stitching.**—Stitch, seam and stitching types used shall conform

TABLE II.—*Physical requirements, canton flannel*

Weight per square yard	Yarns per inch		Breaking strength (grab method)		Weave
	Warp	Filling	Warp	Filling	
Ounces			*Pounds*	*Pounds*	
10	64	35	100	50	3/1 four harness twill

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

to Federal Standard No. 751 as outlined in table III herein. All seaming and stitching shall be done with not less than 8 nor more than 10 stitches per inch. All seam ends shall be backstitched not less than ⅜ inch or shall be caught in another seam.

3.6 Cutting.—The leather shall be block or clicker cut. Undesirable portions of the sides such as hard or tender weak parts shall not be cut for use in the gloves. The leather components shall consist of 8 pieces as follows:

1. Palm, underside of thumb, and reinforcement piece (type I) (1 piece)[1]
2. Top of thumb (1 piece).
3. Second and third fingers (1 piece).
4. One strip of welting for insertion along base of second and third fingers (1 piece).
5. Four tips for back of fingers (4 pieces).

[1] Unit reinforcement piece for type II gloves.

3.7 Construction.—The gloves shall be made by and with the use of all operations listed in table III. The contractor is not required to follow the exact sequence of operations.

3.8 Label.—Each glove shall have a combination size and identification label on the back outside of cuff of type I glove and on back outside of hand part of type II glove. The size will be represented by "M" for Men's and "W" for Women's.

3.8.1 *Printing medium.*—The label shall be applied to the glove by direct printing or stamping with a black marking medium, and shall be clearly legible and show good colorfastness after being subjected to the laundering test specified in 4.3.1.1.

3.8.2 *Printing.*—The label shall be printed in bold-face type with lettering and numbers not less than ⅛-inch in height. The content of the label shall be as follows:

Size
Nomenclature
Stock No.
Contract No.

3.9 Measurements. — The finished gloves shall conform to the measurements shown in table IV.

3.10 Pairing.—The gloves shall be matched, paired, and tacked together with thread ½ to 1 inch from the finished top of gloves. Type I shall be tacked at the closing seam of gauntlet; type II, 1¼ to 1½ inches from edge of knitted cuff. Tacking shall be done with not less than two stitches, using a ply thread which will permit the gloves to be pulled apart without tearing the fabric.

3.11 Workmanship. — The finished glove shall conform to the quality and grade of product established by this specification. The occurrence of defects shall not exceed the levels set by the applicable acceptable quality levels.

TABLE III.—*Requirements*

No.	Manufacturing operations requirements	Stitch type	Seam and stitching type	Stitches per inch	Thread	
					Needle	Bobbin or looper
1.	Join fourchettes to palm by inseaming with one row of stitching, ⅛- to 3/16-inch gage. The welting strip is to be securely caught in the seaming at base of second and third fingers. The finished welt shall measure not less than 1/16 nor more than 3/16 inch wide from the closing seam.	301	SSa–1	8–10	20/4	20/4

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

TABLE III.—*Requirements*—Continued

No.	Manufacturing operations requirements	Stitch type	Seam and stitching type	Stitches per inch	Thread	
					Needle	Bobbin or looper
2.	The thumb piece shall be inseam sewn to the palm with one row of stitching ⅛- to 3/16-inch gage.	301	SSa–1	8–10	20/4	20/4
3.	The palm, thumb, and inner palm or surface of fingers are to be lined with flannel securely caught in entire length of closing side seam, cuff joining seams and tacked at the tips of the thumb and fingers.	301	SSa–1	8–10	20/4	20/4
4.	Join the leather on thumb side to canton flannel with lapped seam by a double row of stitching 1/16- to 3/16-inch gage.	301	LSa–2	8–10	20/4	20/4
5.	The leather tips shall be stitched to canton flannel across the back of each finger 1¼ ± ⅛ inch down from tip of finger with one row of stitching 1/16- to 3/16-inch gage and caught in the closing seams.	301	SSa–1	8–10	20/4	20/4
6.	The closing shall be full inseamed, each end of the closing seam being secured by backstitching not less than ⅜ inch.	301	SSa–1	8–10	20/4	20/4
7.	The leather reinforcement piece shall be stitched to the front (palm side) of the gauntlet with one row of stitching around the sides and top edge, 1/16- to 3/16-inch gage and caught in seam joining cuff gauntlet to hand portion.	301	SSa–1	8–10	20/4	20/4
8.	Type I.—(Gauntlet cuff)					
	a. The gauntlet, made of laminated cotton fabrics, shall be attached to top of hand at wrist by a double row of stitching.	301	SSa–2	8–10	20/4	20/4
	b. The bottom edge (edge attached at wrist) of gauntlet shall be bound with cotton binding and the binding turned under 3/16 to ¼ inch on the outside.	301	BSb–1	8–10	30/4	30/4

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

TABLE III.—*Requirements* —Continued

No.	Manufacturing operations requirements	Stitch type	Seam and stitching type	per Stitches inch	Thread	
					Needle	Bobbin or looper
9.	Type II.—(Knitted wristlet) The knitted cotton tubing shall be cut a sufficient length to permit the wristlet to be formed double thickness by folding over and inseaming the bottom edge of wristlet to top of hand portion at wrist with a double row of stitching ¼- to ⅜-inch gage.	301	SSa–2	8–10	20/4	20/4
10.	Bind top edge (edge at open end of glove) of gauntlet cuff with raw edges of binding turned in 3/16 to ¼ inch and caught within the seaming.	301	BSc–1	8–10	30/4	30/4
11.	Forming. All gloves shall be formed on heated forms. Thumbs and seams shall be worked out over the forms.					

TABLE IV.—*Measurements* [1]

	Location	Type			Tolerance
		I, Class 1	II, Class 1	II, Class 2	plus or minus
		Inches	*Inches*	*Inches*	*Inch*
A	Over-all length, tip of 2nd finger to top of cuff	12½	10¼	10	½
B	Hand length, top of 2nd finger to wrist seam	7½	7½	7¼	¼
C	Length of thumb, crotch to tip	3⅛	3⅛	2¾	⅛
D	Reach, base of thumb to tip of 2nd finger	5½	5½	5⅛	½
E	Length of 2nd finger, crotch to tip	3½	3½	3¼	⅛
	Length of other fingers in proportion				
F	Length of tabs on back	1¼	1¼	1¼	⅛
G	Length of cuff, top to wrist seam	5	2¾	2¾	¼
H	Width of pull tab on cuff	3¼	---	---	½
I	Width of glove at thumb	5¼	5¼	4½	¼
J	Width of cuff, top opening	7	3¼	2½	¼
K	Depth of pull tab	1¾	---	---	¼

[1] See figure 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

4. SAMPLING, INSPECTION, AND TEST PROCEDURES

4.1 Contractor inspection responsibility.— Unless otherwise specified herein, the supplier is responsible for the performance of all inspection requirements prior to submission for Government inspection and acceptance. Except as otherwise specified, the supplier may utilize his own facilities or any other commercial laboratory acceptable to the Government. Inspection records of the examination and tests shall be kept complete and available to the Government as specified in the contract or order.

4.2 Pre-acceptance inspection.—Inspection of the preproduction sample shall be made of a completely fabricated pair of gloves for all the provisions of this specification applicable to the end item.

4.3 Inspection for acceptance. — Except when otherwise specified by Civil agencies, inspection shall be in accordance with Military Standard MIL–STD–105, except where otherwise indicated herein. In addition to sampling inspection of Military Standard MIL–STD–105, process inspection will be performed during manufacture of the gloves to determine compliance with all required operations and processes which cannot be determined in the completely fabricated gloves and to assure that good workmanship has been employed. Any deviation from requirements or poor workmanship found in process inspection may be cause for rejection of the item or items.

4.3.1 *Inspection of components.*

4.3.1.1 *Testing of components.* — In addition to the quality assurance provisions of the subsidiary specifications and drawings, inspection shall be performed on components and materials listed in table V for the characteristics shown. The inspection level for all test characteristics shall be L–2, with the exception of testing of leather which shall be as indicated in table V. Tests for leather shall be conducted as specified in Federal Specification KK–L–311 and fabrics tested as specified in Federal Specification CCC–T–191.

4.3.1.1.1 *Flexibility after soaking.*—Test the dry leather for flex stiffness according to test method 5206 of Federal Specification CCC–T–191, then soak leather in distilled water at 70 degrees F (± 5 degrees F). Retest the dried leather for flex stiffness and indicate the percent increase in flex stiffness resulting from the soaking.

4.3.2 *Inspection of the end item.*

4.3.2.1 *Examination of the end item.*—The defects found during examination of the end product shall be classified in accordance with 4.3.2.1.1 and 4.3.2.1.2. The applicable inspection levels and acceptable quality levels (AQL's) shall be as indicated in 4.3.2.1.3. The sample unit for this examination shall be one glove and the selection shall be by pairs. The sample unit for pairing defects shall be one pair. Defects of pairing shall be classified as a single defect.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

TABLE V.

Component and lot size expressed in terms of:	Characteristic	Requirement paragraph	Test method	Requirements applicable to		No. determinations per sample unit	Results reported as		Inspection level	Sample unit	AQL
				Sample unit	Lot average		Pass or fail	Numerically to nearest			
Leather (1 side)-----	Tannage	3.3.1.1	Std. com'l.	--	X	1	X	----	1	1	N/A
	Thickness	table I	1011 of KK-L-311	---	X	5	--	1/28 inch	1	1	N/A
	Chromic oxide (%)	table I	6511 or 6515 of KK-L-311	--	X	2	--	.1%	1	1	N/A
	Chloroform extract (%)	table I	6311 of KK-L-311	--	X	2	--	.1%	1	1	N/A
	Ash (%)	table I	6421 of KK-L-311	--	X	2	--	.1%	1	1	N/A
	Acidity (pH)	table I	6621 of KK-L-311	--	X	2	--	.1pH	1	1	N/A
	Tensile strength	table I	2011 of KK-L-311	--	X	1	--	10 lb. p.s.i.	1	1	N/A
	Tongue tearing strength	table I	2111 of KK-L-311	--	X	1	--	1 lb	1	1	N/A
	Flexibility after soaking	3.3.1.5	5206 of CCC-T-191 and 4.3.1.1.1	X	--	1	--	1.0%	1	1	6.5

[1] The sample unit for all required tests is one 8- by 8-inch piece of leather and the sample size shall consist of 15 pieces; one piece selected from each of 15 skins. Sampling procedure and location from which the sample unit is to be obtained shall be in accordance with section 6 of Federal Specification KK-L-311.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

TABLE V. (Continued)

Component and lot size expressed in terms of:	Characteristic	Requirement paragraph	Test method	Requirements applicable to		No. determinations per sample unit	Results reported as		Inspection level	Sample unit	AQL
				Sample unit	Lot average		Pass or fail	Numerically to nearest			
Canton flannel (1 yard full width)---	Material identification	3.3.2	1200 of CCC-T-191	X	--	1	X	----	L-2	1 yard full width	6.5
	Weave	3.3.2	Visual	X	--	1	X	----			6.5
	Weight	table II	5041 of CCC-T-191	X	--	5	--	.1 ounce			6.5
	Yarns per inch: Warp	table II	5050 of CCC-T-191	X	--	5	--	Whole yarn			6.5
	Filling	table II	5050 of CCC-T-191	X	--	5	--	Whole yarn			6.5
	Breaking strength: Warp	table II	5100 of CCC-T-191	X	--	5	--	1.0 lb.			6.5
	Filling	table II	5100 of CCC-T-191	X	--	5	--	1.0 lb.			6.5
	Color fastness of ink to laundering (if applicable)	3.8.1	5610 of CCC-T-191	X	--	1	Good, fair or poor	----		One 2 in. by 4 in. marked specimen	6.5

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

TABLE V. (Continued)

Component and lot size expressed in terms of:	Characteristic	Requirement paragraph	Test method	Requirements applicable to		No. determinations per sample unit	Results reported as		Inspection level	Sample unit	AQL
				Sample unit	Lot average		Pass or fail	Numerically to nearest			
Flannel lining (1 yd. full width)--------	Material identification	3.3.3	1200 of CCC–T–191	X	--	1	X	----	L-2	1 yd. full width	6.5
	Weight	3.3.3	5041 of CCC–T–191	X	--	5	--	.1 ounce			6.5
	Breaking strength: Warp	3.3.3	5100 of CCC–T–191	X	--	5	--	1.0 lb.			6.5
	Filling	3.3.3	5100 of CCC–T–191	X	--	5	--	1.0 lb.			6.5
Knitted cotton tubing (1 yd. full width)----------	Material identification	3.3.4	1200 of CCC–T–191	X	--	1	X	----	L-2	½ yd. full width	6.5
	Cuff construction	3.3.4	Visual	X	--	1	X	----			6.5
	Weight	3.3.4	5041 of CCC–T–191	X	--	5	--	0.1 yd. per lb.			6.5
	Yarns per inch: Wales	3.3.4	5070 of CCC–T–191	X	--	5	--	1 wale			6.5
	Courses	3.3.4	5070 of CCC–T–191	X	--	5	--	1 course			6.5

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

TABLE V. (Continued)

Component and lot size expressed in terms of:	Characteristic	Requirement paragraph	Test method	Requirements applicable to		No. determinations per sample unit	Results reported as		Inspection level	Sample unit	AQL
				Sample unit	Lot average		Pass or fail	Numerically to nearest			
Laminated fabric (1 yard full width)	Material identification	3.3.5	1200 of CCC–T–191	X	--	1	X	----	L-2	½ yd. full width	6.5
	Weight of face fabric	3.3.5	5041 of CCC–T–191	X	--	5	--	.1 oz. per sq. yd.			6.5
	Weight of back fabric	3.3.5	5041 of CCC–T–191	X	--	5	--	.1 oz. per sq. yd.			6.5
	Weight of rubber	3.3.5	5041 of CCC–T–191	X	--	5	--	.1 oz. per sq. yd.			6.5
	Total weight	3.3.5	5041 of CCC–T–191	X	--	5	--	.1 oz. per sq. yd.			6.5
	Color fastness of ink to laundering	3.8.1	5610 of CCC–T–191	X	--	1	Good, fair or poor	----		One 2 in. by 4 in. marked specimen	6.5

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

4.3.2.1.1 *Visual examination.*—The gloves shall be examined for defects in finish, design, material, construction, workmanship, and marking and pairing.

Examine	Defect	Classification	
		Major	Minor
Pairing	Not properly mated, e.g., not right and left of the same size	X	
	Badly shaded, wide variation in color		X
	Not tacked together as specified		X
Cleanliness	Any spot, stain or foreign matter clearly noticeable		X
Color and finish	Not as specified in color or finish	X	
	Color not uniform		X
Type	Not type specified	X	
Material			
General	Any component not fabricated of the specified material (unless otherwise classified herein)	X	
Leather	Not horsehide or cowhide	X	
	Not split leather as specified		X
	Loose, spongy, or flanky leather seriously affecting serviceability	X	
	Loose, spongy, or flanky leather affecting serviceability but not seriously		X
	Any open cut or open scratch	X	
	Any open vein seriously affecting serviceability	X	
	Open vein affecting serviceability but not seriously		X
	Any hole or rupture	X	
	Not soft or pliable	X	
	Any scar, brittle or bony area, weak or thin spot, abraded area, seriously affecting serviceability	X	
	Any scar, brittle or bony area, abraded area affecting serviceability but not seriously		X
Knitted cotton tubing (Type II)	Any hole, run, cut, tear, or dropped stitches	X	
	Slubby yarn		X
	Any thin area or mend	X	
Laminated fabric (Type I)	Any cut, hole, tear, burn, or mend	X	
	Any evidence of delamination		X
	Any slub, wrinkle, pick or skip		X
Flannel lining	Any hole, cut, tear, or rip	X	
	Not napped	X	
Construction and workmanship, general (applicable to all components unless otherwise indicated herein)	Any component misplaced, operation omitted seriously affecting serviceability or appearance, e.g., fingers badly twisted or distorted	X	
	Any component misplaced or operation omitted affecting serviceability but not seriously		X
	Any component missing	X	
	Any factory damage seriously affecting serviceability	X	
	Any factory damage affecting serviceability but not seriously		X
	Any repair	X	
	Needle chews which may develop into a hole	X	
	Not assembled as specified	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

Examine	Defect	Classification	
		Major	Minor
Seams and stitching	Any open seam	X	
Note.—	When one or more stitches are broken or two or more consecutive skipped stitches or run-offs occur on a single stitched seam or on both rows of stitching on a double stitched seam, it shall be classified as a major defect. When one or more stitches are broken or two or more continuous skipped stitches or run-offs occur on only one row of a double stitched seam, it shall be classified as a minor defect.		
	Not specified seam type	X	
	Not specified stitch type	X	
	Loose stitch tension resulting in a loosely secured seam	X	
	Tight tension resulting in cutting of leather, puckering of fabric or stitches may break in use of glove	X	
	Any row of stitching omitted	X	
	One or two stitches per inch less than specified		X
	Three or more stitches per inch less than specified	X	
	More than the specified number of stitches per inch but not damaging material		X
	More than the specified number of stitches per inch damaging material	X	
	Gauge of stitching irregular or not as specified		X
	End of seam not backstitched as specified (not applicable to end of a seam that is caught in another row of stitching)		X
Welting	Not securely caught in seam	X	
	Width not uniform or does not protrude a uniform distance from seam		X
Fit of parts	Any part or assembly not properly affixed causing discomfort to wearer, e.g., flannel lining seriously wrinkled or excessive bulk in crotch of fingers, etc.	X	
Reinforcement piece	Reinforcement piece not stitched around sides and top edge	X	
Knitted wristlet	Not double thickness of material	X	
Finishing	Loose threads not trimmed throughout glove		X
	Not neatly laid off, i.e., glove is wrinkled or does not otherwise present a neat appearance		X
Markings	Missing, incomplete, incorrect, not legible, not specified type or size, not in proper location or not accomplished in the specified manner		X

4.3.2.1.2 *Dimensional examination of gloves.*—The gloves shall be examined for dimensional defects. Any dimension that is not within the established tolerance shall be classified as a defect.

4.3.2.1.3 *Inspection levels and acceptable quality levels (AQL's).*—The inspection levels and acceptable quality levels, expressed in defects per hundred units, shall be as follows:

	Inspection level	AQL's	
		Major	Total
For defects applicable to 4.3.2.1.1	II	4.0	10.0
For defects applicable to 4.3.2.1.2	L–6	---	4.0

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

4.3.3 *Examination of preparation for delivery.*—An examination shall be made to determine compliance with the packaging, packing and marking requirements. Defects shall be scored in accordance with the list below. The sample unit shall be one shipping container fully prepared for delivery. The lot size shall be the number of containers in the inspection lot. The inspection level shall be L–4 and the AQL shall be 4.0 defects per 100 units.

Examine	Defect
Markings (exterior and interior)	Omitted, incorrect, illegible, of improper size, location, sequence, or method of application.
Materials	Any component missing or damaged, affecting serviceability.
Workmanship	Inadequate application of components such as incomplete closure of case liners, container flaps, loose strapping, etc. Bulging or distortion of containers.
Weight or content (exterior and interior)	Number per container is more or less than required; gross/net weight exceeds requirement.

5. PREPARATION FOR DELIVERY

(Federal Standard No. 102 shall be referred to for definitions and applications of the various levels of packaging and packing protection for supplies and equipment (for civil agencies only)).

5.1 **Packaging.**—Packaging shall be level A, B, or C as specified (see 6.2).

5.1.1 *Level A and B.*—Six pairs of matched gloves of one type, class, and color only shall be stacked one on another with the ends of each pair alternatively reversed and packaged in a snug-fitting white colored setup paperboard box conforming to type I or II, class A, style 4 of Federal Specification PPP–B–676; or in a snug-fitting white colored folding paperboard box conforming to style III, type B, class a or b of Federal Specification PPP–B–566. The depth of the cover for the partial telescope boxes shall be not less than 1½ inches. Each box shall be secured with gummed paper tape, minimum two inches in width, conforming to class 2 of Federal Specification UU–T–111, applied around the center width of the box. Inside dimensions of the paperboard boxes containing type I, class I gloves shall approximate 13 inches in length, 7½ inches in width, and 4½ inches in depth, and for type II, classes 1 and 2 gloves, 11 inches in length, 5½ inches in width, and 4½ inches in depth.

5.1.2 *Level C.*—The gloves shall be packaged in accordance with the manufacturer's commercial practice.

5.2 **Packing.**—Packing shall be level A, B, or C as specified (see 6.2).

5.2.1 *Level A.*—One hundred and twenty pairs of gloves of one type, class, and color only, packaged as specified in 5.1, shall be packed in the most compact manner in a snug-fitting fiberboard shipping container conforming to class 2, V3c or V3s, style RSC of Federal Specification PPP–B–636. Alternatively, shipping containers may be used that conform to overseas type of Federal Specification PPP–B–591, PPP–B–601, or Military Specification MIL–B–10377; or class 2, style 2 or 4 of Federal Specification PPP–B–621, except that the requirements for additional battens or cleats shall not apply. Level A packages shall be packed on edge two in length, five in width, and two in depth within a shipping container. Inside dimensions of the shipping container containing type I, class 1 gloves shall approximate 26¾ inches in length, 23¼ inches width, and 15½ inches in depth, and for type II, classes 1 and 2 gloves, 23¾ inches in length, 22 inches in width, and 11½ inches in depth. Exact dimensions shall be determined by the contractor to insure that contents fit snugly in the shipping container. Each shipping container shall be provided with a type I or II, grade B or C, class 2 sealed case liner conforming to Military Specification MIL–L–10547. Each shipping container shall be closed and strapped in accordance with the appendix of the applicable container specification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

5.2.2 *Level B.*—One hundred and twenty pairs of gloves of one type, class, and color only, packaged as specified in 5.1, shall be packed in the most compact manner in a snug-fitting fiberboard shipping container conforming to type I or II, class 1, style RSC of Federal Specification PPP–B–636, except that the minimum bursting strength of the fiberboard shall be 275 p.s.i. All flaps of the fiberboard shipping containers shall be securely sealed with an adhesive commercially used for the specific product being packed by application throughout the entire area of contact between the flaps, or by a combination of metal stitching the bottom flaps and sealing the top flaps with adhesive. Alternatively, shipping containers may be used that conform to domestic type, style A or B of Federal Specification PPP–B–591, PPP–B–601, or Military Specification MIL–B–10377; or class 1, style 2 or 4 of Federal Specification PPP–B–621, except that the requirements for additional battens or cleats shall not apply.

5.2.3 *Level C.*—The gloves, packaged as specified in 5.1, shall be packed in a manner to insure carrier acceptance and safe delivery at destination. Shipping containers shall conform to carrier rules and regulations applicable to the mode of transportation.

5.3 **Marking.**

5.3.1 *Civil agencies.*—In addition to any special marking required by the contract or order, interior packages and shipping containers shall be marked in accordance with Federal Standard No. 123.

5.3.2 *Military agencies.*—In addition to any special marking required by the contract or order, interior packages and shipping containers shall be marked in accordance with Military Standard MIL–STD–129.

6. NOTES

6.1 **Intended use.**—The gloves covered by this specification are primarily work gloves for use by personnel of the Military Services and Civil Government Agencies.

6.2 **Ordering data.** — Procurement documents should specify the following:

(*a*) Title, number, and date of this specification.
(*b*) Type and class required (see 1.2).
(*c*) Selection of applicable levels of packaging and packing (see 5.1 and 5.2).
(*d*) Preproduction sample, when required (see 3.2).

6.3 **Sample.**—For access to the guide sample, address the procurement office issuing the invitation for bids.

6.4 **Transportation description.**—The transportation description and minimum weight applicable to this commodity are:

Rail:
Gloves, Workman's, Cotton with Leather-Palm.
Carload minimum weight 24,000 pounds, subject to Rule 34, Uniform Freight Classification.

Motor:
Gloves, Workman's, Cotton with Leather-Palm.
Truckload minimum weight (W) 24.1 pounds, (W) subject to Rule 34, National Motor Freight Classification.

Notice. — When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded, by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

MILITARY CUSTODIANS:
Army—E M Q
Navy—S.

Copies of this specification may be purchased for

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.