SUPERSEDING
Int. Fed. Spec. KK–B–00151c (Docks)
April 15, 1959 and
Fed. Spec. KK–B–151a
June 27, 1955

FEDERAL SPECIFICATION

BELT, SAFETY, INDUSTRIAL; HARNESS, SAFETY, INDUSTRIAL; STRAP, SAFETY INDUSTRIAL

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope.—This specification covers leather safety belts for use as construction and maintenance workers' belts, leather and nylon safety straps for attaching thereto, and leather harnesses for raising or lowering injured workers from entrapped locations.

1.2 Classification.

1.2.1 *Types, models, classes, and materials.*—Belts, straps, and harnesses shall be of the following types, models, classes, and materials as specified:

Type I.—Industrial safety belt.
  Model A.—Linemen's.
    Class 1.—Commercial rolled edge design.
    Class 2.—LC–23–E design.
  Model B.—Electricians'.
  Model C.—Structural iron workers'.
Type II.—Industrial safety strap.
  Material L.—Leather.
  Material N.—Nylon.
Type III.—Industrial safety harness.

1.2.2 *Sizes.*

1.2.2.1 Type I, model A, class 1 and model B shall be furnished in the following sizes, as specified:

Size 36.—approximate 36-inch waist.
Size 38.—approximate 38-inch waist.
Size 40.—approximate 40-inch waist.
Size 42.—approximate 42-inch waist.
Size 44.—approximate 44-inch waist.
Size 46.—approximate 46-inch waist.
Size 48.—approximate 48-inch waist.

1.2.2.2 Type I, model A, class 2 shall be furnished in the following sizes, as specified:

Size 18.
Size 20.
Size 22.
Size 24.
Size 26.
Size 28.
Size 30.

1.2.2.3 Type I, model C belts shall be of one size only, adjustable through the range of sizes 36 to 44.

1.2.2.4 Type II leather straps shall be 70 inches in length and nylon straps shall be 84 inches in length.

1.2.2.5 Type III harnesses shall be of one size only, adjustable through the range of sizes 36 to 44.

2. APPLICABLE SPECIFICATIONS AND STANDARDS

2.1 The following specifications and standards, of the issues in effect on date of invitation for bids, form a part of this specification:

Federal Specifications:
  O–L–164—Leather Dressing; Mildew-Preventive.
  V–T–291—Thread, Linen.
  FF–R–556—Rivets, Solid, Small; Rivets, Split, Small; Rivets, Tubular, Small; and Caps, Rivets; General Purpose.
  FF–W–92—Washers, Metal, Flat (Plain).
  KK–L–156—Leather, Cattlehide, Harness, Vegetable-Tanned.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

KK-L-311—Leather, Methods of Sampling and Testing.
QQ-P-416—Plating, Cadmium (Electrodeposited).
QQ-S-636—Steel; Carbon (Low-Carbon), Sheets and Strips.
QQ-T-830—Tube, Steel, Carbon, Mechanical, Round; Seamless and Welded.
QQ-W-461—Wire, Steel, Carbon (Round, Bare and Coated).
PPP-B-585—Boxes, Wood, Wirebound.
PPP-B-591—Boxes, Fiberboard, Wood-Cleated.
PPP-B-601—Boxes, Wood, Cleated-Plywood.
PPP-B-621—Boxes, Wood, Nailed and Lock-Corner.
PPP-B-636—Box, Fiberboard.

Federal Standards:

Fed. Std. No. 102—Preservation, Packaging, and Packing Levels.
Fed. Std. No. 123—Marking for Domestic Shipment (Civilian Agencies).
Fed. Std. No. 751—Stitches, Seams, and Stitchings.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications, Standards, and Handbooks and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U.S. Government Printing Office, Washington 25, D.C.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, Los Angeles, Seattle, and Washington, D.C.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications, Standards, and Handbooks from established distribution points in their agencies.)

Military Specifications:

MIL-P-79—Plastic-Materials, Laminated, Thermosetting Rods and Tubes.
MIL-P-116—Preservation, Methods of.
MIL-T-3530—Treatment, Mildew-Resistant, for Thread and Twine.
MIL-B-10377—Boxes, Wood-Cleated, Veneer, Paper-Overlaid.
MIL-M-13231—Marking of Electronic Items.
MIL-C-17711—Coatings, Chromate, for Zinc Alloy Castings and Hot-Dip Galvanized Surfaces.
MIL-Z-17871—Zinc-Coating (Hot-Dip Galvanizing).

Military Standards:

MIL-STD-105—Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129—Marking for Shipment and Storage.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

3. REQUIREMENTS

3.1 Preproduction sample.—Unless otherwise specified, as soon as practicable after award of the contract or order and prior to submission of any complete units for final acceptance, the contractor shall furnish a preproduction sample for inspection to determine conformance with this specification. Approval of the proproduction sample by the activity concerned shall not relieve the contractor of his obligation to supply equipment conforming to this specification. No changes or deviations from the preproduction sample will be acceptable without prior written approval from the contracting officer.

3.2 Quantity of belts, straps, and harnesses required.—The quantity of belts, straps, and harnesses required shall consist of the quantity included in the contract or order, plus the pre-production sample, plus the samples required in the drop tests, hereinafter referred to as destructive tests. Belts, straps, and harnesses subject to these tests shall be destroyed in the presence of the Government inspector.

3.3 Material.—Material shall be as specified herein. Material not definitely specified shall be of the quality regularly used by the manufacturer in the product he sells on the commercial, as distinguished from the governmental supply, market. Material shall be free from

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

all defects and imperfections that might affect the serviceability and appearance of the finished product.

3.3.1 *Leather.*—Leather shall be russett, light, selection A, type I conforming to Federal Specification KK–L–156, except that minimum thicknesses shall be as detailed in the accompanying figures and mildew-resistance treatment shall be applied after cutting with a leather dressing conforming to Federal Specification O–L–164 as specified (see 6.1). The finished belt, strap, or harness shall contain no leather which has open grub holes, open cuts or scratches on the grain or flesh sides, brand marks, or soft and spongy spots.

3.3.2 *Nylon strap.*—The nylon strap shall be nylon fabric of plied construction, impregnated and coated with neoprene, and of a color as furnished commercially by the manufacturer with the center ply or plies of a contrasting color. The strap shall have a minimum width of 1¾ inches, a minimum thickness of 0.10 inch, and a minimum breaking strength, without buckle holes, of 5500 pounds.

3.4 Dee rings, snaphooks, and buckles.—Dee rings, snaphooks, and buckles shall be steel drop forgings and shall be zinc coated, cadmium plated or zinc-chromate coated as specified (see 6.1). Zinc coating shall be in conformance with Military Specification MIL–Z–17871. Cadmium plating shall be in conformance with Federal Specification QQ–P–416, type II, class 1 (0.0005 inch thick). Zinc-chromate coating shall be zinc coated, as above, and then coated with an olive-drab-chromate finish conforming to Military Specification MIL–D–17711.

3.4.1 *Dee rings.*—Dee rings shall be as indicated in figure 10 and shall be proportioned so as to avoid the possibility of roll-out and accidental disengagement of a snaphook (3.4.2) caused by depression of the snaphook keeper latch by the dee ring. Each dee ring shall have installed a suitable copper or steel safety liner to prevent wear between the bar of the dee ring and the fabric or leather enclosing it. Dee rings shall be capable of withstanding a tensile load of 1500 pounds without deforming more than 1/64 inch when tested as described in 4.6.3.1. No cracks or fractures shall be visible in the dee rings when subjected to the test described in 4.6.3.2.

3.4.2 *Snaphooks.*—Snaphooks shall be of the round-nose type with closed stirrup essentially as detailed on figure 10. The round nose shall overlap the keeper latch in such manner as to prevent the latch from being accidentally engaged by the dee ring to release the snap. Snaphooks shall be capable of withstanding a tensile load of 1500 pounds without deforming more than 1/32 inch when tested as described in 4.6.4.1. No cracks or fractures shall be visible in the snaphooks when subjected to the test described in 4.6.4.2.

3.4.2.1 *Keeper.*—Keeper shall fit snugly, without binding, between the sides of the nose of the hook and shall extend into the round-nose housing in the direction of the long axis of the keeper not less than 5/32 inch.

3.4.3 *Buckles.*—Buckles shall be as indicated on figure 10 and shall be single or double tongued, as required herein.

3.4.3.1 *Buckle frames.*—Buckle frames shall be capable of withstanding a tensile load of 1500 pounds without deforming more than 1/64 inch when tested as described in 4.6.5.1. No cracks or fractures shall be visible in the buckle frames when subjected to the test described in 4.6.5.2.

3.4.3.2 *Buckle tongues.*—No cracks or fractures shall be visible in the buckle tongues when subjected to the test described in 4.6.5.2.

3.5 Rivets and washers.—Rivets shall conform to Federal Specification FF–R–556 and as detailed on figures 2, 3, and 7. Washers shall conform to Federal Specification FF–W–92 and as detailed in figures 2 and 7.

3.6 Thread.—Six-ply linen thread, type B conforming to Federal Specification V–T–291, treated for mildew resistance in accordane with Military Specification MIL–T–3530, class 1 (see 4.6.2) and waxed, shall be used for stitching leather products.

3.6.1 *Stitching.*—There shall be not less than 5 nor more than 7 stitches per inch and stitch type 301, Federal Standard No. 751 shall be used. Cross stitching is prohibited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

3.7 Type I, industrial safety belt.

3.7.1 *Model A, linemen's belt.*—Model A, linemen's belt shall be furnished in the following classes. There shall be no fracture nor rupture of the component parts when subjected to the test described in 4.6.7.1.

3.7.1.1 *Class 1, commercial rolled edge design.*—Class 1, commercial rolled edge design shall be in accordance with figure 1 except that dimensions given for width and thickness of the leather are minimums and buckles may be single or double-tongued. When double-tongued buckles are used, the body belt shall be a minimum of 2 inches in width. The belts shall conform to the dimensional requirements shown in table I.

TABLE I.—*Dimensions of type I, class 1, model A, commercial rolled edge design linemen's belt*

Size	Dimensions in inches (see figure 1)					
	A±½	B	C±¼	D	E	F
36	45½	36	20	8	17½	3½
38	47½	38	21	8½	18	4
40	49½	40	22	9	18½	4½
42	51½	42	23	9½	19	5
44	54¼	44	24	10	19½	4¾
46	56¼	46	26	10	20¼	4¾
48	59	48	28	10	21	4

3.7.1.2 *Class 2, LC–23–E design.* The class 2, LC–23–E belt shall conform to figures 2, 3, and 4.

3.7.1.2.1 *Miscellaneous parts of belt.*—The following named parts of the belt shall conform to details shown on figure 4 and shall be in accordance with the listed specifications:

Clip and Tool Holder—steel, condition No. 2, Federal Specification QQ–S–636

Base—steel, tubing, MT 1020, Federal Specification QQ–T–830

Tape Holder—steel, wire, Steel No. 1010, finish 4, Federal Specification QQ–W–461.

The clip, tool holder, base, and tape holder shall be zinc-coated in accordance with Military Specification MIL–Z–17871 and then coated with an olive drab chromate finish conforming to Military Specification MIL–C–17711.

Bushing—plastic, type, PBE, Military Specification MIL–P–79.

Strap, keeper, and filler—leather treated for mildew resistance, each as specified in 3.3.1.

3.7.2 *Model B, electricians' belt.*—Model B, electricians' belt shall be in accordance with figure 5 except that dimensions given for width and thickness of the leather are minimums and buckles may be single or double-tongued. When double-tongued buckles are used, the body belt shall be a minimum of 2 inches in width. There shall be no fracture nor rupture of the component parts when subjected to the test described in 4.6.7.1. The belts shall conform to the dimensional requirements shown in table II.

TABLE II.—*Dimensions of type I, model B, electricians' belt*

Size	Dimensions in inches (see figure 5)					
	A±½	B	C±¼	D	E	F
36	44	36	20	8	16	3½
38	46	38	21	8½	16½	4
40	48	40	22	9	17	4½
42	50	42	23	9½	17½	5
44	52¾	44	24	10	18	4¾
46	54¾	46	26	10	18¾	4¾
48	57½	48	28	10	19½	4

3.7.3 *Model C, structural iron workers' belt.*—Model C, structural iron workers' belt shall be in accordance with figure 6 except that dimensions given for width and thickness of the leather are minimums. Structural iron workers' belts shall be of one size only, adjustable by means of a double-tongue buckle through the range of sizes 36 to 44. Approximately 20 inches of the hole end of the body belt shall be reinforced with rawhide nominally one-eighth inch thick and two inches wide. There shall be no fracture nor rupture of the component parts when subjected to the tests described in 4.6.7.2 and 4.6.7.3.

3.7.3.1 *Length.*—Length shall be 48½ inches with a tolerance of plus or minus one-half inch.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

3.8 Type II, industrial safety strap.

3.8.1 *Material L, leather.*—Leather safety straps shall be in accordance with figure 7. Leather safety straps shall be of one size only, adjustable by means of a double-tongue buckle. There shall be no fracture nor rupture of the component parts when subjected to the test described in 4.6.7.1.

3.8.2. *Material N, nylon.*—Nylon safety straps shall be in accordance with figure 8 except that the width dimension is minimum. Nylon safety straps shall be of one size only, adjustable by means of a single-tongue buckle. There shall be no fracture nor rupture of the component parts when subjected to the test described in 4.6.7.1.

3.9 Type III, industrial safety harness.—Type III, industrial safety harness shall be in accordance with figure 9 except that dimensions given for width and thickness of the leather are minimums. Industrial safety harnesses shall be of one size only, adjustable by means of a double-tongue buckle on the body belt and single or double-tongue buckles on the shoulder straps through the range of sizes 36 to 44. Approximately 16 inches of the hole end of the body belt shall be reinforced with rawhide nominally one-eighth inch thick and two inches wide. There shall be no fracture nor rupture of the component parts when subjected to the test described in 4.6.7.3.

3.10 Instructions for care of leather and nylon.—The manufacturer shall include with each belt written recommendations describing care of the leather and nylon during its anticipated useful lifetime. The recommendations shall include special treatment required to withstand climatic tests such as rapid changes in humidity, cold and heat normally encountered in storage.

3.11 Marking.

3.11.1 *Army requirements.*—Markings and materials for the marking of the type I, model A, class 2 (LC–23–E) belt and the type II leather strap shall be in accordance with Military Specification MIL–M–13231 and as detailed on figure 2.

3.11.2 *Other requirements.*—Each body belt, strap, and harness shall have a suitable metal marker attached on which the manufacturer's name, the month and year of manufacture, and the manufacturer's serial number shall be permanently stamped.

3.12 Workmanship.—Workmanship shall be of the highest grade throughout and in accordance with the best standard practice for this type of equipment. Tolerances shall conform to any limitations specified herein, and otherwise to the standards of good commercial practice.

4. SAMPLING, INSPECTION, AND TEST PROCEDURES

4.1 Unless otherwise specified herein, the supplier is responsible for the performance of all inspection requirements prior to submission for Government inspection and acceptance. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. Inspection records of the examinations and tests shall be kept complete and available to the Government as specified in the contract or order.

4.2 Preproduction sample.—Unless otherwise specified, the preproduction sample shall be tested at the place of manufacture. Tests shall be in conformance with the applicable tests of 4.6.7.

4.3. Lot.—A lot shall consist of all belts, straps, and harnesses of the same type, model, class, material, and size offered for delivery at the same time plus the quantity required for destructive tests.

4.4 Sampling.

4.4.1 *Sampling for examination.*—Sampling for examination of critical defects does not apply since all belts, straps, and harnesses are required to be examined for critical defects (see 4.5.1). Sampling for examination for minor defects (see 4.5.2) shall be in accordance with Military Standard MIL–STD–105, with lot acceptance or rejection based on an Acceptable Quality Level (A.Q.L.) of 2.5 percent defective.

4.4.2 *Sampling for tests.*—Sampling for the leather cracking test (see 4.6.6) does not apply since all belts, straps, and harnesses are required to meet this cracking test. Sampling

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

for all other tests, except those required by material specifications (4.6.1.1 and 4.6.2) and the test specified for nylon webbing (see 4.6.1.2), shall be in accordance with Military Standard MIL–STD–105, using inspection Level L–4 and an A.Q.L. of 4.0 percent defective. For the nylon webbing test three samples shall be taken.

4.5 Examination.

4.5.1 *Examination for critical defects.*—Each belt, strap, and harness presented for acceptance shall be visually and dimensionally examined for critical defects as listed below. A belt, strap, or harness having any one or more of the listed defects shall be considered defective and shall be rejected.

CLASSIFICATION OF CRITICAL DEFECTS

1. Less than minimum specified width or thickness for belt, strap, or harness.
2. Grub holes in the leather.
3. Cracks, cuts, or wrinkles resulting in softening of leather or in reducing thickness below minimum.
4. Poor riveting.
5. Broken or incorrect stitching.
6. Incorrect dimension (where dimensions are specifically toleranced).
7. Incorrect assembly.
8. Missing, loose, cracked, broken, or distorted parts.
9. Delamination of nylon plies.

4.5.2 *Examination for minor defects.*—Samples selected in accordance with 4.4.1 shall be examined for minor defects as listed below. Any sample having any one of the listed defects shall be considered a defective unit.

CLASSIFICATION OF MINOR DEFECTS

51. Poorly peened rivets.
52. Rust on metallic parts or poor plating.
53. Two sixty-fourths of an inch or more below minimum thickness for holster.
54. Inadequate coating of nylon.
55. Blisters in coating.

4.6 Tests.—The preproduction sample and other complete belts, straps, and harnesses furnished for destructive tests shall be in addition to the number specified for delivery in the contract or order. All component parts and complete belts subjected to the following destructive tests shall be destroyed upon completion of these tests:

(*a*) Tensile load. (See 4.6.3.1, 4.6.4.1, and 4.6.5.1.)

(*b*) Cracking. (See 4.6.3.2, 4.6.4.2, and 4.6.5.2.)

(*c*) Drop tests. (See 4.6.7.1, 4.6.7.2, and 4.6.7.3.)

4.6.1 *Belt and strap material.*

4.6.1.1 *Leather.*—Leather shall be tested in conformance with Federal Specification KK–L–156. (See 3.3.1.)

4.6.1.2 *Nylon webbing.*—The three samples of the nylon fabric shall be tested for tensile breaking strength. Each sample shall be secured in the testing machine and a total load of 5,500 pounds applied with a steady pull at a rate of 4 inches per minute. There shall be no indication of breaking. If either sample shows signs of breaking the entire lot shall be rejected.

4.6.2 *Thread.*—Thread shall be tested in conformance with Federal Specification V–T–291. Mildew resistance shall be tested in conformance with Military Specification MIL–T–3530. (See 3.6.)

4.6.3 *Dee rings.*—Samples selected in accordance with 4.4.2 shall be tested as detailed below.

4.6.3.1 *Tensile load.*—A metal clasp approximately 1½ inches wide shall be attached to the base of the dee ring and the clasp inserted in one set of jaws of the testing machine. The curved portion opposite the base shall be inclosed in a wire loop, the loose ends of the wire inserted in the other set of jaws of the testing machine, and a total load of 1500 pounds applied to the dee ring. After releasing the load, the dee ring shall be examined for any indication of failure. (See 3.4.1.)

4.6.3.2 *Cracking.*—A load shall be applied on the base and opposite curved portion of the dee ring, either in a testing machine or a hand vise, sufficient to close the jaws of the dee ring to a distance of approximately one-half of the original distance of the opening. After releas-

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

ing the load, the dee ring shall be examined for cracks or fracture. (See 3.4.1.)

4.6.4 *Snaphooks.*—Samples selected in accordance with 4.4.2 shall be tested as detailed below.

4.6.4.1 *Tensile load.*—A metal clasp shall be attached on the barrel roller around the bar in the stirrup of the snaphook and the clasp inserted in one set of jaws of the testing machine. The eye of the hook shall be inclosed in a wire loop, the loose ends of the wires inserted in the other set of jaws of the testing machine, and a total load of 1500 pounds applied to the snaphook. After releasing the load, the snaphook shall be examined for any indication of failure. (See 3.4.2.)

4.6.4.2 *Cracking.*—The bill of the hook shall be bent outward approximately 30 degrees in the plane of the shank. This may be conveniently done with a pipe slipped over the bill of the hook and resting on the base of the eye. The straight portion of the shank shall be bent through an angle of 180 degrees over a mandrel one-half inch in diameter. After bending the hook, it shall be examined for cracks and any indication of fracture. (See 3.4.2.)

4.6.5 *Buckles.*—Samples selected in accordance with 4.4.2. shall be tested as detailed below.

4.6.5.1 *Tensile load.*—Metal clasps shall be attached to opposite sides of the buckle frame, and the clasps inserted in the jaws of the testing machine and a total load of 1500 pounds applied to the buckle. After releasing the load, the buckle shall be examined for any indication of failure. (See 3.4.3.1.)

4.6.5.2 *Cracking.*—Any portion of the buckle or any tongue shall be bent through an angle of 180 degrees and examined for cracks or indications of fracture. (See 3.4.3.1 and 3.4.3.2.)

4.6.6 *Hand cracking tests.*—Each complete belt, leather strap, and harness shall be subjected to the hand cracking test of method 4021, Federal Specification KK–L–311. The test shall be made in one or more convenient places of the belt, strap, or harness, substituting the equipment for the specified specimens. Any visual cracking of the leather shall be cause for the rejection of the belt, strap, or harness.

4.6.7 *Drop tests.*—Unless otherwise specified, preproduction samples and samples of complete belts, straps, and harnesses, selected in accordance with 4.4.2, shall be tested as described below.

4.6.7.1 *Linemens's belt, electricians' belt, and safety strap.*—When linemen's belts or electrician's belts are procured with safety straps the belt and strap shall be tested together. When the belts or straps are procured separately the item under procurement shall be tested as described below with a strap or belt provided by the supplier. The body belt shall be securely fastened around a 250-pound bag of sand. The safety strap shall be passed over a securely anchored 2-inch-diameter bar and fastened, by means of snaphooks, to the dee rings of the body belt. The bar shall be positioned at such a height that the sand bag will be suspended at least 2 feet above the ground or floor. The sand bag shall then be raised and permitted to fall free a distance of 2 feet before being stopped by the belt and strap. This shall be repeated for a second drop. After the second drop the component parts of the belt and/or strap shall be examined for any fracture or rupture.

4.6.7.2 *Structural iron workers' belt.*—The body belt shall be securely fastened around a 250-pound bag of sand. One end of a suitable length of manila rope, having a breaking strength of not less than 5000 pounds, shall be attached to one of the side dee rings, the other end passed over a 2-inch-diameter bar and fastened to the other side dee ring. The bar shall be positioned at such a height that the sand bag will be suspended at least 2 feet above the ground or floor. The sand bag shall then be raised and permitted to fall free a distance of 3.2 feet before being stopped by the belt and strap. This shall be repeated for a second drop. After the second drop the component parts of the belt shall be examined for any fracture or rupture.

4.6.7.3 *Structural iron workers' belt and harnesses.*—The body belt shall be securely fastened around a 250-pound bag of sand. One end of a manila rope having a breaking strength of not less than 5000 pounds shall be

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

secured to the back dee ring, the other to a fixed fastening so that the sand bag will be suspended at least 2 feet above the ground or floor. The sand bag shall then be raised and permitted to fall free a distance of 3.2 feet before being stopped by the belt and rope. This shall be repeated for a second drop. After the second drop the component parts of the belt shall be examined for any fracture or rupture.

4.7 Rejected lots.—Disposition of rejected lots shall be in accordance with Military Standard MIL–STD–105.

4.8 Inspection of preparation for delivery.—The preservation, packaging, packing, and marking of the belts, harnesses, and straps shall be examined and tested to determine conformance with the requirements of Section 5 of this specification. Examination of packing and marking requirements not covered by referenced specifications shall be in accordance with Military Standard MIL–STD–105, using an AQL of 4.0 percent defective.

4.8.1 *Classification of defects.*—For packing and marking requirements not covered by referenced specifications.

DEFECTS

1. Exterior shipping container not as specified.
2. Closure of exterior shipping container not correct.
3. Strapping missing when required.
4. Strapping not as specified.
5. Gross weight of exterior shipping container exceeds weight limit specified.
6. Marking incorrect, illegible, or missing.

5. PREPARATION FOR DELIVERY

(For civil agency procurement the levels of preservation, packaging and packing protection used are defined in Federal Standard No. 102.)

5.1 Preservation and packaging.—Preservation and packaging shall be level A or C, as specified. (See 6.1.)

5.1.1 *Level A.*—Each complete individual belt, each complete individual harness, and each complete individual strap shall be preserved by method 1C–2 or 1C–5 in accordance with Military Specification MIL–P–116. Containers shall be of a size which will snugly contain the belt, harness, or strap in minimum cubage.

5.1.2 *Level C.*—Belts, harnesses, and straps shall be preserved and packaged in accordance with the supplier's standard practice.

5.2 Packing.—Packing shall be level A, B, or C, as specified. (See 6.1.)

5.2.1 *Level A.*—Preserved and packaged belts, harnesses, and straps of identical type, model, class, material, and size shall be packed in snug-fitting boxes conforming to Federal Specification PPP–B–585 (class 3), PPP–B–591 (overseas type), PPP–B–621 (class 2), PPP–B–636 (class 2, V3c or V3s), or Military Specification MIL–B–10377 (overseas type). Boxes shall be closed and strapped in accordance with the appendix to the applicable box specification. Strapping shall be type I, class B. The gross weight of wood and wood cleated boxes shall not exceed approximately 200 pounds. The gross weight of fiberboard boxes shall not exceed 70 pounds.

5.2.2 *Level B.*—Preserved and packaged belts, harnesses, and straps of identical type, model, class, material, and size shall be packed in snug-fitting boxes conforming to Federal Specifications PPP–B–585 (class 1), PPP–B–591 (domestic type), PPP–B–601 (domestic type), PPP–B–621 (class 1), PPP–B–636 (class 1), or Military Specification MIL–B–10377 (domestic type). Boxes shall be closed and strapped in accordance with the appendix to the applicable box specification. The gross weight of wood and wood cleated boxes shall not exceed approximately 200 pounds. The gross weight of fiberboard boxes shall be subject to the weight limitations of the fiberboard box specification.

5.2.3 *Level C.*—Preserved and packaged belts, harnesses, and straps shall be packed in a manner which will insure arrival at destination in satisfactory condition and which will be acceptable to the carrier at lowest rates or ratings. Containers and packing shall comply with Uniform Freight Classifications Rules or National Motor Freight Classification Rules, or with other carrier rules and regulations as applicable to the mode of transportation without assessment of penalty charges.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

5.2.4 *Level D.*—To be furnished.

5.3 Marking.

5.3.1 *Civil agencies.*—Marking shall be in accordance with Federal Standard No. 123.

5.3.2 *Miliary agencies.*—Interior packages and shipping containers shall be marked in accordance with Military Standard MIL–STD–129.

6. NOTES

6.1 Ordering data.—Purchasers should include the following information in the invitation for bids and contracts and should exercise any other desired options offered herein:

(*a*) Title, number, and date of specification.

(*b*) Type, model, class and size of belt and whether leather or nylon safety straps are required. (See 1.2.1, 1.2.2, 3.7, 3.8, and 3.9.)

(*c*) If preproduction sample is not required. (See 3.1.)

(*d*) Type dressing, Federal Specification O–L–164, required. (See 3.3.1.)

(*e*) Which coating, zinc, cadmium, or zinc-chromate, is required. (See 3.4.)

(*f*) Where preproduction sample will be tested if other than at place of manufacture. (See 4.2.)

(*g*) If drop tests are not required. (See 4.6.7.)

(*h*) The level of preservation and packaging, and the level of packing required. (See 5.1 and 5.2.)

6.2 Federal specifications do not include all types, models, classes, sizes, etc., of the commodities indicated by the titles of the specifications, or which are commercially available, but are intended to cover the types, models, etc., which are suitable for Federal Government requirements.

6.3 Transportation description.—Transportation description and minimum weight applicable to this commodity are:

Rail:

LEATHER

Straps, leather, fitted with buckles, hooks or other fastenings, not otherwise indexed by name.

Carload minimum weight 20,000 pounds, subject to Rule 34, Uniform Freight Classification.

NYLON

Belts, not otherwise indexed by name, other than chain belts.

Carload minimum weight 30,000 pounds.

Motor:

LEATHER

Straps, leather, fitted with buckles, hooks or other fastenings, not otherwise indexed.

Motor volume minimum weight 20,000 pounds.

NYLON

Belts, not otherwise indexed.

Truckload minimum weight (w) 30.6 pounds, (w) subject to Rule 34, National Motor Freight Classification.

Notice.—When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

MILITARY INTEREST:
Army—Sig C E M O Q T
Navy—Y CG Sh S
Air Force—AF

551944—60——2

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.


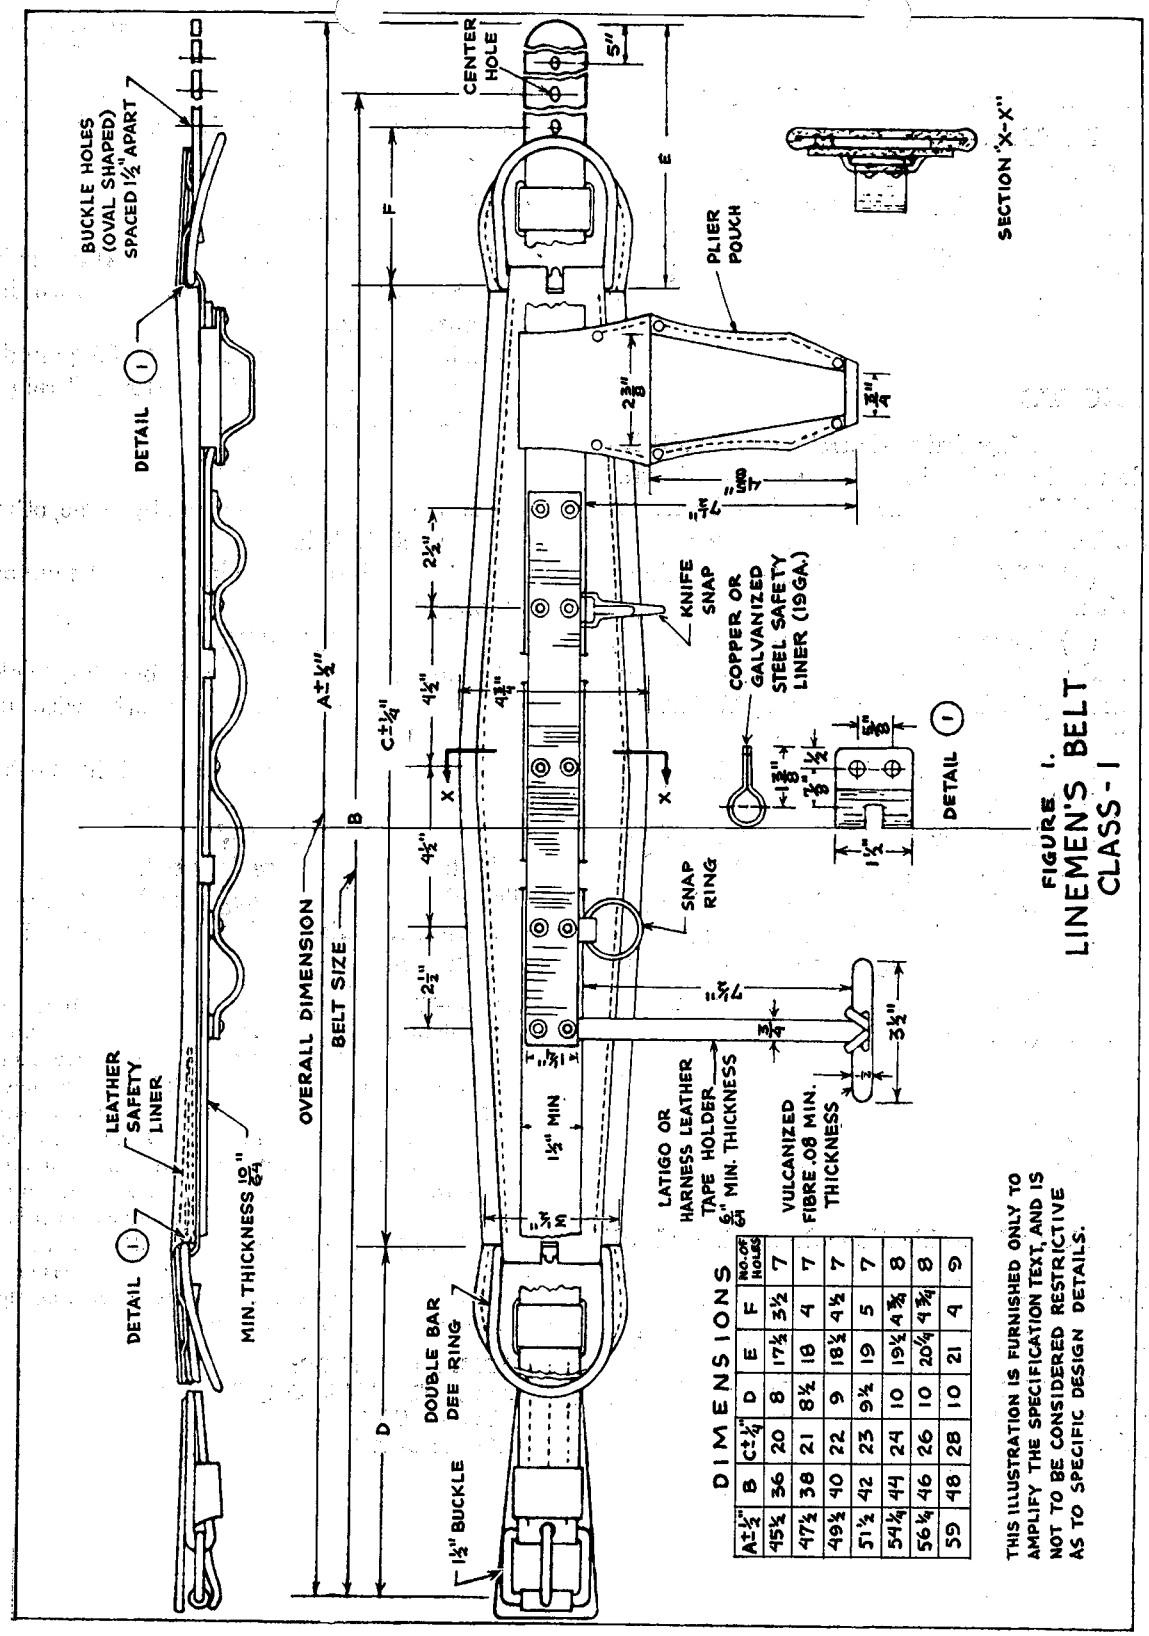



FIGURE 1.
LINEMEN'S BELT
CLASS-1

THIS ILLUSTRATION IS FURNISHED ONLY TO AMPLIFY THE SPECIFICATION TEXT, AND IS NOT TO BE CONSIDERED RESTRICTIVE AS TO SPECIFIC DESIGN DETAILS.


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

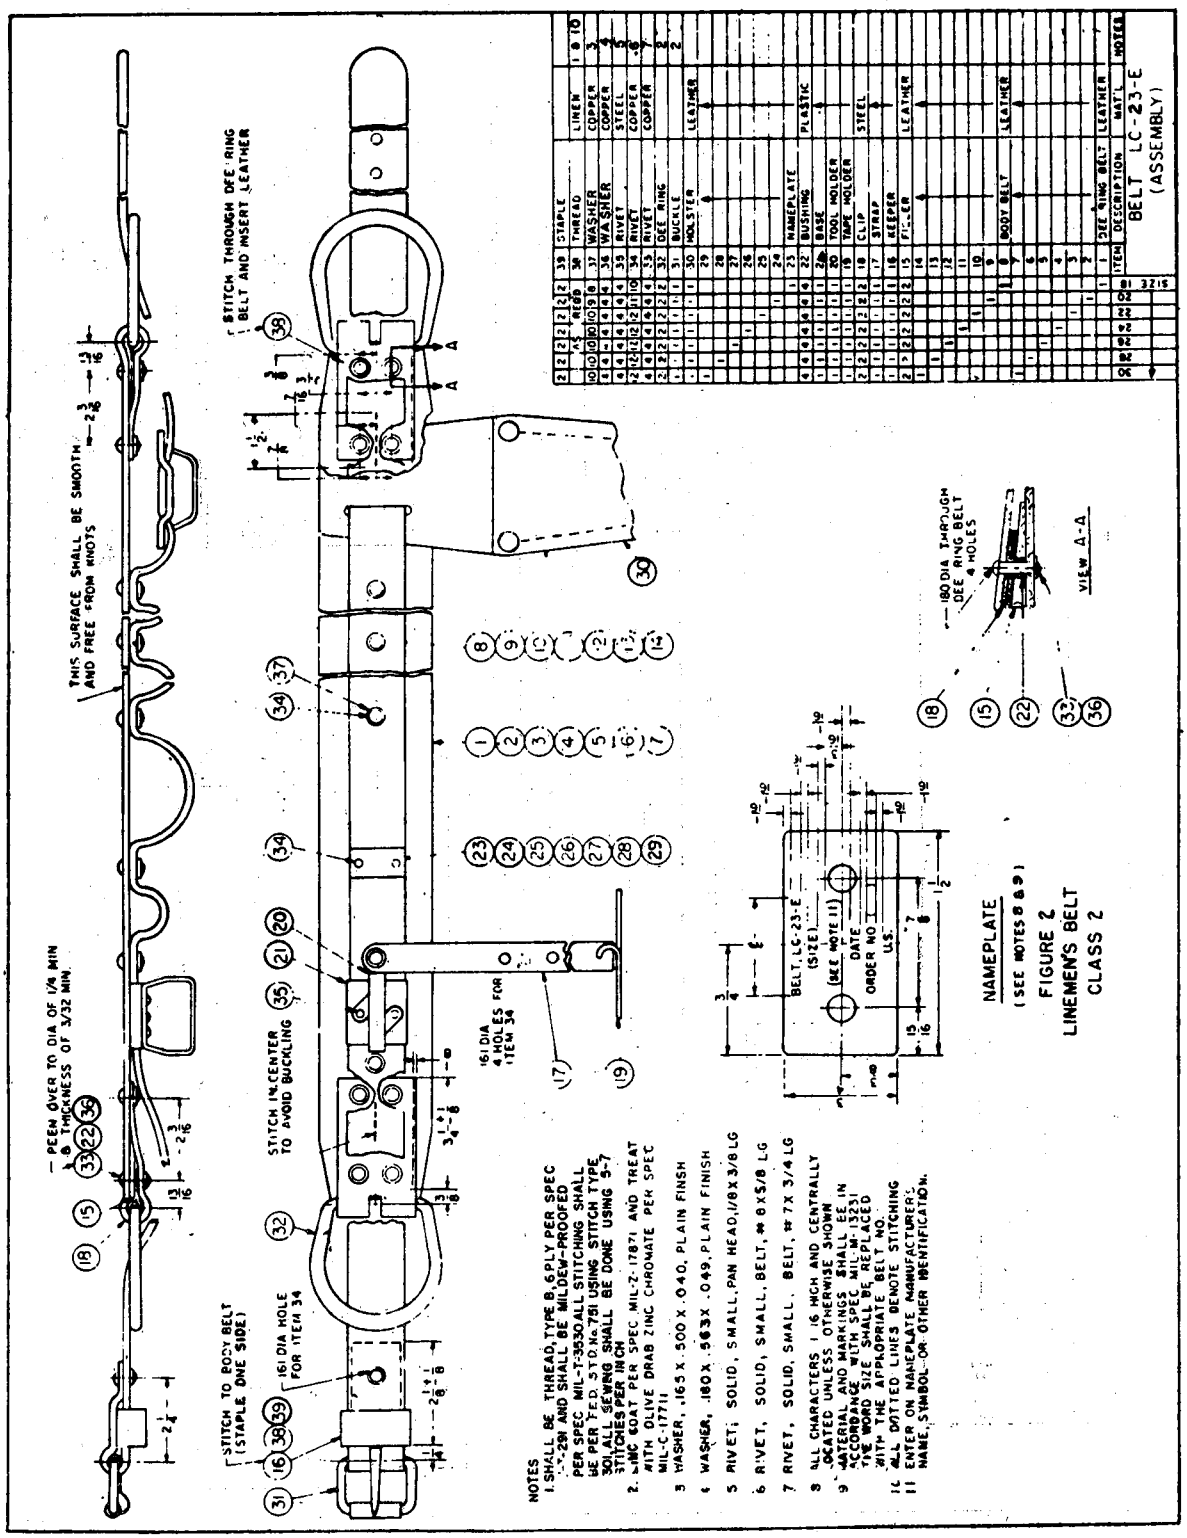

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

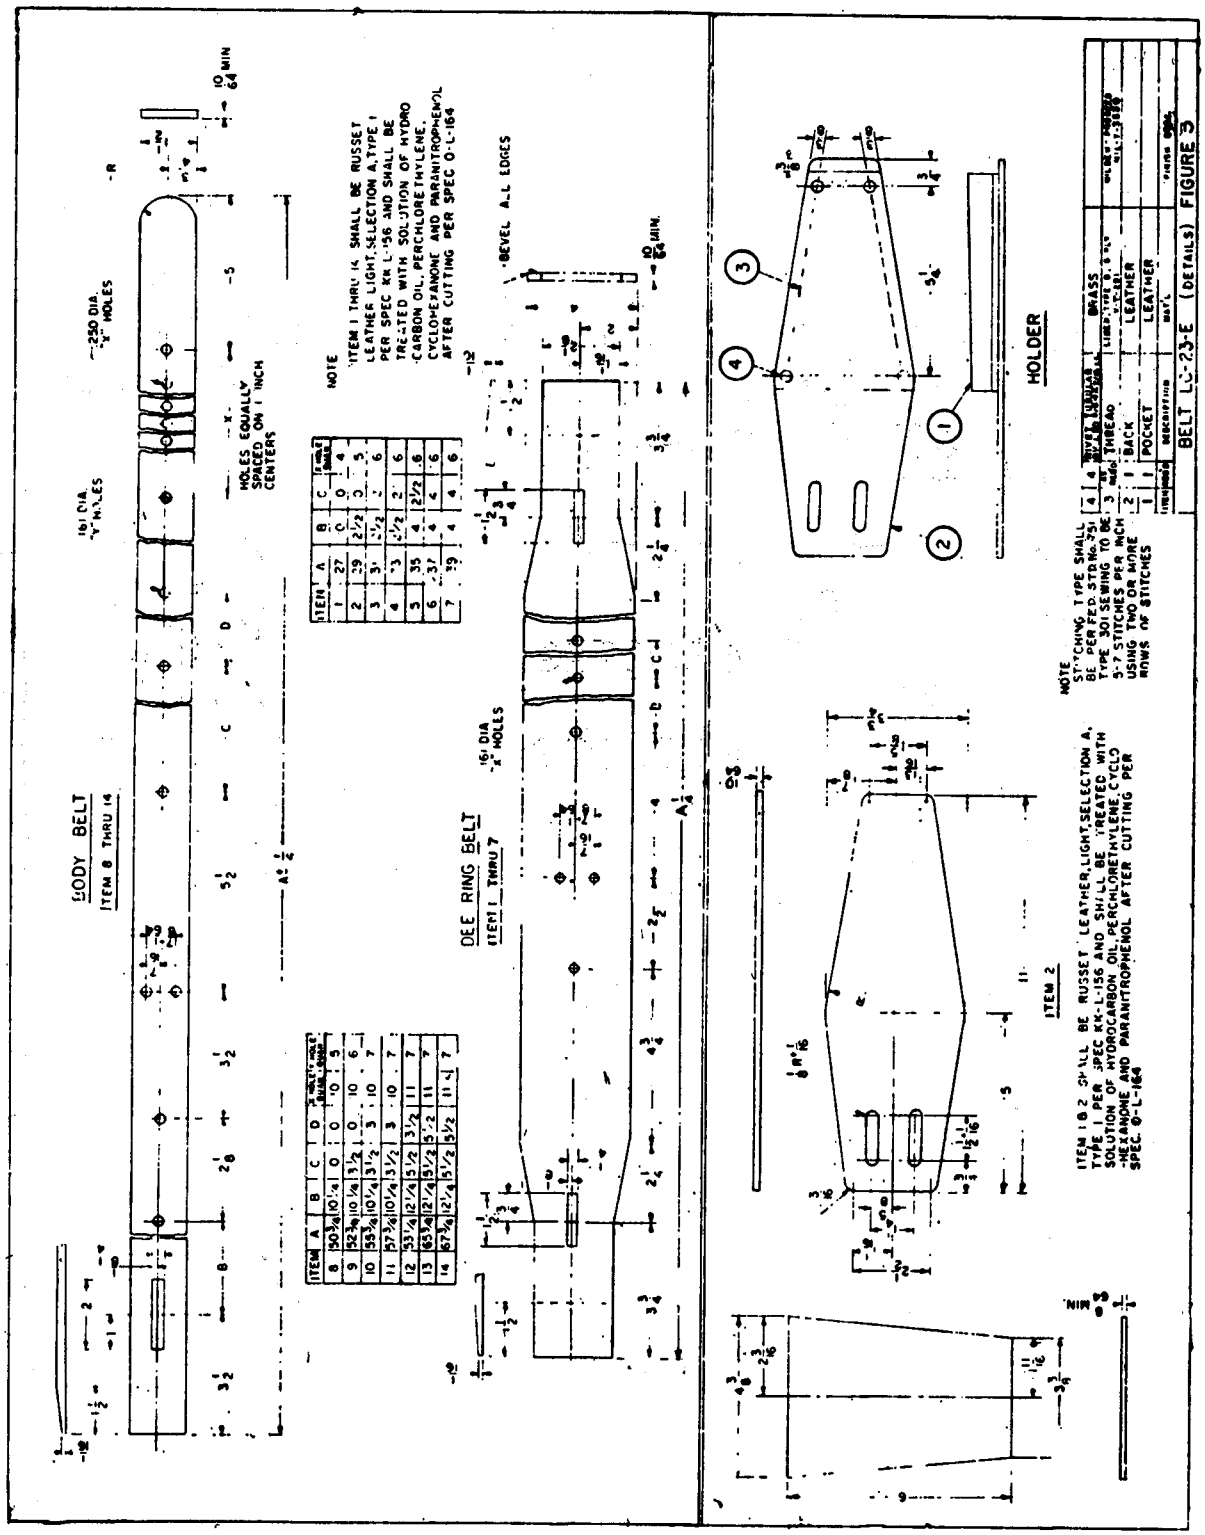

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

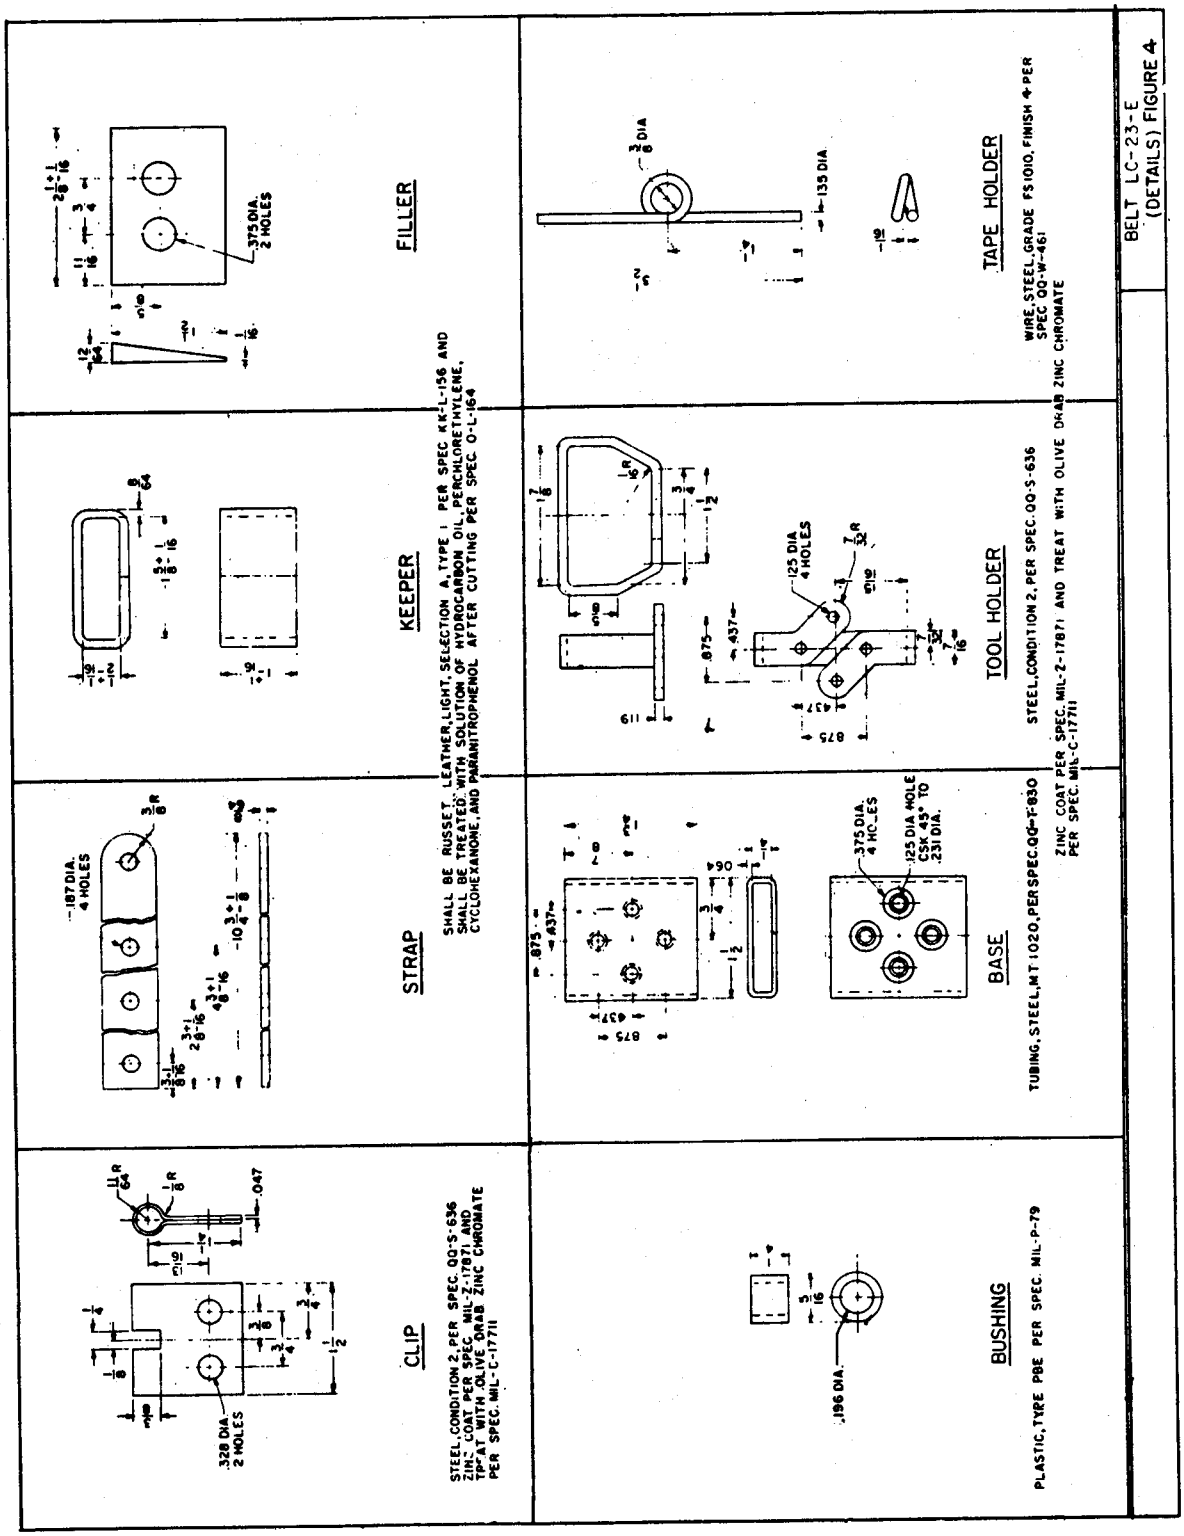

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

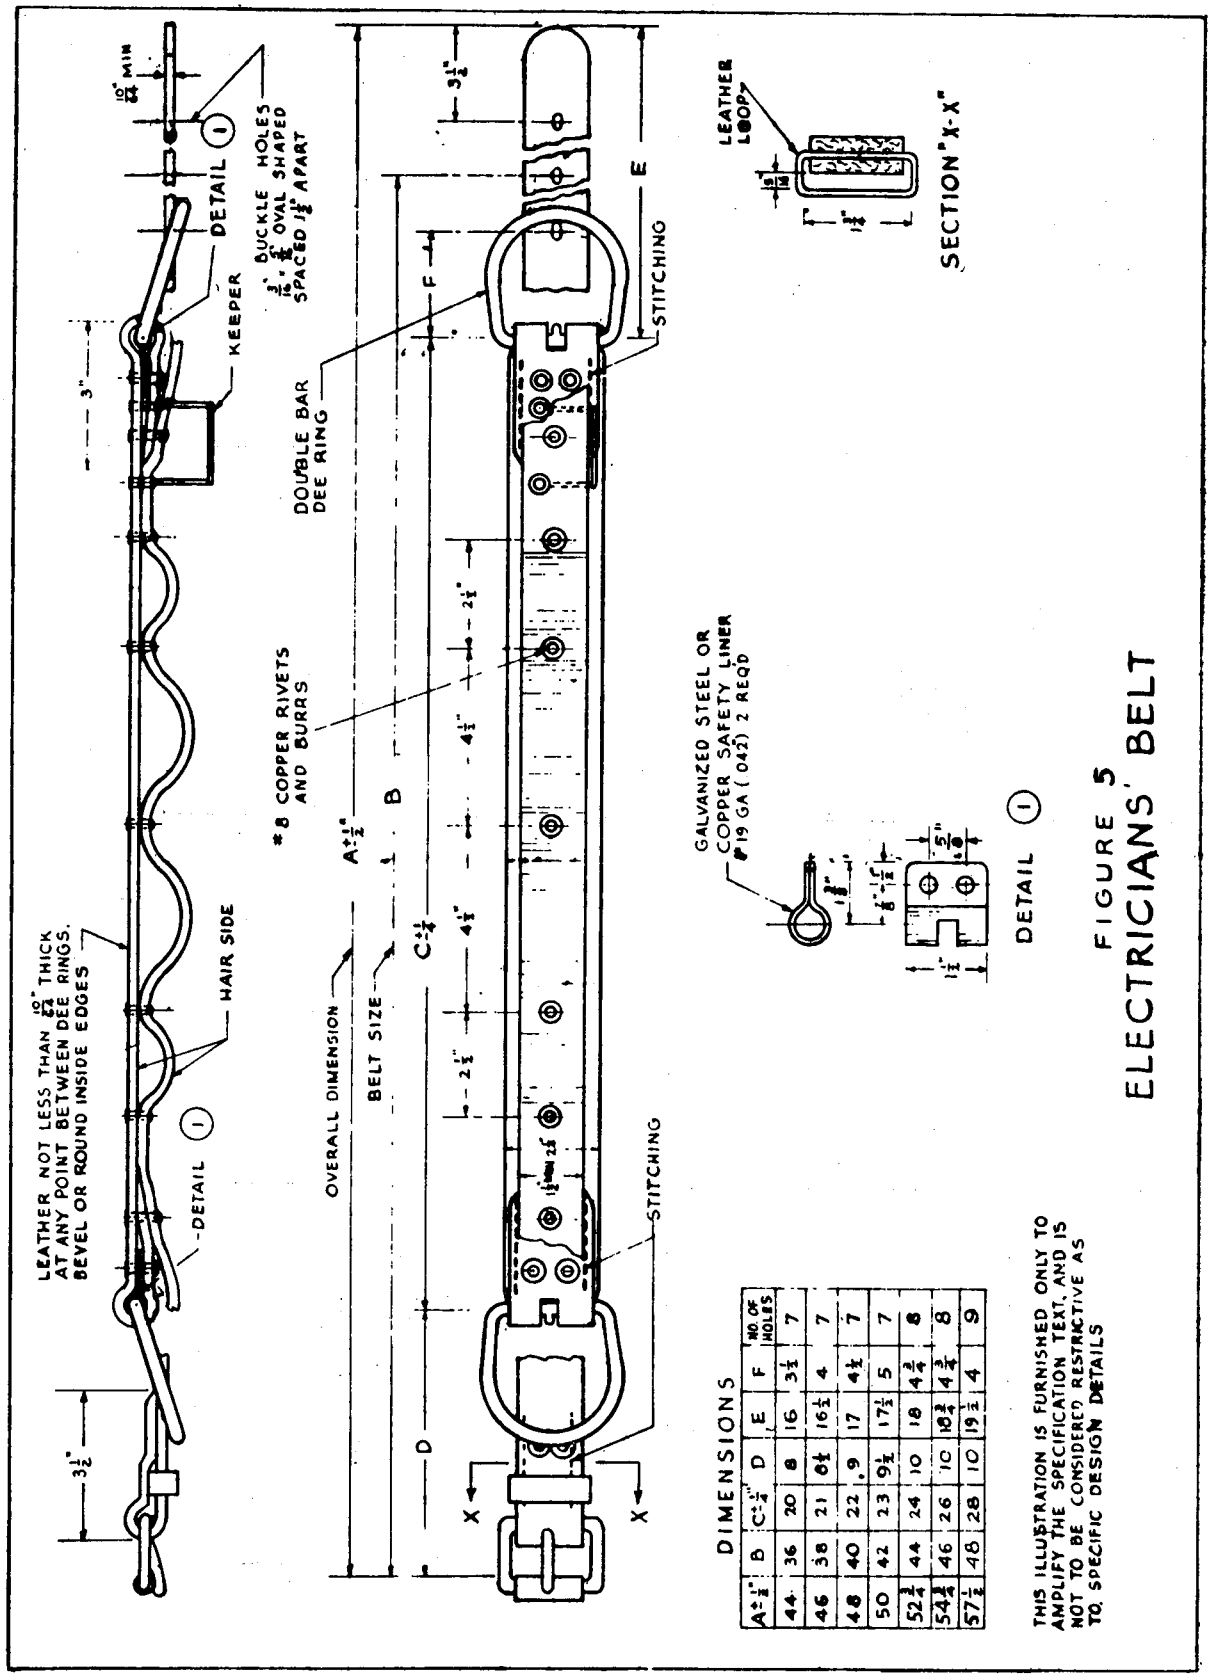


FIGURE 5

ELECTRICIANS' BELT

DIMENSIONS

A±½"	B	C±¼"	D	E	F	NO. OF HOLES
44	36	20	8	16	3½	7
46	38	21	8½	16½	4	7
48	40	22	9	17	4½	7
50	42	23	9½	17½	5	7
52½	44	24	10	18	4¾	8
54½	46	26	10	18½	4¾	8
57½	48	28	10	19½	4	9

THIS ILLUSTRATION IS FURNISHED ONLY TO AMPLIFY THE SPECIFICATION TEXT, AND IS NOT TO BE CONSIDERED RESTRICTIVE AS TO SPECIFIC DESIGN DETAILS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

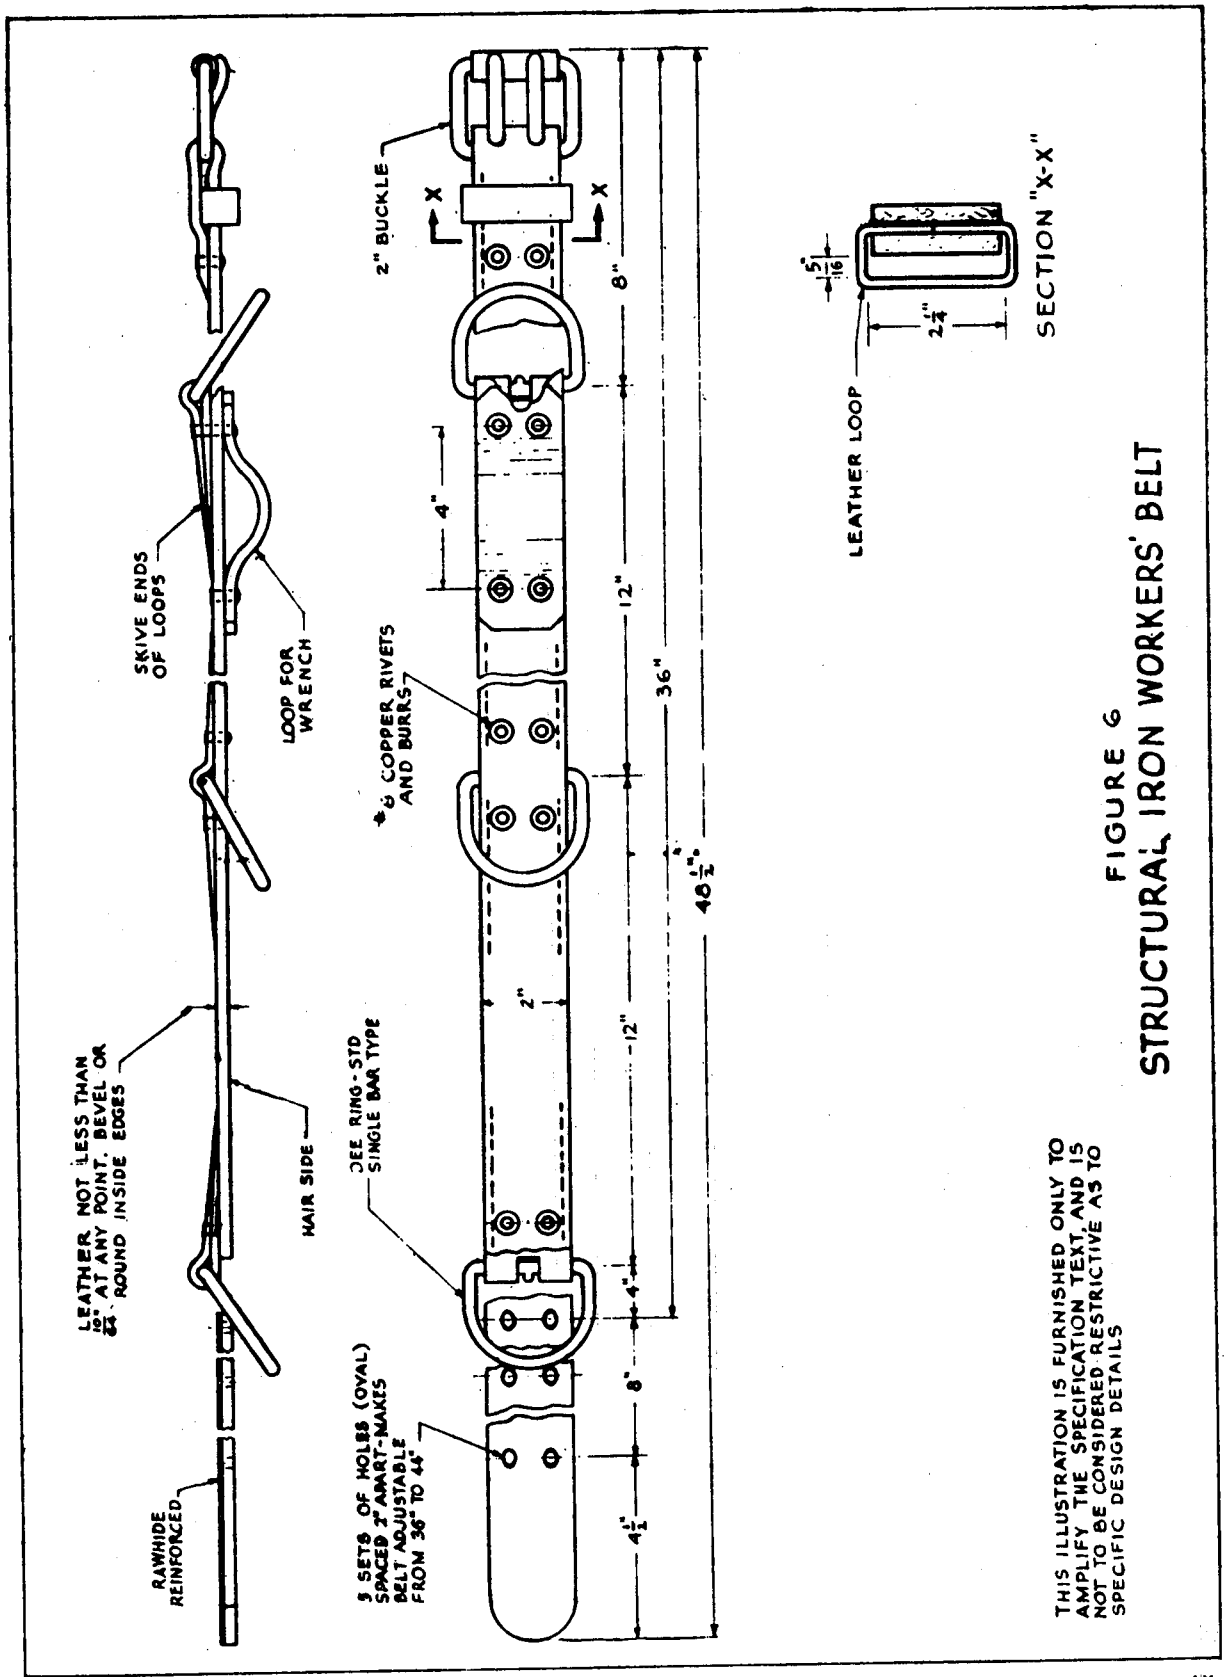


FIGURE 6

STRUCTURAL IRON WORKERS' BELT

THIS ILLUSTRATION IS FURNISHED ONLY TO AMPLIFY THE SPECIFICATION TEXT, AND IS NOT TO BE CONSIDERED RESTRICTIVE AS TO SPECIFIC DESIGN DETAILS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.


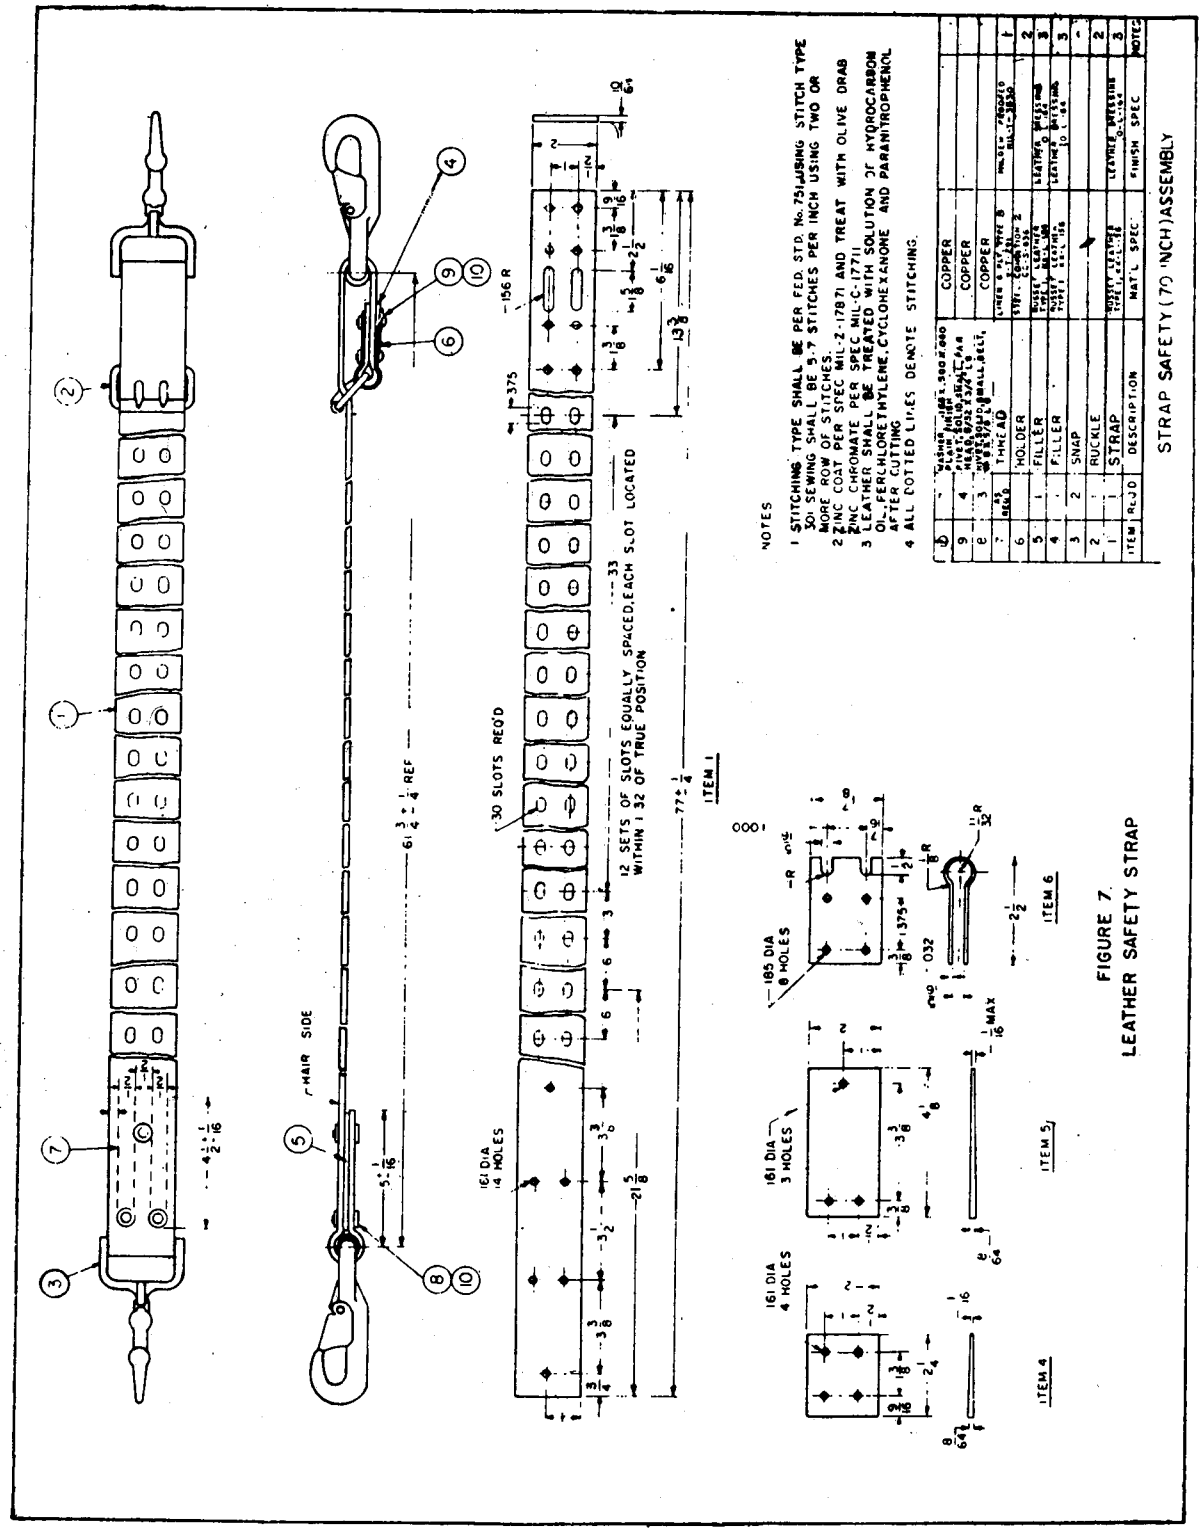


FIGURE 7.
LEATHER SAFETY STRAP

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

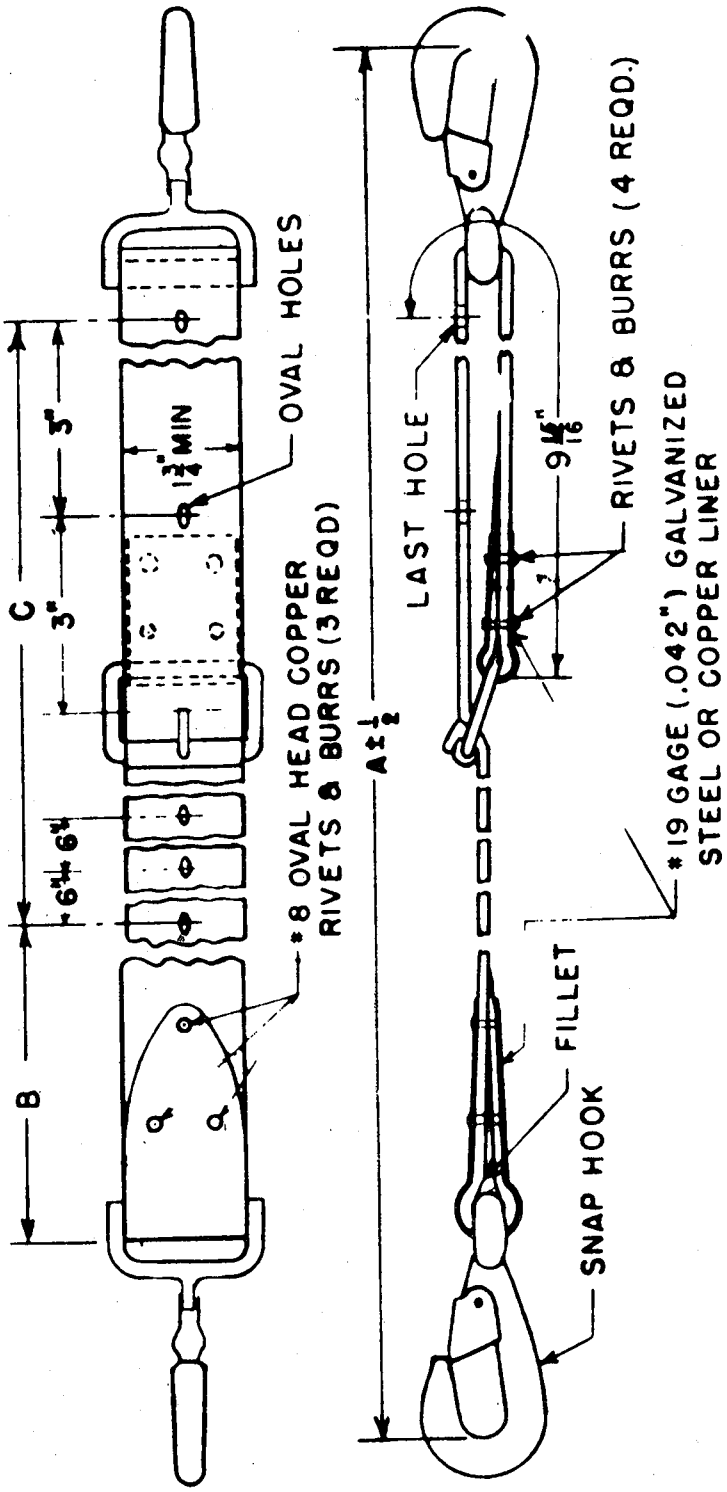

DIMENSIONS IN INCHES

A ± ½	B	C
84	11 1/8	60

NOTE
THIS ILLUSTRATION IS FURNISHED ONLY TO AMPLIFY THE SPECIFICATION TEXT, AND IS NOT TO BE CONSIDERED RESTRICTIVE AS TO SPECIFIC DESIGN DETAILS

FIGURE 8
NYLON SAFETY STRAP
NOT TO SCALE

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

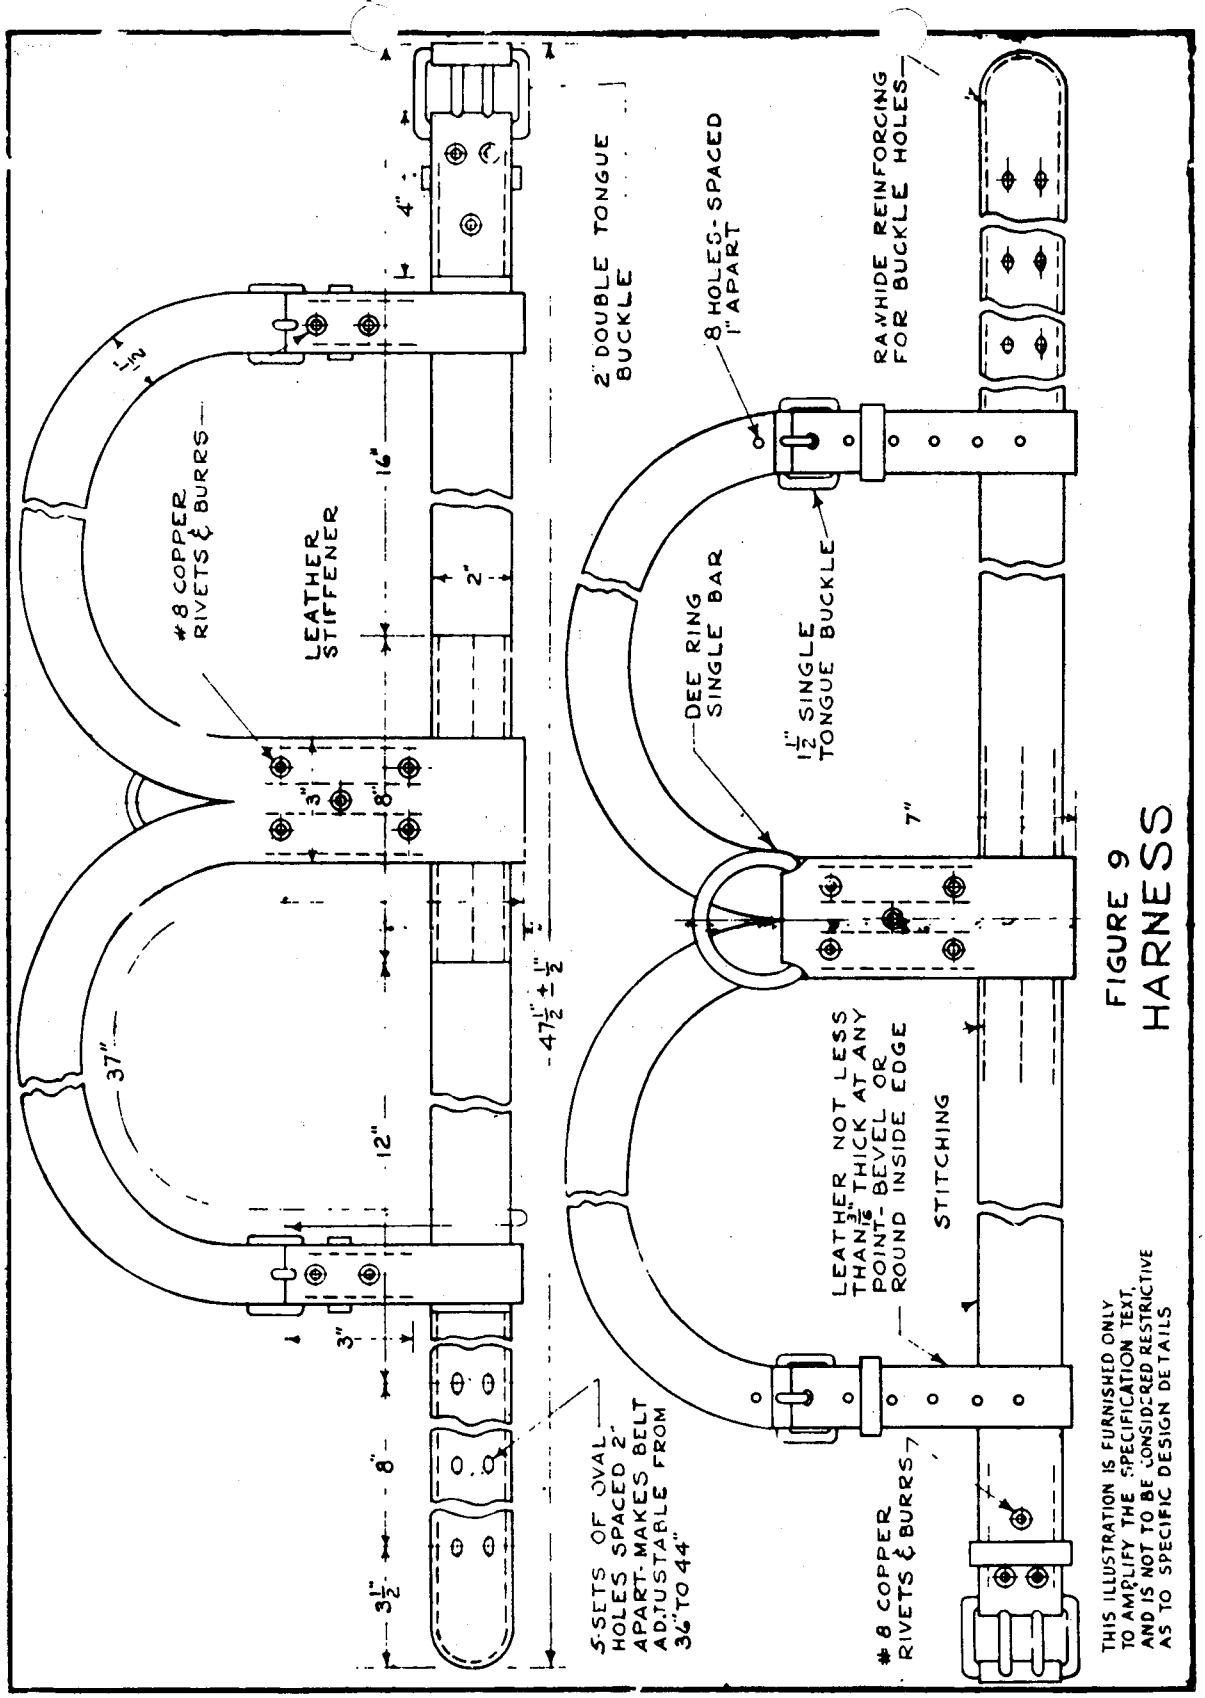


FIGURE 9
HARNESS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.

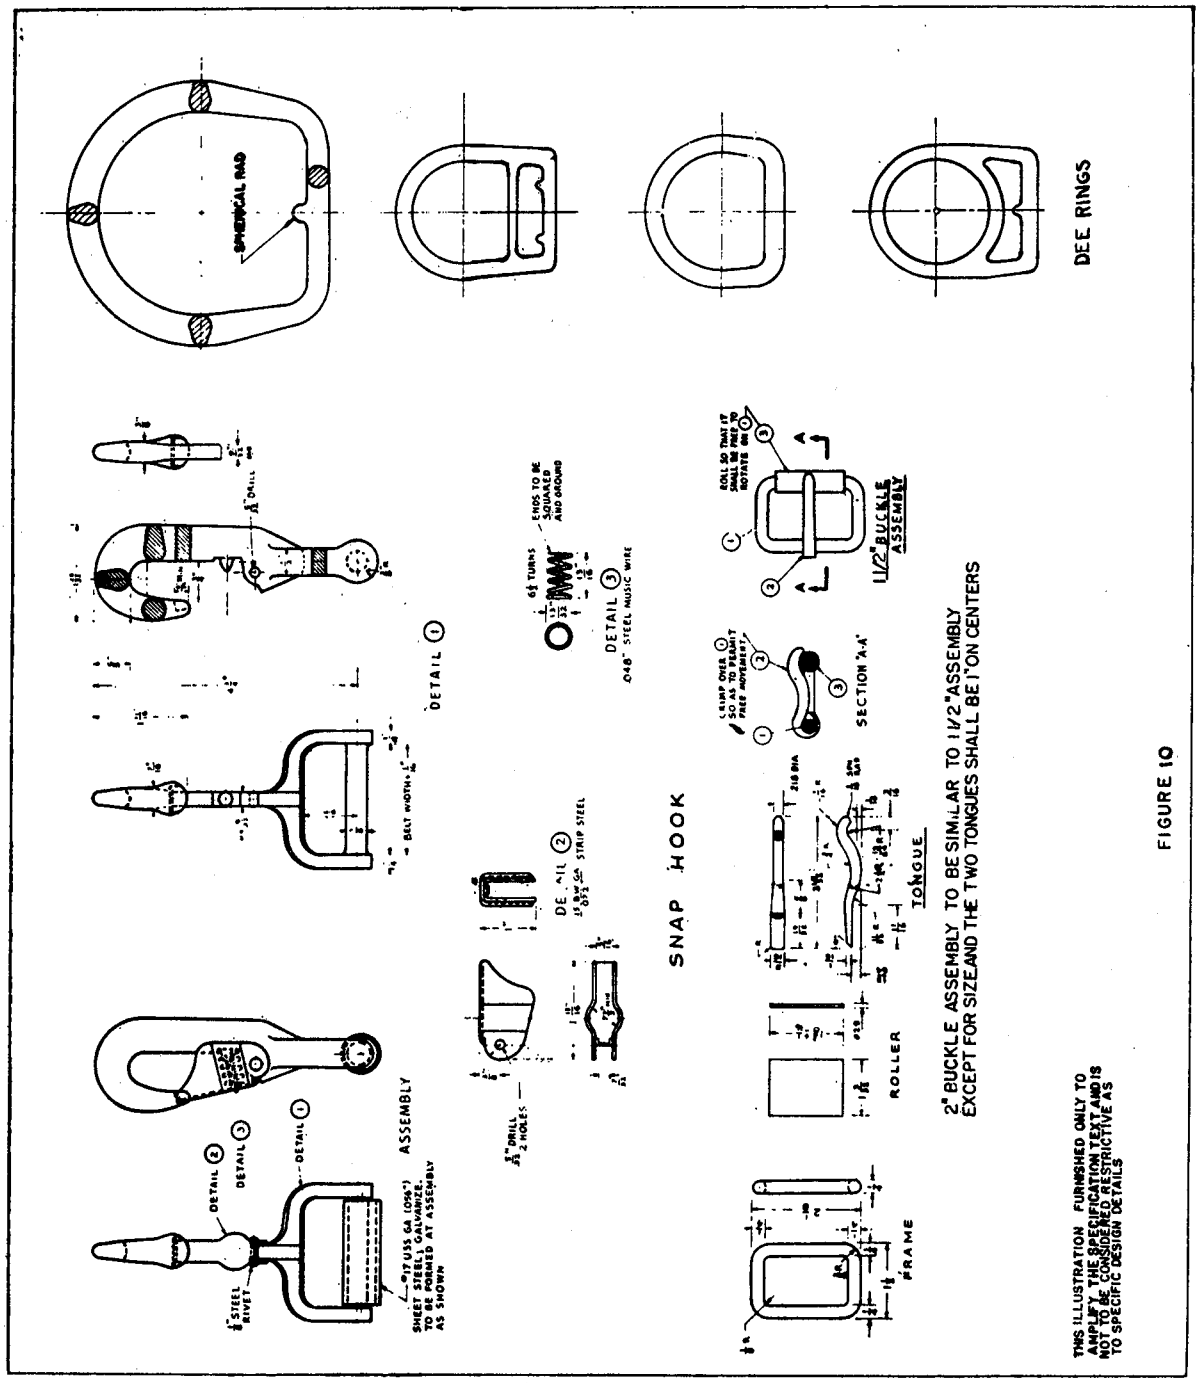


FIGURE 10

For sale by the Superintendent of Documents
Washington 25, D.C.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:56Z
Check the source to verify that this is the current version before use.