MIL-S-43272E
13 August 1984
SUPERSEDING
MIL-S-43272D
27 August 1980

MILITARY SPECIFICATION

SNOWSHOES: TRAIL, MAGNESIUM

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This document covers one type and size of magnesium frame trail snowshoe (see 6.1).

2. APPLICABLE DOCUMENTS

* 2.1 Government Documents. Unless otherwise specified, the following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of this document to the extent specified herein.

SPECIFICATIONS

FEDERAL

QQ-M-31	-	Magnesium Alloy, Bars, Rods, and Special Shaped Sections, Extruded
TT-E-529	-	Enamel, Alkyd, Semi-Gloss
TT-P-1757	-	Primer Coating, Zinc Chromate, Low-Moisture-Sensitivity
UU-P-268	-	Paper, Kraft, Wrapping
PPP-B-636	-	Boxes, Shipping, Fiberboard

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: U.S. Army Natick Research and Development Center, Natick, MA 01760-5014, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or letter.

FSC 8465

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:03Z
Check the source to verify that this is the current version before use.

MILITARY

MIL-M-3171 - Magnesium Alloy, Processes for Pretreatment and Prevention of Corrosion On
MIL-R-6944 - Rods and Wire, Welding, Magnesium Alloys
MIL-W-18326 - Welding of Magnesium Alloys, Gas and Arc, Manual and Machine Processes For
MIL-W-83420 - Wire Rope, Flexible, For Aircraft Control

STANDARDS

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129 - Marking for Shipment and Storage
MIL-STD-147 - Palletized Unit Loads

DRAWINGS

U.S. ARMY NATICK RESEARCH AND DEVELOPMENT CENTER

2-10-59 - Snowshoe, Trail, Magnesium; Assembly Complete
2-10-60 - Snowshoe, Trail, Magnesium; Frame

(Copies of documents required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer).

* 2.2 Other publications. Unless otherwise specified, the following documents of the issue in effect on date of invitation for bids or request for proposal form a part of this document to the extent specified herein.

AMERICAN SOCIETY FOR TESTING MATERIALS STANDARDS (ASTM)

A 109 - Steel, Carbon, Cold-Rolled Strip

B 633 - Electrodeposited Coatings of Zinc on Iron and Steel

D 789 - Standard Specification for Nylon Injection Molding and Extrusion Materials

D 3951 - Standard Practice for Commercial Packaging

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Technical society and technical association documents are generally available for reference from libraries. They are also distributed among

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:03Z
Check the source to verify that this is the current version before use.

technical groups and using Federal agencies.)

CANADIAN GOVERNMENT SPECIFICATION BOARD

CGSB1-GP-132 - *Primer Zinc Chromate, for Aircraft Use*

(Application for copies should be addressed to the Department of National Defense, Directorate of Interservice Development, Canada.)

* 2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document shall take precedence.

3. REQUIREMENTS

* 3.1 First article. When specified a sample shall be subjected to first article inspection (see 4.3, 6.2, and 6.3).

3.2 Materials (see 6.4).

* 3.2.1 Magnesium, extruded. The extruded magnesium shall conform to QQ-M-31. The chemical compositions shall be AZ31B, AZ61A and AZ80A, as applicable. Both shall be furnished in the extruded (F) temper.

* 3.2.2 Rods, welding. Welding rods shall conform to alloy composition AZ61A of MIL-R-6944.

3.2.3 Cable. The cable shall conform to type I, composition A of MIL-W-83420 except, the requirements for qualification, lubricant, endurance, and identification of product, are not applicable. The cable for the heel and toe section shall have 3 by 7 construction and a 1/32-inch diameter. The cable for the center section and edge or rim lacing of the toe and heel sections shall have 7 by 7 construction and a 1/16-inch diameter. The cable shall not be spliced and shall have a uniform, transparent, uncolored, continuous, nylon, extruded covering. The nylon shall conform to type VIII, grade 2 of ASTM D 789 (see 6.7). The nominal cable diameter with covering shall be 1/16 inch and 3/32 inch for the 3 by 7 and 7 by 7 constructions respectively.

3.2.4 Primer. The primer shall conform to composition G or L (as applicable), color Y of TT-P-1757; or Canadian Government Specification Board CGSB1-GP-132 (when applicable).

* 3.2.5 Enamel. The enamel shall be epoxy resin base, white color enamel (see 6.5), or shall conform to type II as applicable, color No. 27875 of TT-E-529.

* 3.2.6 Polyester coating. As an alternate to the primer and enamel specified in 3.2.4 and 3.2.5, a polyester coating conforming to Polymer Corporation PCA 1575 GP19^{O}K white number 21008, or equal, may be used. Prior

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:03Z
Check the source to verify that this is the currentversion before use.

to use of an "or equal" item, the contractor shall submit the item to the Contracting Officer with supporting data for approval.

* 3.2.7 Steel strip. Steel strip shall conform to cold rolled, temper No. 4, finish No. 1 and No. 4 round edge rolled of ASTM A 109.

3.3 Design and construction. The snowshoe design and construction shall conform to Drawings 2-10-59, 2-10-60, and as specified herein.

* 3.3.1 Frame. The snowshoe frame, except cross bars and gripping strips, shall be fabricated of composition AZ80A magnesium specified in 3.2.1 and be one continuous length. The snowshoe frame countersunk lacing holes shall be machined and spaced as shown on Drawing 2-10-60. The snowshoe frame shall be bent to shape with the side flanges of the ends butting together forming the tail section and welded as shown on Drawing 2-10-60.

3.3.1.1 Cross bars. The cross bars shall be fabricated of composition AZ31B magnesium specified in 3.2.1 and shall be located as shown on Drawing 2-10-60. Prior to positioning and welding the front and rear cross bars, the countersunk lacing holes shall be machined in the cross bars.

* 3.3.1.2 Gripping strips. The gripping strips shall be fabricated of composition AZ80A or AZ61A magnesium specified in 3.2.1, and shall be welded to the snowshoe frame as shown on Drawing 2-10-60 and as specified in 3.3.2.

3.3.2 Welding. All welding shall be done with inert-gas metal arc (tungsten electrode) using welding rods specified in 3.2.2 and in accordance with MIL-W-18326 except the requirements for checking welds by radiography shall not be applicable. Weld types and weld dimensions shall be as shown on Drawing 2-10-60. The completed welded assemblies shall be stress-relieved for 15 minutes at 500°F (plus 0°F, minus 20°F) and then air cooled. The time interval between welding and heat treatment shall not exceed 12 hours. Care shall be taken to insure that the frame maintains proper shape throughout the welding and stress relieving operations. The welding technique and time shall be such as to minimize melting of the frame beyond the weld deposit, avoid excessive penetration into the frame members, and produce welds that blend smoothly with the adjacent members. In conjunction with avoiding excessive penetration, heat should be concentrated on cross bars during welding of cross bars to frame.

3.3.3 Finish.

* 3.3.3.1 Pretreatment. After welding, the stress-relieved frames shall be given a pretreatment for prevention of corrosion in accordance with type III or VIII of MIL-M-3171.

* 3.3.3.2 Priming and enameling. The prepared frame shall be given a coat of the primer specified in 3.2.4. After the primer has dried, the frame shall be given a baked on coat of the enamel specified in 3.2.5.

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:03Z
Check the source to verify that this is the currentversion before use.

* 3.3.3.3 Coating. As an alternate to priming and enameling, the prepared frame shall be coated with the polyester coating specified in 3.2.6.

3.2.4 Lacing. The enamel shall be thoroughly dry before lacing the snowshoe. The snowshoe shall be laced by passing the cable specified in 3.2.3 through each lacing hole in the frame to form an interlaced web pattern similar to that partially shown on Drawing 2-10-59 which shall meet the requirements specified in 3.3.4.1 and 3.3.4.2. The ends of all lacing shall extend through to the ends of connectors or sleeves, and all lacing ends shall be enclosed by and secured with connectors or sleeves specified in 3.3.5 by crimping. Lacing ends shall not extend over 1/2 inch beyond connector or sleeve end.

3.3.4.1 Toe and heel section lacing. The toe and heel sections shall each be laced with not more than two lengths of cable. The lacing in the toe and heel sections shall not deflect more than 1/4 inch under a 30-pound dead load when tested as specified in 4.4.5. After the load is removed, the lacings shall not have a permanent set greater than 1/32 inch. The minimum number of crossing cables running in each direction shall be as shown in figure 1.

3.3.4.2 Center section lacing. The center section shall be laced with not more than three lengths of cable. The lacing in the center section shall not deflect more than 1 inch under a 200-pound dead load when tested as specified in 4.4.5. After the load is removed, the lacing shall not have a permanent set greater than 1/8 inch.

3.3.5 Connectors. The connectors shall be fabricated of steel specified in 3.2.6 and shall be as shown on Drawing 2-10-59. Connectors shall be closed over and around all lacing ends and crimped without flattening. Connector prongs shall be crimped over and shall not protrude. In lieu of connectors, lacing ends may be secured with seamless cylindrical sleeves made of aluminum, or zinc plated copper (see 6.6).

* 3.3.5.1 Plating. The connectors shall be given an electrodeposited zinc plating conforming to type I, classification No. Fe/Zn 13, service condition SC3 of ASTM B 633.

3.4 Identification marking. Prior to pretreatment for finishing, the letters "US", the contractors name and year of manufacture of the snowshoe shall be indented on the frame. The size and location of the markings shall be as shown on Drawing 2-10-60. The markings shall be legible after finishing.

3.5 Replacement of defective components. During the manufacturing process, components having material defects or damages that are classified as defects in 4.4.2.1, 4.4.2.2 or 4.4.3 shall be removed from production and replaced with non-defective and properly matched components.

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:03Z
Check the source to verify that this is the currentversion before use.

* 3.6 Workmanship. The finished snowshoe shall not be sprung, malformed or bent out of shape, and shall have all sharp edges and burrs removed. The finish shall be dry, adherent and uniform; and shall be free from runs, wrinkles, blisters, peeling or flaking, and areas of no film or thin film with primer or base metal showing through. Welds shall be sound and care shall be taken to eliminate weld flaws such as cracks, porosity, incomplete penetration, incomplete fusion, notches and undercuts. The occurence of defects shall not exceed the specified acceptable quality levels.

4. QUALITY ASSURANCE PROVISIONS

* 4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the document where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Classification of inspection. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3)
b. Quality conformance inspection (see 4.4)

4.3 First article inspection. When a first article is required (see 6.2), it shall be examined for the defects specified in 4.4.3 and 4.4.4 and tested for the characteristics specified in table I. The presence of any defect or failure of any test shall be cause for rejection of the first article.

4.4 Quality conformance inspection. Unless otherwise specified, inspection shall be in accordance with MIL-STD-105.

* 4.4.1 Component and material inspection. In accordance with 4.1, components and materials shall be inspected in accordance with all the requirements of referenced documents unless otherwise excluded, amended, modified, or qualified in this document or applicable purchase document.

4.4.2 In-process examination.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:03Z
Check the source to verify that this is the current version before use.

4.4.2.1 Operation examination. Examination shall be made of the operations listed below to determine compliance with the indicated requirements. Whenever nonconformance is noted, correction shall be made to affected items and process.

Operation	Requirement paragraph
Welding is accomplished with inert-gas metal arc (tungsten electrode)	3.3.2
Stress relieving of completed welded assemblies	3.3.2
Pretreatment process for prevention of corrosion	3.3.3.1
Application of primer prior to enameling (when applicable) (when alternate polyester coating is used there is no primer)	3.3.3.2
Identification marking before pretreatment	3.4

4.4.2.2 Welding examination. Prior to pretreatment process, the snowshoes shall be examined for defects listed below. The lot shall be expressed in units of one snowshoe. The sample unit shall be one snowshoe. The inspection level shall be S-3 and the acceptable quality level (AQL), expressed in terms of defects per hundred units, shall be 2.5 for major defects and 6.5 for total (major and minor combined) defects.

Examine	Defect	Classification Major	Minor
Welds and welding	Weld missing	X	
	Weld not in specified location		X
	Weld is less than specified length	X	
	Weld not type specified	X	
	Evidence of burn through on frame	X	
	Undercut on cross bars or frame	X	
	Weld is incomplete, e.g., not continuous (all around) where required	X	
	Unsound, cracked, porous, fractured, or otherwise not fused	X	
	Slag inclusion, flash, or flux deposit not removed		X
	Not smooth or not uniform	X	

4.4.3 End item visual examination. The end item shall be examined for the defects listed below. The lot size shall be expressed in units of one snowshoe. The sample unit shall be one completely fabricated snowshoe. The

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:03Z
Check the source to verify that this is the current version before use.

inspection level shall be II and the AQL, expressed in terms of defects per hundred units, shall be 1.5 for major defects and 4.0 for total (major and minor combined) defects.

Examine	Defect	Classification Major	Minor
Finish	Not adherent, i.e., flaking, blistering, or peeling	X	
	Dirt or foreign matter imbedded		X
	Finish not dry, i.e., tacky to touch		X
	Color not white	X	
	Not a close match to specified color		X
	Scratch, scuff, dig or abrasion exposing bare metal		X
	Area of thin film, e.g., base metal shows through	X	
	Area of thin film, e.g., primer shows through		X
	Not smooth and not uniform, i.e., run, sag, drop, or wrinkle		X
	Area of no film	X	
Frame	Hole missing	X	
	Component missing	X	
	Hole not countersunk		X
	Hole not free from burrs or rough edges		X
	Gripping strip extends beyond contour of frame	X	
	Frame surface not free from sharp edges or burrs	X	
	Sprung, malformed, cracked, or bent out of shape	X	
	Cross bar not positioned as shown on drawing		X
	Tail end corners not broken all around		X
Lacing	Lacing not through each hole	X	
	Lacing end not secured with connector or sleeve	X	
	Lacing end extends more than 1/2 inch beyond connector or sleeve		X
	Interlaced web pattern form not similar to that as partially shown on Drawing 2-10-59		X
	Number of crossing cables in toe or heel sections less than the minimum shown in figure 1	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:03Z
Check the source to verify that this is the current version before use.

Examine	Defect	Classification Major	Minor
Cable	Broken, spliced, or permanently kinked	X	
	Nylon covering cracked, fractured, deformed, not smooth, or not uniform		X
	More than three lengths used in center section	X	
	More than two lengths used in toe or heel section	X	
	Does not pass through loop and around cross bars as shown	X	
	Does not extend through full length of connector or sleeve	X	
Connector or sleeve (as applicable)	Not free from burrs and sharp edges	X	
	Not properly crimped, i.e., crushed, flattened, or prong on connector not meshed (point protrudes)		X
Marking	Missing, incomplete, illegible, incorrect, or characters not accomplished as specified		X

* 4.4.4 Dimensional examination. The end item shall be examined for compliance with dimensions specified. Any dimension that is not within the specified tolerances shall be classified as a defect. The lot size shall be expressed in units of one snowshoe. The sample unit shall be one snowshoe. The inspection level shall be S-2 and the AQL, expressed in terms of defects per hundred units, shall be 4.0.

4.4.5 End item testing. The end item shall be tested as specified in table I. The lot size shall be expressed in units of one snowshoe. The sample unit shall be one completely fabricated snowshoe. The inspection level shall be S-1 and the AQL, expressed in terms of defects per hundred units, shall be 2.5.

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:03Z
Check the source to verify that this is the current version before use.

Table I. End item tests

Characteristic	Requirement paragraph	Test paragraph	No. determinations per sample unit	Results reported as
Toe and heel section:				
Deflection	3.3.4.1	4.5.1	2 (1 each at heel and toe section)	Deflection to nearest 1/16 inch
Permanent set	3.3.4.1	4.5.1	2 (1 each at heel and toe section)	Pass or fail
Center section:				
Deflection	3.3.4.2	4.5.1	1	Deflection to nearest 1/16 inch
Permanent set	3.3.4.2	4.5.1	1	Pass or fail
Connectors	3.3.5	1/	--	--

1/ When sleeves are used, the contractor shall submit a certificate of compliance indicating whether the sleeves are aluminum or zinc plated copper.

4.4.6 Packaging inspection. An examination shall be made to determine that packing and marking comply with the section 5 requirements. Defects shall be scored in accordance with the list below. The sample unit shall be one shipping container fully packaged. The lot size shall be the number of shipping containers in the inspection lot. The inspection level shall be S-2 and the AQL, expressed in terms of defects per hundred units, shall be 2.5.

Examine	Defect
Marking (exterior and interior)	Omitted; incorrect; illegible; of improper size, location, sequence, or method of application.
Materials	Any component missing, damaged, or not as specified.
Workmanship	Bulged or distorted container. Snowshoe not packed on edge.

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:03Z
Check the source to verify that this is the current version before use.

Examine	Defect
Workmanship (cont'd)	Tail edge of snowshoe not positioned in the direction specified. Snowshoes not interleaved with kraft paper or more than four pieces of kraft paper used. Snowshoe in contact with adjacent snowshoe.
Contents	Number of snowshoes per container more or less than required.

4.4.7 Palletization examination. An examination shall be made to determine that the palletization complies with the section 5 requirements. Defects shall be scored in accordance with the list below.. The sample unit shall be one palletized unit load fully packaged. The lot size shall be the number of palletized unit loads in the inspection lot. The inspection level shall be S-1 and the AQL, expressed in terms of defects per hundred units, shall be 6.5.

Examine	Defect
Finished dimensions	Length, width, or height exceeds specified maximum requirement.
Palletization	Pallet pattern not as specified. Interlocking of loads not as specified. Load not bonded with required straps as specified.
Weight	Exceeds maximum load limit.
Marking	Omitted; incorrect; illegible; of improper size, location, sequence, or method of application.

4.5 Methods of inspection.

4.5.1 Deflection and permanent set test.

4.5.1.1 Loading blocks. Low density wood loading blocks shall be used for this test. The loading block for testing the toe and heel sections shall be 3 by 2 by 1/2 inch. The loading block for the center section shall be 8 by 3 by 1/2 inch.

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:03Z
Check the source to verify that this is the currentversion before use.

4.5.1.2 Positioning of toe section. The snowshoe shall be positioned (top side up) by elevating and supporting the tail so that the under surface of the loading block when placed on the toe section will be parallel to floor or test table. The snowshoe frame shall be rigidly supported at front and front cross bar. The longitudinal center lines of the block and snowshoe shall be aligned and the 2-inch dimensioned edge of the block shall be positioned parallel to and not less than 1-1/2 inches from leading edge of the front cross bar. The block shall not rest on the first cross lacing adjacent to the cross bar.

4.5.1.3 Positioning of heel section. The snowshoe frame shall be positioned top side up with lacing parallel to floor or test table and shall be rigidly supported at tail and rear cross bar. The longitudinal center lines of the loading block and snowshoe shall be aligned and the 2-inch dimensioned edge of the block shall be positioned parallel to and not less than 1-1/2 inches from trailing edge of the rear cross bar. The block shall not rest on the first cross lacing adjacent to the cross bar.

4.5.1.4 Positioning of center section. The snowshoe shall be placed in a horizontal position, rigidly supported at the cross bars. The longitudinal center lines of the loading block and snowshoe shall be aligned and the 3-inch dimensioned edge of the block shall be positioned parallel to and not less than 4-1/2 inches from trailing edge of the front cross bar. The block shall not rest on the first cross lacing adjacent to the front cross bar.

4.5.1.5 Procedure. The snowshoe and loading blocks shall be positioned as required for the section to be tested (see 4.5.1.2, 4.5.1.3 and 4.5.1.4). Three measurements shall be made for each section of the snowshoe. Each measurement shall be the perpendicular distance from center of the bottom surface of the loading block to a fixed point on the test table or floor. The first measurement shall be made with no weight applied to the loading block. The second measurement shall be made 1 minute after a dead weight has been evenly distributed on top of the loading block. A 30-pound weight shall be shall be used for the toe and heel sections and a 200-pound weight used for the center section. Immediately after the second measurement, remove the weight and make a third measurement. The difference between the first and second measurements of each section shall be recorded as the deflection of the section. The difference between the first and third measurement of each section shall be recorded as the permanent set of the section.

5. PACKAGING

5.1 Packing. Packing shall be level A, B, or Commercial as specified (see 6.2).

5.1.1 Level A packing. Twelve pairs of snowshoes shall be packed in a snugfitting fiberboard shipping container conforming to grade V2s, style FOL of PPP-B-636. The snowshoes shall be packed on edge, with the first twelve snowshoes positioned with the tail ends in one direction and the remaining twelve snowshoes positioned with the tailends in the opposite direction.

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:03Z
Check the source to verify that this is the currenversion before use.

Snowshoes shall be interleaved with one continuous length of 60-pound minimum basis weight kraft paper conforming to type I, grade A of UU-P-268, in such a manner as to prevent contact between adjacent snowshoes. As an alternative to one continuous length of interleaving paper, four separate pieces may be used. Each shipping container shall be closed in accordance with method III, waterproofed in accordance with method V, and reinforced in accordance with the appendix of PPP-B-636.

5.1.2 Level B packing. Twelve pairs of snowshoes shall be packed in a snugfitting fiberboard shipping container conforming to type CF, variety SW or SF, class domestic, grade 275, style FOL of PPP-B-636. Arrangement of snowshoes and interleaving with paper shall be as specified in 5.1.1. Closure shall be in accordance with method II of the appendix of PPP-B-636.

5.1.2.1 Weather-resistant fiberboard containers. When specified (see 6.2), the shipping container shall be a grade V3c, V3s, or V4s fiberboard box fabricated in accordance with PPP-B-636 and closed in accordance with method III as specified in the appendix thereto.

5.1.3 Commercial packing. Snowshoes shall be packed in accordance with ASTM D 3951.

* 5.2 Palletization. When specified (see 6.2), snowshoes packed as specified in 5.1 shall be palletized on a 4-way entry pallet in accordance with load type Ia of MIL-STD-147. Each prepared load shall be bonded with primary and secondary straps in accordance with bonding means K and L or film bonding means O or P. Pallet patterns shall be in accordance with the appendix of MIL-STD-147. Interlocking of loads shall be effected by reversing the pattern of each course. If the container is of a size which does not conform to any of the patterns specified in MIL-STD-147, the pallet pattern used shall first be approved by the contracting officer.

5.3 Marking. In addition to any special marking required by the contract or purchase order, shipping containers and palletized unit loads shall be marked in accordance with MIL-STD-129 or ASTM D 3951 as applicable.

6. NOTES

6.1 Intended use. The snowshoe is intended for use in traveling over snow covered terrain. The snowshoe can be used on either foot.

6.2 Ordering data. Acquisition documents should specify the following:

a. Title, number, and date of this document.
b. When a first article is required (see 3.1, 4.3, and 6.3).
c. Selection of applicable level of packing (see 5.1).
d. When weather-resistant grade fiberboard shipping containers are required for level B packing (see 5.1.2.1).
e. When palletization is required (see 5.2).

Source: https://assist.dla.mil -- Downloaded: 202640-21T21:03Z
Check the source to verify that this is the currentversion before use.

* 6.3 First article. When a first article is required, it shall be inspected and approved under the appropriate provisions of FAR 52.209-4. The first article should be a preproduction sample consisting of one pair of snowshoes. The contracting officer should include specific instructions in all acquisition instruments regarding arrangements for inspection and approval of the first article.

6.4 Recycled material. It is encouraged the recycled material be used when practical as long as it meets the requirements of the document (see 3.2).

6.5 Enamel. A white epoxy resin base enamel (British Paint Company Part No. B1210 Sinex) has previously given satisfactory results and may be utilized (see 3.2.5).

6.6 Sleeves. The following manufacturer's sleeves have previously been used in lieu of connectors specified in 3.3.5.

Item	Manufacturer	Manufacturer's Part No.
Sleeve for 3/32 cable	Burndy, Canada Ltd.	YSM8C
Sleeve for 1/16 cable	Burndy, Canada Ltd.	YSM10

The above is furnished only to indicate a possible source of supply, but bidders should include the patent indemnity article in all contracts for the acquisition of these items. Any manufacturer's item which conforms to the specified requirements or options will be acceptable.

6.7 Nylon cable covering. Zytel 153 available from E.I. duPont de Nemours and Co. Inc., Plastic Division, Wilmington, DE 19898, has been found to be a suitable covering.

6.8 Changes from previous issue. The margins of this document are marked with an asterisk to indicate where changes (additions, modifications, corrections, deletions) from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:03Z
Check the source to verify that this is the current version before use.

Custodians:

Army - GL
Navy - NU
Air Force - 99

Review activities:

Air Force - 82
DLA - CT

User activities:

Navy - MC
Air Force - 45

Preparing activity:

Army - GL

Project No. 8465-0886

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:03Z
Check the source to verify that this is the current version before use.

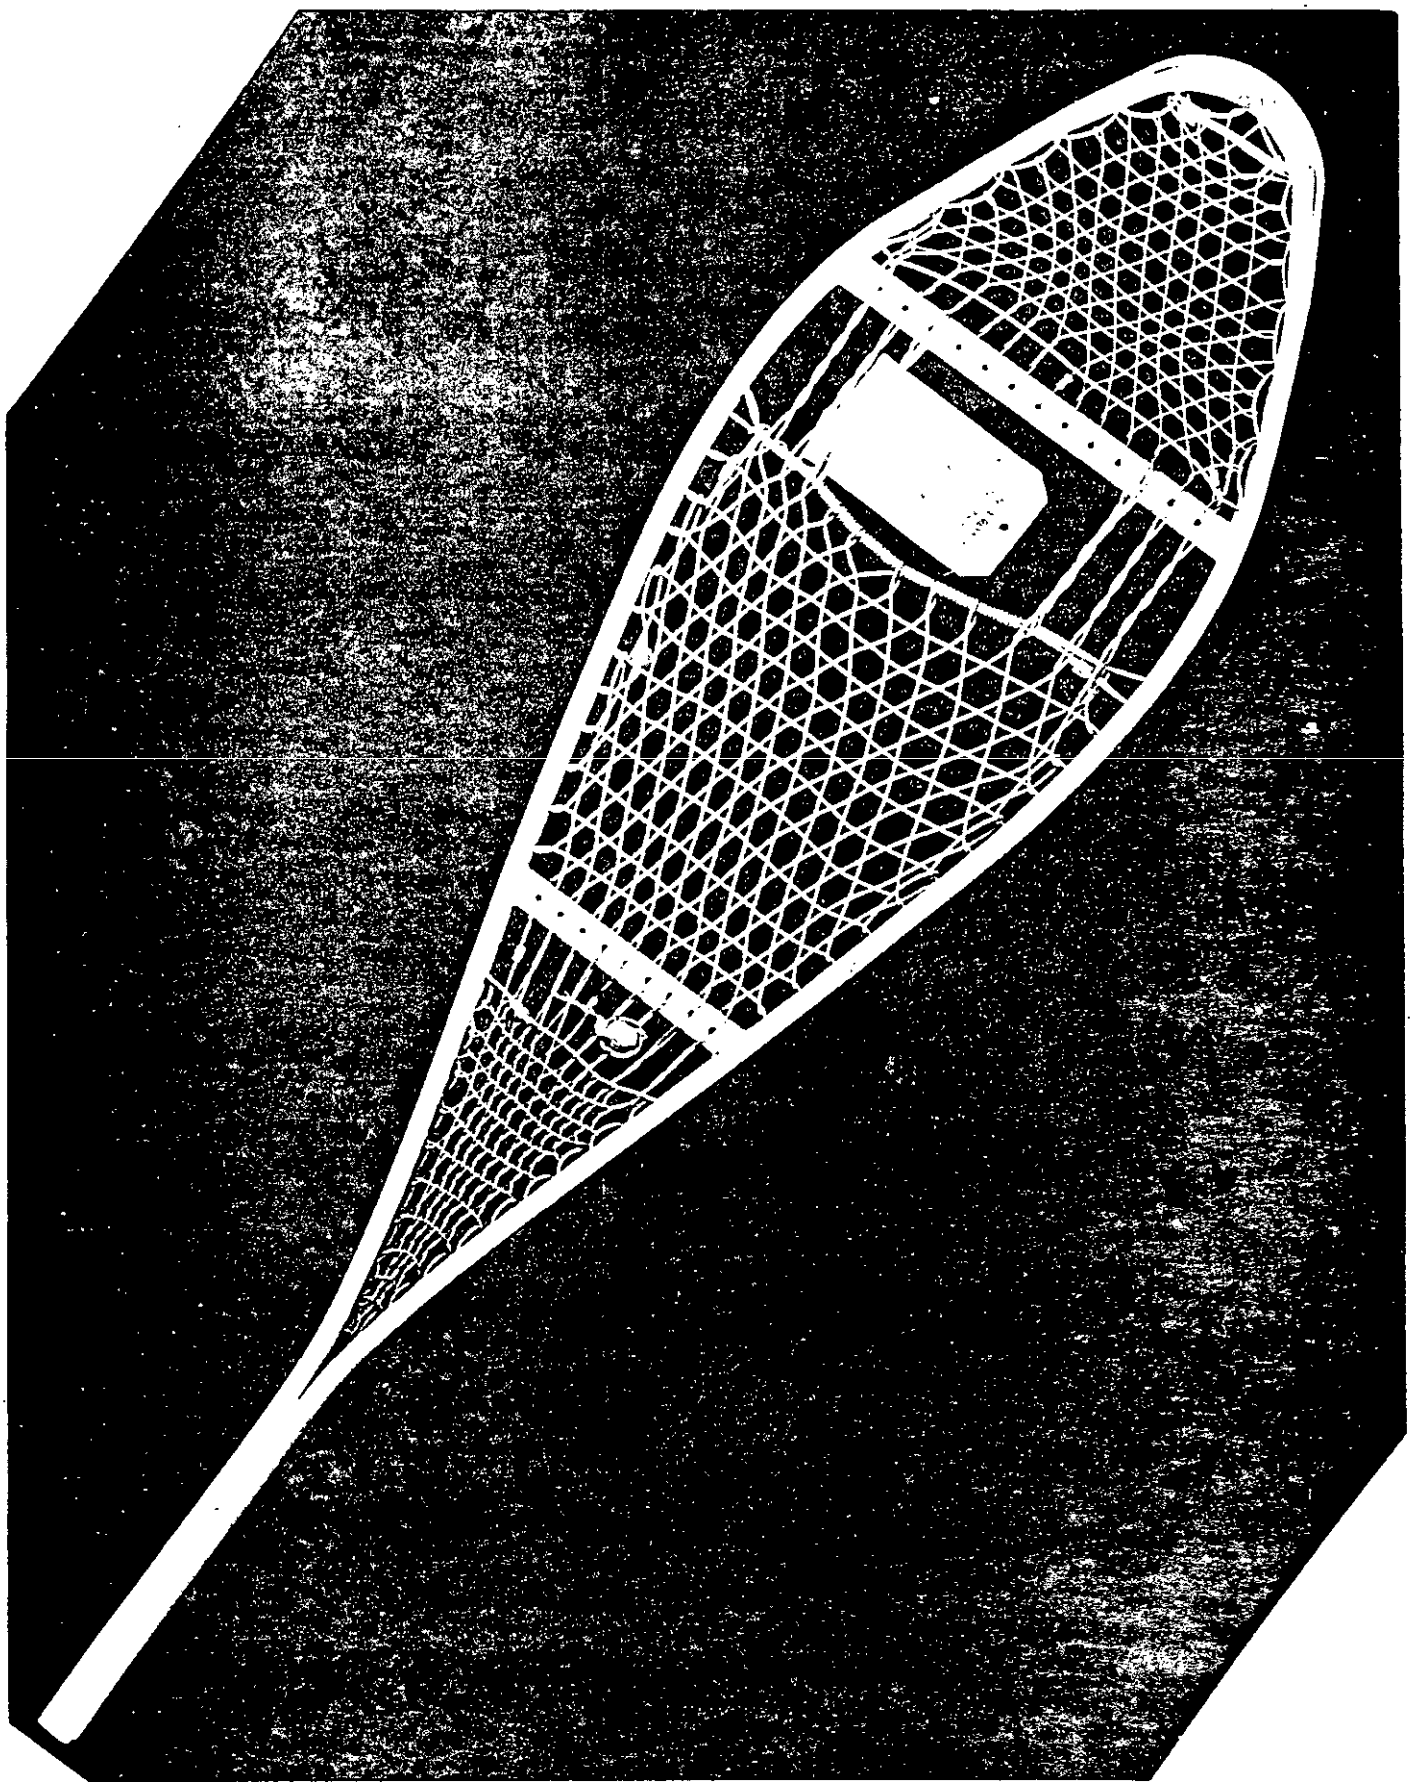


FIGURE 1. Snowshoes, Trail, Magnesium (Lacing Arrangement)

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:03Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY
US Army Natick Research and Development Center
Natick, Massachusetts 01760-5014

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300
STRNC-ES

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
US Army Natick Research and Development Center
ATTN: STRNC-ES
Natick, MA 01760-5014

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:03Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL–S–43272E	Snowshoes: Trail, Magnesium

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR ☐ USER ☐ MANUFACTURER ☐ OTHER *(Specify)*: _____
b. ADDRESS *(Street, City, State, ZIP Code)*	

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

NATICK OP, 1 Apr 84

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:03Z
Check the source to verify that this is the current version before use.