
MS9693

FED. SUP CLASS 5306

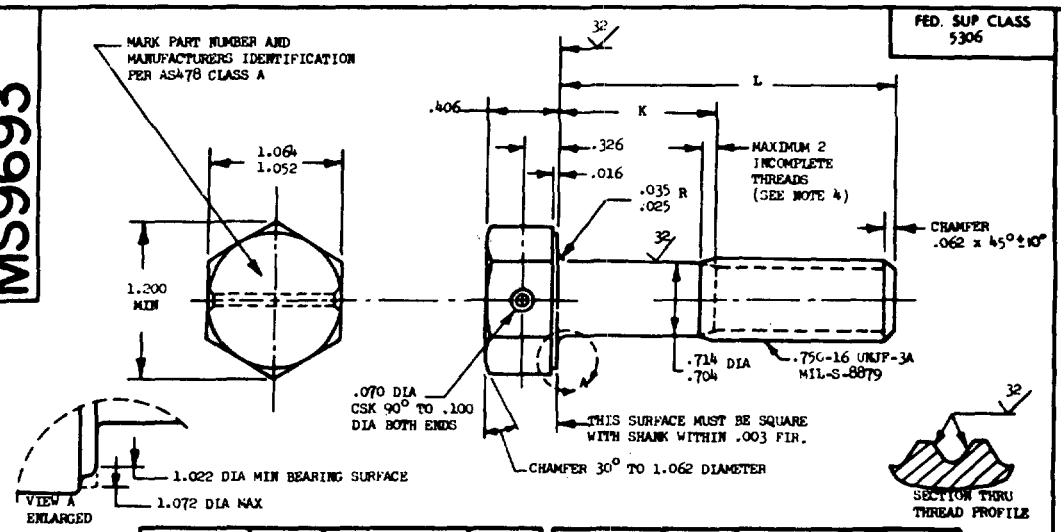

PART NUMBER	L	K	APPROX WEIGHT LB/100
MS9693-05	1.125	.129- .149	24.13
MS9693-06	1.250	.129- .149	24.83
MS9693-07	1.312	.129- .149	25.53
MS9693-08	1.375	.129- .149	26.22
MS9693-09	1.438	.129- .149	26.91
MS9693-10	1.500	.129- .149	27.60
MS9693-11	1.562	.129- .149	28.30
MS9693-12	1.625	.129- .149	28.99
MS9693-13	1.688	.129- .149	29.68
MS9693-14	1.750	.129- .149	30.38
MS9693-15	1.812	.129- .149	31.07
MS9693-16	1.875	.129- .149	31.76
MS9693-17	1.938	.129- .188	32.45
MS9693-18	2.000	.190- .250	33.15
MS9693-19	2.125	.315- .375	34.53
MS9693-20	2.250	.440- .500	35.92
MS9693-21	2.375	.565- .625	37.30
MS9693-22	2.500	.690- .750	38.69
MS9693-23	2.625	.815- .875	40.07
MS9693-24	2.750	.940-1.000	41.45
MS9693-25	2.875	1.065-1.125	42.84
MS9693-26	3.000	1.190-1.250	44.22
MS9693-27	3.125	1.315-1.375	45.61
MS9693-28	3.250	1.440-1.500	46.99
MS9693-29	3.375	1.565-1.625	48.38
MS9693-30	3.500	1.690-1.750	49.77
MS9693-31	3.625	1.815-1.875	51.16
MS9693-32	3.750	1.940-2.000	52.54
MS9693-33	3.875	2.065-2.125	53.92
MS9693-34	4.000	2.190-2.250	55.31
MS9693-35	4.125	2.315-2.375	56.69
MS9693-36	4.250	2.440-2.500	58.08
MS9693-37	4.375	2.565-2.625	59.46
MS9693-38	4.500	2.690-2.750	60.85
MS9693-39	4.625	2.815-2.875	62.23
MS9693-40	4.750	2.940-3.000	63.62
MS9693-41	4.875	3.065-3.125	65.00
MS9693-42	5.000	3.190-3.250	66.38
MS9693-43	5.125	3.315-3.375	67.77
MS9693-44	5.250	3.440-3.500	69.15
MS9693-45	5.375	3.565-3.625	70.54
MS9693-46	5.500	3.690-3.750	71.93
MS9693-47	5.625	3.815-3.875	73.32
MS9693-48	5.750	3.940-4.000	74.70
MS9693-49	5.875	4.065-4.125	76.08
MS9693-50	6.000	4.190-4.250	77.47

1. SHANK SHALL BE STRAIGHT WITHIN .002 TOTAL PER INCH OF BOLT LENGTH.
2. THE CONCENTRICITY OF THREAD PD IN RELATION TO THE SHANK SHALL BE WITHIN .006 FIR.
3. THE CONCENTRICITY OF THE SHANK IN RELATION TO THE WASHER FACE DIAMETER AND HEXAGON SHALL BE WITHIN .032 FIR.
4. INCOMPLETE THREADS NOT TO ENTER FILLET.
5. MATERIAL: STEEL AMS 6304.
6. HARDNESS: ROCKWELL C42-46.
7. FINISH: DIFFUSED NICKEL CADMIUM PLATE PER AMS 2416. DIMENSIONS SPECIFIED ARE AFTER PLATING. CONTACT POINTS PERMISSIBLE.
8. MANUFACTURING SPECIFICATION: AMS 7459.
9. MAGNETIC PARTICLE INSPECTION PER AMS 2640 BEFORE PLATING.
10. SURFACE TEXTURE: USAS B46.1-1962. UNLESS OTHERWISE SPECIFIED, SURFACES TO BE 125 MICROINCHES EXCEPT UPSET HEAD.
11. BREAK SHARP EDGES .003-.015 UNLESS OTHERWISE SPECIFIED.
12. DIMENSIONS IN INCHES. UNLESS OTHERWISE SPECIFIED, TOLERANCES: LINEAR DIMENSIONS ± .010, ANGULAR DIMENSIONS ± 5°.
13. DO NOT USE UNASSIGNED PART NUMBERS.

AS & AMS ARE SOCIETY OF AUTOMOTIVE ENGINEERS, INC. PUBLICATIONS.
THIS STANDARD WAS DEVELOPED COOPERATIVELY WITH THE MILITARY SERVICES BY THE SAE AEROSPACE PART STANDARDS DIVISION.

APPROVED 8 Jul 71 REVISED

P.A. Air Force-11	INTERNATIONAL INTEREST	TITLE	MILITARY STANDARD
Other Cust Navy-AS	ASCC AIR STD 17/2	BOLT, MACHINE - HEXAGON HEAD, DRILLED, 1 HOLE, PD SHANK, STEEL AMS 6304, DIFFUSED NICKEL CADMIUM PLATE, .750-16 UNJF-3A	MS9693
PROCUREMENT SPECIFICATION AMS7459		SUPERSEDES:	SHEET 1 OF 1

DD FORM 672-1 (Limited coordination) PREVIOUS EDITIONS OF THIS FORM ARE OBSOLETE

☆ U. S. GOVERNMENT PRINTING OFFICE: 1971-714-157/823

This standard has been approved by the Department of the Navy, and is mandatory for use by the activity. All other military activities are required to employ this standard where suitable.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T13:22Z
Check the source to verify that this is the current version before use.