DDD–B–421e
September 14, 1962

SUPERSEDING
Fed. Spec. DDD-B-421d
January 6, 1960

FEDERAL SPECIFICATION

BLANKET, BED (OTHER THAN ALL WOOL)

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers blankets other than all wool (see 6.1).

1.2 Classification.

1.2.1 *Types, classes, and sizes.* Blankets covered by this specification shall be of the following types, classes, and sizes, as specified (see 6.3):

Type I.—All cotton.

Class 1.—Twill (double filling).

Sizes:

1.—30 by 40 inches.
2.—60 by 84 inches.
3.—66 by 84 inches.
4.—66 by 90 inches.

Class 2.—Plain (single filling).

Sizes:

1.—70 by 84 inches.
2.—72 by 90 inches.

Type II.—Cotton warp-wool filling.

Class 1.—Twill (double filling).

Sizes:

1.—60 by 80 inches.
2.—66 by 90 inches.
3.—72 by 90 inches.
4.—66 by 84 inches.

Type III.—Blended nylon-wool-rayon-cotton and other fibers.

Class 1.—Twill (double filling).

Sizes:

1.—60 by 80 inches.
2.—66 by 90 inches.
3.—72 by 90 inches.
4.—66 by 84 inches.

2. APPLICABLE SPECIFICATIONS, STANDARDS, AND OTHER PUBLICATIONS

2.1 Specifications and standards. The following specifications and standards, of the issues in effect on date of invitation for bids, form a part of this specification to the extent specified herein.

Federal Specifications:

L-P-378 — Plastic Film (Polyethylene Thin Gauge).
R-N-91—Naphthalene, Technical.
V-T-276—Thread, Cotton.
CCC-T-191—Textile Test Methods.
DDD-L-20—Label; For Clothing, Equipage, and Tentage, (General Use).
PPP-B-576—Box, Wood, Cleated, Veneer, Paper Overlaid.
PPP-B-591—Boxes, Fiberboard, Wood-Cleated.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

PPP-B-601—Boxes, Wood, Cleated- Plywood.

PPP-B-621—Boxes, Wood, Nailed and Lock-Corner.

PPP-B-636—Box, Fiberboard.

PPP-T-60—Tape; Pressure Sensitive Adhesive, Waterproof — For Packaging and Sealing.

Federal Standards:

Fed. Std. No. 102—Preservation, Packaging, and Packing Levels.

Fed. Std. No. 123—Marking for Domestic Shipment (Civilian Agencies).

Fed. Std. No. 751—Stitches, Seams, and Stitchings.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications, Standards, and Handbooks and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U.S. Government Printing Office, Washington 25, D. C.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D. C., Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, and Auburn, Washington.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications, Standards, and Handbooks from established distribution points in their agencies.)

Military Specifications:

MIL-L-10547—Liners, Case, Waterproof.

Military Standards:

MIL-STD-105 — Sampling Procedures and Tables for Inspection by Attributes.

MIL-STD-129—Marking for Shipment and Storage.

MS 16686—Medical Services Symbol.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids shall apply.

Color Association of the United States, Inc.

U. S. Army Standard Color Card for the Official Colors for Arms and Services.

(Application for copies should be addressed to the Color Association of the United States, Inc., 200 Madison Avenue, New York 16, N.Y.)

Rules and Regulations Under the Wool Products Labeling Act of 1939.

Rules and Regulations Under the Textile Fiber Products Identification Act.

(Copies may be obtained without charge from the Federal Trade Commission, Washington 25, D. C.)

U. S. Department of Agriculture Methods of Test for Grade of Wool.

(Application for copies should be addressed to the U. S. Department of Agriculture, Agricultural Marketing Service, Washington 25, D. C.)

3. REQUIREMENTS

3.1 Standard sample. When a standard sample is available the dyed blanket for delivery shall match the standard sample for shade and all blankets shall be equal to, or better than, the standard sample with respect to all characteristics for which the standard sample is referenced (see 6.2).

3.2 Materials.

3.2.1 *Cotton yarns.* The cotton yarns shall be evenly spun from cleaned cotton of a grade and length of staple to meet the requirements for the finished blankets.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

3.2.2 *Wool yarns.* The wool yarns for type II blankets shall be made from wool, reprocessed wool (as defined by the Wool Products Labeling Act), or any combination thereof and shall be of a grade not lower than 44's U. S. Standard. The wool content of the filling yarn, when tested as specified, shall analyze not less than 99 percent.

3.2.3 *Yarns of nylon-wool-rayon-cotton and other fibers.* The blended fiber yarns for type III blankets shall be made from wool, reprocessed wool (as defined by the Wool Products Labeling Act), new nylon, new rayon, new cotton and other fibers as follows: Not less than 80 percent wool not lower in grade than 44's U. S. Standard. The reprocessed-wool content shall not exceed 50 percent of the wool used in the blend. Not less than 10 percent nylon fibers and not more than 10 percent rayon, cotton and other fibers.

3.2.4 *Thread.*

3.2.4.1 *Thread for overedge stitching and attaching labels.* The thread for overedge stitching the blanket and stitching on labels shall be cotton thread conforming to the requirements for type IC1, or IC2, ticket number B, 3-ply of V-T-276.

3.2.4.2 *Thread for binding stitching.* When binding is specified (see 6.3), the thread used for stitching binding shall be thread, cotton, ticket No. 0, 3-ply, conforming to type IC1 or IC2 of V-T-276.

3.2.4.3 *Color and colorfastness of thread.* The color of the thread shall match the color of the blanket and shall show good colorfastness to laundering and bleaching when tested as specified in V-T-276.

3.2.5 *Binding.* When cloth binding is specified (see 3.11.1.2) the binding shall be rayon or acetate satin weighing not less than 4 ounces per square yard. The binding shall be not less than 4 inches wide when finished, with uniformly constructed edges on both sides, or shall have edges cut parallel to the warp and shall be of sufficient width to meet the requirements of 3.11.1.2.2. The color of the binding shall match the shade of the blanket. The colorfastness shall be as specified in 3.4.4.3.

3.3 Markings.

3.3.1 All markings specified herein shall show colorfastness as specified in 3.4.4.3.

3.3.2 *Letters "U" and "S".* When specified (see 6.3), each blanket shall have the letters "US" in outline block letters, 4±1/8 inches high by 3-1/4 inches ± 1/8 inch wide in the center. The overall width of the lettering shall be 7-1/4 inches ± 1/4 inch.

3.3.3 *Caduceus.* When specified (see 6.3), each blanket shall be a caduceus 6 inches ± 1/8 inch high by 6-1/4 inches ± 1/8 inch wide, centered between the block letters "U" and "S", 2 inches ± 1/8 inch high by 1-1/2 inches ± 1/8 inch wide in the center of the blanket, conforming to MS 16686 (see 2.1).

3.3.4 *Color of letters and caduceus.*

3.3.4.1 *Color of letters and caduceus for type I, class 1, size 1 blankets.* The color shall be cable No. 65017 as shown in the U. S. Army Color Card for the Official Colors for Arms and Services (see 2.2). Colors shall be either stamped, printed, or applied by the dry print heat transfer process and the colorfastness shall be as specified in 3.4.4.3.

3.3.4.2 *Color of letters and caduceus for all other types, classes, and sizes.* The color shall be applied by direct printing, stamping, or dry print heat transfer process wih a black marking medium. The colorfastness shall be as specified in 3.4.4.3.

3.3.5 *Identification label.* Each blanket shall have a 2 inches ± 1/4 inch by 3 inches ± 1/4 inch label attached 2 inches ± 1/2 inch from each edge, on the back of the right-hand corner of the blanket as the blanket is viewed

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

face up. The label shall be attached by stitching, using a 301 stitch type, and there shall be not less than 10 stitches per inch. The label shall conform to type I, class 1 of DDD-L-20. The blanket is intended to be laundered. (Note: This sentence is included only for the purpose of specifying the fastness requirements for the labels in accordance with DDD-L-20). The label shall contain the following information with size of letters as indicated:

Nomenclature (10-point letters)
Contract number (8-point letters)

In addition, type I blankets shall be labeled, ticketed, or invoiced for fiber content in accordance with the Rules and Regulations Under the Textile Fiber Products Identification Act, and types II and III blankets shall be labelled in accordance with the Rules and Regulations Under the Wool Products Labeling Act of 1939. The legend may be incorporated in the identification label.

3.4 Color.

3.4.1 *Type I blankets.* Blankets shall be unbleached, bleached white, or dyed, as specified (see 6.3).

3.4.2 *Types II and III blankets.* When white is specified, the color shall be unbleached white consistent with the natural color of the specified fibers. The wool shall be so selected as to avoid the presence of black fibers. The black fiber content of the finished blanket shall be not more than that shown by the standard sample. When color is required, it shall be as specified (see 6.3).

3.4.3 *Color matching.* The color of all dyed textile components shall match the respective standard sample under natural (north sky) daylight or artificial daylight having a color temperature of 7500° Kelvin and shall be a good approximation to the standard sample under incandescent lamplight at 2800° Kelvin.

3.4.4 *Colorfastness.*

3.4.4.1 *Type I blankets.* When colors are specified, the finished blanket shall show fastness to laundering, bleaching, and crocking equal to or better than the standard sample. If no standard sample is available for colorfastness, the blanket shall show good colorfastness to laundering, bleaching, and crocking. Fastness shall be determined as specified in 4.3.

3.4.4.2. *Types II and III blankets.* When colors are specified, the finished blanket shall show fastness to laundering and crocking equal to, or better than, the standard sample; or if no standard sample is available for colorfastness, the blanket shall show good colorfastness to laundering and crocking. Fastness shall be determined as specified in 4.3.

3.4.4.3 *Component materials.* The colorfastness properties for the component materials used, binding, and marking as applicable shall be equal to those required for the blanket with which they are used when tested as specified in 4.2.1.2. When white blankets are specified, the markings shall show colorfastness equal to the requirements specified for markings on colored blankets.

3.5 Physical requirements. The finished blanket shall conform to the requirements specified in table I.

3.6 Weave.

3.6.1 *Class* 1. Class 1 blankets shall be double woven, having a twill face of one up-three down and a twill back of three up-one down using two sets of filling yarns and one set of warp yarns (see fig. 1). All class 1 blankets shall have woven selvages 1/4 (+ 1/8, — 0) inch.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

TABLE I.—*Physical requirements*

Type	Class	Size	Fiber	Blanket size minimum		Weight per blanket		Yarns per inch, minimum		Breaking strength grab method, minimum	
				Width	Length	Maximum	Minimum	Warp	Filling	Warp	Filling
				Inches	Inches					Pounds	Pounds
I	1	1	Cotton	30	40	9.0 oz.	7.8 ozs.	30	35	23	15
	1	2		60	84	3.2 lbs.	3.0 lbs.	37	36	30	25
	1	3		66	84	3.5 lbs.	3.3 lbs.	37	36	30	25
	1	4		66	90	3.7 lbs.	3.45 lbs.	37	36	30	25
	2	1		70	84	1.3 lbs.	1.2 lbs.	35	24	28	15
	2	2		72	90	1.7 lbs.	1.5 lbs.	27	28	27	17
II	1	1	Cotton warp, wool filling	60	80	3.45 lbs.	3.3 lbs.	52	40	38	36
	1	2		66	90	4.3 lbs.	4.1 lbs.	52	40	38	36
	1	3		72	90	4.6 lbs.	4.4 lbs.	52	40	38	36
	1	4		66	84	4.0 lbs.	3.8 lbs.	52	40	38	36
III	1	1	Blended wool-rayon cotton and other fibers	60	80	3.4 lbs.	3.3 lbs.	22	20	35	30
	1	2		66	90	4.4 lbs.	4.1 lbs.	22	20	35	30
	1	3		72	90	4.6 lbs.	4.4 lbs.	22	20	35	30
	1	4		66	84	4.0 lbs.	3.8 lbs.	22	20	35	30

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

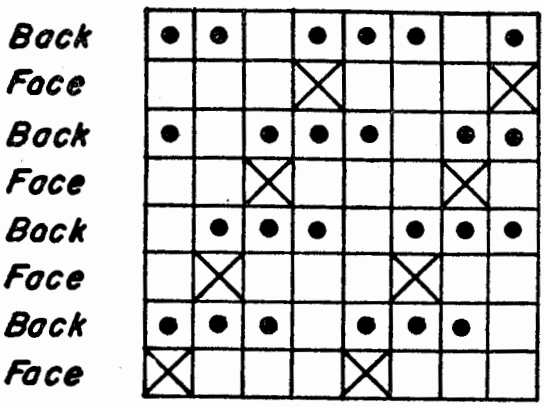


Figure 1. *-Weave diagram*

3.6.2 *Class* 2. Class 2 blankets shall have a plain weave with one warp and one filling, woven with selvages on the side 1/4 (+ 1/8 — 0) inch.

3.7 **Shrinkage.**

3.7.1 *Type I blankets.* The total shrinkage for type I, class 1 blankets shall not exceed 11.0 percent in the warp and 6.0 percent in the filling, and for type I, class 2 blankets shall not exceed 12.0 percent in the warp and 6.0 percent in the filling when a sample is subjected to laundering and then to dry cleaning when tested as specified in 4.3.

3.7.2 *Types II and III blankets.* The total shrinkage for types II and III blankets shall not exceed 10.0 percent in either the warp or filling direction when a sample is subject to laundering and then to dry cleaning when tested as specified in 4.3.

3.8 **Fiber content.**

3.8.1 *Type I blankets.* The fiber content of type I blankets shall be 100 percent cotton.

3.8.2 *Type II blankets.* The fiber content of type II blankets shall be not less than 80 percent wool of any combination thereof and not more than 20 percent cotton when tested as specified in 4.3.

3.8.3 *Type III blankets.* The fiber content of type III blankets shall be not less than 80 percent wool, not more than 10 percent rayon, cotton, and other fibers, and not less than 10 percent nylon when tested as specified in 4.3.

3.9 **Nonfibrous materials.** Sizing, finishing, and other nonfibrous materials shall not exceed 5.0 percent when tested as specified in 4.3, except type I class 2 blankets which shall not exceed 7.0 percent total nonfibrous materials.

3.10 **Finish.** The blankets of all types and classes shall have a finish equal to the standard sample with respect to nap and hand. The character of nap shall be such as will cause the napped fibers to offer considerable resistance to lifting with a needle.

3.11 **Construction.**

3.11.1 *Stitches, seams, and stitchings.*

3.11.1.1 *Type I blankets.* Unless otherwise specified, the blankets shall be cut to size with square corners, except that the corners of type I, class 1, size 1 shall be slightly rounded. All edges of type I, class 1, size 1 blankets and the cut edges of all other type I blankets shall be overstitched 1/4 inch wide with 16 to 20 stitches per inch of cotton thread specified in 3.2.4.1, stitch type 505 and stitching type EFd-1 conforming to Fed. Std. No. 751. The ends of the overedge stitching shall be locked.

3.11.1.2 *Types II and III blankets.* The cut ends of the blankets shall be finished by overedge stitching, binding with the cloth specified in 3.2.5, or by turning under and hemming (binding) 1/2 inch as specified (see 6.3).

3.11.1.2.1 *Overedge stitching for types II and III blankets.* When specified (see 6.3), the cut edges of the finished blankets shall be overedge stitched 1/4 inch wide with 16 to 20 stitches per inch of cotton thread specified

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

in 3.2.4.1 and stitch type 505 and stitching type EFd-1 conforming to Fed. Std. No. 751. The ends of the overedge stitching shall be locked.

3.11.1.2.2 *Binding stitching.* Satin binding shall be as specified in 3.2.5 and shall be attached with two rows of stitching 1/4 inch apart, 1/16 to 1/8 inch from edge, with 6 to 8 stitches per inch of cotton thread specified in 3.2.4.2 using stitch type 301 conforming to Fed. Std. No. 751. Seam type shall be BSa-2 when a binding with woven edges is used, and type BSc-2 on cut binding with stitches 1/8 to 3/16 inch from edge. The turnunder shall be 1/4 inch wide and shall be caught in the outer row of stitching, and the finished binding shall finish 4 inches of total exposed width. The ends of the binding shall have a 1 inch ± 1/8 inch turnunder. The stitching shall be backstitched 1/2 to 1 inch at the ends.

3.11.1.2.3 *Turned-end and hemmed stitching for types II and III blankets.* The ends shall be turned under 1/2 inch ± 1/8 inch hemmed 1/2 ± 1/8 inch and sewn with 2 rows of stitching 1/4 inch apart with 6 to 8 stitches per inch of cotton thread specified in 3.2.4.2 using stitch type 301 conforming to Fed. Std. No. 751. The stitching shall be backstitched 1/2 to 1 inch at the ends.

3.12 **Workmanship.** The finished blanket shall conform to the quality and grade of product established by this specification. Occurrence of defects shall not exceed the applicable acceptable quality levels.

4. SAMPLING, INSPECTION, AND TEST PROCEDURES

4.1 **Contractor's inspection responsibility.** The supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own or any other inspection facilities and services acceptable to the Government. Inspection records of the examination and tests shall be kept complete and available to the Government as specified in the contract of order. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.2 **Inspection for acceptance.** Except when otherwise specified by civil government agencies, sampling and inspection for acceptance shall be performed in accordance with MIL-STD-105, except where otherwise indicated.

4.2.1 *Inspection of components.* In addition to the quality assurance provisions of the subsidiary specifications, inspection shall be performed on components and materials listed in 4.2.1.1 and 4.2.1.2

4.2.1.1 *Examination of components.*

4.2.1.1.1 *Wool.* The wool shall be visually examined for grade (see 3.2.2 and 3.2.3) in scoured form prior to dyeing, picking, or carding by comparison with the applicable U. S. Standard (see 2.2). In the event of a dispute resulting from the above comparison, the grade shall be determined by a width (wedge) method approved by the Government. The examination for grade shall be performed on a composite sample of 1 pound of wool from each 10,000 pounds or fraction thereof in the lot. The composite sample shall be selected from not less than 10 percent of the bales in the lot. The lot shall be unacceptable if any portion of the sample does not conform to the requirements of 3.2.2 and 3.2.3.

4.2.1.2 *Testing of components.* Unless otherwise specified, testing shall be performed on the following components for the characteristics indicated, in accordance with CCC-T-191 wherever applicable and as listed in table III. The physical and chemical values specified in section 3 apply to the average of

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

the determinations made on a sample unit for test purposes as specified in the applicable test method. The sample size shall be in accordance with table II. The lot shall be unacceptable if one or more units fail to meet any requirements specified.

TABLE II.—*Lot and sample size*

Lot size	Sample size
Less than 800	2
801 to 22,000	3
22,001 and over	5

4.2.1.2.1 *Filling yarn (type II blankets.)* The sample unit for test purposes shall be 2 ounces of the yarn. The lot size shall be expressed in units of 1 pound each.

4.2.1.2.2 *Satin binding cloth.* The sample unit for test purposes shall be 9 linear yards of binding. The lot size shall be expressed in units of 1 linear yard each.

4.2.1.2.3 *Marking.* The sample unit for test purposes shall be a caduceus or "US" marking applied to a piece of finished blanket cloth under the same conditions as in production.

4.2.1.2.4 *Thread (for binding, overedge stitching, and attaching label).* The sample unit shall be 1 cone or spool of the thread. The lot size shall be expressed in units of 1 pound.

4.2.2 *In-process inspection.* Inspection shall be made at any point or any phase of the manufacturing process to determine that:

(*a*) Only approved components are used.

(*b*) Fiber materials are blended in the proportions specified.

The Government reserves the right to exclude from consideration for acceptance any blankets for which in-process inspection has indicated nonconformance.

TABLE III.—*Testing of components*

Characteristic	Requirement reference	Test method
Filling yarn:		
Wool content (type II blanket)	3.2.2	2101
Wool content (type III blanket)	3.2.3	2101[1]
Satin binding material:		
Material identification	3.2.5	1500, 1510
Weave	3.2.5	Visual[2]
Weight	3.2.5	5041[3]
Colorfastness of dyed binding to:		
Laundering	3.2.5	5614
Bleaching	3.2.5	5600
Crocking	3.2.5	5651
Colorfastness of markings to:		
Laundering	3.4.4.3	5614
Bleaching	3.4.4.3	5600
Crocking	3.4.4.3	5651

[1]The contractor shall submit a certification with each lot that new cotton, new rayon or new nylon fibers were used and that percent and type of fiber content is in accordance with the requirements of this specification. The certificate of compliance shall be accompanied by actual test, inspection or other verifiable data.

[2]One determination per sample unit and results reported as "pass or fail."

[3]Except that the specimen shall be any size of 2 square inches or more, without the limitations of method 5041.

4.2.3 *Inspection of the end item.*

4.2.3.1 *Examination of the end item.* Defects found during this examination shall be classified in accordance with list shown in 4.2.3.1.1, 4.2.3.1.2 and 4.2.3.1.3.

4.2.3.1.1 *Examination for workmanship.* Each blanket shall be examined on both sides and visual defects classified as listed below. Each blanket shall be given a through-light-

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

ing examination toward a light source for holes, thin or weak areas. The defects found shall be counted regardless of their proximity to each other, except where two or more defects represent a single local condition of the cloth, in which case only the more serious defect shall be counted. The sample unit for this examination shall be one blanket. The acceptable quality levels (AQL's) for this examination shall be 1.0 major and 4.0 total defects (major and minor combined) per 100 units (blankets). The sample size shall be based on level I of MIL-STD-105. The lot size shall be expressed in units of one blanket.

Defect	Classification	
	Major	Minor
Cloth defects:		
Hole, cut, or tear—Any	X	
Smash or clearly visible* mend—Any	X	
Broken or missing yarns:		
Two or more contiguous, 2 inches or more in length	X	
Two contiguous less than 2 inches in length or single more than 4 inches in length		X
Black fiber content in excess of that contained in standard sample (applicable to types II and III white blankets only).	X	
Float or skips:		
Multiple, 1/2 inch or more in combined warp and filling directions	X	
Single, more than 4 inches long		X
Skips, any sequence of two or more, regardless of length		X
Thin, light, or open place—clearly visible*	X	
Abrasion mark, weak place—clearly visible*	X	
Coarse filling bar, heavy place —clearly visible*	X	
Coarse yarns, slub, slough-off, jerked-in-filling—clearly visible*		X
Knot, large, extending from surface of blanket or resulting in clearly noticeable hard spot or bunch		X
Burr, shive, sisal or specks—clearly visible*		X
Selvage edge missing on either side	X	
Shade bar or dye streak, mixed filling—clearly visible*	X	
Spot or stain:		
1 inch or more in combined dimensions and clearly visible*	X	
Less than 1 inch in combined dimensions and clearly visible*		X
Tight yarn or edges—clearly noticeable tight areas or waviness		X
Waviness or rolling at edges will not flatten by manual pressure.		X
Workmanship defects:		
Unfinished—either one or both ends	X	
Needle chews—resulting in a weak place	X	
Seam or splice—blanket composed of two or more parts	X	
Scorch or burn—clearly visible*	X	
Wrong seam or stitch type		X
Loose stitch tension—resulting in an insecure or unsightly end	X	
Run-offs:		
More than 1 inch	X	
One half inch but not more than 1 inch		X
Raw edges (including binding):		
One inch or more	X	
Less than 1 inch		X
Finished ends:		
When overedge stitching is specified:		
Overedge stitching more than 5/16 inch or less than 3/16 inch		X
Less than sixteen overedge stitches per inch		X
Corners not rounded (type I, class 1, size 1 blankets only)		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

Defect	Classification	
	Major	Minor
Finished ends: (*cont'd*)		
When satin binding is specified:		
Stitching overrun, not securely anchored in binding		X
Note.—(Should be trimmed to 3/4 inch and pulled back under binding).		
Less than two rows of stitching	X	
Stitching gage less than 3/16 inch or more than 5/16 inch		X
Binding not adequately turned under (when without woven edges)		X
Turnunder not caught in stitching		X
Less than six stitches per inch		X
Total exposed width of binding less than 4 inches		X
Edge of binding on either corner of blanket not turned under at least 7/8 inch		X
Not backstitched 1/2 to 1 inch at the ends		X
When turned under ends are specified:		
Turned under less that 3/8 inch		X
Less than two rows of stitching	X	
Stitch gage less than 3/16 inch or more than 5/16 inch		X
Less than six stitches per inch		X
Not backstitched 1/2 to 1 inch at the ends		X
Markings, and insignia (as specified):		
Missing, incorrect, illegible or wrong color	X	
Misplaced by more than 2 inches		X
Label insecurely attached or misplaced by more than 1 inch		X
Not labeled in accordance with the Wool Products Labeling Act		X
Finished ends: (*cont'd*)		
Markings, and insignia (as specified) cont'd.		
Not labeled in accordance with the Textile Fiber Products Identification Act (type I)		X
Poor penetration, incomplete	X	
Height or width of lettering other than specified		X
Caduceus not specified size	X	
Shade and finishing defects:		
Off-shade—blanket not within acceptable range	X	
Mottled or cloudy		X
Color of binding or thread does not blend with color of blanket		X
Degree and character of finish not equal to standard	X	
Unevenly napped, clearly visible*	X	
Resistance of nap to lifting with needle not equal to standard sample		X
Rancid or other objectionable odor	X	
Hand of blanket not equal to standard sample		X
Threads not trimmed		X
Unclean overall appearance		X
Excess napping waste, nor properly cleaned from surface of blanket		X

*At normal inspection distance (approximately 3 feet).

4.2.3.1.2 *Examination for dimensions.* Defects found during this examination shall be classified in accordance with the following list. The sample unit shall be 1 blanket. The acceptable quality levels (AQL) shall be 1.5 major and 4.0 total defects per 100 units. The inspection level (sample size) shall be L-7 of MIL-STD-105. The lot size shall be expressed in units of 1 blanket. An approximate equal number of blankets shall be drawn from each shipping container selected for visual examination (see 4.2.3.1.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

Dimensions	Defect	Classification	
		Major	Minor
Size (30 by 40 inches)	Less than 40 inches long but not less than 39 inches		X
	Less than 39 inches	X	
	Less than 30 inches wide but not less than 29 inches		X
	Less than 29 inches wide	X	
	Length or width uneven by more than 2 inches		X
Size (60 by 80 inches)	Less than 80 inches long but not less than 78 inches		X
	Less than 78 inches long	X	
	Less than 60 inches wide but not less than 58 inches		X
	Less than 58 inches wide	X	
	Length or width uneven by more than 2 inches		X
Size (60 by 84 inches)	Less than 84 inches long but not less than 82 inches		X
	Less than 82 inches long	X	
	Less than 60 inches wide but not less than 58 inches		X
	Less than 58 inches wide	X	
	Length or width uneven by more than 2 inches		X
Size (66 by 84 inches)	Less than 84 inches long but not less than 82 inches		X
	Less than 82 inches long	X	
	Less than 66 inches wide but not less than 64 inches		X
	Less than 64 inches wide	X	
	Length or width uneven by more than 2 inches		X

Dimensions	Defect	Classification	
		Major	Minor
Size (66 by 90 inches)	Less than 90 inches long but not less than 88 inches		X
	Less than 88 inches long	X	
	Less than 66 inches wide but not less than 64 inches		X
	Less than 64 inches wide	X	
	Length or width uneven by more than 2 inches		X
Size (70 by 84 inches)	Less than 84 inches long but not less than 82 inches		X
	Less than 82 inches long	X	
	Less than 70 inches wide but not less than 68 inches		X
	Less than 68 inches wide	X	
	Length or width uneven by more than 2 inches		X
Size (72 by 90 inches)	Less than 90 inches long but not less than 88 inches		X
	Less than 88 inches long	X	
	Less than 72 inches wide but not less than 70 inches		X
	Less than 70 inches wide	X	
	Length or width uneven by more than 2 inches		X

4.2.3.1.3 *Examination for weight.* The samples for this examination shall be those selected for dimensional examination. The lot shall be considered unacceptable if the average weight of the blankets in the sample is less than the specified minimum weight or more than the specified maximum weight.

4.2.4 *Examination of preparation for delivery requirements.* An examination shall

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

be made to determine that packaging, packing and marking requirements of section 5 of this specification are complied with. Defects shall be scored in accordance with the list below. The sample unit shall be one shipping container fully prepared for delivery with the exception that it need not be sealed. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be L-4 and the AQL shall be 4.0 defects per hundred units.

Examine	Defect
Marking (exterior and interior)	Omitted, incorrect, illegible, of improper size, location, sequence, or method of application.
Materials	Any component missing or damaged.
Workmanship	Inadequate application of components, such as: incomplete closure of case liners, container flaps, loose strapping, inadequate stapling, improper taping. Bulging or distortion of containers.
Content	Number per package or container is more or less than required.
Preservation (when applicable)	Preservation improper, improperly applied or missing.

4.3 Testing of the end item. The methods of testing specified in CCC-T-191, wherever applicable, and as listed in table IV shall be followed. The physical and chemical values specified in section 3 apply to the average of the determinations made on a sample unit for test purposes as specified in the applicable test method. The lot size shall be expressed in units of one blanket. The sample unit for test purposes shall be one finished blanket except that for type I, class 1, size 1 blankets, the sample unit shall be two finished blankets. The sample size for each characteristic shall be in accordance with table II. The lot shall be unacceptable if one or more units fail to meet any requirements specified.

TABLE IV.—*Tests*

Characteristic	Requirement reference	Test method
Yarns per inch	Table I	5050
Breaking strength	Table I	5100
Weave:		
Class 1	3.6.1	Visual[1]
Class 2	3.6.2	Visual[1]
Shrinkage:		
Type I	3.7.1	5550[2] and 5580
Types II and III	3.7.2	5552[2] and 5580
Wool content:		
(Types II and III)	3.8.2-3.8.3	2101
Nylon content:		
(Type III)	3.8.3	2530
Nonfibrous material	3.9	2611
Colorfastness to:		
Laundering	3.4.4	5614
Crocking	3.4.4	5651
Bleaching	3.4.4	5600

[1]One determination per sample unit and results reported as "pass or fail."

[2]Except that evaluation, calculation of results and report of test methods 5550 and 5552 apply only after pressing operation of test method 5580. The three specimens shall be selected from the cloth (sample unit) as follows: One specimen from each side of the cloth to within 3 inches of selvage and one specimen from the center of the cloth. No two specimens shall contain the same filling yarns. Each elongation value shall be prefixed with a minus sign and both inclosed in parenthesis.

5. PREPARATION FOR DELIVERY

Fed. Std. No. 102 shall be referred to for definitions and application of the various levels of packaging and packing for civilian procurements.

5.1 **Packaging.** Packaging shall be level A, B or C as specified (see 6.3).

5.1.1 *Levels A and B.* Each blanket shall be neatly folded and individually packaged

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

in a snug-fitting polyethylene bag. When specified, three type I, class 1, size 1 blankets shall be packaged in a snug-fitting polyethylene bag. The polyethylene flexible film shall be 0.003 inch thick conforming to type I, grade A, B or C, finish 1 or 2 of L-P-378. All seams shall be effected by heat sealing and shall conform to the heat seal strength requirement in L-P-378. Prior to or during the final heat sealing closure operation, excess air within the bag shall be expelled. One ounce of naphthalene flakes conforming to R-N-91 shall be evenly distributed throughout each blanket containing wool.

5.1.2 *Level C.* Blankets shall be packaged in accordance with the industry's practice.

5.2 **Packing.** Packing shall be level A, B or C as specified (see 6.3).

5.2.1 *Level A.* Seventy-two type I, class 1, size 1 identical blankets; 35 type I, class 2, sizes 1 and 2 identical blankets; or 15 identical blankets of all other types, classes, and sizes, packaged as specified in 5.1, shall be packed in a snugfitting fiberboard shipping container conforming to class 2, V3c or V3s, style RSC-L of PPP-B-636. The inside of each fiberboard shipping container shall be fitted with a taped one-piece double-faced corrugated fiberboard liner conforming to compliance symbol V3c of PPP-B-636. Alternatively shipping containers may be used that conform to overseas type of PPP-B-591, or PPP-B-601; style A or B, class 2, type 2 load of PPP-B-576; or class 2, style 2 or 4 of PPP-B-621. Each shipping container (except fiberboard) shall be provided with type I or II, grade B or C, class 2 sealed case liner conforming to MIL-L-10547. Each shipping container shall be closed and reinforced with flat steel strapping in accordance with the appendix of the applicable container specification, except that fiberboard containers shall not be strapped and, in addition, shall have all seams, corners, and joints sealed by the application of a 3-inch cloth tape conforming to type III, class 1, olive drab color of PPP-T-60.

5.2.2 *Level B.* Seventy-two type I, class 1, size 1 identical blankets; 35 type I, class 2, sizes 1 and 2 identical blankets; or 15 identical blankets of all other types, classes, and sizes packaged as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container conforming to type I or II, class 1, style RSC-L of PPP-B-636. The minimum bursting strength of the fiberboard shall be 275 p.s.i. The inside of each fiberboard container shall be fitted with a taped one-piece double-faced corrugated fiberboard liner having a minimum bursting strength of 275 p.s.i. All flaps of the fiberboard shipping containers shall be securely sealed with an adhesive commercially used for the specific product being packed by application throughout the entire area of contact between the flaps, or by a combination of metal stitching the bottom flaps and sealing the top flaps with adhesive. Alternatively, shipping containers may be used that conform to domestic type, style A or B of PPP-B-591 or PPP-B-601; style A or B, class 1, type 2 load of PPP-B-576; or class 1 style 2 or 4 of PPP-B-621.

5.2.3 *Level C.* Blankets, packaged as specified in 5.1, shall be packed in a manner to insure carrier acceptance and safe delivery at destination at the lowest transportation rate for such supplies. Containers shall be in accordance with rules and regulations of carriers applicable to the mode of transportation.

5.3 **Marking.**

5.3.1 *Civil agencies.* In addition to any special marking required by the contract or order, shipping containers shall be marked in accordance with Fed. Std. No. 123.

5.3.2 *Military requirements.* In addition to any special marking required by the contract or order, shipping containers shall be marked in accordance with MIL-STD-129.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.

5.3.3 *Polyethylene bagged packages.* Polyethylene bagged packages shall have the required information legibly printed or stamped in black directly on the bag across the center face or on a white paper label inserted within the bag so as to permit ready identification. The bag or label shall indicate the following information:

Stock number
Nomenclature
Type, Class and Color
Size
Quantity

6. NOTES

6.1 Intended use. Type I, class 1, size 1 blanket is intended for infants' used in hospitals and nurseries. Other types and classes are primarily used as bed covering. Type I, class 2 blankets are also used as sheet and bath blankets.

6.2 Standard sample. For access to a standard sample address the procuring office issuing the invitation for bids.

6.3 Ordering data. Purchasers should exercise any desired options offered herein, and procurement documents should specify the following:

(a) Title, number, and date of this specification.
(b) Type, class, size, and color of blanket required.
(c) Whether or not paragraph 3.3.2 or 3.3.3 applies.
(d) Finish required for cut end of type II and III blankets (see 3.11.1.2).
(e) Selection of applicable levels of packaging and packing (see 5.1 and 5.2).

6.4 Transportation description. The transportation descriptions and minimum weights applicable to this commodity are:

Type I, classes 1 *and* 2

Rail:

Blankets, made wholly of cotton.
Carload minimum weight—any quantity.

Motor:

Blankets, not otherwise indexed.
Motor volume minimum weight—any quantity.

Type II, class 1, *Type III, class* 1

Rail:

Blankets, not otherwise indexed by name.
Carload minimum weight—any quantity.

Motor:

Blankets, not otherwise indexed.
Motor volume minimum weight—any quantity.

Notice. When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

MILITARY INTERESTS:
Army—M Q
Navy—S
Air Force—MAA

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:34Z
Check the source to verify that this is the current version before use.