MIL-B-21880D(SA)
13 June 1978
SUPERSEDING
MIL-B-21880C(SA)
25 February 1972

MILITARY SPECIFICATION

BELT, MILITARY POLICE (WHITE)

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope This specification covers the requirements for one type of woven adjustable belt.

2. APPLICABLE DOCUMENTS

* 2.1 Issues of documents The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

SPECIFICATIONS

FEDERAL

V-T-276	- Thread, Cotton
QQ-B-613	- Brass, Leaded and Nonleaded: Flat Products (Plate, Bar, Sheet, and Strip)
QQ-B-626	- Brass, Leaded and Nonleaded: Rod, Shaped, Forgings, and Flat Products with Finished Edges (Bar and Strip)
QQ-C-390	- Copper Alloy Castings (Including Cast Bar)
DDD-L-20	- Label, For Clothing, Equipage, and Tentage (General Use)

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Officer in Charge, Navy Clothing and Textile Research Facility, 21 Strathmore Road, Natick, MA 01760, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

FSC 8465

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T10:42Z
Check the source to verify that this is the current version before use.

MILITARY

MIL-F-411	- Fasteners, Belt; Clips, End, Strap, with Hook; and Keepers, Slide
MIL-W-530	- Webbing, Textile, Cotton, General Purpose, Natural or in Colors
MIL-F-10884	- Fasteners, Snap
MIL-B-17757	- Boxes, Shipping, Fiberboard, (Modular Sizes) or in Colors

STANDARDS

FEDERAL

FED-STD-751	- Stitches, Seams, and Stitchings

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	- Marking for Shipment and Storage

(Copies of specifications, drawings, standards, and publications required by contractor in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer).

LAWS AND REGULATIONS

US POSTAL SERVICE MANUAL

(Copies of the manual may be obtained from the Superintendent of Documents, US Government Printing Office, Washington, DC 20402.)

2.2 Other publications The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issues in effect on date of invitation for bids or request for proposal shall apply.

NATIONAL MOTOR FREIGHT TRAFFIC ASSOCIATION, INC., AGENT

National Motor Freight Classification

(Application for copies should be addressed to American Trucking Associations, Attn: Traffic Order Section, 1616 P Street, N.W., Washington, DC 20036.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T10:42Z
Check the source to verify that this is the current version before use.

UNIFORM CLASSIFICATION COMMITTEE, AGENT

Uniform Freight Classification

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, ILL 60606.)

3. REQUIREMENTS

3.1 Guide sample Samples, when furnished, are solely for guidance and information to the contractor (see 6.3). Variations from this specification may appear in the sample, in which case this specification shall govern.

* 3.2 First article approval When specified (see 6.2), the contractor shall furnish sample unit(s) for first article inspection and approval (see 4.3).

3.3 Materials

* 3.3.1 Webbing The webbing for the belt shall be 2 1/4 inches (57.15mm) wide, 3.40 minimum ounces per linear yard (105.75 gr. per meter), conforming to type IV, class 2 of MIL-W-530.

* 3.3.2 Tape The tape for binding the ends of the belt shall be 7/8 or 1 inch (22.23mm or 25.40mm) wide, conforming to type I, class 2 of MIL-T-43566.

* 3.3.3 Thread The thread for seaming and stitching shall be shade White AG, cable No. 66050, conforming to type IIIB, ticket No. 10, 3 ply of V-T-276.

3.3.4 Hardware

3.3.4.1 Snap fasteners The snap fasteners shall be brass conforming to style 2, 24 line (size 1), MS 27980-1, button and MS 27980-6, socket, construction A of MIL-F-10884, except that the button shall be copper alloy No. 268 of QQ-B-613 or QQ-B-626 and the finish shall be as specified in 3.3.5.

3.3.4.2 Belt fastener The belt fastener shall be brass conforming to type I, style 2, construction A of MIL-F-411, except that the fastener shall be Alloy A3 brass of QQ-C-390 and the finish shall be as specified in 3.3.5.

3.3.4.3 Slide keeper The slide keeper shall be brass conforming to type III, size 2, construction A or C of MIL-F-411, except that the finish shall be as specified in 3.3.5.

3.3.4.4 Adjusting buckle The adjusting buckle shall be brass, copper alloy No. 268 of QQ-B-613 or QQ-B-626 and the finish shall be as specified in 3.3.5. Design and dimensions shall be as shown in figure 1.

Source: https://assist.dla.mil -- Downloaded: 202610-19T10:42Z
Check the source to verify that this is the currentversion before use.

3.3.5 Finish All hardware components shall be given a mirror like polished finish with the surfaces and edges clean, smooth, and free from burrs, tool marks, sharp edges and roughness. All components shall be thoroughly lacquered with a clear synthetic lacquer. The dry lacquer film shall be continuous, level, adherent, and free from lint or other foreign inclusions. The components shall be free from pits, dents, nicks and scratches.

3.3.5.1 Change in appearance There shall be no change in appearance of the lacquered surface except for an overall yellowing and not more than three dark spots each not exceeding 1/32 inch (0.79mm) in the largest dimension when tested as specified in 4.4.1.

3.3.5.2 Tackiness Tissue paper shall not adhere to the lacquered surface when tested as specified in 4.4.1.

3.3.5.3 Flaking and chipping The lacquered surface shall show no flaking or chipping when tested as specified in 4.4.1.

* 3.4 Marking Each belt shall have the contract number applied to the inside of the belt, centered, 2 (± 1/2) inches (50.80 ± 12.70mm) from the snap fastener. The marking shall be black, conforming to type III or IV, class 9 of DDD-L-20, with height of numerals approximately 1/2 inch (12.70mm). The label shall show a minimum of "fair" colorfastness to laundering.

3.5 Design The belt shall be of white cotton webbing having two slide keepers, a female snap fastener and a hook type belt closure. It shall have an adjusting buckle enabling an adjustment range of the finished belt from 25 inches (63.50cm) to 42 inches (106.68cm) in length.

3.5.1 Figure Figure 1 is furnished for detail dimensional requirements. To the extent of any inconsistencies between the written specification and the figure, the written specification shall govern.

3.6 Construction

* 3.6.1 Stitch, seam and stitching types Stitch, seam and stitching types specified in Table I shall conform to FED-STD-751. Seam allowances shall be maintained with seams properly sewn so that no raw edges, runoffs, twists, pleats, or open seams will result.

3.6.2 Thread breaks and ends of seams Ends of all seams and stitchings shall be backtacked not less than 3/8 inch (9.53mm). Thread breaks shall be secured by stitching back of the break not less than 1/2 inch (12.70mm).

3.6.3 Stitches per inch The minimum and maximum number of stitches per inch (25.40mm) shall be as specified in Table I.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T10:42Z
Check the source to verify that this is the current version before use.

* 3.7 Manufacturing operations requirements The belts shall be manufactured in accordance with the operation requirements specified in Table I. The contractor is not required to follow the exact sequence of operations listed provided the finished belts are identical to those produced by following the sequence of operations as listed in Table I.

Source: https://assist.dla.mil -- Downloaded: 202610-19T10:42Z
Check the source to verify that this is the current version before use.

Table I - Construction of belt

No.	Description of Operation	Stitch Type	Seam and Stitching Type	Stitches Per Inch	Thread	
					Needle	Bobbin or Looper
*1	Assembling a. The belt shall be constructed from one continuous length of 2 1/4 (57.15mm) wide webbing cut not less than 50 inches (127.00cm) long.					
*	b. The raw edges of the belt shall be bound with 7/8 or 1 inch (22.23mm or 25.40mm) wide tape cut not less than 4 3/4 inches (12.07cm) long with the tape centered over the ends of the belt. The stitching shall be along the entire length of the binding.	301	BSa-1	6-8	10/3	10/3
9	c. One end of the belt shall be looped over the center bar of the adjusting buckle, with the ends of the binding turned under, and securely boxstitch 3/8 ± 1/16 inch (9.53 ± 1.59mm) wide (see figure 1). The resulting loop shall be 2 ± 1/4 inches (50.80 ± 6.35mm) long.	301	Boxstitch	6-8	10/3	10/3
*	d. The other end of the webbing shall be threaded through the two keepers and male fastener, back through the two keepers and through the adjusting buckle.					
	e. Insert free end through female fastener with ends of the binding turned under, and securely boxstitch 3/8 ± 1/16 inch (9.53 ± 1.59mm) wide (see figure 1). The resulting loop shall be 2 ± 1/4 inches (50.80 ± 6.35mm) long.	301	Boxstitch	6-8	10/3	10/3

NCTR Form 1, 15 Sep 1967

Source: https://assist.dla.mil -- Downloaded: 2026/10-19T10:42Z
Check the source to verify that this is the current version before use.

Table 1 - Construction of belt (cont'd)

No.	Description of Operation	Stitch Type	Seam and Stitching Type	Stitches Per Inch	Thread	
					Needle	Bobbin or Looper
*1.	Assembling (cont'd) f. The outer row of boxstitching shall be 3/16 ± 1/16 inch (4.76 ± 1.59mm) from folded edge of binding. The boxstitching shall finish 3/16 ± 1/16 inch (4.76 ± 1.59mm) from the edges of the webbing.					
2.	Finished length The minimum adjustable range of the finished belt shall be from 25 inches (63.50cm) to 42 inches (106.68cm).					
3.	Attach snap fastener The button and socket shall be positioned and securely clinched to the belt. The button shall be on the outside of the belt, centered 3 1/2 (± 1/4) inches (88.90 ± 6.35mm) from the folded end of the belt, measured from the center of the button.					
4.	Clean belts a. Trim all thread ends. b. Remove all loose threads. c. Remove all spots and stains.					

NCTR Form 1, 15 Sep 1967

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T10:42Z
Check the source to verify that this is the current version before use.

3.8 Workmanship The finished belts shall conform to the quality established by this specification. The occurrence of defects shall not exceed the applicable acceptable quality levels.

4. QUALITY ASSURANCE PROVISIONS

* 4.1 Responsibility for inspection Unless otherwise specified in the contract, contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to the prescribed requirements.

4.1.1 Certificate of compliance Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

* 4.2 Classification of inspection The inspection requirements specified herein are classified as follows:

1. First article inspection (see 4.3).
2. Quality conformance inspection (see 4.4).

4.3 First article inspection When required, the first article submitted in accordance with 3.2 shall be inspected for compliance with design, construction, workmanship, appearance, and dimensional requirements.

* 4.4 Quality conformance inspection Inspection shall be performed in accordance with the provisions set forth in MIL-STD-105, except where otherwise indicated herein.

4.4.1 Component and material inspection In accordance with 4.1 above, components and materials shall be inspected and tested in accordance with the requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified or qualified in this specification or applicable purchase document. In addition, the components listed in Table II shall be tested for the characteristics specified. The sample unit shall be one each of the components. The lot shall be expressed in units of each component. One determination shall be performed per sample unit and the results reported as "pass" or "fail". The lot shall be unacceptable if one or more units fail to meet any requirement specified. The sample size shall be as follows:

Source: https://assist.dla.mil -- Downloaded: 202640-19T10:42Z
Check the source to verify that this is the current version before use.

Lot Size	Sample size
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

Table II - Test methods

Component	Characteristic	Requirement Paragraph	Test Method
Snap fastener	Change in appearance	3.3.5.1	4.4.1.1
	Tackiness	3.3.5.2	4.4.1.2
	Flaking and chipping	3.3.5.3	4.4.1.3
Belt fastener	Change in appearance	3.3.5.1	4.4.1.1
	Tackiness	3.3.5.2	4.4.1.2
	Flaking and chipping	3.3.5.3	4.4.1.3
Slide keeper	Change in appearance	3.3.5.1	4.4.1.1
	Tackiness	3.3.5.2	4.4.1.2
	Flaking and chipping	3.3.5.3	4.4.1.3
Adjusting buckles	Change in appearance	3.3.5.1	4.4.1.1
	Tackiness	3.3.5.2	4.4.1.2
	Flaking and chipping	3.3.5.3	4.4.1.3

4.4.1.1 Change in appearance The hardware component shall be immersed in a 2 percent by weight of CP liver of sulphur (potassium sulfide) water solution at a temperature of 100°F to 110°F (37.78°C to 43.33°C) for 3 minutes. The hardware shall then be removed and rinsed in warm, then cold, then hot water after which it shall be wiped gently with an absorbent cellulose material or whirled to remove residual moisture, allowed to air dry at room temperature for 1 hour and examined for compliance with 3.3.5.1.

4.4.1.2 Tackiness A piece of tissue paper shall be pressed against the finished lacquered hardware component surface at room temperature (60°to 80°F) (15.56°C to 26.67°C) for 15 seconds with any pressure capable of being exerted by the thumb and two fingers. At the completion of 15 seconds, the finger pressure shall be released to determine compliance with 3.3.5.2.

Source: https://assist.dla.mil -- Downloaded: 202610-19T10:42Z
Check the source to verify that this is the current version before use.

4.4.1.3 Flaking and chipping Draw a knife edge across the face side of a test specimen making four parallel scores 1/16 inch (1.59mm) apart. Repeat this process, drawing the knife edge this time perpendicular to the previously scored lines, making small blocks in the finish. No flaking or chipping of the small blocks shall occur.

* 4.4.2 Examination of the end item Examination of the end item shall be in accordance with 4.4.2.1 and 4.4.2.2. The applicable inspection levels and acceptable quality levels (AQL's) shall be as indicated in 4.4.2.3. The sample unit shall be one finished belt. The lot size shall be expressed in units of belts.

* 4.4.2.1 Visual examination The belt shall be examined for defects classified in accordance with the list below:

Defect	Classification Major	Minor
MATERIAL DEFECTS AND WORKMANSHIP		
a. Any hole, needle chew, cut or tear	X	
b. Any weakening defect such as smash or float	X	
c. Any mend	X	
WEBBING		
a. Spliced, i.e., not one continuous piece	X	
b. Not firmly or tightly woven, edges frayed or scalloped	X	
BINDING		
a. Omitted or wrong type	X	
b. Stitching not along entire length		X
THREAD		
Not size or color specified		X
HARDWARE		
General		
a. Any burr, tool mark or sharp edge	X	
b. Corroded	X	
c. Not highly polished, clean and smooth	X	

Source: https://assist.dla.mil -- Downloaded: 202610-19T10:42Z
Check the source to verify that this is the current version before use.

Defect	Classification Major	Minor
HARDWARE (cont'd)		
Finish		
a. Not lacquered	X	
b. Lacquer peeling, has run, sag or contains foreign inclusions	X	
c. Any pits, nicks, dents or scratches	X	
d. Lacquer wet or tacky	X	
Snap fastener		
a. Improperly clinched		X
b. Not positioned as specified		X
Keepers		
Broken or malformed, failing to serve intended purpose	X	
Belt fastener		
a. Male or female part set in reversed position	X	
b. Male or female part broken or malformed failing to effect a smooth closure	X	
Adjusting buckle		
Broken or malformed, failing to serve intended purpose	X	
CLEANNESS		
a. Any permanent spot or stain	X	
b. Any spot or stain easily removed		X
c. Thread ends not trimmed		X
COMPONENTS AND ASSEMBLY		
Any component part or operation omitted (unless otherwise classified herein)	X	
MARKING		
a. Exposed on outside of belt	X	
b. Omitted, illegible, incorrect, misplaced, or size of characters not as specified		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T10:42Z
Check the source to verify that this is the current version before use.

Defect	Classification Major	Minor
SEAMS AND STITCHING		
a. Accuracy of stitching		
1. Thread ends not secured or stitching back of the break less than 1/2 inch (12.70mm)		X
2. Ends of all seams and stitching backtacked less than 3/8 inch (9.52mm)		X
b. Gauge of stitching		
1. Irregular, i.e., unevenly gauged, not uniform		X
2. Beyond range of width specified or varies more than 1/16 inch (1.59mm) when no gauge is specified	X	
c. Open seams		
NOTE: Two or more broken stitches or two or more consecutive skipped or runoff stitches constitute an open seam		
d. One broken stitch		X
e. Seam and stitch type Not specified seam or stitch type	X	
f. Stitch tension Loose tension resulting in loose seam	X	
g. Stitches per inch Not within specified range		X

* 4.4.2.2 Dimensional examination The belts shall be examined for defects in dimension in accordance with the following:

a. Maximum adjustable length less than 42 inches (106.56cm).
b. Minimum adjustable length more than 25 inches (63.48cm).
c. Adjusting buckle or female fastener loop, less than 1 3/4 inches (44.45mm) or greater than 2 1/4 inches (57.15mm) long.
d. Webbing width not as specified.
e. All other figure 1 dimensions not within specified tolerance.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T10:42Z
Check the source to verify that this is the current version before use.

4.4.2.3 Inspection levels and acceptable quality levels The inspection levels and acceptable quality levels (AQL's) expressed in defects per 100 units, for visual and dimensional examinations shall be as follows:

	AQL's	Inspection level
For examination in 4.4.2.1		
Major	2.5	II
Total (Major and Minor combined)	10.0	II
For examination in 4.4.2.2	4.0	S-3

*4.4.3 Examination of packaging requirements An examination shall be made to determine that packaging, packing and marking complies with Section 5 requirements of this specification. Defects shall be scored in accordance with the list below. The sample unit shall be one shipping container fully prepared for delivery, except that it need not be closed. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 and the AQL shall be 2.5 defects per 100 units (DHU).

Examine	Defect
Marking (exterior)	Omitted, incorrect, illegible, of improper size, location, sequence, or method of application.
Materials	Any component missing, damaged or not as specified.
Workmanship	Inadequate application of components, such as: incomplete closure of container flaps, improper taping, strapping, or inadequate stapling. Bulging or distortion of containers.
Content	Number of bundles per container is more or less than required. Number of belts per bundle is more or less than required. 1/

1/ For this defect, four bundles shall be examined from each shipping container in the sample.

5. PACKAGING

5.1 Preservation-packaging Packaging shall be level A or C as specified (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 202610-19T10:42Z
Check the source to verify that this is the current version before use.

5.1.1 Level A Each belt shall be folded in half with the adjusting buckle placed on the outside of the fold. The folded belt shall measure approximately 14 1/2 inches (36.79cm) in length. Six folded belts shall be neatly stacked in a bundle with every three belts alternately reversed end to end. Alternatively, six folded belts shall be neatly stacked in a bundle with every other belt reversed end for end. Each bundle shall be securely tied with cotton tape or twine approximately 2 inches (50.80mm) in from each end.

* 5.1.2 Level C (Commercial) Belts shall be packaged to afford adequate protection against physical damage during shipment from the supply source to the first receiving activity. The package and the quantity per package shall be the same as normally used by the contractor for retail distribution.

5.2 Packing Packing shall be level A, B, or C as specified (see 6.2).

* 5.2.1 Level A One hundred and forty-four belts packaged as specified in 5.1, shall be packed in a fiberboard shipping container assembled, closed and reinforced conforming to class weather-resistant, grade V2s, size 3A of MIL-B-17757. The fiberboard for the box liner shall conform to type CF, class weather-resistant, variety DW, grade V15c of MIL-B-17757. Level A packages shall be packed on edge, four in length, one in width, and six in depth within a shipping container. Each container shall have the contents completely covered on the top and bottom with a sheet of commercial grade kraft paper.

* 5.2.2 Level B One hundred and forty-four belts packaged as specified in 5.1, shall be packed in a fiberboard shipping conainer assembled and closed conforming to class domestic, grade 200, size 3A of MIL-B-17757. The fiberboard for the box liner shall conform to type CF, class domestic, variety DW, grade 200 of MIL-B-17757. Level A packages shall be packed on edge, four in length, one in width and six in depth within a shipping container. Each container shall have the contents completely covered on the top and bottom with a sheet of commercial grade kraft paper.

* 5.2.2.1 When specified (see 6.2), the shipping container shall be a grade V2s, V3s, or V4s fiberboard box fabricated in accordance with MIL-B-17757 and closed in accordance with the appendix of the box specification.

Source: https://assist.dla.mil -- Downloaded: 202610-19T10:42Z
Check the source to verify that this is the current version before use.

* 5.2.3 Level C (Commercial) Belts, packaged as specified in 5.1, shall be packed in a manner to insure carrier acceptance and safe delivery at destination at the lowest transportation rate for such supplies. The quantity per shipping container shall be the same as that normally used by the contractor for retail distribution. Containers shall comply with the US Postal Service Manual, Uniform Freight classification Rules, or National Motor Freight Classification Rules, as applicable.

5.3 Marking In addition to any special marking required by the contract, shipping containers shall be marked in accordance with MIL-STD-129.

6. NOTES

6.1 Intended use The belt is intended for wear by Navy personnel performing duties as military police, honor guard, and at other specified occasions.

6.2 Ordering data Procurement documents should specify the following:

a. Title, number and date of this specification.
b. When first article sample is required (see 3.2).
c. Selection of applicable levels of packaging and packing (see 5.1 and 5.2).
d. When weather-resistant grade fiberboard shipping containers are required for level B packing (see 5.2.2.1).

6.3 Samples For access to samples, address the procuring activity issuing the invitation for bids.


* 6.4 The margins of this specification are marked with an asterisk (*) to indicate where changes (additions, modification, corrections, deletions) from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

Custodian:
Navy - SA

Preparing activity:
Navy - SA

Project No. 8465-N669

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T10:42Z
Check the source to verify that this is the current version before use.

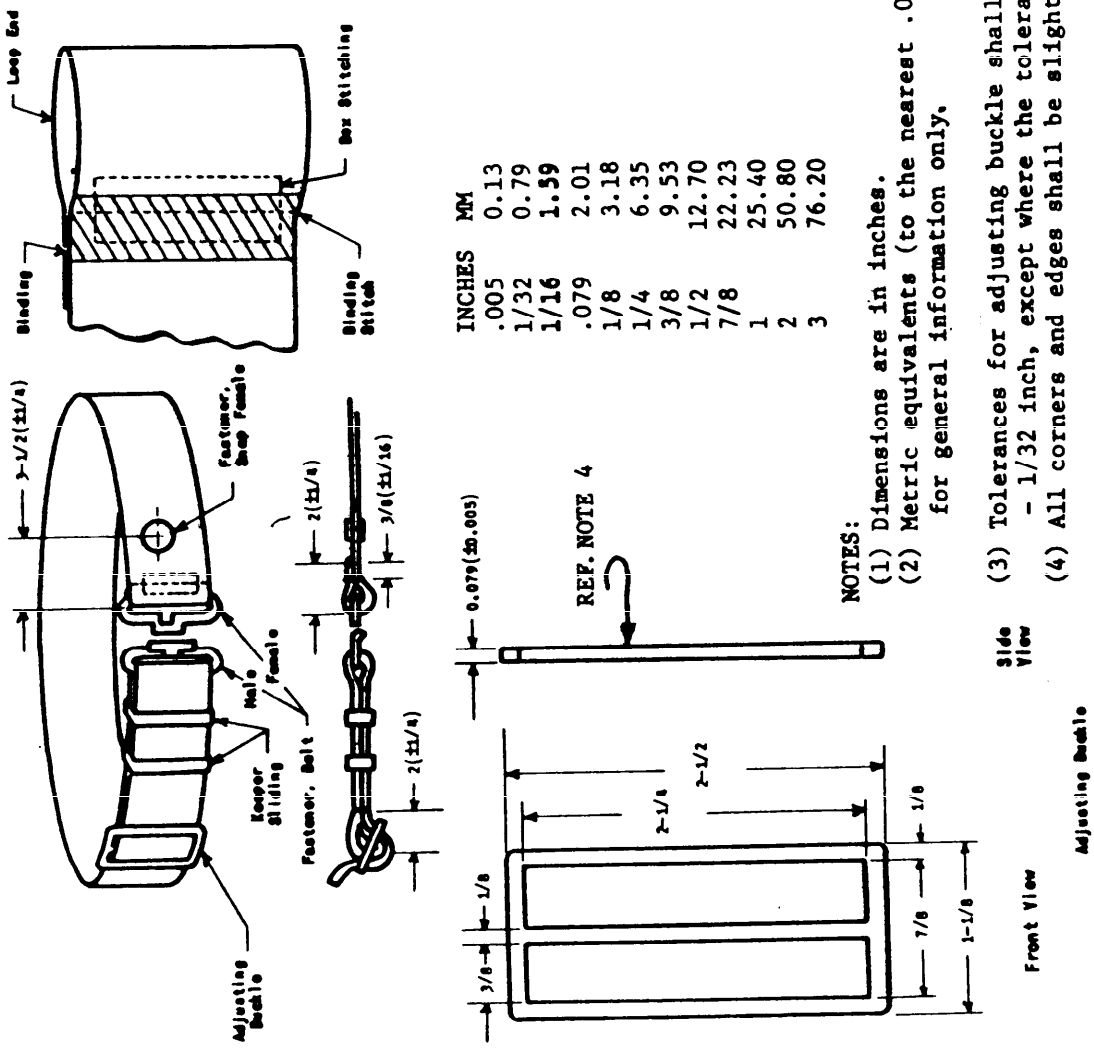

INCHES	MM
.005	0.13
1/32	0.79
1/16	1.59
.079	2.01
1/8	3.18
1/4	6.35
3/8	9.53
1/2	12.70
7/8	22.23
1	25.40
2	50.80
3	76.20

NOTES:
(1) Dimensions are in inches.
(2) Metric equivalents (to the nearest .01mm), are given for general information only.
(3) Tolerances for adjusting buckle shall be + 1/16, - 1/32 inch, except where the tolerance is indicated.
(4) All corners and edges shall be slightly beveled.

Figure 1 — BELT, MILITARY POLICE, (WHITE)

☆U.S. GOVERNMENT PRINTING OFFICE: 1978 — 703-122/3155

Source: https://assist.dla.mil -- Downloaded: 202610-19T10:42Z
Check the source to verify that this is the currentversion before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS: This form is provided to solicit beneficial comments which may improve this document and enhance its use. DoD contractors, government activities, manufacturers, vendors, or other prospective users of the document are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Attach any pertinent data which may be of use in improving this document. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity. A response will be provided to the submitter, when name and address is provided, within 30 days indicating that the 1426 was received and when any appropriate action on it will be completed.

NOTE: This form shall not be used to submit requests for waivers, deviations or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

DOCUMENT IDENTIFIER *(Number)* AND TITLE

MIL-B-21880D BELT, MILITARY POLICE (WHITE)

NAME OF ORGANIZATION AND ADDRESS OF SUBMITTER

☐ VENDOR ☐ USER ☐ MANUFACTURER

1. ☐ HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE? ☐ IS ANY PART OF IT TOO RIGID, RESTRICTIVE, LOOSE OR AMBIGUOUS? PLEASE EXPLAIN BELOW.

A. GIVE PARAGRAPH NUMBER AND WORDING

B. RECOMMENDED WORDING CHANGE

C. REASON FOR RECOMMENDED CHANGE(S)

2. REMARKS

SUBMITTED BY *(Printed or typed name and address — Optional)*

TELEPHONE NO.

DATE

DD FORM 1426 1 OCT 76

Replaces edition of 1 Jan 72 which may be used.

S/N 0102-LF-001-4260

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T10:42Z
Check the source to verify that this is the current version before use.

FOLD

OFFICER IN CHARGE
NAVY CLOTHING & TEXTILE RESEARCH FACILITY
21 STRATHMORE ROAD
NATICK, MA 01760

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

POSTAGE AND FEES PAID
DEPARTMENT OF THE NAVY
DoD-316

U.S.MAIL

OFFICER IN CHARGE
NAVY CLOTHING & TEXTILE RESEARCH FACILITY
21 STRATHMORE ROAD
NATICK, MA 01760

FOLD

Source: https://assist.dla.mil -- Downloaded: 202610-19T10:42Z
Check the source to verify that this is the current version before use.