The documentation and process conversion measures necessary to comply with this revision shall be completed by 6 November 1999

INCH-POUND

MIL-PRF-19500/260E
6 August 1999
SUPERSEDING
MIL-S-19500/260D
21 April 1989

PERFORMANCE SPECIFICATION SHEET

SEMICONDUCTOR DEVICE, DIODE, SILICON, POWER RECTIFIER,
TYPES 1N1202A, 1N1204A, 1N1206A, 1N3671A, 1N3673A AND AR VERSIONS
JAN, JANTX, JANTXV, JANS, JANHC AND JANKC

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for silicon semiconductor power rectifier diodes. Four levels of product assurance are provided for each encapsulated device type as specified in MIL-PRF-19500, and two levels of product assurance for each unencapsulated device type. For normal and reverse (AR suffix) type devices see 3.3.1.

1.2 Physical dimensions. See figure 1 (DO-203AA, formerly DO – 4) and figure 2 (JANHC and JANKC).

1.3 Maximum ratings.

Type	V_{RSM}	V_{RWM}	I_O 1/ T_C = 150°C	$I_{f(surge)}$ T_C = 150°C T = 1/120 s	T_J and T_{STG}	Barometric pressure (reduced)	t_{rr}
	V (pk)	V dc	A dc	A dc	°C	mmHg	µs
1N1202A	240	200	12	240	-65 to +200	N/A	10
1N1204A	480	400	12	240	-65 to +200	8	10
1N1206A	720	600	12	240	-65 to +200	16	10
1N3671A	960	800	12	240	-65 to +200	30	10
1N3673A	1200	1000	12	240	-65 to +200	54	10

1/ Derate linearly 2 percent of I_O per °C for T_C = 150°C to T_C = 200°C.

1.4 Primary electrical characteristics. $R_{\theta JC}$ = 2.0 °C/W maximum.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, Defense Supply Center Columbus, ATTN: DSCC-VAC, 3990 East Broad St., Columbus, OH 43216-5000, by using the addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 5961

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements documents cited in section 3 and 4 of this specification, whether or not they are listed.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATION

DEPARTMENT OF DEFENSE

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

STANDARD

FEDERAL

FED-STD H28 -- Screw Thread Standards for Federal Services

MILITARY

MIL-STD-750 - Test Methods for Semiconductor Devices.

(Unless otherwise indicated, copies of the above specifications, standards, and handbooks are available from the Defense Automated Printing Service, Building 4D (DPM-DODSSP), 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

2.2 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein (except for associated detail specifications, specification sheets or MS standards), the text of this specification takes precedence. Nothing in this specification, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Associated specification. The individual item requirements shall be in accordance with MIL-PRF-19500, and as specified herein.

3.2 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500.

3.3 Interface requirements and physical dimensions. The Interface requirements and physical dimensions shall be as specified in MIL-PRF-19500 and on figures 1 (DO-203AA, formerly DO – 4) and figure 2 (JANHC and JANKC).

3.3.1 Normal and reverse (AR suffix) types. Reverse and normal types are identical except: The normal types have the cathode connected to the stud and the reverse types have the anode connected to the stud. Designated values are applicable to both types.

3.3.2 Lead finish. Lead finish shall be solderable in accordance with MIL-PRF-19500, MIL-STD-750 and herein. Where a choice of lead finish is desired, it shall be specified in the contract or purchase order (see 6.2).

3.4 Marking. Marking shall be in accordance with MIL-PRF-19500.


3.4.1 Polarity. The polarity shall be indicated by a graphic symbol with the arrow pointing toward the negative end for forward bias. The reversed units shall also be marked with an R following the last digit in the type number.

3.5 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I herein.

3.6 Electrical test requirements. The electrical test requirements shall be the subgroups specified in table I herein.

3.7 Qualification. Devices furnished under this specification shall be products that are authorized by the qualifying activity for listing on the applicable qualified manufacturer's list before contract award (see 4.2 and 6.4).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

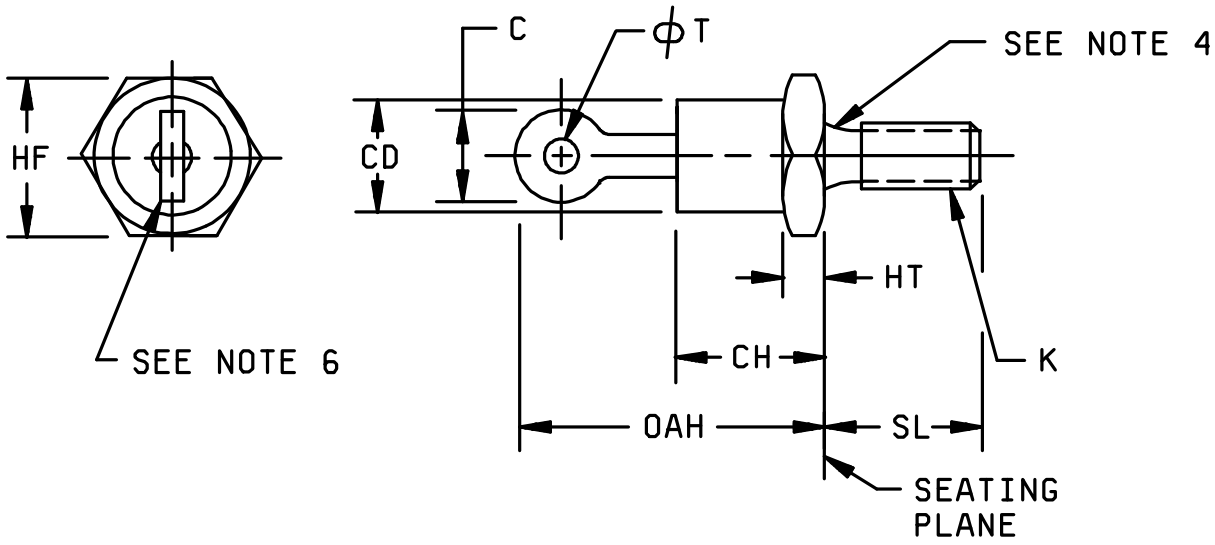


Ltr	Dimensions				Notes
	Inches		Millimeters		
	Min	Max	Min	Max	
CH		0.405		10.29	
CD		0.424		10.77	
HF	0.424	0.437	10.77	11.10	
HT	0.075	0.175	1.90	4.44	
OAH		0.800		20.32	
C		0.250		6.35	9
ϕT	0.060			1.52	
SL	0.422	0.453	10.72	11.51	
K					3,5,7

NOTES:
1. Dimensions are in inches.
2. Metric equivalents are given for general information only.
3. Units must not be damaged by torque of 15 inch-pounds applied to 10-32NF-2B nut assembled on thread.
4. Diameter of unthreaded portion 0.189 inch (4.80 mm) max and 0.163 inch (4.14 mm) min.
5. Complete threads to extend to within 2.5 threads of seating plane.
6. Angular orientation of this terminal is undefined.
7. Max pitch diameter of plated threads shall be basic pitch diameter 0.169 inch (4.31 mm) reference FED-STD-H28 (Screw Thread Standards for Federal Services.)
8. The A.S.A. thread reference is 10-32UNF2.
9. Terminal end shape is unrestricted.
10. Reversed (anode to stud) units shall be marked with an R following the last digit in the type number.

FIGURE 1. Physical dimensions (DO-203AA, formerly DO – 4).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

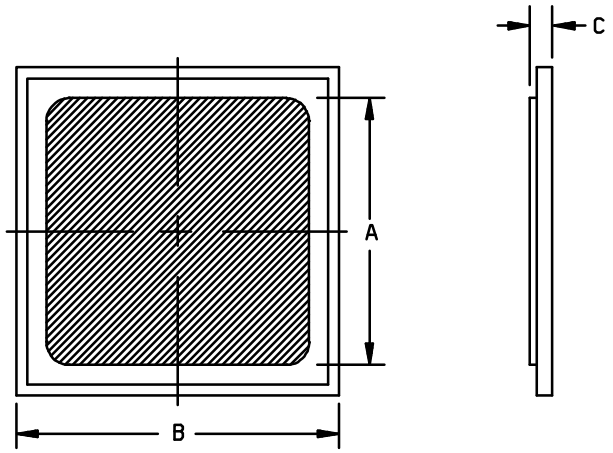

A Version

Ltr	Dimensions			
	Inches		Millimeters	
	Min	Max	Min	Max
A	0.116	0.122	2.95	3.10
B	0.147	0.153	3.73	3.89
C	0.009	0.012	0.229	0.305

NOTES:
1. Dimensions are in inches.
2. Metric equivalents are given for general information only.
3. The physical characteristics of the die are: Metallization {front (anode), consists of: Ti thickness = 1,200 Å minimum, Ni thickness = 2,000 Å minimum, Ag thickness = 4,000 Å minimum. Metallization {back, (cathode)} consists of: Ti thickness = 1,200 Å minimum, NI thickness = 2,000 Å minimum, Ag thickness = 4,000 Å minimum.

FIGURE 2. Physical dimensions JANHC and JANKC.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

4.VERIFICATION

4.1 Classification of Inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3)

c. Conformance inspection (see 4.4).

4.1.1 Sampling and inspection. Sampling and inspection shall be in accordance with MIL-PRF-19500 and herein, except for accumulation period shall be 3 months in lieu of 6 weeks.

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500 and herein.

4.2.1 JANHC and JANKC devices. Qualification for JANHC and JANKC devices shall be in accordance with MIL-PRF-19500.

4.3 Screening. Screening shall be in accordance with MIL-PRF-19500 (table IV), and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen (see table IV of MIL-PRF-19500)	Measurement	
	JANS level	JANTX and JANTXV levels
1/	Surge (see 4.3.1) Thermal response (see 4.3.2)	Surge (see 4.3.1) Thermal response (see 4.3.2)
4	Not applicable	Not applicable
9	V_{F2} and I_{R1} 2/	V_{F2} and I_{R1} 2/
10	MIL-STD-750, method 1038, test condition A, t = 96 hours	MIL-STD-750, method 1038, test condition A, t = 48 hours
11	V_{F2} and I_{R1}; Subgroup 2 of table I herein, $\Delta V_{F2} = \pm 0.1$ V(pk) from initial value; $\Delta I_{R1} = 5$ µA dc or 100 percent from the initial value, whichever is greater.	Subgroup 2 of table I herein, $\Delta V_{F2} = \pm 0.1$ V(pk) from initial value; $\Delta I_{R1} = \pm 5.0$ µA dc or 100 percent from the initial value, whichever is greater. 3/
12	Burn-in, see 4.3.3 and 4.5.1. MIL-STD-750, method 1038, test condition B.	Not applicable
13	Subgroups 2 and 3 of table I herein; $\Delta V_{F2} = \pm$ 0.1 V (PK); $\Delta I_{R1} = 5$ µA dc or 100 percent from the initial value, whichever is greater.	Not applicable

1/ Surge shall precede thermal response. These tests shall be performed anytime after screen 3 and before screen 9.
2/ I_{R1} measurement shall not be indicative of an open condition.
3/ PDA of screen 13 shall apply to screen 11.

4.3.1 Surge current. Surge current, see MIL-STD-750, method 4066. $I_O = 0$; $V_{RM}(w) = 0$; $I_{FSM} = 325$; six surges; $T_A = 25°C$, $t_p = 8.3$ ms, one surge per minute maximum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

4.3.2 Thermal response. The thermal response measurements shall be performed in accordance with method 3101 of MIL-STD-750. The thermal response conditions and maximum thermal response limit shall be derived by each vendor. The chosen thermal response measurement and conditions for each device in the qualification lot shall be submitted in the qualification report and a thermal response curve shall be plotted. The chosen thermal response values shall be considered final after the manufacturer has had the opportunity to test five consecutive lots. Heating current (I_H) ≥ rated I_O; t_H = 150 to 400 ms; t_{MD} = 50 to 300 µs; 50 mA ≤ I_M ≤ 250 mA.

4.3.3 Power burn-in. Power burn-in conditions are as follows:

MIL-STD-750, method 1038, test condition B. T_C = 150°C, f = 60 Hz, I_O = 12 A dc (see 4.5.1); V_R = rated V_R (pk) (see 1.3).

4.3.4 Screening (JANHC and JANKC). Screening of JANHC and JANKC die shall be in accordance with MIL-PRF-19500. As a minimum, die shall be 100-percent probed to ensure compliance with I_{R1} of group A, subgroup 2.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500, and as specified herein.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with MIL-PRF-19500, and table I herein.

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VIa (JANS) and table VIb (JAN, JANTX, and JANTXV) of MIL-PRF-19500 and paragraphs 4.4.2.1 and 4.4.2.2 herein. Electrical measurements (end-points) shall be in accordance with table I, subgroup 2 herein. Delta measurements shall be in accordance with table II herein.

4.4.2.1 Group B inspection, table VIa (JANS) of MIL-PRF-19500.

Subgroup	Method	Condition
B3	4066	T_C = 150°C; V_R = Rated V_R (see 1.3), i_f (surge) = 240 A; I_O = 12 A dc; six 1/120 s surges. 1 surge per minute maximum. t_p = 8.3 ms.
B4	1037	0.25 Rated I_O ≤ I_O applied ≤ Rated I_O (see 4.5.2) 2,000 cycles.
B5	1027	I_F = 4 A dc; V_R = rated V_R (see 1.3), T_A = 125°C; or adjusted as required by the chosen T_A to give an average lot T_J = 275°C (see 4.5.1), f = 60 Hz.
B6	3101	$R_{\theta JC}$ = 2.0°C/W maximum; I_M = 50 – 250 mA; I_H ≥ rated I_O; t_H = 150 to 400 ms; t_{MD} = 50 to 300 µs.

4.4.2.2 Group B inspection, table VIb (JAN, JANTX and JANTXV) of MIL-PRF-19500.

Subgroup	Method	Condition
B2	4066	T_C = 150°C; V_R = Rated V_R (see 1.3), i_f (surge) = 240 A; I_O = 12 A dc; six 1/120 s surges. 1 surge per minute maximum. t_p = 8.3 ms.
B3	1037	0.25 Rated I_O ≤ I_O applied ≤ Rated I_O (see 4.5.1) 2,000 cycles.
B3	1038 or 1049	Condition A; 340 hrs.
B5		Not required.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VII of MIL-PRF- and as follows. Electrical measurements (end-points) shall be in accordance with table I, subgroup 2 herein. Delta measurements shall be in accordance with table II herein.

4.4.3.1 Group C inspection, table VII of MIL-PRF-19500.

Subgroup	Method	Condition
C2	1056	Test condition B.
C2	2036	Test condition A, Weight = 10 pounds, t = 15 s.
C2	2036	Test condition F, method B, weight = 5 pounds, t = 15 s.
C2	2036	Test condition D1, seal torque = 10 ounce-inches, t = 15 s.
C2	2036	Test condition D2, stud torque = 15 pound-inches, t = 15 s.
C5	3101	$R_{\theta JC}$ = 2.0°C/W maximum; I_M = 50 – 250 mA; $I_H \geq$ rated I_O; t_H = 150 to 400 ms; t_{MD} = 50 to 300 µs.
C6	1037	0.25 Rated $I_O \leq I_O$ applied $\leq$ Rated I_O (see 4.5.1) 6,000 cycles.

4.4.4 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in table IX of MIL-PRF-19500. Electrical measurements (end-points) shall be in accordance with table I, subgroup 2 herein. Delta measurements shall be in accordance with table II herein.

4.4.4.1 Group E inspection, table IX of MIL-PRF-19500.

Subgroup	Method	Condition	Sampling plan
E1	1056	0°C to 100°C, 100 cycles.	22 devices, c = 0
E2	1038 or 1049	Condition A; 1,000 hrs.	22 devices, c = 0
E3	2101	Photos of cross sections shall be submitted In the qualification report. Vendors shall Retain duplicate photos.	3 devices, c = 0
E4	3101	$R_{\theta JC}$ = 2.0°C/W maximum; I_M = 50 - 250 mA; $I_H \geq$ rated I_O; t_H = 150 to 400 ms; t_{MD} = 50 to 300 µs	22 devices, c = 0
E5	1001	Hg = rated Hg (see 1.3), t = 60 s, While the test is being performed, I_R shall be monitored and shall not exceed group A limits.	22 devices, c = 0

	Voltage during test
1N1202A	N/A
1N1204A	400 V dc
1N1206A	600 V dc
1N3671A	800 V dc
1N3673A	1,000 V dc

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

4.5 Methods of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows.

4.5.1 Burn-in and steady-state operation life tests. These tests shall be conducted with a half-sine waveform of the specified peak voltage impressed across the diode in the reverse direction followed by a half-sine waveform of the specified average rectifier current. The forward conduction angle of the rectified current not be greater than 180 degrees nor less than 150 degrees.

4.5.2 DC intermittent operation life. A cycle shall consist of an "on" period, when power is applied suddenly, not gradually, to the device for the time necessary to achieve a delta case temperature of 85°C +15°C -5°C followed by an "off" period, when the power is suddenly removed, for cooling. Auxiliary (forced) cooling is permitted during the off period only. 30 s $\leq t_{Heating} \leq$ 60 s, $P = V_F \times I_F$ or $P = V_{FPK} \times I_{av}$ if using sine wave current. DC full wave current (or equivalent half sine wave current) shall be used for the power required during the on period. The test power, or current, shall be at least the free air rating. Within the time interval of 50 cycles before to 500 cycles after the termination of the test, the sample units shall be removed from the specified test conditions and allowed to reach room ambient conditions. Specified end-point measurements for qualification and quality conformance inspection shall be completed within 96 hours after removal of sample units from the specified test conditions. Additional readings may be taken at the discretion of the manufacturer.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 1						
Visual and mechanical inspection	2071					
Subgroup 2						
Forward voltage	4011	I_F = 38 A (pk) pulse; pulse width = 8.5 ms, duty cycle ≤ 2 percent pulse	V_{F2}		1.35	V (pk)
Reverse current	4016	DC method, V_R = Rated $V_{R\ (dc)}$ (see 1.3)	I_{R1}		5	µA dc
Subgroup 3						
High temperature operation:		T_C = 150°C				
Reverse current	4016	DC method, V_R = Rated $V_{R(pk)}$ (see 1.3)	I_{R2}		1	mA dc
Low temperature operation		T_C = -65°C				
Reverse current	4026	DC method, V_R = Rated $V_{R\ (dc)}$ (see 1.3)	I_{R3}		1	mA dc
Subgroups 4 and 5						
Not applicable						
Subgroup 6 2/						
Forward voltage	4011	$I_F = I_{FSM}$, t_P = 800 µs	V_{F1}		2.5	V dc
Forward voltage	4011	$I_F = I_{FSM}$, t_P = 8.3 ms	V_{F1}		2.3	V dc

1/ For sampling plan, see MIL-PRF-19500.

2/ V_{F1} shall be performed with either t_p = 800 µs or t_p = 8.3 ms.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

TABLE II. Groups B, C and E delta measurements. 2/ 3/ 4/ 5/

Step	Inspection	MIL-STD-750		Symbol	Limits		Unit
		Method	Conditions		Min	Max	
1.	Thermal response	3101	See 4.3.2: $R_{\theta JC}$ = 2.0°C/W maximum; I_M = 50 to 250 mA; t_H = 150 to 400 ms; t_{MD} = 50 to 300 µs	ΔV_F			mV dc
2.	Forward voltage	4011	I_F =50 mA dc	ΔV_{F3}	+ 50 mV dc maximum change from previous to post intermittent life and thermal shock measurement tests (JANS only).		
3.	Reverse current	4016	DC method, V_R = Rated V_R(dc) (see 1.3)	ΔI_{R1} 1/	100 percent or 5 µA, (whichever is greater) change from initial group A reading.		

1/ Devices which exceed the group A limits for this test shall be rejected.

2/ The delta electrical measurements for table VIa (JANS) of MIL-PRF-19500 are as follows:

a. Subgroup 3, see table II herein, steps 1 and 2.
b. Subgroup 4, see table II herein, steps 1 and 2.
c. Subgroup 5, see table II herein, step 3.

3/ The delta electrical measurements for table VIb (JAN, JANTX and JANTXV) of MIL-PRF-19500 are as follows:

a. Subgroup 2, see table II herein, step 1.

4/ The delta electrical measurements for table VII of MIL-PRF-19500 are as follows:

a. Subgroup 2 see table II herein, step 1 (JAN, JANTX and JANTXV), steps 1 and 2 (JANS).
b. Subgroup 6, see table II herein, steps 1 and 2 (JANS), and step 1 (JAN, JANTX and JANTXV).

5/ The delta electrical measurements for table IX of MIL-PRF-19500 are as follows:

a. Subgroup 1 see table II herein, step 1.
b. Subgroup 2, see table II herein, step 3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements should be as specified in the contract or order (see 6.2). When actual packaging of material is to be performed by DoD personnel, these personnel need to contact the responsible packaging activity to ascertain requisite packaging requirements. Packaging requirements are maintained by the Inventory Control Points' packaging activity within the Military Department or Defense Agency, or within the Military Departments' System Command. Packaging data retrieval is available from the managing Military Departments' or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Notes. The notes specified in MIL-PRF-19500 are applicable to this specification.

6.2 Acquisition requirements. Acquisition documents must specify the following:

a. Issue of DODISS to be cited in the solicitation (see 2.1.1).

b. The lead finish as specified (see 3.3.2).

c. Type designation and quality assurance level.

d. Packaging requirements (see 5.1).

e. For die acquisition, the JANHC or JANKC letter version shall be specified (see figure 2).

6.3 Suppliers of JANHC and JANKC die. The qualified JANHC and JANKC suppliers with the applicable letter version (example, JANHCA1N1202A) will be identified on the QML.

JANHC and JANKC ordering information	
	Manufacturer 1/
PIN	59377
1N1202A	JANHCA1N1202A
1N1204A	JANHCA1N1204A
1N1206A	JANHCA1N1206A
1N3671A	JANHCA1N3671A
1N3673A	JANHCA1N3673A

1/ For JANKC, replace the "JANHC" suffix with "JANKC".

6.4 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturer's List QML-19500 whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or purchase orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Defense Supply Center Columbus, DSCC-VQE, Columbus, OH 43216.

6.5 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

Custodians:
Army - CR
Navy - EC
Air Force - 11
NASA – NA
DLA - CC

Review activities:
Army - AR, MI
Navy – AS, CG, MC
Air Force - 19, 99

Preparing activity:
DLA - CC

(Project 5961-2142)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.

2. The submitter of this form must complete blocks 4, 5, 6, and 7.

3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER MIL-PRF-19500/260E	2. DOCUMENT DATE 990806

3. **DOCUMENT TITLE**
SEMICONDUCTOR DEVICE, DIODE, SILICON, POWER RECTIFIER, TYPES 1N1202A, 1N1204A, 1N1206A, 1N3671A, 1N3673A AND AR JAN, JANTX, JANTXV, JANS. JANHC AND JANKC

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) COMMERCIAL DSN FAX EMAIL	7. DATE SUBMITTED

8. PREPARING ACTIVITY

a. Point of Contact Alan Barone	b. TELEPHONE Commercial: 614-692-0510 DSN: 850-0510 FAX: 614-692-6939 EMAIL: alan_barone@dscc.dla.mil
c. ADDRESS Defense Supply Center Columbus, ATTN: DSCC-VAC, 3990 East Broad Street, Columbus, OH 43216-5000	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Standardization Program Office (DLSC-LM) 8725 John J. Kingman, Suite 2533, Fort Belvoir, VA 22060-6221 Telephone (703) 767-6888 DSN 427-6888

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:57Z
Check the source to verify that this is the current version before use.