INCH-POUND

MIL-DTL-2710E
18 August 2026
SUPERSEDING
MIL-DTL-2710D
w/AMENDMENT 1
4 January 2021

DETAIL SPECIFICATION

LINKS, CHAIN, DETACHABLE, REGULAR AND PEAR-SHAPED

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers regular and pear-shaped, detachable, chain links for hulls with flash butt welded stud link chain in accordance with MIL-DTL-24633.

1.2 Classification. The detachable links are of the following types, classes, and sizes as specified (see 6.2):

1.2.1 Type I. Regular

a. Class 1 – Standard

Sizes (inches):
¾; ⅞; 1; 1⅛; 1¼; 1⅜; 1½; 1⅝; 1¾;1⅞; 2; 2⅛; 2¼; 2⅜; 2½; 2⅝; 2¾; 2⅞; 3; 3⅛; 3¼; 3⅜; 3½; 3⅝; 3¾; 3⅞; 4; 4¾

b. Class 2 – Heavy duty

Sizes (inches):
2¾; 3; 3½

1.2.2 Type II. Pear-shaped

Sizes (inches):
Number 2: ¾ - ⅞
Number 3: 1 - 1⅛
Number 4: 1¼ - 1½
Number 5: 1⅝ - 2
Number 6: 2⅛ - 2⅜
Number 7: 2½ - 3⅛
Number 8: 3¼ - 3½

2. APPLICABLE PUBLICATIONS

2.1 General. The publications listed in this section are specified in sections 3 and 4 of this specification. This section does not include publications cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, users of this document are cautioned that they must meet all specified requirements of publications cited in sections 3 and 4 of this specification, whether or not they are listed.

Comments, suggestions, or questions on this document should be addressed to Commander, Naval Sea Systems Command, ATTN: SEA 05T, 1333 Isaac Hull Avenue, SE, Stop 5160, Washington Navy Yard, DC 20376-5160 or emailed to CommandStandards@navy.mil, with the subject line "Document Comment". Since contact information can change, you may want to verify the currency of this address information using ASSIST at https://assist.dla.mil.

AMSC N/A FSC 4010

Distribution Statement A. Approved for public release: distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

2.2 Government publications.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these publications are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-10924 - Grease, Automotive and Artillery

MIL-DTL-24633 - Chain, Anchor, Stud Link, Flash-Butt Welded, Low Alloy Steel

MIL-PRF-24635 - Coating System, Weather-Resistant, Exterior Use

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-1916 - DoD Preferred Methods for Acceptance of Product

MIL-STD-2035 - Nondestructive Testing Acceptance Criteria

(Copies of these publications are available online at https://quicksearch.dla.mil.)

2.2.2 Other Government publications. The following other Government publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these publications are those cited in the solicitation or contract.

NAVAL SEA SYSTEMS COMMAND (NAVSEA) DRAWINGS

803-6397316 - Link, Detachable, Pear Shaped

803-860062 - Links, Detachable, Standard and Heavy Duty

804-840327 - Tool Boxes and Tools (Steel Box) for Assembling and Disassembling Detachable Links

(Copies of these publications are available online via Model Based Product Support (MBPS) at https://mbps.navsea.cloud.navy.mil/Windchill. To request an MBPS account, submit a ticket to the ServiceNow Assistance Portal (SNAP), https://snap.navair.navy.mil/mbps (DoD PKI Certificate required).)

NAVAL SEA SYSTEMS COMMAND (NAVSEA) PUBLICATIONS

T9074-AS-GIB-010/271 - Requirements for Nondestructive Testing Methods

(Copies of this publication are available online via Model Based Product Support (MBPS) at https://mbps.navsea.cloud.navy.mil/Windchill. To request an MBPS account, submit a ticket to the ServiceNow Assistance Portal (SNAP), https://snap.navair.navy.mil/mbps (DoD PKI Certificate required).) This publication is available for ordering (hard copy) via the Naval Logistics Library (NLL) at https://nll.navsup.navy.mil. For questions regarding the NLL, contact the NLL Customer Service at nllhelpdesk@navy.mil, (866) 817-3130, or (215) 697-2626/DSN 442-2626.)

2.3 Non-Government publications. The following publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these publications are those cited in the solicitation or contract.

AMERICAN SOCIETY FOR QUALITY (ASQ)

Zero Acceptance Number Sampling Plans

(Copies of this publication are available online at https://asq.org.)

ASSOCIATION FOR MATERIALS PROTECTION AND PERFORMANCE (AMPP)

SSPC-SP 10/NACE No 2 - Near-White Metal Blast Cleaning

(Copies of this publication are available online at www.ampp.org.)

ASTM INTERNATIONAL

ASTM A322 - Standard Specification for Steel Bars, Alloy, Standard Grades

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

ASTM A370	-	Standard Test Methods and Definitions for Mechanical Testing of Steel Products
ASTM A580/A580M	-	Standard Specification for Stainless Steel Wire
ASTM A581/A581M	-	Standard Specification for Free-Machining Stainless Steel Wire and Wire Rods
ASTM A582/A582M	-	Standard Specification for Free-Machining Stainless Steel Bars
ASTM E4	-	Standard Practices for Force Calibration and Verification of Testing Machines

(Copies of these publications are available online at www.astm.org.)

SAE INTERNATIONAL

SAE AMS-STD-595	-	Colors Used in Government Procurement

(Copies of this publication are available online at www.sae.org.)

2.4 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 First article. When specified (see 6.2), a sample shall be subjected to first article inspection (see 6.3) in accordance with 4.2.

3.2 Material and components. Material for the detachable link components shall be as specified in 3.2.1 through 3.2.5.1. Material used in normal production shall be the same composition as material used for the first article sample in chemistry, quality, and properties.


3.2.1 Detachable link components. Detachable links shall consist of the following components (see figure 1 and figure 2):

a. C-link
b. Coupling plate - right hand
c. Coupling plate - left hand
d. Taper pin
e. Hairpin (hairpin shall be furnished only for detachable links used in an outboard swivel shot (see 6.2))
f. Lead plug

WARNING

The plug contains lead and antimony, both of which are considered hazardous materials. Extreme care shall be taken when manufacturing, inspecting, and testing the plug. Required personal protection equipment shall be worn, and the room shall be well ventilated.


Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

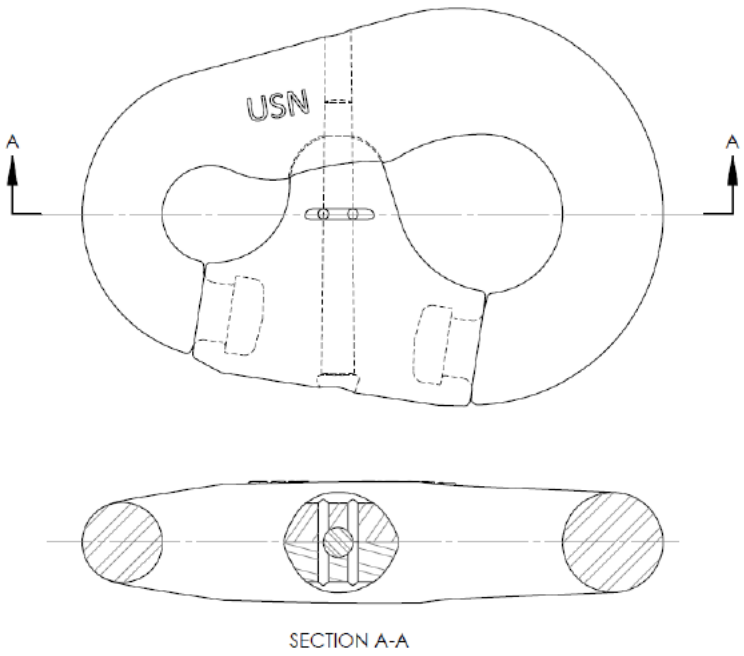

NOTE: Groove in taper pin, holes and recess in coupling plates, and hairpin are furnished only for links used in outboard swivel shots.

FIGURE 1. Pear-shaped detachable link with hairpin.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

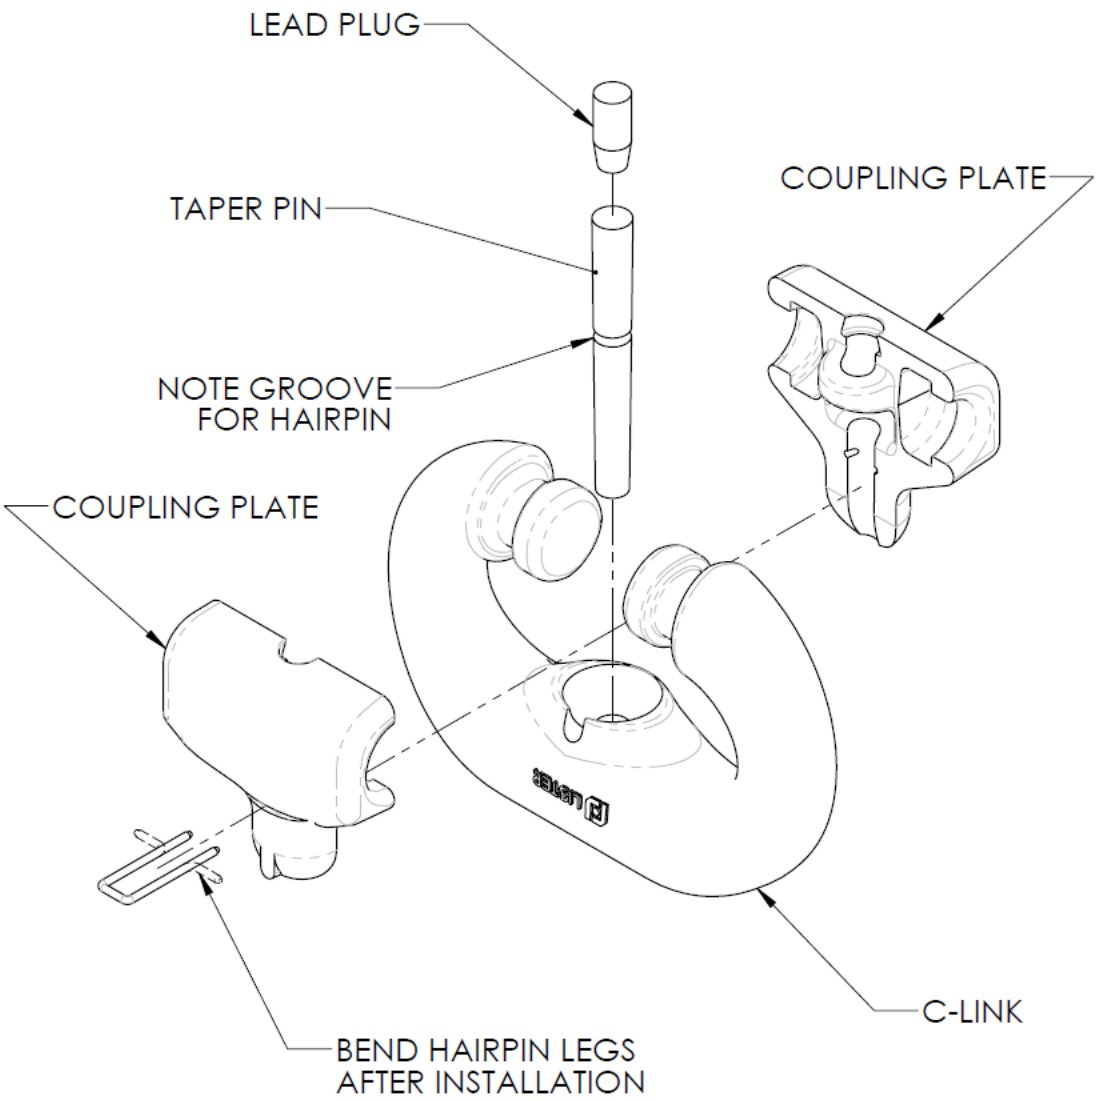

NOTE: Groove in taper pin, holes and recess in coupling plates, and hairpin are furnished only for links used in outboard swivel shots.

FIGURE 2. C-shaped detachable link with taper pin.

3.2.2 C-link and right- and left-hand coupling plates. Steel used in the manufacture of the C-link and coupling plates shall be forged from alloy steel as specified in table I.

3.2.2.1 C-link and coupling plate material chemical composition. The chemical composition of the steel of the C-link and coupling plates shall conform to the chemical composition of the ASTM A322 alloy steel grades specified in table I (see 4.5.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

TABLE I. C-link and coupling plates material.

Detachable link classification	ASTM A322, grade
Type II Number 2 and number 3	UNS G863700 or UNS G43400
Type I, class 1 ¾-inch and over Type I, class 2 2¾-inch, 3-inch, and 3½-inch Type II Number 4 through and including number 8	UNS G43400 or UNS G86400

3.2.3 Taper pin. The taper pin shall be machined from type Unified Numbering System (UNS) S41600 stainless steel with no center holes due to machining. The finished taper pin shall conform to ASTM A582/A582M, condition H.

3.2.3.1 Taper pin material chemical composition. The chemical composition of the stainless steel of the taper pin shall conform to the chemical composition of type UNS S41600 stainless steel in accordance with ASTM A582/A582M (see 4.5.1).

3.2.4 Plug. The plug shall be cast from antimony alloy and lead.

WARNING

Lead and antimony are considered hazardous materials. Extreme care shall be taken when manufacturing, inspecting, and testing the plug. Required personal protection equipment shall be worn, and the room shall be well ventilated.

3.2.4.1 Plug material chemical composition. The chemical composition of the plug shall be 8±0.5 percent antimony alloy and the remaining element shall be lead (see 4.5.1).

3.2.5 Hairpin. The hairpin, when specified (see 6.2), shall be formed from stainless steel wire, type UNS S30400 or UNS S30300, condition A, conforming to ASTM A580/A580M or ASTM A581/A581M, respectively.

3.2.5.1 Hairpin material chemical composition. The chemical composition of the stainless steel of the hairpin shall conform to the chemical composition of type UNS S30400 of ASTM A580/A580M or type UNS S30300 of ASTM A581/A581M (see 4.5.1).

3.2.6 Recycled, recovered, environmentally preferable, or biobased materials. Recycled, recovered, environmentally preferable, or biobased materials should be used to the maximum extent possible, provided that the material meets or exceeds the operational and maintenance requirements, and promotes economically advantageous life cycle costs.

3.3 Heat treatment. C-link and coupling plates shall be heat treated above the upper transformation temperature, at a combination of temperature and time to produce a fine grain structure throughout the component and produce a minimum tensile strength of 170,000 pounds per square inch (lb/in²) (with a recommended Brinell hardness 341 (minimum) (see 4.5.6) or direct equivalent in accordance with ASTM A370 (see 6.4)). The components shall not be heated more than twice. Heat treatment records shall be made available for inspection and shall include time and temperature, quenching, stress relieving, and cooling method.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

3.4 Mechanical properties. The unmachined C-link and coupling plate samples shall be sectioned for determination of the tensile strength specified in 3.3. If it is impracticable to take specimens from finished components, the specimens may be taken from stock of the same heat or melt of steel and heat treated as specified in 3.3.

3.5 Brinell hardness - C-link and right- and left-hand coupling plates. The Brinell hardness shall be established for a first article sample of the C-link and coupling plates as specified in 3.3 and in accordance with 4.5.6.

3.6 Brinell hardness - taper pin. The finished taper pin surface shall have a Brinell hardness of 350 (minimum) (see 4.5.5) or direct equivalent in accordance with ASTM A370 (see 6.4).

3.7 Dimensions. Dimensions and tolerance for type I and type II detachable link components shall be in accordance with the drawings specified below (see 4.4.1) and in accordance with the Forging Industry Association:

a. Type I, class 1 and class 2 - Drawing 803-860062.

c. Type II - Drawing 803-6397316.

3.7.1 Pull draft angles, C-link and coupling plates. All pull draft angles of C-links and coupling plates of detachable links shall be measured in accordance with 4.4.1.1. The pull draft angle limits shall be 3 degrees minimum and 10 degrees maximum. Draft angles greater than 10 degrees are not acceptable and the link shall be rejected.

3.8 C-link and coupling plate surfaces. Flashing, burrs, irregularities, and rough edges shall be contour ground to a fair surface. No surface shall be ground after proof test of the detachable link. The forgings shall be free from surface irregularities, dents, and undercutting in excess of the amounts specified in table II (see 4.4.2).

TABLE II. Allowable surface defects of forgings.

Detachable link size		Allowable surface defect (inches)
Type I (inches)	Type II (size no.)	
¾ to 1½	Numbers 2 to 4	1/32
1⅝ to 2½	Numbers 5 and 6	1/16
2⅝ to 3½	Numbers 7 and 8	3/32
3⅝ to 4	-	⅛
4¾	-	5/32

3.9 Taper pin surface. The taper pin machine surface quality shall be in accordance with the applicable drawing specified in 3.7 (see 4.4.3).

3.10 Fit of coupling plates on C-link. Coupling plates shall be fitted to the C-link in accordance with the applicable drawings specified in 3.7. There shall not be any movement between the coupling plates and C-link at the C-link opening (see 4.4.6).

3.11 Taper pin engagement. The taper pin shall be driven into the assembled detachable link (see figure 2) with the required assembly punch specified in Drawing 804-840327. The taper pin depth of engagement in the coupling plates shall be as specified in the drawings specified in 3.7 (see 4.4.7).

3.12 Hairpin fit. Hairpin, when specified (see 6.2), shall be installed after the taper pin is driven home (see 3.11, figure 1, and figure 2). With the hairpin fully seated in the groove of the coupling plate, the ends of the hairpin shall project a minimum of 2½ hairpin diameters and a minimum of 3 hairpin diameters beyond the groove of the opposite coupling plate (see 4.4.8).

3.13 Proof load. The detachable link shall withstand the proof load specified in tables III through IV (type I) and table V (type II) without developing any surface fracture or defects that would interfere with the serviceability or disassembly of the detachable link (see 4.5.3). Note that the proof load and minimum breaking load values for tables III and V are pulled from table IV in MIL-DTL-24633.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

TABLE III. Physical properties for type I, class 1, detachable links.

Link size (inches)	Proof load (pounds)	Minimum breaking load (pounds)
¾	48,000	75,000
⅞	64,400	98,000
1	84,000	129,000
1⅛	106,000	161,000
1¼	130,000	198,000
1⅜	157,000	235,000
1½	185,000	280,000
1⅝	216,000	325,000
1¾	249,000	380,000
1⅞	285,000	432,000
2	318,000	454,000
2⅛	357,000	510,000
2¼	396,000	570,000
2⅜	440,000	628,000
2½	484,000	692,000
2⅝	530,000	758,000
2¾	578,000	826,000
2⅞	628,000	897,000
3	679,000	970,000
3⅛	732,000	1,046,000
3¼	787,000	1,124,000
3⅜	843,000	1,204,000
3½	900,000	1,285,000
3¾	1,019,000	1,455,000
4¾	1,700,000	2,550,000

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

TABLE IV. Physical properties for type I, class 2, detachable links.

Link size (inches)	Proof load (pounds)	Minimum breaking load (pounds)
2¾ HD	584,100	882,900
3 HD	685,800	1,035,000
3½ HD	972,000	1,530,000
NOTE: HD = Heavy-duty detachable links		

TABLE V. Physical properties for type II detachable links.

Link number	Link size (inches)	Proof load (pounds)	Minimum breaking load (pounds)
5	-	-	-
	2	318,000	454,000
6	2⅛, 2⅜	440,000	628,000
7	2½, 3⅛	732,000	1,046,000
	2¾ HD	762,000	1,150,000
	3 HD	762,000	1,150,000
8	3¼, 3½	900,000	1,285,000
	3½ HD	1,080,000	1,700,000

3.14 Breaking load. The detachable link shall withstand the minimum breaking load specified in tables III and IV (type I) or table V (type II) without failure (see 4.5.2).

3.15 Markings. Markings shall be as described in 3.15.1 and 3.15.2.

3.15.1 Size markings. Each C-link and right-hand coupling plate of the detachable link shall be permanently marked in raised letters and figures to indicate the size of the link. The letters and figures shall be clear, readable, and of the size, embossed height, and location as specified in the drawing specified in 3.7 (see 4.4.4).

3.15.2 Property markings. The property marking "USN" per the applicable drawing is not required. If a property marking is included, the C-link of the detachable link may be marked with "US", "U.S.", or "USN". The letters and figures shall be clear, readable, and of the size, embossed height, and location as specified in the drawing specified in 3.7 (see 4.4.4).

3.16 Matched identification numbers. The C-link and coupling plates of each detachable link assembly shall be marked as specified (see 6.2) with matched identification numbers. The numbers on all components of a link shall be the same in order to identify the link and ensure mating of parts. Each link of the lot shall have a different identification number. The number shall be indented a minimum of 0.063 inch and a maximum of 0.094 inch. The identification number shall be stamped on the C-link and coupling plates after the coupling plates have been tightly closed on the C-link (see 3.10). The indented numbers shall be 0.250 inch high minimum and located in the areas shown on figure 3. Stamping dies shall be of the round bottom, low stress type (see 4.4.5). The identification numbers shall be assigned by the manufacturer and be traceable to production and test inspection records.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

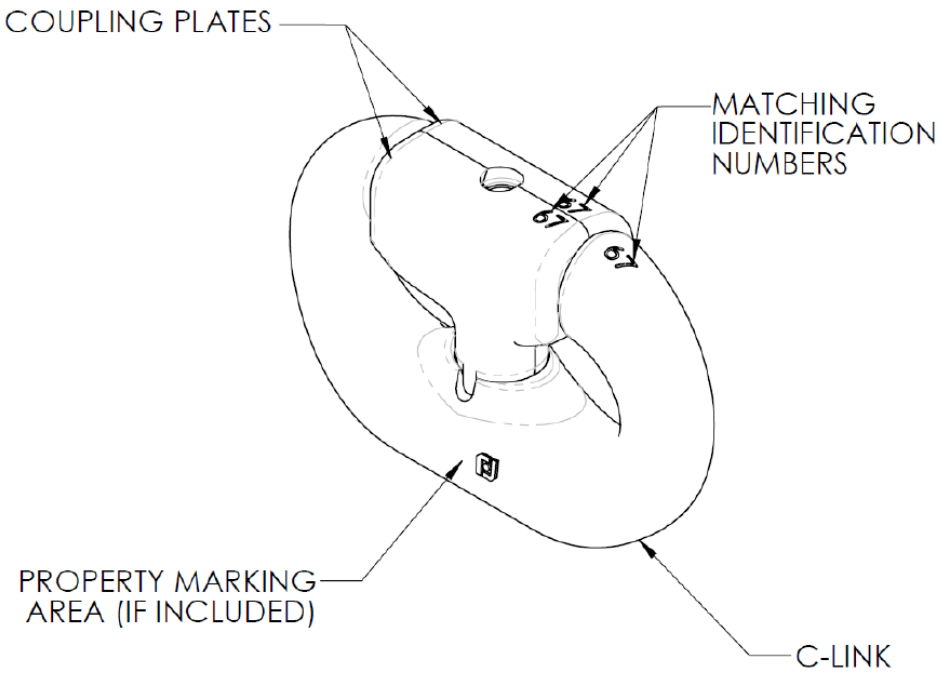


FIGURE 3. Detachable link markings.

3.17 Finish. The C-link and right- and left-hand coupling plates shall be thoroughly cleaned by tumbling or sand blasting (see 6.5) in accordance with SSPC-SP-10/NACE No 2 finish. After satisfactory completion of all tests and inspections, the detachable link shall be assembled with the taper pin. Before shipment, the taper pin shall be coated with grease conforming to MIL-PRF-10924 and lightly driven into the assembled detachable link for ease of disassembly (plug and hairpin shall not be installed). The assembled detachable link shall be coated with one coat of MIL-PRF-24635, type V, class 2, grade B, color SAE AMS-STD-595/26270 5 to 8 mils thick followed by one coat of MIL-PRF-24635, type V, class 1, grade A, color SAE AMS-STD-595/17038 5 to 8 mils thick. The maximum total paint thickness shall be 16 mils. The minimum total thickness shall be 3 mils. Other alternate finishes require approval by the contracting officer. The plug bore in the C-link shall be protected to prevent paint from contacting the bore surface (see 4.4.7 and 4.4.9).

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.2).

b. Conformance inspection (see 4.3).

4.2 First article inspection. First article inspection shall be performed when a first article sample is required (see 3.1). First article samples shall be selected in accordance with 4.2.1 and shall consist of the examinations and tests specified in table VI (see 6.3). The samples shall be clean, bright, and free of paint or other coating that would tend to conceal defects during the testing and inspection.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

TABLE VI. First article examinations and tests.

Inspection	Requirement paragraph	Examination or test paragraph
Detachable link		
Proof load test	3.13	4.5.3
Breaking load test	3.14	4.5.2
Finish	3.17	4.4.7, 4.4.9
C-link component		
Chemical composition	3.2.2.1	4.5.1
Tensile test	3.4	4.5.4
Pull draft angle	3.7.1	4.4.1.1
Brinell hardness test 1/	3.5	4.5.6
Dimension conformance	3.7	4.4.1
Surface	3.8	4.4.2
Markings	3.15, 3.15.1	4.4.4
Identification numbers	3.16	4.4.5
Right- and left-hand coupling plates		
Chemical composition	3.2.2.1	4.5.1
Tensile test	3.4	4.5.4
Pull draft angle	3.7.1	4.4.1.1
Brinell hardness test 1/	3.5	4.5.6
Dimension conformance	3.7	4.4.1
Surface	3.8	4.4.2
Markings (right-hand coupling plate only)	3.15	4.4.4
Identification numbers	3.16	4.4.5
Fit	3.10	4.4.6
Taper pin		
Chemical composition	3.2.3.1	4.5.1
Brinell hardness test 1/	3.6	4.5.5
Dimension conformance	3.7	4.4.1
Surface	3.9	4.4.3
Engagement	3.11	4.4.7
Plug		
Chemical composition	3.2.4.1	4.5.1
Dimension conformance	3.7	4.4.1
Hairpin (when specified (see 6.2))		
Chemical composition	3.2.5.1	4.5.1
Dimension conformance	3.7	4.4.1
Fit	3.12	4.4.8

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

TABLE VI. First article examinations and tests – Continued.

NOTE:
1/ Hardness measurement methods, tests, and testers, such as Rockwell, Knoop, and Vickers, shall be direct equivalents to Brinell and may be substituted solely in accordance with ASTM A370 (see 6.4). Conversions shall be expressed as specified in ASTM A370.

4.2.1 First article inspection samples. The following samples shall be prepared for the first article inspection examinations and tests specified in table VI. Samples shall be clean, bright, and free of paint or other coatings that would tend to conceal defects during inspection or testing. Detachable link samples shall consist of a minimum of:

4.2.1.1 Finished detachable link without hairpin and without plug installed. One finished detachable link, without the hairpin installed (see 6.2) and without the plug installed, for the following inspections and tests:

a. Dimension conformance:
   (1) C-Link.
   (2) Right- and left-hand coupling plates.
   (3) Taper pin.
   (4) Plug.
   (5) Hairpin.
   (6) Pull draft angle for C-link and coupling plates.
b. Surface examination:
   (1) C-link.
   (2) Right- and left-hand coupling plates.
   (3) Taper pin.
c. Marking examination:
   (1) C-link.
   (2) Right- and left-hand coupling plates.
d. Identification number examination:
   (1) C-link.
   (2) Right- and left-hand coupling plates.
e. Taper pin engagement.
f. Hairpin fit.
g. Proof test:
   (1) Assembled detachable link. The assembled detachable link shall be subjected to a proof test after the above examinations have been accomplished.

4.2.1.2 Unmachined detachable link components. The following unmachined detachable link components, heat treated as necessary, for the test noted:

a. C-link and coupling plate (right or left hand):
   (1) Chemical composition.
   (2) Tensile test.
   (3) Brinell hardness test.
b. Taper pin:
   (1) Chemical composition.
   (2) Brinell hardness test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

c. Plug:

(1) Chemical composition.

d. Hairpin:

(1) Chemical composition.

4.2.1.3 Finished detachable link for breaking load test. One finished detachable link for a breaking load test. The detachable link used for the proof test from 4.2.1.1(g) above with the hairpin installed may be used for the breaking test.

4.3 Conformance inspection. Detachable link samples shall be selected in accordance with 4.3.1 and shall consist of the examinations and tests specified in table VII. The samples shall be cleaned in accordance with SSPC-SP 10/NACE No 2 to be bright and free of paint or other coating that would tend to conceal defects during the testing and inspection.

TABLE VII. Conformance examinations and tests.

Inspection	Requirement paragraph	Examination or test paragraph
Detachable Link		
Proof load test	3.13	4.5.3
Breaking load test	3.14	4.5.2
Finish	3.17	4.4.7, 4.4.9
C-Link component		
Tensile test	3.4	4.5.4
Dimension conformance	3.7	4.4.1
Pull draft angles	3.7.1	4.4.1.1
Brinell hardness test 1/	3.5	4.5.6
Surface	3.8	4.4.2
Markings	3.15, 3.15.1	4.4.4
Identification numbers	3.16	4.4.5
Right- and left-hand coupling plates		
Tensile test	3.4	4.5.4
Dimension conformance	3.7	4.4.1
Pull draft angles	3.7.1	4.4.1.1
Brinell hardness test 1/	3.5	4.5.6
Surface	3.8	4.4.2
Markings (right hand coupling plate only)	3.15	4.4.4
Identification numbers	3.16	4.4.5
Fit	3.10	4.4.6
Taper pin		
Dimension conformance	3.7	4.4.1
Surface	3.9	4.4.3
Engagement	3.11	4.4.7
Brinell hardness test 1/	3.6	4.5.5

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

TABLE VII. Conformance examinations and tests – Continued.

Plug		
Dimension conformance	3.7	4.4.1
Hairpin (when specified (see 6.2))		
Dimension conformance	3.7	4.4.1
Fit	3.12	4.4.8

NOTE:

1/ Hardness measurement methods, tests, and testers, such as Rockwell, Knoop, and Vickers, shall be direct equivalents to Brinell and may be substituted solely in accordance with ASTM A370 (see 6.4). Conversions shall be expressed as specified in ASTM A370.

4.3.1 Sampling for conformance inspection. Sampling shall be to an "accept at zero" (c=0) sampling plan such as MIL-STD-1916 at verification level IV or Zero Acceptance Number Sampling Plans at the Acceptance Quality Limit (AQL) specified (see 6.2).

4.3.1.1 Sampling of finished detachable links. For the purpose of sampling finished detachable links, extra detachable links and detachable link components (see 4.3.1.2) shall be provided in each lot. A lot shall consist of not more than 100 finished detachable links (without plug or hairpin (see 6.2) installed) of the same type, class, and size. Each detachable link component shall be manufactured consecutively and from the same heat or melt of steel.

4.3.1.2 Conformance inspection of detachable link components. Each of the following detachable link components of the lot shall be subjected to the following inspections prior to proof testing (see 4.4.1, 4.4.1.1, 4.4.2, 4.4.3, 4.4.4, 4.4.5, and 4.5.6):

a. C-link dimension conformance.
b. C-link surface examination.
c. C-link Brinell hardness testing.
d. C-link pull draft angles examination.
e. Right- and left-hand coupling plates dimension conformance.
f. Right- and left-hand coupling plates surface examination.
g. Right- and left-hand coupling plates Brinell hardness testing.
h. Right- and left-hand coupling plates pull draft angles examination.
i. C-link and right-hand coupling plate marking examination.
j. C-link and coupling plates identification number examination.
k. Taper pin dimension conformance.
l. Taper pin surface examination.
m. Taper pin Brinell hardness testing.
n. Plug dimension conformance.
o. Hairpin dimension conformance.

4.3.1.3 Conformance inspection of 10 detachable links. After satisfactory completion of inspections specified in 4.3.1.2, a random sampling of 10 detachable links shall be selected from each lot and shall be subjected to the following inspections (see 4.4.6, 4.4.7, and 4.4.8):

a. Fit of right- and left-hand coupling plates on C-link examination.
b. Taper pin engagement examination.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

c. Hairpin fit examination.

4.3.1.4 Conformance inspection of each detachable link. After satisfactory completion of inspections specified in 4.3.1.3, each detachable link of the lot shall be subjected to a proof test (see 4.5.3) and a finish (paint) inspection (see 4.4.9).

4.3.1.5 Conformance inspection of sample detachable links and components. An extra detachable link, with hairpin when specified (see 6.2), and plug installed shall be furnished for each lot for the breaking load test (see 4.5.2). In addition to the extra detachable link for the breaking load test, an extra C-link and coupling plate (left or right hand) or stock (see 3.4) shall be furnished for a component specimen tensile test (see 4.5.4).

4.3.1.6 Disposition of chain samples. Test samples and unused samples shall be either shipped and the finished detachable link retained at the manufacturing facility or scrapped at the discretion of the contracting officer. If retention or shipping is desired, each sample shall be identified.

4.4 Examination methods.

4.4.1 Dimension conformance of detachable link components. The dimensions of each detachable link component (C-link, coupling plates, taper pin, plug, and hairpin (when specified (see 6.2)) shall be measured with equipment that has been calibrated within the previous 12 months. Calibrations shall be National Institute of Standards and Technology (NIST) traceable in accordance with ASTM E4. The measurements of each detachable link component shall be as specified on the applicable drawing specified in 3.7. The C-link and right- and left-hand coupling plates shall be remeasured after proof testing. The detachable link shall be rejected if any one of its components does not conform to the dimensional requirements of 3.7. The plug or hairpin shall be rejected if it does not conform to the dimensional requirements of 3.7.

4.4.1.1 Measurement of pull draft angles. The measurements of pull draft angles of C-links and coupling plates of ¾- through 1½-inch detachable links shall be carried out with an optical comparator to comply with the requirements in 3.7.1. The pull draft angles of 1⅝- through 4¾-inch detachable links shall be performed with a template capable of measuring pull draft angles of a maximum of 10 degrees. All measurements of pull draft angles will be made at 90-degree increments.

4.4.2 Surface examination of C-link and right and left hand coupling plates. After cleaning all surfaces and before proof testing, all surfaces shall be visually examined. After proof testing and before painting, the surfaces shall be completely inspected using the magnetic particle method of examination in accordance with NAVSEA T9074-AS-GIB-010/271 and MIL-STD-2035. If a surface irregularity, dent, or undercut exceeding the criteria of 3.8 is found on the C-link or coupling plates surfaces, the detachable link shall be rejected.

4.4.3 Surface examination of taper pin. After cleaning the taper pin, the machine surface quality of the taper shall be visually examined and compared to a machine surface roughness gauge made from pure nickel. If the taper pin machine surface quality is less than the requirement of 3.9, the taper pin shall be rejected.

4.4.4 Marking examination. The markings on the C-link and right-hand coupling plate surfaces shall be visually examined. If the letters and figures are poorly embossed and unreadable, it will be permissible to machine or grind the embossing to produce readable letters and figures. Machining or grinding below the surface line of the C-link or coupling plate is not permitted and shall be cause for rejection of the detachable link. Markings shall meet the requirements specified in 3.15 through 3.15.2.

4.4.5 Identification numbers examination. The identification numbers on the C-link and coupling plate shall be visually examined. If the stamping exceeds the maximum depth or if the stamping was struck by dies other than the low stress type, the detachable link shall be rejected. The identification numbers shall be as specified in 3.16.

4.4.6 Examination of coupling plates fit on C-link. The coupling plates shall be placed on the C-link and the taper pin installed. There shall not be any movement between the coupling plates and the C-link as specified in 3.10. If there is movement between the coupling plates and the C-link, it will be permissible to refit the coupling plates on the C-link (see 3.10) and the fit reinspected. If movement is still present, the detachable link shall be rejected. If more than two detachable links are rejected because of the coupling plate fit, the entire lot of detachable links shall be inspected.

4.4.7 Examination of taper pin engagement. The taper pin, when driven tightly into the detachable link, shall be visually examined. The finish shall be as specified in 3.17. If the taper pin engagement in the coupling plates does not conform to the required dimensions, the detachable link shall be rejected. If more than two detachable

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

links are rejected, then the entire lot of detachable links shall be inspected for taper pin engagement. The taper pin shall meet the requirements specified in 3.11.

4.4.8 Examination of hairpin fit. The fit of the hairpin and the projection of the hairpin ends beyond the coupling plate shall be in accordance with 3.12. If the ends of the hairpin project less than the minimum specified length beyond the coupling plate, the hairpin shall be rejected. The hairpin ends shall not be bent and the hairpin shall be removed following the examination.

4.4.9 Examination of finish. The paint shall show no film failures, such as loss of adhesion, blistering, pinholing, checking, or cracking. The plug bore in the coupling plates shall be examined for evidence of paint on the surface. The finish shall meet the requirements specified in 3.17.

4.5 Testing methods.

4.5.1 Chemical composition. The material samples selected in accordance with 4.2.1.2 shall be analyzed to determine the chemical composition. The chemical composition of the material used in the manufacture of the C-link and coupling plates (see 3.2.2.1), the taper pin (see 3.2.3.1), the plug (see 3.2.4.1), and the hairpin (see 3.2.5.1) for the first article and product testing shall be verified by a chemical or spectrographic analysis conducted by the detachable link manufacturer. Material not within the composition tolerances shall be rejected.

4.5.2 Detachable link breaking load test. Samples for the break tests shall be tested for breaking load. If, in normal production only, it is considered that the test equipment would be endangered by a sudden break, it shall be considered acceptable if the detachable link is loaded to the required breaking strength and maintained at load for 15 seconds. Samples used in first article testing shall be tested to destruction. The break testing machine shall have been calibrated within the 12 months previous to the breaking load test. The samples shall meet the breaking load requirements of tables III through table V. Samples that break below the level specified in tables III through V shall be cause for rejection of the entire lot.

4.5.3 Detachable link proof test. Detachable links shall be proof tested by securing them in a testing machine either singly or assembled into sections. The proof load testing machine shall have been calibrated within the 12 months previous to the detachable link proof load test. The calibration shall be NIST traceable in accordance with ASTM E4. If there is a sign of fracture, including breaking or cracking, during the proof test, the detachable link shall be rejected. Recording of the applied load shall be taken of all proof load tests during both first article and conformance tests. Detachable links shall meet the requirements specified in 3.13.

4.5.4 Tensile test. A tensile specimen shall be taken from the C-link and one coupling plate (left or right) if both are produced from the same heat of steel. Left and right coupling plates produced from separate heats of steel shall require separate tensile specimens for the right and left plates. The tensile test shall be conducted with procedures using standard specimens conforming to ASTM A370 (see 3.4, 4.2.1.2, and 4.3.1.5). If the tensile test fails to meet the requirements of 3.4, but is within 3,000 lb/in² of the required tensile strength, a retest of another specimen selected from the same sample will be permissible. The test specimens shall meet the requirements of 3.4.

4.5.5 Brinell hardness test for taper pin. The Brinell hardness test shall be conducted in accordance with ASTM A370. If the hardness of the taper pin surface fails to meet the minimum hardness requirements of 3.6, the taper pin shall be rejected.

4.5.6 Brinell hardness test for C-link and coupling plates. The Brinell scale hardness of the sample components (see 4.2.1.2) shall be conducted in accordance with ASTM A370.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful but is not mandatory.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

6.1 Intended use. The detachable links covered by this specification are intended for use in anchor chain connecting applications and connecting other chain appendages as specified in 1.1. Current stock of detachable links manufactured to MIL-DTL-2710D with amendment 1, dated 4 January 2021, may be used as replacement parts until depleted; future requisitions for detachable links for flash butt welded anchor chain should refer to the current version of this specification.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Type, class, and size of detachable link required (see 1.2).

c. When first article inspection is required (see 3.1).

d. Hairpin, if required (see 3.2.1, 3.2.5, 3.12, 4.2.1.1, table VI, table VII, 4.3.1.1, 4.3.1.5, and 4.4.1).

e. AQL (see 4.3.1).

f. Identification number, location, and type of identification for the C-link and coupling plates (see 3.16).

g. Packaging requirements (see 5.1).

6.3 First article. When first article inspection is required, the contracting officer should provide specific guidance to offerors whether the item(s) should be a preproduction sample, a first article sample, a first production item, a sample selected from the first production items, or a standard production item from the contractor's current inventory (see 3.1); and the number of items to be tested as specified in 4.2.1. The contracting officer should also include specific instructions in acquisition documents regarding arrangements for examinations, approval of first article test results, and disposition of first articles. Preparation of first article reports should conform to MIL-HDBK-831, "Preparation of Test Reports". Invitations for bids should provide that the Government reserves the right to waive the requirement for samples for first article inspection to those bidders offering a product that has been previously acquired or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending contract. Bidders should not submit alternate bids unless specifically requested to do so in the solicitation.

6.4 Hardness testing. Although Brinell scale hardness testing has been specified throughout this document, users may employ government-approved alternate methods of hardness testing in sole accordance with ASTM A370. For consistency, all non-Brinell hardness scale measurements should be converted to direct equivalent Brinell scale values and conversions should be expressed as specified in ASTM A370.

6.5 Caution. Caution should be taken during cleaning and coating processes as described in 3.17. The contractor is responsible for the safe reutilization and disposal of all materials generated by this process in accordance with ASTM A380/A380M, "Standard Practice for Cleaning, Descaling, Pickling, and Passivation of Stainless Steel Parts, Equipment, and Systems".

6.6 Subject term (key word) listing.

Anchor
Anchoring
Appendages
C-link
Coupling plate
Ground tackle
Hairpin
Heavy duty
Mooring
Plug
Swivel shot
Taper pin

6.7 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.

CONCLUDING MATERIAL

Custodians:
Navy – SH
DLA – GS

Preparing activity:
Navy – SH
(Project 4010-2026-002)

Review activity:
Navy – YD

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using ASSIST at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:17Z
Check the source to verify that this is the current version before use.