The documentation and process conversion measures necessary to comply with this revision shall be completed by 24 Aug 92

INCH POUND

MIL-S-19500/116J
23 July 1992
SUPERSEDING
MIL-S-19500/116H
9 June 1989

MILITARY SPECIFICATION

SEMICONDUCTOR DEVICE, DIODE, SILICON, SWITCHING
TYPES 1N914, 1N4148-1 AND 1N4531
JAN, JANTX, AND JANTXV

JANS1N4148-1 is a superseded by MIL-S-19500/578 JANS16642 (see 6.3 and 6.3.1). Device types 1N914 and 1N4531 are inactive for new design after the date of this specification.

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the detail requirements for silicon, diffused, computer diodes. Three levels of product assurance are provided for each device type as specified in MIL-S-19500.

1.2 Physical dimensions. See figure 1.

1.3 Maximum ratings.

Type	$V_{(BR)}$	V_{RWM}	I_O T_A = 25°C	I_{FSM} t_p = 1/120 s	T_{STG}	T_J	$Z_{\theta JX}$	$R_{\theta JL}$
	V dc	V (pk)	mA	A (pk)	°C	°C	°C/W	°C/W
1N914	100	75	75 1/	1	-65 to +200	-65 to +175	50	250
1N4531	100	75	125 2/	1	-65 to +200	-65 to +175		
1N4148-1	100	75	200 3/	2	-65 to +200	-65 to +200		

1/ Derate at 0.5 mA/°C above T_A = 25°C.
2/ Derate at 0.83 mA/°C above T_A = 25°C.
3/ Derate at 1.14 mA/°C above T_A = 25°C.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, Defense Electronics Supply Center, ATTN: DESC-ECT, 1507 Wilmington Pike, Dayton, OH 45444-5280, by using the Standardization Document Improvement Proposal DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 5961

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

1.4 Primary electrical characteristics at T_A = +25°C, unless otherwise indicated.

Type	V_{F1}		V_{F2}		I_{R1} at V_R = 20 V dc	I_{R2} at V_R = 75 V dc	I_{R3} at V_R = 20 V dc T_A = 150°C	I_{R4} at V_R = 75 V dc T_A = 150°C	t_{fr} at V_{fr} = 5.0 V (pk) and I_F = 50 mA dc	t_{rr}
	I_F (mA dc)	V dc	I_F (mA dc)	V dc	nA dc	µA dc	µA dc	µA dc	ns	ns
1N914	10	0.8	50	1.2	25	0.5	50	100	20	5
1N4148-1	10	0.8	100	1.2	25	0.5	50	100	20	5
1N4531	10	0.8	100	1.2	25	0.5	50	100	20	5

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATION

MILITARY

MIL-S-19500 - Semiconductor Devices, General Specification for.

STANDARD

MILITARY

MIL-STD-750 - Test Methods for Semiconductor Devices.

(Unless otherwise indicated, copies of federal and military specifications, standards, and handbooks are available from the Standardization Document Order Desk, Building 4D, 700 Robbins Avenue, Philadelphia, PA 19120-5094.)

2.2 Order of precedence. In the event of a conflict between the text of this document and the references cited herein (except for related associated detail specifications, specification sheets, or MS standards), the text of this document shall take precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Detail specification. The individual item requirements shall be in accordance with MIL-S-19500, and as specified herein.

3.2 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-S-19500.

V_{fr} - - - - - - - - - Forward recovery voltage. Specified maximum forward voltage used to determine forward recovery time.
TCV_F - - - - - - - - Temperature coefficient of forward voltage.
LS - - - - - - - - - Lead spacing distance between device body and electrical/mechanical contact on lead.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

3.3 Design, construction, and physical dimensions. The design, construction, and physical dimensions shall be as specified in MIL-S-19500, and figure 1 herein.

3.3.1 Lead finish. Lead finish shall be solderable in accordance with MIL-STD-750, MIL-S-19500, and herein. Lead finish may be specified in the contract (see 6.2), without affecting the qualified product status of the device or applicable JAN marking.

3.3.2 Diode construction. All devices shall be metallurgically bonded double plug construction in accordance with the requirements of category I or II, (see MIL-S-19500).

3.4 Marking. Marking shall be in accordance with MIL-S-19500, except at the option of the manufacturer, the following marking may be omitted from the body of the device:

a. Country of origin.

b. The "1N" portion of the type designation.

c. "-" portion of the type designation.

d. Lot identification code.

3.5 Polarity. The polarity shall be indicated with a contrasting color band to denote the cathode end. No color coding will be permitted.

4. QUALITY ASSURANCE PROVISIONS

4.1 Sampling and inspection. Sampling and inspection shall be in accordance with MIL-S-19500, and as specified herein.


4.1.1 Process control monitors. Each vendor by means of Process Control shall derive an I_{R3} limit. When three successive production lots (minimum) have exhibited control in accordance with EIA557, the data from these lots shall be used to establish an I_{R3} monitor on all date codes.

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-S-19500, and as specified herein.

4.2.1 Construction verification. Cross sectional photos from 3 devices shall be submitted in the qualification report.

4.2.2 Group E inspection. Group E inspection shall be in accordance with MIL-S-19500 and table IV herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

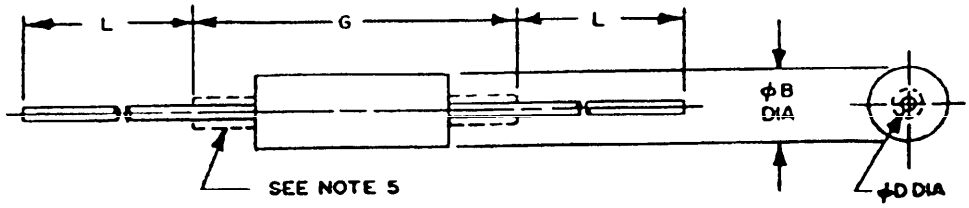

Types	Dimensions					Notes
	Ltr	Inches		Millimeters		
		Min	Max	Min	Max	
1N4148-1 1N914	G	.140	.180	3.56	4.57	1, 2, 5
	ϕB	.056	.075	1.42	1.90	1, 2, 3, 4
	L	1.000	1.500	25.40	38.10	1, 2
	ϕD	.018	.022	0.46	0.56	1, 2, 6
1N4531	G	.080	.120	2.03	3.05	1, 2
	ϕB	.050	.075	1.27	1.90	1, 2, 3, 4
	L	1.000	1.500	25.40	38.10	1, 2
	ϕD	.018	.022	0.46	0.56	1, 2, 6

NOTES:
1. Dimensions are in inches.
2. Metric equivalents are given for general information only.
3. The maximum dimension of ϕB shall apply for dimension G.
4. The minimum dimension of ϕB shall apply over at least .075 (1.90 mm) of dimension G.
5. Ferrule is optional on types 1N4148-1 and 1N4531 for dimension G.
6. The specified lead diameter applies in the zone between .050 (1.27 mm) for 1N914, and 1N4148-1, and .010 (0.25 mm) for 1N4531 from the diode body to the end of the lead. Outside of this zone the lead shall not exceed ϕB.

FIGURE 1. Semiconductor device, diode, types 1N914, 1N4148-1, and 1N4531.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

4.3 Screening (JAN, JANTX, and JANTXV levels only). Screening shall be in accordance with MIL-S-19500 (table II), and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen (see table II of MIL-S-19500)	Measurement		
	JAN level	Option A 3/ JANTX and JANTXV level	Option B JANTX and JANTXV level
3A	Temperature cycling in accordance with MIL-S-19500	Temperature cycling	Temperature cycling
1/ 3C	Thermal impedance (see 4.5.5)	Thermal impedance (see 4.5.5)	Thermal impedance (see 4.5.5)
9	Not applicable	Not applicable	Not applicable
10	Not applicable	Method 1038, condition A, t = 48 hours	Method 1038, condition A, t = 48 hours
11	Not applicable	2/ I_{R1}, V_{F1} and subgroup 2 of table I	I_{R1} and V_{F1}
12	Not applicable	Not applicable	Method 1038, condition B, t = 48 hours (see 4.3.1)
13	Not applicable	Not applicable	4/ Subgroup 2 of table I herein ΔV_{F1} = ±0.025 V(pk) ΔI_{R1} = 100% of initial value or ±15 nA, whichever is greater

1/ Thermal impedance shall be performed any time after sealing provided temperature cycling is performed in accordance with MIL-S-19500, screen 3 prior to this thermal test.
2/ For option A only, PDA = 4% shall apply to screen 11 I_{R1}, V_{F1} and subgroup 2 of table I herein.
3/ See 4.5.7.
4/ Thermal impedance ($Z_{\theta JX}$) is not required in screen 13.

4.3.1 Power burn-in test conditions. All devices shall be operated under one of the following conditions (see 4.5.1).

Type	T_A = 30°C ±5°C, V_{RWM} = 75 V(pk), f = 60 Hz	T_A = 30°C ±5°C
	mA	mA dc
1N914	I_O = 75	I_F = 150
1N4531	I_O = 125	I_F = 175
1N4148-1	I_O = 200	I_F = 175

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

4.4 Quality conformance inspection. Quality conformance inspection shall be in accordance with MIL-S-19500, and as specified herein.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with MIL-S-19500, and table I herein. (End-point electrical measurements shall be in accordance with the applicable steps of table III herein.)

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in table IVb (JAN, JANTX and JANTXV) of MIL-S-19500, as follows. Electrical measurements (end points) and delta requirements shall be in accordance with the applicable steps of table III herein.

4.4.2.1 Group B inspection, table IVb of MIL-S-19500.

a. Subgroup 3

Steady-state operational life, method 1027, T_A = 30°C ±5°C, V_{RWM} = 75 V(pk) f = 60 Hz (see 4.5.1) for:

1N914	I_O = 75 mA
1N4531	I_O = 125 mA
1N4148-1	I_O = 200 mA

b. Subgroup 4

Decap internal visual design verification and (scribe and break), method 2075, see 4.5.4 herein.

c. Thermal resistance, method 3101 or 4081, see 4.5.6 herein.

4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table V of MIL-S-19500, and as follows. Electrical measurements (end points) and delta requirements shall be in accordance with the applicable steps of table III herein.

4.4.3.1 Group C inspection, table V of MIL-S-19500.

a. Subgroup 1

Physical dimensions: Method 2066, see figure 1 herein.

b. Subgroup 2

Thermal shock (glass strain): Method 1056, 100 cycles.
Terminal strength (tension): Method 2036, test condition A, t = 15s, weight = 10 pounds.
Lead fatigue, test condition E.

c. Subgroup 6, steady-state operation life: Method 1026, T_A = 30°C ±5°C. V_{RWM} = 75 V(pk), f = 60 Hz (see 4.5.1) for:

1N914	I_O = 75 mA
1N4531	I_O = 125 mA
1N4148-1	I_O = 200 mA

4.5 Methods of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows:

4.5.1 Life tests. AC tests shall be conducted with a half-sine wave of the peak voltage specified herein impressed across the diode in the reverse direction, followed by a half-sine waveform of the average rectified current specified herein. The forward conduction angle of the rectified current shall be not greater than 180° nor less than 150°.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

4.5.2 Forward recovery voltage and time. Forward recovery time shall be measured as the time interval between zero time and the point where the pulse has decreased to 110 percent of the steady-state value of V_F when I_F = 50 mA dc. The maximum rise time of the response detector shall be 1 ns.

4.5.3 Pulse measurements. Conditions of pulse measurements shall be specified in section 4 of MIL-STD-750.

4.5.4 Decap internal visual scribe and break . Scratch glass at cavity area with diamond scribe. Carefully snap open. Using 30X magnification examine the area where die (or bond material) are in contact with the plugs, verify metallurgical bonding area. If the verification of the metallurgical bonding area is in question, the test method 3101 and test conditions and limits herein shall be used to determine suitability for use.

4.5.5 Thermal impedance. Thermal impedance $Z_{\theta JX}$ measurements shall be performed in accordance with MIL-STD-750, method 3101. The maximum limit for $Z_{\theta JX}$ in screening (table II of MIL-S-19500) shall be derived by each vendor by means of Process Control. When three minimum lot date codes have exhibited control, the data from these three minimum lot date codes will be used to establish a fixed screening limit, (not to exceed the group A, subgroup 2 limit). Once a fixed limit has been established, monitor all future sealing lots using a five piece (min) sample from each production lot to be plotted on the applicable X, R chart.

I_H = 300 mA to 500 mA

t_H = 10 ms

I_M = 1 mA to 10 mA

t_{MD} = 70 µs maximum

4.5.5.1 For Initial qualification and requalification. Read and record data ($Z_{\theta JX}$) shall be supplied to the qualifying activity on one lot (random sample of 500 devices minimum) prior to shipment. Twenty-two samples shall be serialized and provided to the qualifying activity for test correlation.

4.5.6 Thermal resistance. Thermal resistance measurement shall be performed in accordance with MIL-STD-750, method 3101 or 4081. Forced moving air or draft shall not be permitted across the device during test. The maximum limit for $R_{\theta JL}$ under these test conditions shall be $R_{\theta JL(max)}$ = 250°C/W. The following conditions shall apply when using method 3101:

I_H = 75 mA to 300 mA

t_H = 25 seconds minimum

I_M = 1 mA to 10 mA

t_{MD} = 70 µs maximum

LS = Lead spacing = 3/8 inch as defined on figure 2 below:

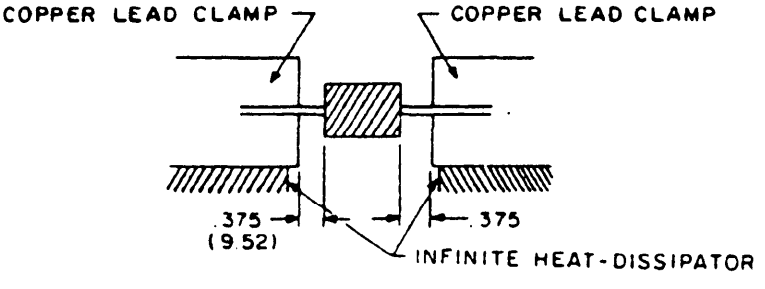



FIGURE 2. Mounting arrangement.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

4.5.6.1 For initial qualification and requalification. Thermal resistance read and record data, in accordance with group E herein, shall be included in the qualification report.

4.5.7 Screening option A verification requirements.

a. Prior to invoking screening option A, each vendor must complete option B screens 12 and 13 herein following completion of screening option A from the same three successive lot date codes minimum with zero failures. The following diagram illustrates the appropriate flow.

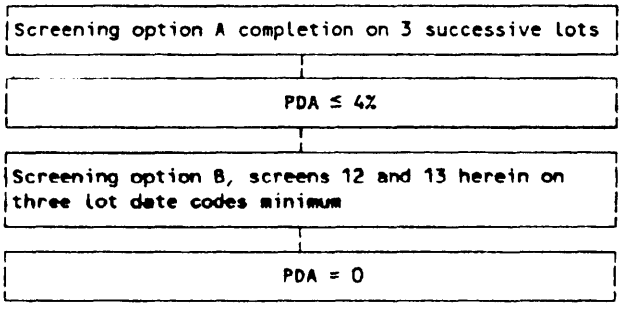

b. Each vendor by means of Process Control shall derive an I_{R1} limit. When three successive lot date codes (minimum) have exhibited control, the data from these lots shall be used to establish an I_{R1} screening limit, (not to exceed the group A subgroup 2 limit herein). This I_{R1} screening limit shall be invoked anytime after assembly.

c. Option A requires the written approval of the qualifying activity. The qualifying activity may revoke option A for quality reasons at any time.

d. Option A is prohibited for designs which do not exhibit a full area metallurgical bond. Written approval from the qualifying activity is required to verify a full area metallurgical bond. $Z_{\theta JX}$ = 30°C/W minimum.

Source: https://assist.dla.mil -- Downloaded: 202610-18T13:15Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 1						
Visual and mechanical inspection	2071					
Subgroup 2						
Thermal impedance	3101	See 4.5.5	$Z_{\theta JX}$		50	°C/W
Forward voltage	4011	I_F = 10 mA dc	V_{F1}		0.8	V dc
Breakdown voltage	4021	I_R = 100 µA dc	V_{BR1}	100		V dc
Reverse current	4016	DC method V_R = 20 V dc	I_{R1}			
1N914					25	nA dc
1N4531					25	nA dc
1N4148-1					25	nA dc
Reverse current	4016	DC method V_R = 75 V dc	I_{R2}		500	nA dc
Forward voltage	4011		V_{F2}			
1N914		I_F = 50 mA dc			1.2	V dc
1N4531		I_F = 100 mA dc			1.2	V dc
1N4148-1		I_F = 100 mA dc			1.2	V dc
Subgroup 3						
High temperature operation:		T_A = +150°C				
Reverse current	4016	DC method V_R = 20 V dc	I_{R3}		50	µA dc
1N914						
1N4531						
1N4148-1						
Reverse current	4016	DC method V_R = 75 V dc	I_{R4}			
1N914					100	µA dc
1N4531					100	µA dc
1N4148-1					100	µA dc
Forward voltage	4011	I_F = 10 mA dc	V_{F3}			
1N914					0.8	V dc
1N4531					0.8	V dc
1N4148-1					0.8	V dc

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 3 - Continued						
Low temperature operation:		T_A = -55°C				
Forward voltage	4011		V_{F4}			
1N914		I_F = 50 mA dc			1.3	V dc
1N4531		I_F = 100 mA dc			1.3	V dc
1N4148-1		I_F = 100 mA dc			1.3	V dc
Subgroup 4						
Junction capacitance	4001	V_R = 0 V dc f = 1 MHz V_{sig} = 50 mV_{p-p} maximum	C_1			
1N914					4.0	pF
1N4531					4.0	pF
1N4148-1					4.0	pF
Junction capacitance	4001	V_R = 1.5 V dc f = 1 MHz V_{sig} = 50 mV_{p-p} maximum	C_2		2.8	pF
Reverse recovery time	4031	Condition A C ≥ 1 nF $I_F = I_R$ = 10 mA dc R_L = 100Ω ±5% I_{RR} = 1.0 mA dc R ≥ 1000Ω	t_{rr}		5	ns
1N914						
1N4531						
1N4148-1						
Subgroup 5						
Not applicable						

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

Inspection	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 6						
Surge current	4066	Condition A (sine wave) $i_{f(surge)}$ = 1 A (pk) for 1N914 and 1N4531 $i_{f(surge)}$ = 2 A (pk) for 1N4148-1 I_O = maximum rated dc current = 0 V_{RM} = 0 10 surges, 8.3 ms width each, one surge per minute, T_A = 25°C or Condition B (square wave) $I_{F(surge)}$ = 0.704 A (pk) for 1N914 and 1N4531 $I_{F(surge)}$ = 1.41 A (pk) for 1N4148-1 t_p = 8.3 ms 10 surges one surge per minute T_A = 25°C				
Electrical measurements		See table III, steps 2 and 3				
Subgroup 7						
Forward recovery voltage and time	4026	I_F = 50 mA dc (see 4.5.2)	V_{fr} t_{fr}		5.0 20	V (pk) ns

1/ For sampling plan, see MIL-S-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

TABLE II. Group E inspection (all quality levels) for qualification only.

Inspection	MIL-STD-750		Sampling plan
	Method	Conditions	
Subgroup 1			45 devices c = 0
Thermal shock (glass strain)	1056	500 cycles	
Electrical measurements		See table III, steps 1, 2, 3, 4, and 7	
Subgroup 2			45 devices c = 0
Steady-state dc intermittent operating life	1037	6,000 cycles	
Electrical measurements		See table III steps 1, 2, 3, 4, 5, 6, and 7	
Subgroup 3			
Not applicable			
Subgroup 4			22 devices c = 0
Thermal resistance	3101 or 4081	See 4.5.6	
Subgroup 5			45 devices c = 0
Monitored mission temperature cycling	1055		
Electrical measurements		See table III, steps 2, 3, and 7	

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

TABLE III. Groups A, B, C, and E electrical measurements.

Step	Inspection	MIL-STD-750		Symbol	Limits		Unit
		Method	Conditions		Min	Max	
1.	Forward voltage	4011	Pulse width = 8.3 ms maximum; duty cycle = 2% maximum	V_{F1}			
	1N914		I_F = 10 mA dc			0.8	V dc
	1N4531, 1N4148		I_F = 10 mA dc			0.8	V dc
	1N4148-1		I_F = 10 mA dc			0.8	V dc
2.	Forward voltage	4011	Pulse width = 8.3 ms maximum; duty cycle = 2% maximum	V_{F2}			
	1N914		I_F = 50 mA dc			1.2	V dc
	1N4531 and 1N4148-1		I_F = 100 mA dc			1.2	V dc
3.	Reverse current	4016	DC method; V_R = 20 V dc	I_{R1}			
	1N914					25	nA dc
	1N4531 and 1N4148-1					25	nA dc
4.	Reverse current	4016	DC method; V_R = 75 V dc	I_{R2}		300	nA dc
5.	Capacitance	4001	V_R = 0 V dc; f = 1 MHz ac signal = 50 mV_{p-p} maximum	C_1			
	1N914					4.0	pF
	1N4531 and 1N4148-1					4.0	pF
6.	Capacitance	4001	V_R = 1.5 V dc f = 1 MHz; ac signal = 50 mV_{p-p} maximum	C_2		2.8	pF
7.	Thermal impedance	3101	See 4.5.5	$Z_{\theta JX}$		50	°C/W

1/ Devices which exceed the group A limits for this test shall be rejected.
2/ The electrical measurements for table IVb (JAN, JANTX, and JANTXV) of MIL-S-19500 are as follows:
   a. Subgroup 2, see table III herein, steps 2, 3, 4, and 7.
   b. Subgroup 3, see table III herein, steps 1, 3, 5, and 6.
   c. Subgroup 6, see table III herein, steps 1, 3, 5, and 6.
3/ The electrical measurements for table V of MIL-S-19500 are as follows:
   a. Subgroup 2, see table III herein, steps 2, 3, 4, and 7.
   b. Subgroup 6, see table III herein, steps 1, 3, 5, and 6.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging requirements. The requirements for packaging shall be in accordance with MIL-S-19500.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Notes. The notes specified in MIL-S-19500 are applicable to this specification.

6.2 Acquisition requirements. Acquisition documents must specify the following:

a. Issue of DODISS to be cited in the solicitation.

b. Lead finish as specified (see 3.3.1).

c. Type designation and product assurance level.

6.3 Substitution information. The 1N6638 or 1N6642 or 1N6643 (MIL-S-19500/578) is preferred in lieu of the 1N4148-1. The JANS1N6638 or 1N6642 is substitutable for the JANS1N4148-1 and should be used in lieu of the JANS1N4148-1.

6.3.1 Cross reference supersession list. JANS level will no longer be built to this specification. Devices in stock are acceptable provided the date code does not exceed the date of implementation of this specification. Devices required for space flight applications are found on MIL-S-19500/578. A PIN for PIN replacement table follows, and these devices are directly interchangeable:

JANS Nonpreferred PIN	JANS Preferred PIN
1N4148-1	1N6638 1N6642

6.4 Changes from previous issue. Asterisks are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

CONCLUDING MATERIAL

Custodians:
Army - ER
Navy - EC
Air Force - 17
NASA - NA

Review activities:
Army - AR, MI
Navy - SH
Air Force - 19, 85, 99
DLA - ES
NASA - LRC, MSF

User activities:
Army - SM
Navy - AS, CG, MC, OS

Preparing activity:
Navy - EC

Agent:
DLA - ES

(Project 5961-1256)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T13:15Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8 In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER MIL-S-19500/116J	2. DOCUMENT DATE (YYMMDD) 920723

3. DOCUMENT TITLE
Semiconductor for Devices, Diode, Silicon Switching

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle Initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) (1) Commercial (2) AUTOVON (If applicable)	7. DATE SUBMITTED (YYMMDD)

8. PREPARING ACTIVITY

a. NAME Mr. Alan Barone	b. TELEPHONE (Include Area Code) (1) Commercial (513) 296- 6048	(2) AUTOVON 986-6048
c. ADDRESS (Include Zip Code) Commander, Defense Electronics Supply Center Attn: DESC-ECT 1507 Wilmington Pike Dayton OH 45444- 5280	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 AUTOVON 289-2340	

Source: https://assist.dla.mil -- Downloaded: 202610-18T13:15Z
Check the source to verify that this is the current version before use.