MIL-H-53027A(ME)
29 May 1985
SUPERSEDING
MIL-H-53027(ME)
27 July 1983

MILITARY SPECIFICATION

HOSE ASSEMBLY, RUBBER: LIGHTWEIGHT COLLAPSIBLE, 6-INCH; FOR DRINKING (POTABLE) WATER

This specification is approved for use by the USA Belvoir Research and Development Center, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers a 6-inch, lightweight, collapsible rubber hose assembly for drinking (potable) water; swivel, and flaking box.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. Unless otherwise specified, the following specifications and standards of the issue listed in that issue of the Department of Defense Index of Specifications and Standards (DoDISS) specified in the solicitation, form a part of this specification to the extent specified herein.

SPECIFICATION

FEDERAL

WW-C-440	- Clamps, Hose, (Low-Pressure).

MILITARY

MIL-C-104	- Crates, Wood; Lumber and Plywood Sheathed, Nailed, and Bolted.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: USA Belvoir Research and Development Center, ATTN: STRBE-DS, Fort Belvoir, VA 22060-5606 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

FSC 4720

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:52Z
Check the source to verify that this is the current version before use.

MIL-T-704	- Treatment and Painting of Materiel.
MIL-C-3774	- Crates, Wood: Open, 12,000- and 16,000-Pound Capacity.
MIL-A-8625	- Anodic Coatings, for Aluminum and Aluminum Alloys.
MIL-C-10387	- Couplings, Clamp, Pipe; with Bolts and Synthetic-Rubber Gaskets, for Grooved-End Pipe and Tube.
MIL-G-20241	- Gasket Material, Wool Felt, Impregnated, Adhesive, Pressure-Sensative.
MIL-P-23377	- Primer Coatings: Epoxy-Polyamide, Chemical and Solvent Resistant.
MIL-S-81733	- Sealing and Coating Compound, Corrosion Inhibitive.

STANDARDS

FEDERAL

FED-STD-595	- Colors.

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129	- Marking for Shipment and Storage.
MIL-STD-130	- Identification Marking of US Military Property.
MIL-STD-889	- Dissimilar Metals.
MIL-STD-1186	- Cushioning, Anchoring, Bracing, Blocking, and Waterproofing; with Appropriate Test Methods.

2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this specification to the extent specified herein.

DRAWING

ME

D13225E9182 - Flaking Box Assembly.

FOOD AND DRUG ADMINISTRATION (FDA)

Title 21, Code of Federal Regulations, Chapter 1, Part 177.

(The Code of Federal Regulations [CFR] and the Federal Register [FR] are for sale on a subscription basis by the Superintendent of Documents, US Government

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:52Z
Check the source to verify that this is the current version before use.

Printing Office, Washington, DC 20402. When indicated, reprints of certain regulations may be obtained from the Federal agency responsible for issuance thereof.)

(Copies of specifications, standards, and drawings required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

2.2 Other publications. The following document(s) form a part of this specification to the extent specified herein. The issues of the documents which are indicated as DoD adopted shall be the issue listed in the current DoDISS and the supplement thereto, if applicable.

AMERICAN PUBLIC HEALTH ASSOCIATION, INC. (APHA)

Standard Methods for the Examination of Water and Wastewater.

(Application for copies should be addressed to the American Public Health Association, Inc., 1015 18th Street, Washington, DC 20036.)

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

ASTM B 247 - Aluminum Alloy Die and Hand Forgings.
ASTM D 380 - Rubber Hose.
ASTM D 412 - Rubber Properties in Tension.
ASTM D 471 - Rubber Property-Effect of Liquids.
ASTM D 518 - Rubber Deterioration-Surface Cracking.
ASTM D 1149 - Rubber Deterioration-Surface Ozone Cracking in a Chamber (Flat Specimen).
ASTM D 3951 - Standard Practice for Commerical Packaging.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

SOCIETY OF AUTOMOTIVE ENGINEERS (SAE)

SAE J 1086 - Numbering Metals and Alloys.

(Application for copies should be addressed to the Society of Automotive Engineers, 400 Commonwealth Drive, Warrendale, PA 15096.)

(Industry association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:52Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 Description. The hose assembly shall consist of one 500-foot section of hose. Each hose shall be fitted with grooved end adaptors on each end, and a grooved end coupling on one end. This assembly shall be packed in a flaking box.

3.1.1 Drawing. The drawings forming a part of this specification are end product drawings. No deviation from the prescribed dimensions or tolerances is permissible without prior approval of the contracting officer. Where tolerances could cumulatively result in incorrect fits, the contractor shall provide tolerances within those prescribed on the drawings to insure correct fit, assembly, and operation of the flaking box. Any data (e.g., shop drawings, layouts, flow sheets, processing procedrues, etc.) prepared by the contractor or obtained from a vendor to support fabrication and manufacture of the production item shall be made available, upon request, for inspection by the contracting officer or his designated representative.

3.2 First article. When specified (see 6.2), a sample shall be subjected to first article inspection (see 4.3 and 6.3).

3.2.1 Sample selection plan. As part of the first article test, the contractor shall furnish a sample selection plan within the time specified (see 6.2). The plan shall assure all production hose assemblies are processed in the same manner and with production personnel as the first article hose assembly, using the same materials and methods as the first article hose assembly.

3.3 Process data. Within the time span specified (see 6.2), the contractor shall make available to the Government, on the site of manufacture, a description of materials and a documented inspection instruction which will be used by the contractor to assure that each production hose assembly is a duplicate of the first article hose assembly. Change of materials, procedures, or sources of supply from those initially selected shall be subject to the approval of the contracting officer (see 6.3 and 6.5).

3.4 Materials. Materials shall be as specified herein and on the drawings. Materials not specified shall be selected by the contractor and shall be subject to all provisions of this specification (see 6.5).

3.4.1 Material deterioration and control. The hose assembly shall be fabricated from compatible materials, inherently corrosion resistant or treated to provide protection against the various forms of corrosion and deterioration that may be encountered in any of the applicable storage and operating environment to which the item may be exposed.

3.4.1.1 Dissimilar metals. Dissimilar metals, as defined in MIL-STD-889, shall be electrically insulated from one another to minimize or prevent galvanic corrosion. Insulation may be provided by an insulating barrier such as a coat of epoxy primer conforming to MIL-P-23377, or corrosion inhibiting sealant con-

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:52Z
Check the source to verify that this is the current version before use.

forming to MIL-S-81733 or chromate tape conforming to MIL-G-20241. Protection against any galvanic corrosion could also be obtained by exclusion of the electrolyte if feasible.

3.4.1.2 Identification of materials and finishes. The contractor shall identify the specific material, material finish or treatment for use with components and sub-components, and shall make information available, upon request, to the contracting officer or designated representative.

3.4.2 Elastomer or rubber.

3.4.2.1 Tube. The basic material for the tube shall be a natural or a synthetic compound conforming to the Federal Food, Drug and Cosmetic Food Additives, title 21, Part 177.2600, Chapter I, Code of Federal Regulations. The compounds listed in sections 177.1020, 177.1030, 177.1040, 177.1050, and 177.1480 of the above document shall not be acceptable materials. Questions pertinent to this effect shall be referred by the procuring activity to the departmental medical services, who will act as an advisor to the procuring activity.

3.4.2.2 Cover. The cover shall be elastomeric or rubber compound for water, ozone, and oil resistance. The color shall be a visual match to FED-STD-595 color number 33303.

3.4.2.3 Reinforcement material. The reinforcing material shall consist of one or more plies of high-strength synthetic fabric, evenly and firmly fabricated, free from dirt, knots, lumps, irregularities of twist, or other defects.

3.4.3 Unified numbering system (UNS). Where applicable, metal alloys are identified by UNS in accordance with SAE J 1086.

3.5 Hose assembly. The hose assembly shall consist of one 500-foot hose section with grooved-end adapters on each end and a grooved end coupling on one end. Each assembly shall be packed in a flaking box as shown in figure 1. The hose assembly shall have no twist when flaked in the box. The ends shall be sealed to prevent foreign matter from entering to the hose.

3.5.1 Hose. The hose shall consist of an inner tube, one or more plies of reinforcement material, and a protective cover. All layers shall be bonded to their adjacent layers so as to produce a unified hose wall. The color of the exterior surface of the hose shall be a visual match to FED-STD-595, color chip 33303. The hose shall be marked in white letters, 1.0 inch tall at intervals no greater than 30 feet, "DRINKING WATER ONLY." The marking shall be in a straight line, so as to give the effect of a lay-line. Handling, bending, water, oil, or environmental effects shall not adversely affect the markings. Continuous branding shall be acceptable.

3.5.1.1 Dimensions and weight. The hose shall have an inside diameter of 6 inches +3/16 inch or -1/8 inch. Unless otherwise specified (see 6.2), the

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:52Z
Check the source to verify that this is the current version before use.

length of each hose section, including the two end couplings, shall be 500 feet ±5 feet. The weight of the hose shall not exceed 2.75 pounds per linear foot.

3.5.2 Hose to grooved adapter. Each end of each hose section shall be equipped with a one piece aluminum adapter with grooved end conforming to MIL-C-10387, figure 2. The aluminum shall conform to ASTM B 247, alloy UNS A96061, temper T6. Adapters shall be firmly affixed to the hose with not less than three clamps conforming to WW-C-440, type H, corrosion-resisting steel, 0.75 inch width. L290 Band-it clamps or continuous stainless steel banding shall be acceptable.

3.5.3 Grooved couplings. The grooved couplings shall conform to MIL-C-10387, class A, size 6 inch. Use of Victaulic coupling, style 77A or equal is acceptable.

3.5.4 Flaking box. The flaking boxes shall be in accordance with 13225E9182. Unless otherwise specified, the flaking boxes shall be cleaned, treated, and painted in accordance with MIL-T-704, type F or G, as applicable, with the topcoat color camouflage sand.

3.5.4.1 Proof load. The completed flaking box shall show no permanent deformation when subjected to load specified in 4.5.2.5.

3.5.5 Taste and odor. The hose shall not impart taste to a rating level higher than 4 or impart odor to an intensity greater than threshold odor No. 2 to chlorinated (drinking) water when tested in accordance with American Public Health Association Standard Methods for the Examinations of Water and Wastewater.

3.6 Physical properties.

3.6.1 Adhesion.

3.6.1.1 Original adhesion. The original adhesion between tube and plies, between the plies, and between the cover and the plies, shall be not less than 10 pounds.

3.6.1.2 Adhesion after immersion in water. After immersion in distilled water for 14 days at 158° F (70° C), ±3.6° F (±2° C), the adhesion between the tube and plies, between the plies, and between the cover and the plies shall be not less than 6 pounds.

3.6.1.3 Low temperature flexibility. When tested as specified in 4.5.2.4.5, there shall be no evidence of craking, lack of flexibility, or any other defects.

3.6.2 Tensile strength. The tensile strength of the tube shall be not less than 1,250 pounds per square inch (psi) and the tensile strength of the cover shall be not less than 1,500 psi. The tensile strenth of the tube and cover (after immersion), shall be not less than 80 percent or less than 1000 psi (whichever is greater) of the tensile strength obtained before immersion.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:52Z
Check the source to verify that this is the current version before use.

3.6.3 Ultimate elongation. The ultimate elongation of the tube and cover shall be not less than 300 percent, and the elongation after immersion shall be not less than 200 percent.

3.6.4 Ozone resistance. The hose cover shall withstand 50 parts of ozone per 100 million parts of air (pphm), maintained at +104° F (+40° C) for 168 hours without evidence of cracking when observed under 7-power magnification.

3.6.5 Oil resistance. The hose cover shall have a maximum volume swell of 80 percent after immersion in ASTM oil No. 3.

3.6.6 Hydrostatic pressure. The hose assembly shall withstand an internal hydrostatic pressure of not less than 225 psi without rupture or leak (see 6.4), either in the hose body or around the couplings and without any deformation of the couplings.

3.6.7 Elongation and twist. The hose section (500-foot), when subjected to an internal hydrostatic pressure of 150 psi shall not show elongation greater than one percent in length or twist, either right or left, by more than 1/2 turn per hose section when tested as specified in 4.5.2.2.

3.6.8 Burst pressure. The hose shall withstand a burst pressure of not less than 500 psi without rupture or failure (see 6.4.2).

3.7 Identification marking. The hose assembly shall be identified in accordance with MIL-STD-130. Each hose assembly shall have at approximately 50-foot intervals the following information:

Date of manufacture (quarter and year).
Contract or order number.
Manufacturer's name and trademark.

3.8 Metallic component finish. Unless otherwise specified herein, aluminum parts shall have a dyed, anodized coating conforming to MIL-A-8625, type II, class 2, color to approximate color No. 33303 of FED-STD-595. The anodic coating shall be not less than 0.0007 inch thick.

3.9 Workmanship. The hose assembly shall have no defects affecting appearance or serviceability. The hose shall be of uniform quality and shall be free from cracks, pitting, or other defects.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right

Source: https://assist.dla.mil -- Downloaded: 202640-22T21:52Z
Check the source to verify that this is the currentversion before use.

to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Component and material inspection. The contractor is responsible for insuring that components and materials used are manufactured, examined, and tested in accordance with referenced specifications, standards, and drawings, as applicable.

4.1.2 Disassembly inspection. Failure of any examination or test by the first article flaking box shall be cause for disassembly, in the presence of a Government representative, of the first article flaking box to the extent necessary to determine the cause of the failure. Each disassembled part shall be examined in detail for compliance with this specification and referenced drawing in regard to materials, dimensions, tolerances, and workmanship. Parts not complying with such requirements shall be rejected and shall be cause for rejection of the first article flaking box. Reassembly with replacement parts and retesting shall be the responsibility of the contractor.

4.2 Classification of inspection. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3).
b. Quality conformance inspection (see 4.4).
c. Inspection of packaging (see 4.6).

4.3 First article inspection.

4.3.1 Examination. The first article hose assembly shall be examined as specified in 4.5.1. Presence of one or more defects shall be cause for rejection or for performing the flaking box disassembly inspection specified in 4.1.2 if the defects are found in the flaking box.

4.3.2 Tests. The first article hose assembly shall be subjected to the tests marked "X" in column 1 of table I. Samples for adhesion tests shall be cut from a length of hose. Samples of the synthetic rubber compound shall be representative of materials used to fabricate the hose assembly. Failure of any test shall be cause for rejection of the hose assembly or for performing the flaking box disassembly inspection specified in 4.1.2 if the defects are found in the flaking box.

4.4 Quality conformance inspection.

4.4.1 Sampling.

4.4.1.1 Examination. Sampling of hose assemblies for examination shall be in accordance with MIL-STD-105.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:52Z
Check the source to verify that this is the current version before use.

4.4.1.2 Tests.

4.4.1.2.1 Elastomeric or rubber compound. Four test slabs, each 6 inches by 6 inches by .075 inch, ±.010 inch thick, of each elastomeric and natural rubber compound and of equivalent cure used to fabricate the hose assemblies, shall be supplied with each lot.

4.4.1.2.2 Hose. Sampling of hose for tests shall be in accordance with MIL-STD-105. Test sections shall be cut from the hose and shall be sufficient length for the performance of the required tests.

4.4.1.2.3 Flaking boxes. Sampling of flaking boxes for tests shall be in accordance with MIL-STD-105, inspection level S-2. AQL shall be 4.0 percent defective.

4.4.2 Examination. Sample hose assemblies selected in accordance with 4.4.1.1 shall be examined as specified in 4.5.1. AQL shall be 2.5 percent defective.

4.4.3 Tests.

4.4.3.1 Individual. Each hose assembly shall be subjected to the test marked "X" in column 2 of table I. Failure of the tests shall be cause for rejection.

4.4.3.2 Samples. Samples selected in accordance with 4.4.1.2.1, 4.4.1.2.2, and 4.4.1.2.3 shall be subjected to the tests marked "X" in column 3 of table I. Failure of any test shall be cause for rejection of the hose assemblies represented by the samples.

4.5 Inspection procedure.

4.5.1 Examination. The hose assembly shall be examined as specified herein for the following defects:

101. Components missing.
102. Material not as specified.
103. Materials are not corrosion resistant or treated to be made corrosion resistant for the applicable storage and operating environment.
104. Dissimilar metals as defined in MIL-STD-889 are not effectively insulated from each other.
105. Contractor does not have documentation available for identification of material; material finishes or treatments.
106. Hose twisted when flaked in boxes.
107. Hose not as specified.
108. Dimensions and weight not as specified.
109. Hose to grooved adapter not as specified.
110. Bands not as specified.
111. Grooved couplings not as specified.
112. Flaking boxes not as specified.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:52Z
Check the source to verify that this is the current version before use.

113. Marking missing, incomplete, or illegible.
114. Finish not as specified.
115. Workmanship not as specified.
116. Identification of metal alloys not as specified.
117. Ends of nose not sealed.

4.5.2 Tests.

4.5.2.1 Test schedule.

TABLE I. Test schedule.

First article	Quality conformance: Individual	Quality conformance: Sample	Test	Test paragraph	Requirement paragraph
1	2	3	4	5	6
			Hose assembly		
X	X	-	Hydrostatic pressure.	4.5.2.2.1	3.6.6
X	X	X1/	Elongation and twist.	4.5.2.2.2	3.6.7
			Elastomeric or rubber compounds		
X	-	X	Initial tensile strength.	4.5.2.3	3.6.2
X	-	X	Tensile strength after immersion.	4.5.2.3	3.6.2
X	-	X	Ultimate elongation, initial.	4.5.2.3	3.6.3
X	-	X	Ultimate elongation after immersion.	4.5.2.3	3.6.3
X	-	X	Ozone resistance.	4.5.2.3	3.6.4
X	-	X	Oil resistance.	4.5.2.3	3.6.5
X	-	-	Taste and odor.	4.5.2.3.1	3.5.5
			Hose		
X	-	X	Burst pressure.	4.5.2.4.1	3.6.8
X	-	X	Weight.	4.5.2.4.2	3.5.1.1
X	-	X	Original adhesion.	4.5.2.4.3	3.6.1.1
X	-	X	Adhesion after immersion in water.	4.5.2.4.4	3.6.1.2
X	-	X1/	Low temperature flexibility.	4.5.2.4.5	3.6.1.3
			Flaking boxes		
X	-	X	Proof Load.	4.5.2.5	3.5.4.1

1/ One lot testing required for each ten lots submitted.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:52Z
Check the source to verify that this is the current version before use.

4.5.2.2 Hose assembly.

4.5.2.2.1 Hydrostatic pressure. Each hose section shall be subjected to the hydrostatic tests, using water as a test fluid, of ASTM D 380 for proof pressure. Nonconformance to 3.6.5 shall constitute failure of this test. The hydrostatic test shall be performed with drinking (potable) water. After testing, the hose shall be dried and the ends shall be sealed.

4.5.2.2.2 Elongation and twist. Elongation and twist measurement shall be on a hose length not less than 500 feet, laid out straight. One end of the hose shall be fixed and not allowed to turn. Twist shall be measured at the free end and recorded as clockwise or counterclockwise. Pressurize the hose section, using drinking (potable) water as a test fluid, to 10 psi and hold for not more than two minutes and mark the length and twist position. After two minutes increase the pressure to 150 psi and mark the length and twist position. Nonconformance to 3.6.6 shall constitute failure of this test.

4.5.2.3 Elastomeric or rubber compounds. Elastomeric or rubber compound samples shall be tested as follows:

Property	Test method
Initial tensile strength	ASTM D 412
Tensile strength after immersion	ASTM D 471 2/
Ozone resistance	ASTM D 1149 1/
Volume swell	ASTM D 471 3/
Initial ultimate elongation	ASTM D 412
Ultimate elongation after immersion	ASTM D 471 2/

1/ Specimens mounted in accordance with procedure B, ASTM D 518, ozone concentration shall be 50 ±10 parts per 100,000,000 (pphm). Time exposure shall be 168 hours, temperature of exposure shall be 104° F (40° C).
2/ The samples shall be immersed in distilled water for 14 days at 158° F (70° C), ±3.6° F (2° C).
3/ Hose cover samples shall be exposed in ASTM oil No. 3 for 70 hours at 100° C (212° F).

Nonconformance to 3.6.2, 3.6.3, or 3.6.4 shall constitute failure of these tests.

4.5.2.3.1 Taste and odor. Taste and odor test shall be performed in accordance with procedures outlined in American Public Health Association, Standard Methods for Examination of Water and Wastewater. A sample of the hose shall be filled with distilled water having a 0.2 parts per million of total available chlorine at the start of the 70-hour test. The samples shall be long enough to expose 36 square centimeters of inner tube to one liter of chlorinated distilled water. Nonconformance to 3.5.5 shall constitute failure of this test.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:52Z
Check the source to verify that this is the current version before use.

4.5.2.4 Hose.

4.5.2.4.1 Burst pressure. The test section of hose selected under 4.4.1.2.2 shall be subjected to the straight bursting test of ASTM D 380. Nonconformance to 3.6.7 shall constitute failure of this test.

4.5.2.4.2 Weight. A section 12 inches long shall be cut from the test section of hose selected under 4.4.1.2.2 and weighed. Nonconformance to 3.5.1.1 shall constitute failure of this test.

4.5.2.4.3 Original adhesion. From the test section of hose selected under 4.4.1.2.2, prepare ring specimens as described in ASTM D 380. The adhesion of the ring specimen shall be determined in accordance with ASTM D 380, machine method. Nonconformance to 3.6.1.1 shall constitute failure of this test.

4.5.2.4.4 Adhesion after immersion in water. Specimens prepared as described in 4.5.2.4.3 shall be immersed as described in 3.6.1.2. Within 5 minutes after removal from immersion, the adhesion shall be determined as described in 4.5.2.4.3. Nonconformance to 3.6.1.2 shall constitute failure of this test.

4.5.2.4.5 Low temperature flexibility. A sample 8-foot length of hose shall be folded 180 degrees and tied in the folded position. The hose shall then be conditioned for 72 hours at -25° F (-31.7° C). The hose shall be removed from the test chamber and unfolded 180 degrees using a force of not more than 10 pounds within 5 seconds. The unfolding shall be accomplished within 3 minutes after removal from the test chamber. The hose sample shall then be hydrostatic pressure tested at 225 psig in accordance with ASTM D 380. Hose fabricated with splices shall have two hose test samples, one hose sample folded without a splice, and the other sample folded at the splice. Nonconformance of any test sample to 3.6.1.3 shall constitute failure of this test.

4.5.2.5 Proof load. Distribute equally a minimum 4,800 pound load in four flaking boxes. The boxes shall be filled and stacked one on top of the other. Attach a lifting sling to the bottom flaking box and lift boxes to a height of not less than 1 foot. After the lifted boxes come to a complete rest, hold load for not less than 5 minutes. Lower flaking boxes to the ground and inspect all welding and riveting on flaking boxes and lifting brackets. Nonconformance to 3.5.4.1 shall constitute failure of this test.

4.6 Inspection of packaging.

4.6.1 Quality conformance inspection of pack.

4.6.1.1 Unit of product. For the purpose of inspection, a completed pack prepared for shipment shall be considered a unit of product.

4.6.1.2 Sampling. Sampling for examination shall be in accordance with MIL-STD-105.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:52Z
Check the source to verify that this is the currentversion before use.

4.6.1.3 Examination. Samples selected for examination in accordance with 4.6.1.2 shall be examined for applicable defects listed in table II. The acceptable quality level (AQL) shall be 2.5 percent defective.

TABLE II. Examinaton.

No.	Defect	A	B	Comm
117.	More than four flaking boxes packed per crate.	5.1.1	5.1.2	
118.	Exterior containers not as specified.	5.1.1	5.1.2	5.1.3
119.	Contents not shrouded as specified.		5.1.2	
120.	Blocking, bracing, anchoring, closure, and strapping not as specified.	5.1.1	5.1.2	
121.	Hold down devices not as specified (if required).	5.1.1	5.1.2	
122.	Marking not as specified.	5.2.1	5.2.1	5.2.2

5. PACKAGING

5.1 Packing. Packing shall be level A, level B, or commercial, as specified (see 6.2).

5.1.1 Level A. The flaking boxes, with the hose assemblies positioned inside in the manner specified in 3.5 (see figure 1), shall be packed in quantities of four boxes in a crate conforming to MIL-C-104, type I, class 1 or 2, style A. Blocking, bracing and anchoring of the boxes within the crate shall be in accordance with the appendix to the specification. Additionally, hold down devices of adequate design and quantity shall be utilized as required, to reduce to a minimum, the vertical movement of the hose assembly within the flaking box. Non-abrasive cushioning material shall be used between the hold down devices and the hose assemblies, as required, to prevent damage to the hose. Hold down device shall be secured in position.

5.1.2 Level B. The flaking boxes, with the hose assemblies positioned inside in the manner specified in 3.5 (see figure 1), shall be packed, in quantities of four boxes in a crate conforming to MIL-C-3774, type I, style A. The contents shall be protected with a waterproofed shroud and its application shall be in accordance with MIL-STD-1186. The crate closure and strapping shall be in accordance with the appendix to the crate specification. Additionally, the application of the hold down devices specified in 5.1.1 shall be utilized, as required, to immobilize and protect the hose assemblies.

5.1.3 Commercial. The flaking boxes, with the hose assemblies positioned inside in the manner specified in 3.5 (see figure 1), shall be packed in accordance with ASTM D 3951.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:52Z
Check the source to verify that this is the current version before use.

5.2 Marking.

5.2.1 Levels A and B. In addition to any special or other identification marking required by the contract (see 6.2), each crate shall be marked in accordance with MIL-STD-129.

5.2.2 Commercial. Commercial marking shall be in accordance with the requirements of ASTM D 3951. Additionally, each shippng container shall be marked with the cube and gross weight.

6. NOTES

6.1 Intended use. The hose assembly is intended for use with light-weight, collapsible-hose pipelines in drinking (potable) water systems.

6.2 Ordering data. Acquisition documents should specify the following:

a. Title, number, and date of this specification.
b. When a first article is required for inspection and approval and the number of units required (see 3.2).
c. Time frame required for submission of sample selection plan and process data (see 3.2.1 and 3.3).
d. Length of hose if other than 500 feet (3.5.1.1).
e. Degree of packing required (see 5.1).
f. Any special marking instructions (see 5.2.1).

6.3 First article. When a first article inspection is required, the item will be tested and should be an initial production model. The first article should consist of one or more units. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examination, test, and approval of the first article.

6.4 Definitions.

6.4.1 Leak. A leak is defined as any passage of fluid from the inner portion of the hose assembly to the outer portion of the hose assembly as determined by sight or touch. A leak shall include but is not limited to fluid passing through a hose assembly fitting, fluid passing through the hose body, or fluid passing through the junction of the hose and an attached fitting.

6.4.2 Rupture. A rupture in the hose assembly is defined as a split or crack in the hose, or any split or crack at the junction of hose and a fitting.

6.5 Recycled material. It is encouraged that recycled material be used, when practical, as long as it meets the requirements of this specification (see 3.4).

Custodian:
Army - ME

Preparing activity:
Army - ME

Project 4720-A687

Source: https://assist.dla.mil -- Downloaded: 202640-22T21:52Z
Check the source to verify that this is the currenversion before use.

X-4092A

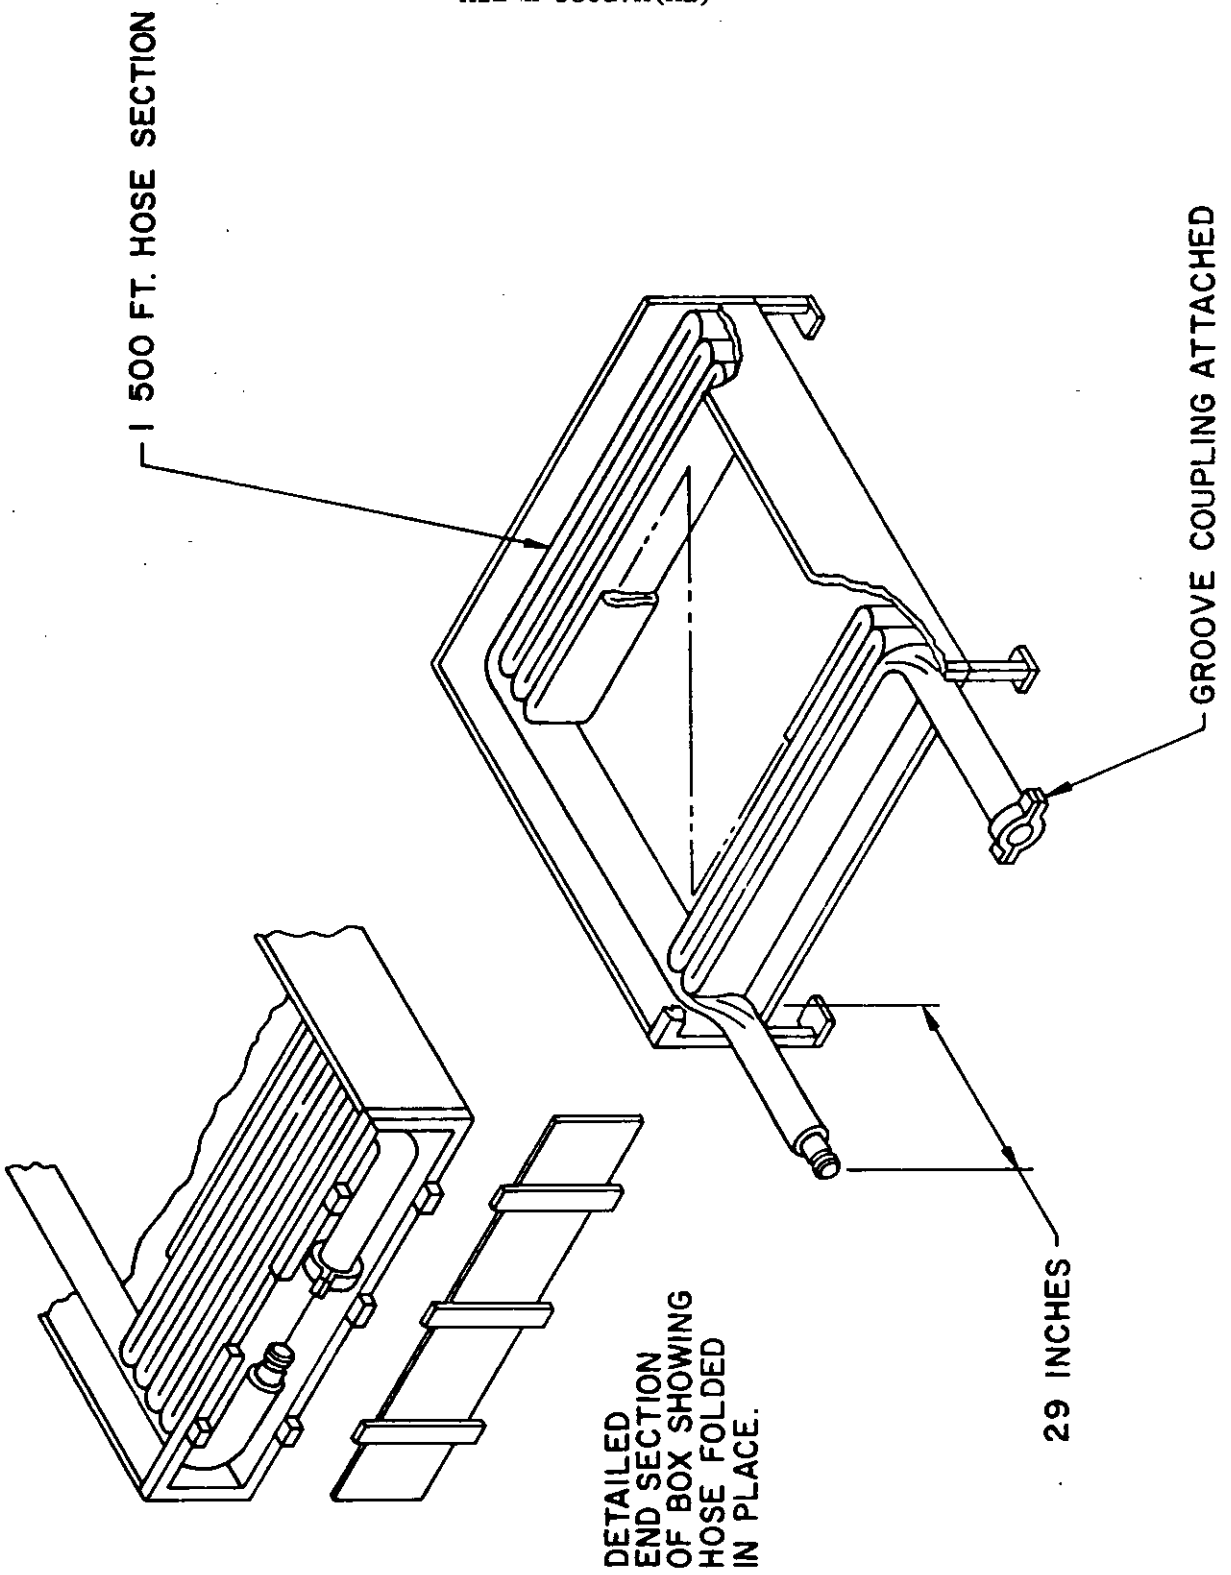


FIGURE 1. Method of packing hose in flaking boxes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:52Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
Belvoir R & D Center
ATTN: STRBE-DS
Fort Belvoir, VA 22060-5606

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:52Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-H-53027A(ME)	Hose Assembly, Rubber: Lightweight Collapsible, 6-Inch; for Drinking (Portable) Water

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR ☐ USER ☐ MANUFACTURER ☐ OTHER *(Specify)*: _____
b. ADDRESS *(Street, City, State, ZIP Code)*	

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

(TO DETACH THIS FORM, CUT ALONG THIS LINE.)

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:52Z
Check the source to verify that this is the current version before use.