
FED. SUP CLASS
6145

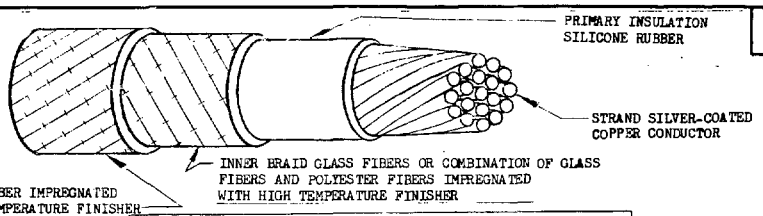

PHYSICAL PROPERTIES OF PRIMARY INSULATION	
CHARACTERISTIC	REQUIREMENT
TENSILE STRENGTH (MIN)	BEFORE AGING 800 PSI
	AFTER AGING 600 PSI
ELONGATION (MIN)	BEFORE AND AFTER AGING
	1-1/2 INCHES (2-INCH
	SPECIMEN STRETCHED TO
	3-1/2 INCHES)

PERFORMANCE DETAILS

WIRE SIZE	ABRASION TESTS: RESISTANCE INCHES OF TAPE	ABRASION TESTS: TENSION LOAD (LBS)	ABRASION TESTS: WEIGHT SUPPORT BRACKET	ABRASION TESTS: WEIGHT (LBS)	FLAW TESTS: MIN AC VOLTAGE 60 CYCLE RMS: PRIMARY INSULATION	FLAW TESTS: MIN AC VOLTAGE 60 CYCLE RMS: FINISHED WIRE	INSULATION AND SURFACE RESISTANCE: HUMIDITY RESISTANCE MEGOHMS PER 200 FT (MIN)	INSULATION AND SURFACE RESISTANCE: INSULATION RESISTANCE MEGOHMS PER 50 FT (MIN)	INSULATION AND SURFACE RESISTANCE: SURFACE RESISTANCE MEGOHMS INCHES (MIN)	LIFE CYCLE AND COLD BEND: MANDREL DIA INCHES (MAX): LIFE CYCLE	LIFE CYCLE AND COLD BEND: MANDREL DIA INCHES (MAX): COLD BEND	LIFE CYCLE AND COLD BEND: TEST LOAD LIFE CYCLE COLD BEND (LBS)
22	22	1	A	1	2,000	5,000	500	100	5.0	4.5	3	.75
20	22	1	A	1	2,000	5,000	500	100	5.0	4.5	3	.75
18	22	1	A	1	2,000	5,000	500	100	5.0	4.5	3	1.0
16	30	2	A	1	2,000	5,000	500	100	5.0	6.5	3	1.0
14	13	2	B	3	2,000	5,000	500	100	5.0	6.5	6	1.0
12	17	2	B	3	2,000	5,000	500	100	5.0	6.5	6	3.0
10	20	2	B	3	3,000	5,000				10	6	3.0
8	25	2	B	3	3,000	5,000				10	6	3.0
6	25	2	C	3	4,000	5,000				10	10	6.0
4	33	2	C	4.25	4,000	5,000				10	10	6.0
2	34	2	C	4.25	4,000	5,000				10	10	6.0
1	35	2	C	4.25	4,000	5,000				10	18	6.0
0	48	2	C	4.25	4,000	5,000				10	18	10.0
00	48	2	C	4.25	4,000	5,000				10	18	10.0

DASH NO	WIRE SIZE	FINISHED WIRE CONSTRUCTION: NUMBER OF STRANDS	FINISHED WIRE CONSTRUCTION: MAX DIA OF STRANDED CONDUCTOR	FINISHED WIRE CONSTRUCTION: MAX RESISTANCE AT 20°C (68°F) OHMS/1000 FT	DIAMETER		MAX WEIGHT LBS/1000 FT
-22	22	19	.033	15.2	.085	±.005	5.8
-20	20	19	.041	9.42	.095	±.005	7.8
-18	18	19	.052	6.03	.110	±.005	10.8
-16	16	19	.060	4.76	.125	±.005	13.5
-14	14	19	.074	2.99	.143	±.007	20.0
-12	12	19	.093	1.88	.163	±.007	29.0
-10	10	49	.128	1.16	.193	±.007	45.0
-8	8	133	.176	.70	.248	±.007	72.0
-6	6	133	.218	.436	.303	±.007	107.0
-4	4	133	.272	.274	.360	±.010	165.0
-2	2	665	.345	.179	.425	±.010	262.0
-1	1	817	.384	.144	.460	±.010	317.0
-01	0	1,045	.432	.114	.535	±.015	390.0
-02	00	1,330	.490	.090	.585	±.015	500.0

(C) REQUIREMENT: DURING AND FOLLOWING THE THERMAL SHOCK OR FLASH TEST, THE PRIMARY INSULATION SHALL NOT SHRINK GREATER THAN .060 FOR ALL SIZES.

(C) INTERNATIONAL INTEREST: CERTAIN PROVISIONS OF THIS STANDARD ARE THE SUBJECT OF INTERNATIONAL STANDARDIZATION AGREEMENT (ASCC AIR STD 12/5) (NATO STANAG 3317). WHEN REVISION OR CANCELLATION OF THIS STANDARD IS PROPOSED, THE DEPARTMENTAL CUSTODIAN WILL INFORM THEIR RESPECTIVE DEPARTMENTAL STANDARDIZATION OFFICE SO THAT APPROPRIATE ACTION MAY BE TAKEN RESPECTING THE INTERNATIONAL AGREEMENT CONCERNED.

DIMENSION IN INCHES.

FOR DESIGN FEATURE PURPOSES, THIS STANDARD TAKES PRECEDENCE OVER PROCUREMENT DOCUMENTS REFERENCED HEREIN. REFERENCED DOCUMENTS SHALL BE OF THE ISSUE IN EFFECT ON DATE OF INVITATIONS FOR BID.

User activities:

Review activities:
Army-AV
Navy-AS
USAF-11

APPROVED 1 Aug 60 REVISED (A) 4 Nov 63 (B) 7 Mar 66 (C) 6 Jan 69

This military standard is approved by the Department of Defense and is mandatory on all activities. Selection for all new engineering and design applications and for repetitive use shall be made from this document.

P.A. USAF-11	INTERNATIONAL INTEREST	TITLE	MILITARY STANDARD
Other Cust ARMY -EL NAVY -AS	SEE NOTE	WIRE, ELECTRICAL - SILICONE - INSULATED, COPPER, 600 VOLT, 200° C, POLYESTER JACKET	MS25471
PROCUREMENT SPECIFICATION MIL-W-8777		SUPERSEDES:	SHEET 1 OF 1

DD FORM 1 SEP 67 672-1 (Coordinated) PREVIOUS EDITIONS OF THIS FORM ARE OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T15:11Z
Check the source to verify that this is the current version before use.