INCH-POUND
MIL-C-24640/23B
31 July 1989
SUPERSEDING
MIL-C-0024640/23A(SH)
23 October 1985
USED IN LIEU OF
MIL-C-24640/23
10 August 1984

MILITARY SPECIFICATION SHEET

CABLE, ELECTRICAL, 600 VOLTS, LIGHTWEIGHT, MULTI-CONDUCTOR, AWG 18, TYPE MXCW (INCLUDING VARIATION TYPES MXCOW AND MXCWA)


This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and the issue of the following specification listed in that issue of the Department of Defense Index of Specifications and Standards (DoDISS) specified in the solicitation: MIL-C-24640.

AMSC N/A FSC 6145

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 202640-19T23:47Z
Check the source to verify that this is the current version before use.

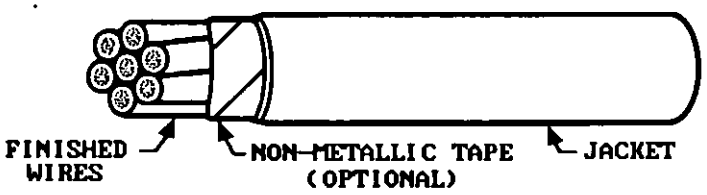

SH 12770

FINISHED WIRES:

(B) First - Copper conductor, uncoated, AWG 18, 7 stranding in accordance with ASTM B 8. Nominal diameter of stranded conductor .049 inch.

Second - Coat wire with free-stripping waterblocking compound.

(B) Third - MICA-glass tape, insulation 0.0029 ± 0.0002 inch (50 percent overlap maximum and minimum overlap of 45 percent).

Fourth - Opaque pigmented polyimide tape 0.001 inch (50 percent overlap minimum).

Fifth - Opaque pigmented polyimide tape 0.001 inch with 0.0001 inch fluorinated ethylene propylene (FEP) both sides (50 percent overlap minimum).

(B) Sixth - Modified aromatic polyimide resin coating 0.0005 inch minimum (0.001 inch nominal). Finished wire diameter 0.066 inch minimum and 0.070 inch maximum.

FIGURE 1. Construction (watertight with circuit integrity).

(B) denotes changes.

(B) TABLE I. Construction details-unarmored.

PIN M24640/23	Type number	Number of conductors	Jacket thickness (inch) (minimum)	Cable diameter (inch)		Cable weight (pounds per 1000 feet) (max)
				(min)	(max)	
-01UN	MXCW-7	7	0.038	0.295	0.319	87.0
-02UN	MXCW-10	10	.041	.375	.405	136.0
-03UN	MXCW-14	14	.041	.402	.434	166.0
-04UN	MXCW-19	19	.041	.440	.474	208.0
-05UN	MXCW-24	24	.044	.520	.560	281.0
-06UN	MXCW-30	30	.044	.547	.589	325.0
-07UN	MXCW-37	37	.044	.584	.630	384.0
-08UN	MXCW-44	44	.044	.656	.708	472.0
-09UN	MXCW-61	61	.047	.729	.785	612.0

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:47Z
Check the source to verify that this is the current version before use.

(B) TABLE II. Construction details-armored.

PIN M24640/23	Type number	Number of conductors	Jacket thickness (inch) (minimum)	Cable diameter (inch) (min)	Cable diameter (inch) (max)	Cable weight (pounds per 1000 feet) (max)
-01AN	MXCWA-7	7	0.038	0.345	0.369	110.0
-02AN	MXCWA-10	10	.041	.425	.455	177.2
-03AN	MXCWA-14	14	.041	.452	.485	215.8
-04AN	MXCWA-19	19	.041	.490	.524	264.4
-05AN	MXCWA-24	24	.044	.570	.610	337.0
-06AN	MXCWA-30	30	.044	.597	.639	385.3
-07AN	MXCWA-37	37	.044	.634	.680	452.9
-08AN	MXCWA-44	44	.044	.706	.758	547.7
-09AN	MXCWA-61	61	.047	.779	.835	564.0

(B) TABLE III. Construction details-overall shield.

PIN M24640/23	Type number	Number of pairs	Diameter over shield (inch) (nom)	Jacket thickness (inch) (minimum)	Cable diameter (inch) (min)	Cable diameter (inch) (max)	Cable weight (pounds per 1000 feet) (max)
-01U0	MXCOW- 7	7	0.226	0.038	0.340	0.366	134.0
-02U0	MXCOW-10	10	.297	.041	.415	.447	184.0
-03U0	MXCOW-14	14	.325	.041	.440	.474	219.0
-04U0	MXCOW-19	19	.370	.041	.477	.515	267.0
-05U0	MXCOW-24	24	.441	.044	.557	.601	350.0
-06U0	MXCOW-30	30	.469	.044	.584	.630	399.0
-07U0	MXCOW-37	37	.514	.044	.622	.670	466.0
-08U0	MXCOW-44	44	.585	.047	.697	.751	553.0
-09U0	MXCOW-61	61	.652	.047	.757	.817	694.0

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:47Z
Check the source to verify that this is the current version before use.

REQUIREMENTS:

Qualification required.
Construction details: See tables I, II and III.

Finished wire:

For polyimide tape constructions, the following additional tests shall be applicable in accordance with MIL-W-81381:

Temperature rating: 150°C (302°F) maximum conductor temperature.
Voltage rating: 600 volts root mean square (rms) at sea level.
Blocking: Oven temperature, 200 ± 2°C (392 ± 3.6°F); no sticking of conductors.
Color: White.
Flammability: 3 seconds (maximum) after-flame.
3.0 inches (maximum) flame travel.
No flaming of tissue paper.
Humidity resistance: 5 megohms-1,000 feet, minimum insulation resistance after humidity exposure.
(B) Identification of product: Standard identification code method 1.
Impulse dielectric test: 100 percent test; impulse voltage at 8 kV.
Insulation resistance: 2,500 megohms-1,000 feet (minimum).
Polyimide cure test: No cracking.
Shrinkage: 0.062 inch (maximum) at 180°C.
Surface resistance: 5 megohms-inches (minimum), initial and final readings.
Thermal shock: Oven temperature, 150 ± 2°C (302 ± 3.6°F). Change in measurement, 0.031 inch (maximum).
Wet dielectric test: 2,500 volts rms.

When this cable is manufactured with armor, the following additional requirements shall apply:

(B) (a) Braided metal armor shall be added.
(b) Cable surface marking will not be required.

When this cable is manufactured with an overall shield, the following additional requirements shall apply:

(a) An overall tin-coated copper braid shall be added.
(B) (b) Braid coverage shall be not less than 90 percent determined in accordance with MIL-C-27500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:47Z
Check the source to verify that this is the current version before use.

EXAMINATION AND TESTS:

	Requirements
Basic electrical:	
Conductor resistance - ohms/1000 feet, at 25°C, maximum (B)	7.07
Voltage withstand - volts, root mean square, minimum (B)	
Conductor to conductor	2000
Conductor to shield	1000
Shield to shield	Not applicable
Insulation resistance - megohms/1000 feet, minimum	2500
Conductor and shield continuity (type MXCOW only)	No failure
Jacket flaws (type MXCOW only)	No failure
Group A:	
Visual and dimensional	No failure
Capacitance:	
Mutual capacitance - at 1 MHz, picofarads/foot (pF/ft), maximum	Not applicable
Capacitance unbalance - percent, maximum	Not applicable
Characteristic impedance - at 1 MHz, ohms	Not applicable
Watertightness (see table XI of MIL-C-24640 for limits of water leakage)	No failure
Weight	No failure
Group B:	
Cold bending	No failure
Drip	Zero
Tear - pounds per inch thickness, minimum	35
Physicals (unaged)	
Jacket	
Tensile strength - lb/in², minimum	1300
Elongation - percent, minimum	160
Attenuation - at 3 MHz, dB/100 feet, maximum	Not applicable
Gas flame (1 hour)	No failure
Group C:	
Physicals (aged)	
Jacket	
Air oven	
Tensile strength - percent of unaged, minimum	60
Elongation - percent of unaged, minimum	60
Hot oil immersion	
Tensile strength - lb/in², minimum	50
Elongation - percent, minimum	50
Permanence of printing (conductor) - cycles, minimum	50
Permanence of printing (jacket) - cycles, minimum	250

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:47Z
Check the source to verify that this is the current version before use.

EXAMINATION AND TESTS: - Continued

	Requirements
Armor (type MXCWA only) - conformance to material, construction and coverage	No failure
Shield (type MXCOW only) - conformance to material, construction and coverage	No failure
Heat distortion - percent unaged, maximum	30
Cable filler removability	No failure
Shrinkage	No failure
Mutual inductance - dB/1000 feet, maximum	Not applicable
Surface transfer impedance (type MXCOW only)	
Milliohms per meter, maximum	700
EMP response, dB, minimum	60
Pulse response time - ms/500 feet	
Rise time, maximum	Not applicable
Decay time, maximum	Not applicable

QUALIFICATION INSPECTION:

Qualification inspection shall include basic electrical, all of groups A, B, and C, plus the following:

Aging and compatibility (cable)	No failure
Acid gas equivalent - percent, maximum	
Jacket	2
Fillers	2
Insulation	18
Halogen content - percent, maximum	
Jacket	0.2
Fillers	0.2
Flame propagation	No failure
Immersion	
Tensile strength - percent of unaged, minimum	50
Elongation - percent of unaged, minimum	50
Smoke index, maximum	
Jacket	25
Fillers	--
Insulation	10
Toxicity index, maximum	
Jacket	5
Fillers	5
Insulation	1.5
Durometer - (type A) hardness, minimum	80
Weathering	No failure
Fungus resistance	No failure
Abrasion resistance	No failure
Gas flame (3 hour)	No failure
Finished wire	No failure

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:47Z
Check the source to verify that this is the current version before use.

Preparing activity:
Navy - SH
(Project 6145-1004-23)

Custodians:
Army - MI
Navy - SH

Review activities:
Navy - EC
DLA - IS

User activities:
Army - ME, AR
Navy - CG

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:47Z
Check the source to verify that this is the current version before use.