MIL-F-10135B
2 MARCH 1955
SUPERSEDING
MIL-F-10135A(Cml C)
5 APRIL 1954

MILITARY SPECIFICATION

FACEBLANKS, FIELD PROTECTIVE MASK, NATURAL RUBBER; GENERAL SPECIFICATION

This specification has been approved by the Department of Defense for use of the Departments of the Army, the Navy, and the Air Force.

1. SCOPE

1.1 Scope.—This specification covers field protective mask faceblanks molded from an 85-percent natural rubber compound.

1.2 Classification. — Faceblanks shall be furnished in the type, size, and color specified in the invitation for bids (see 6.2).

2. APPLICABLE DOCUMENTS

2.1 The following specifications, and standards, of the issue in effect on date of invitation for bids, form a part of this specification:

SPECIFICATIONS

FEDERAL

ZZ-R-601 —Rubber Goods; General Specifications (Methods of Physical Tests and Chemical Analyses).
LLL-B-631 —Boxes; Fiber Corrugated (For Domestic Shipment).
PPP-B-601 —Boxes, Wood, Cleated-Plywood.

MILITARY

JAN-P-103 —Packaging and Packing for Overseas Shipment—Boxes; Wood Cleated; Solid Fiberboard.
JAN-P-106 —Packaging and Packing for Overseas Shipment—Boxes; Wood, Nailed.
MIL-P-116 —Preservation, Methods of.
JAN-P-138 —Packaging and Packing for Overseas Shipment—Boxes, Wood, Fiberboard-Lined.

STANDARDS

MILITARY

MIL-STD-105 —Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 —Marking for Shipment and Storage.

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. — The following document forms a part of this specification. Unless otherwise indicated, the issue in effect on date of invitation for bids shall apply.

AMERICAN SOCIETY FOR TESTING MATERIALS.

D624—Methods of Test for Tear Resistance of Vulcanized Rubber.

(Copies of A.S.T.M. publications may be obtained from the American Society for Testing Materials, 1916 Race Street, Philadelphia 3, Pa.)

Source: https://assist.dla.mil -- Downloaded: 202640-17T13:36Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 Material.

3.1.1 *Rubber compound.* — The rubber compound shall be nonblooming and shall contain not less than 85 percent, by volume, of new natural rubber. A slight wax-type bloom shall not be considered a violation of the nonblooming requirement of this specification.

3.1.2 *Antioxidants and accelerators.* — Only approved antioxidants and accelerators shall be used in the rubber compound (see 6.3 and 6.4).

3.1.3 *Sun checking retardant.*—The rubber compound shall contain a sun checking retardant.

3.1.4 *Copper and manganese inhibitor.*— The rubber compound shall contain a copper and a manganese inhibitor.

3.1.5 *Coloring materials.* — The rubber compound shall be colored by mineral pigments and carbon black.

3.2 Manufacture. — Faceblanks shall be manufactured by the conventional process of molding under heat and pressure. Each type and size faceblank specified in the contract or order shall be manufactured in accordance with the applicable drawings listed in the contract or order.

3.3 Imperfections.—The inner and outer surfaces of the faceblank shall be free from porous areas, cracks, checks, flash, abrasions, or blisters. The rubber shall be compact and free from bubbles and foreign matter. Ridges of mold parting lines on outer surfaces, when closely trimmed, shall not be considered as flash.

3.3.1 *Restoration of flaws.* — Faceblanks with small flaws in noncritical areas may be repaired and accepted, provided the color of the repaired areas shows no contrast to the color of the faceblank when tested as specified in 4.4.4. and there is no change in material or surface continuity (see 6.5).

3.4 Physical properties.

3.4.1 *Unaged.*

3.4.1.1 *Tensile strength.* — The average tensile strength shall be not less than 2,600 p.s.i.

3.4.1.2 *Ultimate elongation.*—The average ultimate elongation shall be not less than 650 percent.

3.4.1.3 *Tensile stress.*—The average tensile stress shall not exceed 400 p.s.i. nor be less than 200 p.s.i. at 200-percent elongation. No individual test specimen shall be less than 190 p.s.i.

3.4.1.4 *Tear resistance.*—The average tear resistance shall be not less than 165 pounds per inch.

3.4.1.5 *Permanent set.*—The average permanent set shall not exceed 10 percent when specimens are stretched 600 percent, held for 10 minutes, released, and rested for 10 minutes.

3.4.1.6 *Hardness.*—The average hardness shall be 45 $\pm$ 5 as measured by a Shore "A" durometer.

3.4.2 *Aged (oven process).*

3.4.2.1 *Tensile strength and ultimate elongation.*—After aging, the average tensile strength shall increase not more than 20 percent or decrease no more than 15 percent and the average ultimate elongation shall increase no more than 20 percent or decrease no more than 25 percent.

3.4.2.2 *Tensile stress.*—After aging, the average tensile stress shall be less than 400 p.s.i. and greater than 200 p.s.i. at 200-percent elongation.

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:36Z
Check the source to verify that this is the current version before use.

3.4.2.3 *Tear resistance.*—After aging, the average tear resistance shall decrease no more than 30 percent.

3.5 **Toxicity.** — The faceblank material shall be nontoxic to the skin when applied locally (see 4.4.3). The contractor shall make no major change (see 6.10) in rubber formulation or the curing process after receiving approval of a formulation from the procuring agency (see 4.4.3 and 6.8).

4. QUALITY ASSURANCE PROVISIONS

4.1 Lot.

4.1.1 *Pilot lot.*—Prior to the start of regular production and following any change in regular production methods, or rubber formulation, a pilot lot of 25 faceblanks shall be produced using the same methods, materials, and equipment as will be employed during regular production.

4.1.2 *Regular production.* — A lot shall consist of a number of faceblanks produced in sequence during one month as indicated by the dots on the medallion on the faceblank. A sublot shall consist of a number of faceblanks produced in 24 consecutive hours or less. A new lot shall be established following the occurrence of any event affecting the homogeneity of the lot or use of an alternate approved formulation. Acceptably repaired faceblanks from any accepted parent lot may be incorporated into and assume the lot number of current production. The inspection lot for nondestructive inspection, within the above limitations, shall be designated by the inspector. A change in the size and/or canister mounting position of the faceblank shall not be cause to establish a new lot within the above limitations.

4.2 Sampling.

4.2.1 *For nondestructive inspection.*

4.2.1.1 *Pilot.*—Each faceblank shall be inspected for conformance to the applicable drawings and specification requirements.

4.2.1.2 *Regular.*—Sampling shall be conducted by or under the supervision of the Government inspector in accordance with the classification of defects (see 4.3.4) and Standard MIL-STD-105.

4.2.2 *For destructive tests.*

4.2.2.1. *Physical properties.*

4.2.2.1.1 *Pilot lot.*—Fifteen representative faceblanks shall be taken from each pilot lot for the physical properties tests (see 4.4).

4.2.2.1.2 *Regular production lot.*—Thirty representative faceblanks shall be taken from each sublot for the physical properties tests (see 4.4).

4.2.2.2 *Toxicity.*—Twenty faceblanks and four test slabs having equivalent cures shall be submitted, before production begins, for toxicity tests. When faceblank molds are not available, 24 test slabs shall be submitted for the toxicity tests. These samples shall be accompanied by a report giving the cure time and temperature, and the quantities of the ingredients (with manufacturer's tolerances) used in the test slabs and faceblanks submitted for toxicity tests (see 6.11). Samples shall be forwarded to the agency designated by the Office of the Chief Chemical Officer, Washington 25, D. C. The samples shall be marked with the following information:

Samples for toxicity tests.
Name of material.
Manufacturer's designation.
Manufacturer's name.

Samples shall be taken for toxicity tests whenever a major change is made (see 6.10).

4.3 Inspection.

4.3.1 *Mold cavity contours.*—Prior to the initiation of production, the inspector shall ascertain that each applicable mold has been approved by the Cml C Inspection Equip-

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:36Z
Check the source to verify that this is the current version before use.

ment Agency, Army Chemical Center, Md. (see 6.7).

4.3.2 *Toxicity.*—Before production begins, the inspector shall ascertain that the rubber formulation to be used in the manufacture of faceblanks has been tested and found acceptable from a toxicity standpoint (see 4.4.3).

4.3.3 *Packaging, packing, and marking.*—The inspector shall inspect the packaging, packing, and marking for compliance with section 5.

4.3.4 *Classification of defects.*—Inspection of the faceblank shall be conducted as follows:

4.3.4.1 *Faceblank.*—(See applicable drawings for type and size).

Categories and defects

Major	*AQL 1.0 percent*
1.	Rubber thickness.
2.	Porous and spongy areas.
3.	Nonfills (excluding air traps).
4.	Deformation.
5.	Holes and cuts.
6.	Mismatched mandrels (when applicable).
7.	Split at register.
8.	Flow cracks which enlarge on probing.
9.	Contamination (grease or oil).
10.	Marking incorrect.
Minor	*AQL 2.5 percent*
51.	Imperfections (see 3.3).
52.	Excess flash and improper trim.
53.	Color.
54.	Tab rivet holes, diameter, piercing or alignment improper.
55.	Contamination (other than Major defect No. 9).
56.	Marking missing, or illegible.
	Incidental
	None.

4.4 Tests.

4.4.1 *Test specimens.*—Two type D specimens, conforming to Specification ZZ-R-601, shall be cut from the flat cheek area of each of 13 sample faceblanks. The specimens shall not be buffed or stretched before testing. Ten specimens shall be tested for tensile strength, ultimate elongation, and tensile stress before aging and 10 specimens tested after aging. Five specimens shall be tested for permanent set before aging. Two type B specimens conforming to ASTM Designation D624, Methods of Test for Tear Resistance of Vulcanized Rubber, shall be cut from the forehead section of each of 10 of the above 13 sample faceblanks. Ten specimens shall be tested before aging and 10 tested after aging. Enough 1- by 1-inch squares shall be cut from cheek and forehead sections to build up 5 specimens for the hardness test, each specimen containing enough layers to be no less than $\frac{1}{10}$ inch thick. The remaining faceblanks shall be used for retest (4.5).

4.4.2 *Physical properties tests.*

4.4.2.1 *Tensile strength, ultimate elongation, permanent set, tensile stress, and hardness.*—Tensile strength, ultimate elongation, permanent set, tensile stress, and hardness shall be determined as specified in Specification ZZ-R-601.

4.4.2.2 *Tear resistance.*—Tear resistance shall be determined as specified in Methods of Test for Tear Resistance of Vulcanized Rubber, A.S.T.M. Designation D624.

4.4.2.3 *Aging (oven process).*—The test specimens selected for oven process aging shall be aged in an air oven at a temperature of 158 ± 2° F. for a continuous period of 168 hours or at a temperature of 212 ± 2° F. for 24 continuous hours, as prescribed in Specification ZZ-R-601 (see 6.12).

4.4.3 *Toxicity.*—All sample slabs or faceblanks and formulations submitted to the Chemical Corps for test will be evaluated from the toxicity standpoint by the Office of the Surgeon General, Department of the Army. Such tests, including human skin tests, as are deemed necessary by the Office of the Surgeon General for properly evaluating the toxicity of any formulation, faceblank, or test slab, will be carried out in accordance with the directions of the Surgeon General (see 6.8).

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T13:36Z
Check the source to verify that this is the current version before use.

4.4.4 *Light resistance of restored faceblanks.*—Test only restored faceblanks for resistance to light in accordance with Specification ZZ-R-601, for 12 hours at a distance of 18 inches from the light source. Observe for a distinct color difference between the faceblank proper and the restored section.

4.5 Retest and rejection.

4.5.1 *Pilot lot.*—If any faceblank fails to conform to the applicable drawings and specification requirements, or if the specimens fail to conform to the applicable requirements of 3.4, the pilot lot shall be rejected. The cause of any failure shall be ascertained and corrective action instituted prior to initiation of a new pilot lot. Upon rejection of a pilot lot, a new pilot lot shall be produced and subjected to the same examination and testing as the original pilot lot. Regular production, pending approval of the pilot lot, will be at the risk of the manufacturer and no regular production lot shall be accepted prior to pilot lot approval.

4.5.2 *Regular production.*—If the specimens taken for test fail to conform to any of the applicable requirements of 3.4, a retest shall be made on the requirement or requirements which failed, using the same number of specimens as used for test. If the specimens fail to conform to any of the applicable requirements of 3.4 on retest, the sublot represented shall be rejected.

5. PREPARATION FOR DELIVERY

5.1 Packaging.

5.1.1 *Level A — Military package* — Four identical faceblanks shall be packaged in a corrugated fiberboard box conforming to style RSC of Specification LLL-B-631 for weight and size, in such a manner that a firm pack is obtained and that the natural form and contour of the faceblanks will be maintained during transit and storage. The box shall be closed in compliance with Specification LLL-B-631. The box shall be wrapped and sealed in accordance with method 1A-2 of Specification MIL-P-116.

5.1.2 *Level B—Limited military package.*—Packaging shall be the same as the packing specified in 5.2.2.

5.1.3 *Level C—Minimum military package.*—Packaging shall be the same as the packing specified in 5.2.2.

5.2 Packing.

5.2.1 *Level A—Military pack.*—Ten packages, each conforming to 5.1.1, shall be packed in a nailed wood box conforming to style 4 of Specification JAN-P-106, or a wood-cleated solid fiberboard box conforming to style A of Specification JAN-P-103, or a fiberboard-lined wood box conforming to style 4 of Specification JAN-P-138, or a cleated-plywood box conforming to style A, type II, class 2 of Specification PPP-B-601. The box shall be closed and strapped in accordance with the appendix to the applicable specification.

5.2.2 *Level B—Limited military pack.*—Faceblanks shall be packed in corrugated fiberboard boxes conforming to Specification LLL-B-631 for weight and size, in such a manner that a firm pack is obtained and the natural form and contour of the faceblanks will be maintained during transit and storage. A uniform number of faceblanks shall be packed in each box.

5.2.3 *Level C—Minimum military pack.*—Packing shall be as specified in 5.2.2.

5.3 Marking.

5.3.1 *Interior packages.* — Packages conforming to 5.1.1 shall have permanent, waterproof labels firmly attached to the box, barrier material, wax coating (if not transparent), and final kraft overwrapping. Labels shall be marked in accordance with

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:36Z
Check the source to verify that this is the current version before use.

Standard MIL-STD-129, and shall also bear the following information:

(1) Faceblank size and location of the canister stem, when applicable.
(2) Composition of the faceblank and formulation code.
(3) Nomenclature of the mask to which the faceblank pertains.

5.3.2 *Shipping containers.*—In addition to any special marking required by the contract or order, all shipping containers shall be marked in accordance with Standard MIL-STD-129.

6. NOTES

6.1 **Intended use.**—The faceblank covered by this specification is intended for use as a component of the facepiece specified in the contract or order.

6.2 Ordering data. — Procurement documents should specify:

a. Title, number, and date of the specification.
b. Type, size, and color of faceblank, and, when applicable, location of canister stem.
c. Type of packaging and packing required (see 5.1 and 5.2).
d. Applicable drawings.
e. That the contractor certify:
   (1) The faceblanks furnished are nonblooming and comply with the specified rubber content.
   (2) The name and quantity of antioxidant, accelerators, sun checking retardant, and copper and manganese inhibitors used in the rubber formulation.
   (3) Manufacturer's tolerances (see 6.11).

6.3 **Approved antioxidants and accelerators.**—The following materials have been tested and approved by the Chemical Corps for use in rubber components from which gas mask parts are manufactured.

Antioxidants

Aldol-alpha-naphthylamine (Agerite Resin).
Condensation product of acetone and aniline (Flectol H).
Symmetrical di-beta-naphthyl-para-phenylenediamine (Agerite White).
Reaction product of acetone and phenyl-beta-naphthylamine (BETANOX).
Condensation product of butyraldehyde and aniline (Antox).
Polymerized trimethyldihydroquinoline (Agerite Resin D).
Reaction product of acetone and para-aminodiphenyl (Santoflex B).
Mixture of "Santoflex B" and diphenyl-para-phenylenediamine (Santoflex BX).
Mixture of diphenylamine and substituted diphenylamines (B-L-E).
Phenyl-alpha-naphthylamine (Neozone A).
Reaction product of aniline and acetaldehyde (VGB).
Para-(para-toluenesulfonamine) phenyl-para-tolyamine (M-U-F).
Reaction product of acetone and diphenylamine (Aminox regular) (Aminox special).
Reaction product of diphenylamine and hydrocarbon (Agerite 41).
Diphenylethylenediamine (Stabilite Alba).
Di-ortho-tolylethylenediamine (Stabilite).
Reaction product of acetone and diphenylamine-65 percent and N, N'-diphenyl-para-phenylenediamine-35 percent (B-L-E Powder).
Para-(toluenesulfonamine)-diphenylamine (L-G-F).

Accelerators

Benzothiazyl disulfide (Altax).
Diphenylguanidine phthalate (Guantal).
Ethylidine aniline (A7).
Reaction product of carbon disulfide and methylenedipiperidene (Pipsolene).
Triethyltrimethylenetriamine (Trimene base).
Condensation product of butyraldehyde and aniline (Accelerator 808).
Diphenylguanidine phthalate (Delac P).
Condensation product of mercaptobenzothiazole and cyclohexylamine (Santocure).
Aldehydeamine (alpha-ethyl-beta-propylacryl aniline) (Phenex).
Reaction product of two mols of di-ortho-tolyguanidine and one mol of zinc chloride (Aero Ac 59).
Dibenzothiazyldimethylthiol urea (El Sixty).
Di-ortho-tolylguanidine (ROTG).
Mercaptobenzothiazole (Captex) (Rotax).
Quinoidine (Natural product).
Zinc salt of mercaptobenzothiazole (OXAF) (APEF) (Zenite) (Zenite A: Composed of Zenite-97 percent, plus tetramethylthiuram monosulfide-3 percent).

Source: https://assist.dla.mil -- Downloaded: 202640-17T13:36Z
Check the source to verify that this is the current version before use.

Accelerators (Cont'd)

(Tetramethylthiuram monosulfide in any other combination is not permissible).
Diphenylguanidine acetate (Delac A).
Diphenylguanidine oxalate (Delac G).
2-Mercaptothiazoline (2-MT).
Lead (beta-anilinoethyl)-phenyldimethyldithiocarbamate (SPDX).

6.4 Substitute antioxidants or accelerators.—In case it is desired to use antioxidants and accelerators other than those appearing in the approved list, bidders may submit samples of their rubber compound to Army Chemical Center, Maryland, to be tested for toxicity (see 4.2.2.2). Faceblanks made from rubber compounds which are found to be satisfactory for the purpose will be acceptable under this specification, provided the contractor furnishes a certified statement that the composition of the rubber compound in the faceblanks offered for acceptance is identical with that of the rubber compound in the sample submitted to Army Chemical Center for the toxicity test. This advance test, however, will not be considered as a final acceptance test for toxicity of the faceblanks as the U. S. Government reserves the right to conduct the toxicity test specified in 4.4.3 on all lots or shipments of faceblanks offered for acceptance regardless of any previous test that may have been conducted.

6.5 Restoration of flaws.—The base of the canister stem and those areas of the faceblank to be placed in contact with eyepiece components are considered critical areas. All other areas including the outer end of the canister stem are considered noncritical areas. Repair doughs will be prepared from the original faceblank formulation using additional ingredients when necessary to effect satisfactory repairs.

6.6 Sampling.—When the contractor consistently produces high quality material and operates under a system of quality control acceptable to the Government, the Government, at its discretion, may modify in whole or in part, the sampling and testing procedures specified herein. However, the Government reserves the right to return at any time, without previous notice to the contractor, to the sampling and testing procedures specified in this specification.

6.7 Production mold.—A mold will be furnished by the Chemical Corps to the manufacturer to assist in the fabrication of the production molds. An inspection form conforming to the contours delineated by the mold will be furnished as an aid to the Government inspector.

6.8 Toxicity.—The technique of determining toxicity by means of patch tests is given in Schwartez, Tulipan, and Peck, "Occupational Diseases of the Skin," 2d. Ed., pages 54 to 64 and 302 to 308 (1947).

6.9 Equivalent cure. — Slabs and faceblanks of the same stock and gage are considered to have equivalent cures or the same state of vulcanization when

(1) Their free-sulfur contents do not vary more than 10 percent.
(2) Their average tensile-stress values at any given elongation (other than ultimate elongation) do not vary more than ± 2.5 percent.
(3) Their curing times can be equated in the following equation:

$$t_2 = t_1 \times 1.6^{\left(\frac{T_1 - T_2}{10}\right)}$$

where:

t_1 = Time of cure at temperature T_1 (Minutes).
t_2 = Time of cure at temperature T_2 (Minutes).
T_1 = Temperature of cure for time t_1 (°F.).
T_2 = Temperature of cure for time t_2 (°F.).

For convenience, the nomograph in Figure 1 may be used instead of the mathematical computation of time—temperature relationships in determining equivalent cure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T13:36Z
Check the source to verify that this is the current version before use.

EQUIVALENT CURE TIME FOR NATURAL RUBBER

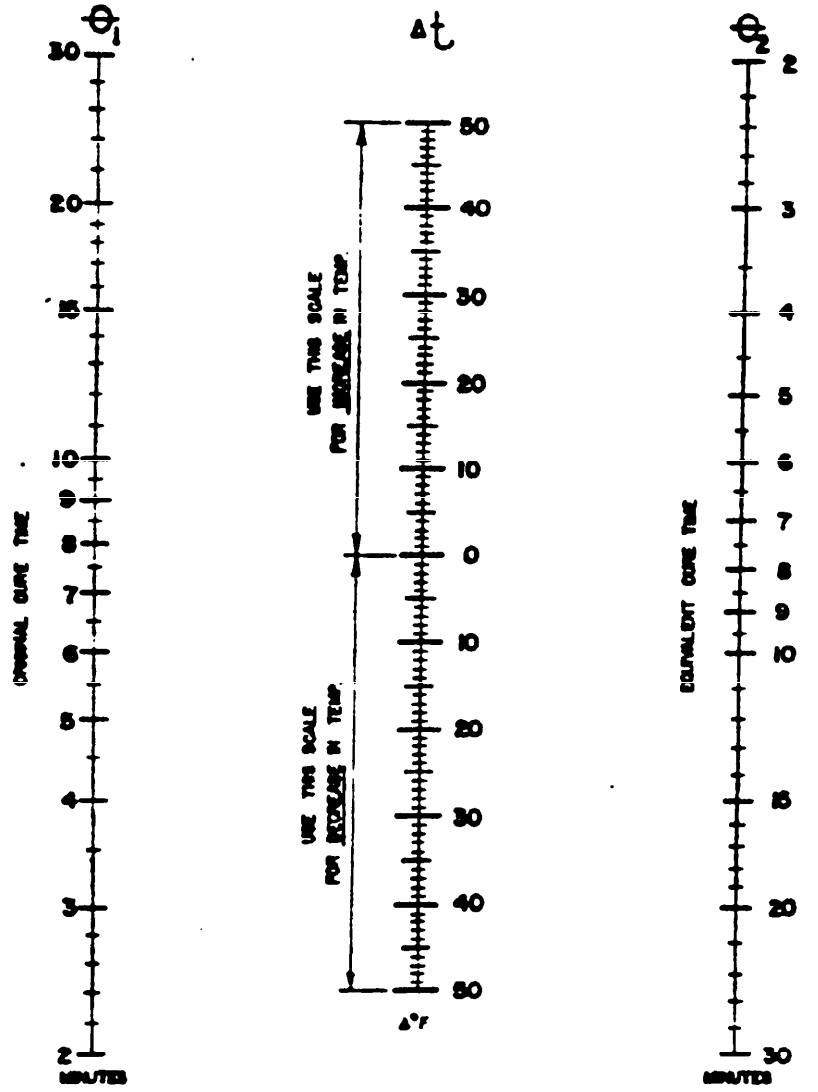


Figure 1.

USING A STRAIGHT EDGE, CONNECT THE ORIGINAL CURE TIME ON θ_1 SCALE WITH THE CHANGE OF CURE TEMPERATURE ON Δt SCALE. EXTEND THE LINE UNTIL IT INTERSECTS θ_2 SCALE AT THE EQUIVALENT CURE TIME.

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:36Z
Check the source to verify that this is the current version before use.

6.10 Major change.—The term applies to any change in formulae, processing, or curing of currently approved rubber stocks which may induce toxic characteristics and cause casualties. The major change should be considered effected when one or more of the following conditions occur:

a. Components of formulae are varied in excess of the limitations stated in the manufacturer's tolerance (see 6.11).

b. The addition or deletion of one or more components of formulae.

c. Substitutes for one or more components of formulae, without advance approval of the Chemical Corps.

d. Deviations from the submitted and approved factory mold cure exceeding +5°F. or —10°F., even though equivalent cure is attained.

e. Use of mold lubricants, dusting powders, or wet sprays not used in preparation or cure of the original specimens submitted for toxicity approval.

6.11 Manufacturer's tolerances. — The manufacturer should submit to the Chemical Corps the variations in amounts used, or tolerances, for accelerators, plasticizers, and softeners. These tolerances are permitted to enable the manufacturer to produce stock which will consistently comply with this specification and will process satisfactorily in the plant. Components of formulae may be submitted on the basis of percentage of the stock or as the number of parts per 100 parts of rubber, and the manufacturer's tolerances recorded in the same units.

6.12 Aging.—Aging at 121 ± 2°F. for a continuous period of 24 hours is slightly more severe on rubber than aging at 158 ± 2°F. for 168 consecutive hours; therefore, specimens that fail to meet requirements when aged at the higher temperature may be discarded and replaced by new specimens aged at 158 ± 2°F. for 168 consecutive hours.

Patent notice.—When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the U. S. Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

Custodians:
Army—Chemical Corps
Navy—Bureau of Yards and Docks
Air Force

Other interest:
Army—M
Navy—SAMC

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:36Z
Check the source to verify that this is the currentversion before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T13:36Z
Check the source to verify that this is the current version before use.

SPECIFICATION ANALYSIS SHEET

Form Approved
Budget Bureau No. 119-R004

INSTRUCTIONS

This sheet is to be filled out by personnel either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity as indicated on reverse hereof.

SPECIFICATION

ORGANIZATION *(Of submitter)*

CITY AND STATE

CONTRACT NO.

QUANTITY OF ITEM PROCURED

DOLLAR AMOUNT
$

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES.

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?

☐ YES ☐ NO IF "YES", IN WHAT WAY?

4. REMARKS *(Attach any pertinent data which may be of use in improving this specification. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity)*

SUBMITTED BY *(Printed or typed name and activity)*

DATE

DD, FORM 1 APR 63 1426 REPLACES NAVSHIPS FORM 4863, WHICH IS OBSOLETE

PLATE NO. 15419

Source: https://assist.dla.mil -- Downloaded: 202640-17T13:36Z
Check the source to verify that this is the current version before use.

FOLD

EPARTMENT OF THE NAVY

POSTAGE AND FEES PAID
NAVY DEPARTMENT

OFFICIAL BUSINESS

COMMANDING OFFICER
U.S. ARMY MUNITIONS COMMAND
ATTN: SMUFA-N1100
PHILADELPHIA, PA. 19137

FOLD

Source: https://assist.dla.mil -- Downloaded: 202610-17T13:36Z
Check the source to verify that this is the current version before use.