INCH-POUND
MIL-R-23074C(SH)
22 May 1990
SUPERSEDING
MIL-R-23074B(SHIPS)
27 November 1964
(See 6.7)

MILITARY SPECIFICATION

RUBBER TILE, RUBBER-AIR-LEAD-TYPE (RAL)

This specification is approved for use by the Naval Sea Systems Command, Department of the Navy, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope This specification covers rubber tile used for reducing the transmission of vibration from metal plates to water

2. APPLICABLE DOCUMENTS

2.1 Government documents

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6 2)

SPECIFICATIONS

FEDERAL

PPP-F-320 - Fiberboard; Corrugated and Solid, Sheet Stock (Container Grade), and Cut Shapes.
PPP-B-636 - Boxes, Shipping, Fiberboard

MILITARY

MIL-L-19140 - Lumber and Plywood, Fire-Retardant Treated.
MIL-A-24456 - Adhesive for Plastic Vibration-Damping Tiles

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to Commander, Naval Sea Systems Command, SEA 55Z3, Department of the Navy, Washington, DC 20362-5101 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 9320
DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

STANDARDS

FEDERAL

FED-STD-601 - Rubber: Sampling and Testing.

MILITARY

MIL-STD-407 - Visual Inspection Guide for Rubber Molded Items
MIL-STD-1186 - Cushioning, Anchoring, Bracing, Blocking and Waterproofing; With Appropriate Test Methods.
MIL-STD-2073-1 - DoD Materiel Procedures for Development and Application of Packaging Requirements

(Unless otherwise indicated, copies of federal and military specifications, standards, and handbooks are available from the Standardization Documents Order Desk, BLDG 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094)

2 2 Non-Government publications. The following document(s) form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the documents cited in the solicitation (see 6.2)

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

D 412 - Standard Test Methods for Rubber Properties in Tension (DoD adopted)
D 471 - Standard Test Method for Rubber Property - Effect of Liquids (DoD adopted)
D 945 - Standard Test Methods for Rubber Properties in Compression or Shear (Mechanical Oscillograph). (DoD adopted)
D 2240 - Standard Test Method for Rubber Property - Durometer Hardness. (DoD adopted)
D 3951 - Standard Practice for Commercial Packaging (DoD adopted)

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103)

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents These documents also may be available in or through libraries or other informational services.)

2 3 Order of precedence In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Materials The tile shall be an assembly of rubber and lead shot having the specified construction. The rubber shall be polymerized chloroprene compounded and vulcanized to have the specified properties

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

3.2 Construction. Unless otherwise specified (see 6.2), the tile shall have the construction and dimensions shown on figure 1. The tile shall be furnished with the base sheet face and the four edges roughened by abrading so that no further processing except solvent cleaning and cement application is required for adherence to steel. The cover sheet and the base sheet of the tile shall be made from the same compound.

3.3 Lead shot. The lead shot shall have a specific gravity between 10.9 and 11.4 and a diameter between 0.080 and 0.095 inch (number 8 shot).

3.4 Airtightness. The tile shall show no blisters or indication of leakage (see 4.3.1).

3.5 Physical properties. The lead content and rubber in the tile shall conform to the requirements specified in table I (see 4.4).

TABLE I. Physical requirements

	Maximum	Minimum	Test procedure
Lead shot content in tile, grams	960	860	4 4.1
Adhesion, tile to steel and cover to tile base, initially, after oven aging and after water immersion, stripping in 3 minutes caused by 20-pound load, inches	3	--	4 4 2
Initial properties of rubber·			
Static modulus, pounds per square inch (lb/in^2)	840	700	4.4.3
Dynamic modulus, lb/in^2	1,240	920	4 4 3
Resilience, percent	84	70	4.4 3
Hardness, durometer points	57	47	4.4 4
Tensile strength, lb/in^2	--	1,400	4.4 5
Ultimate elongation, percent	--	350	4 4.5
Oven aged properties of rubber:			
Tensile strength, percent of initial	--	80	4 4.5.1
Ultimate elongation, percent of initial	--	80	4.4.5.1
Properties after water immersion.			
Volume change, percent	12	0	4.4 6

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

3.6 Marking. The tile shall be marked in colored ink with the manufacturer's name or trademark, the month and year of manufacture, contract number, and specification number.

3.7 Workmanship. The finished item shall meet all the applicable requirements of this specification.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in this specification where such inspections are deemed necessary to ensure supplies and services conform to prescribed requirements.

4 1.1 Responsibility for compliance All items shall meet all requirements of sections 3 and 5 The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract Sampling inspection, as part of the manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to accept defective material.

4.2 Quality conformance inspection

4 2.1 Lot. For purposes of sampling, examinations, and tests, a lot shall consist of all the tile produced in one plant under essentially the same conditions, but not to exceed 1000 titles. In each case, the number of pieces shall be the lot size.

4.2.2 Sampling.

4 2 2.1 Sampling for visual, dimensional and airtightness examinations Sample tiles shall be taken at random from each lot in accordance with the sampling plan in table II for the examinations specified in 4 3 1 (see 6 4)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

TABLE II. Sampling for visual, dimensional and airtightness examinations.

Lot size	Sample size
Number of rubber tiles	Number of rubber tiles
1 to 4	all
5 to 9	5
10 to 25	8
26 to 62	13
63 to 160	20
161 to 410	32
411 to 1,000	50
1,001 to 2,600	80

4.2.2.1 1 Major defect. A major defect is a defect that is likely to result in failure or to reduce materially the usability of the unit of product for its intended purpose.

4.2.3 Sampling for tests Sample tiles shall be taken at random from those selected in 4.2.2.1 in sufficient quantity to conduct the tests specified in 4.3.2.1.

4.2 3.1 Additional rubber samples for test. The manufacturer shall prepare two sheets, each 6 by 6 by 0.080 ± 0.010 inch thick, and one slab 4 by 4 by 0.500 inch thick from each lot These pieces shall be identical in cure and composition to the rubber material in the lot submitted (see 6.3) The tests specified in 4 3.2.2 shall be conducted on these rubber samples

4.3 Quality conformance examinations and tests.

4.3.1 Visual, dimensional, and airtightness examinations. Each of the samples taken in accordance with 4 2.2.1 shall be subjected to an examination for workmanship, dimensions, tolerances and airtightness. MIL-STD-407 shall be used to determine and evaluate defects through visual examination. The examination for airtightness shall be conducted as follows:

(a) A single layer of tiles shall be placed on the platen of a press or between hot plates maintained at 310 degrees Fahrenheit (°F) and arranged to close as specified below.
(b) The press or the hot plates shall be closed against the tiles at the lowest pressure that can be maintained against 1/2-inch thick spacer bars.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

(c) Two minutes after placing the tiles on the hot surface, the pressure shall be released and the heated tiles removed as rapidly as possible.

(d) Each heated tile shall be examined by picking it up and tilting to cross light the patterned surface. Tile that is airtight will exhibit a symmetrical pattern of raised areas over each hole. Areas that are not raised over the holes indicate leakage. Blisters that destroy the symmetry indicate faulty bonding within the tile Any tile exhibiting such blisters or indication of leakage shall be rejected and classified as a major defect.

4.3 1.1 Rejection. Any defective tile shall not be offered for delivery (see 6.4).

4.3 2 Quality conformance tests.

4.3.2.1 Tests on the tile. Each sample taken in accordance with 4 2.3 shall be subjected to the following tests:

Test	Paragraph
Content of lead shot	4 4 1
Adhesion, initial, after oven aging and after water immersion tile to steel and cover to base of tile	4 4 2

4 3 2 2 Tests on rubber samples. Each sample provided in accordance with 4 2 3 1 shall be subjected to the following tests·

Test	Paragraph
Static modulus, dynamic modulus, and resilience	4.4.3
Hardness, Shore A durometer	4 4 4
Tensile strength, initial and after oven aging	4.4 5
Ultimate elongation, initial and after oven aging	4 4.5
Volume change	4 4 6

4 3 2.3 Rejection for nonconformance. If any sample is found not to conform to the requirements of this specification, this shall be cause for rejection of the lot which it represents.

4.4 Test procedures. Unless otherwise indicated in the test procedure, tests shall not be conducted on the test specimens unless a conditioning period of 4 hours at room temperature 27 ± 5 degrees Celsius (°C) (80 ± 9°F) has taken place Sample preparation may be undertaken without regard to this time interval

Source: https://assist.dla.mil Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

4.4.1 Content of lead shot. The content of lead shot in the tile shall be determined as follows:

(a) A tile shall be placed in a pan to catch the lead shot.
(b) At random, four parallel internal rows of shot-filled pockets that have 46 pockets per row shall be selected.
(c) The tile shall be slit along the center line of these four rows.
(d) The shot from these four rows shall be collected.
(e) The collected shot shall be weighed to the closest 0.1 gram.
(f) This weight shall be multiplied by 6.75 to obtain the weight of shot in the entire tile.

4.4.2 Adhesion of tile to steel and cover to base of tile. The adhesion of the tile to steel and of the cover to the base of the tile shall be determined initially, after oven aging and after water immersion as follows.

(a) Six strip specimens (two specimens for each condition) 1-1/2 inches wide and 11 to 12 inches long shall be cut from the tile parallel to the side having the 7/16-inch pitch between holes (see figure 1). The edge of the tile shall be avoided when preparing these specimens.
(b) Each strip specimen shall be adhered to a freshly sandblasted steel plate, not less than 2 by 14 by 1/8-inch thick, using an epoxy adhesive as specified in MIL-A-24456. Manufacturer's instructions for mixing and applying the adhesive shall be followed One end of the strip shall be aligned on the steel plate. The opposite end of the strip shall be held clear of the steel surface. The strip shall be drawn against the steel surface by means of a hand roller (approximately 1-1/2 inches wide by 1-1/2 inches diameter) progressing from the starting end to the opposite end in order to exclude air from the adhesive interface. The rolling operation shall be repeated over the surface of the strip to press it firmly against the steel surface. The assemblies shall be allowed to stand for 1 to 3 days at 70 to 80°F before testing or other conditioning.
(c) The adhesion of the strips of tile to the steel plate shall be measured with a 90 degree angle of pull. The assemblies shall be fastened in a horizontal position with the strip on the bottom side. One end of the strip shall be peeled loose from the steel far enough to fasten a clamp with weight, equal to 20 pounds, onto the strip. The rate of separation shall be observed in inches per minute. The values for the two strips shall be averaged for each condition.
(d) The adhesion between the cover and the base of the tile strips shall be measured on the opposite ends of the specimens tested in 4.4.2(c), initially, after oven aging and after water immersion The same procedure shall be used to test the adhesion as specified above, except that the cover shall be peeled loose (or cut) from the base of the tile strip far enough to fasten the clamp with weight equal to 20 pounds.

4.4 2 1 Oven aging. The adhesion specimens and tensile specimens shall be oven aged in accordance with method 7221 of FED-STD-601

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

4.4 2 2 Water immersion. The adhesion specimens and volume change specimens shall be immersed in distilled water in accordance with method 6001 of FED-STD-601 with the following exceptions:

(a) The temperature of the water shall be 54 ± 1.1°C (130 ± 2°F).
(b) The water pressure shall be 600 ± 10 lb/in^2 gauge.
(c) The duration of immersion under the above conditions shall be 166 ± 1 hours.
(d) The specimens shall be removed from the warm water, immersed in open distilled water at room temperature for 1 to 6 hours, and then tested within 3 minutes after removal from the latter water

4.4.3 Static modulus, dynamic modulus and resilience. The static modulus, dynamic modulus, and resilience of the rubber samples representing the tiles shall be determined using a Yerzley oscillograph, or equal, following the procedure specified in ASTM D 945.

4 4.4 Hardness The hardness of the rubber samples representing the tiles shall be determined in accordance with ASTM D 2240 using a Shore A durometer.

4 4.5 Tensile strength and ultimate elongation. The tensile strength and ultimate elongation of the rubber samples representing the tiles shall be determined in accordance with ASTM D 412. Die C specimens shall be used.

4.4.5 1 Oven-aged tensile strength and ultimate elongation. The tensile strength and ultimate elongation shall be determined after oven aging in accordance with 4 4.2.1.

4 4.6 Volume change in water Specimens 1 by 2 by 0.080 ± 0.010 inch prepared from the rubber samples representing the tiles shall be immersed in distilled water, and the volume change shall be determined in accordance with ASTM D 471

4 5 Inspection of packaging. Sample packages and packs, and the inspection of the preservation, packing, and marking for shipment, storage and stowage shall be in accordance with the requirements of section 5 and the documents specified therein

5. PACKAGING

(The packaging requirements specified herein apply only for direct Government acquisition)

5 1 Preservation. Preservation shall be level A, C, or commercial as specified (see 6.2).

5 1.1 Level A. Fifteen tiles shall be unit packed flat in a snug-fitting fiberboard box conforming to PPP-B-636, class weather-resistant with the type, the variety, the grade, and the box style at the contractor's option. A reinforcing liner and top and bottom pads of the same material as the fiberboard box shall be

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

used. Tiles shall be separated from one another and the pads by a minimum of 4 mil (0.10 millimeter) thick polyethylene film. Separate pieces of polyethylene film shall be used between each tile, and each separator shall be 13 inches (33 centimeters) long by 13 inches wide. Box closure shall be in accordance with 5.2.2.1.2

5.1.2 Level C. Preservation shall be as specified for level A, except that the fiberboard box shall be class-domestic and in accordance with 5.2.1.1 1.2 and 5.2.2.1.

5.1.3 Commercial. Preservation shall be in accordance with ASTM D 3951.

5.2 Packing. Packing shall be level A, B, C, or commercial as specified (see 6.2).

5.2.1 General requirements for levels A, B, and C.

5.2.1.1 Containers. Containers selected (see 5.2.2) shall be of minimum weight and cube to be consistent with the protection required, of uniform size, and contain identical quantities of identical tiles.

5.2.1.1.1 Navy fire-retardant requirements.

5.2.1.1.1.1 Lumber and plywood When specified (see 6.2), all lumber and plywood including laminated veneer material used in the shipping container and pallet construction, members, blocking, bracing, and reinforcing shall be fire-retardant treated material conforming to MIL-L-19140 as follows

Levels A and B - Type II - weather resistant.
Category 1 - general use.
Level C - Type I - non-weather resistant
Category 1 - general use.

5.2.1.1.1.2 Fiberboard. Fiberboard used in the construction of class-domestic, non-weather resistant fiberboard and cleated fiberboard boxes shall meet the flammability and smoke requirements of PPP-F-320

5 2.2 Levels A, B, and C containers. Tiles preserved as specified (see 5 1) shall be packed in shipping containers. The level of packing shall be as specified (see 6 2) in MIL-STD-2073-1 and table VII of appendix C, herein. Unless otherwise specified (see 6.2), container selection shall be at the contractor's option

5 2.2.1 Caseliners, closure, and gross weight

5.2.2.1 1 Caseliners. Unless otherwise specified (see 6.2), level A and when specified (see 6 2) level B, shipping containers shall be provided with waterproof caseliners in accordance with MIL-STD-1186.

5.2.2.1.2 Closure. Container closure, reinforcing, or banding shall be in accordance with the applicable container specification or appendix thereto, except that weather-resistant fiberboard boxes shall be closed in accordance with method V and reinforced with nonmetallic or tape banding and domestic fiberboard boxes shall be closed in accordance with method I using pressure sensitive tape.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

5.2.2.1.3 Weight. Wood, plywood, and cleated type of containers exceeding 200 pounds gross weight shall be modified by the addition of skids in accordance with MIL-STD-2073-1, appendix F, and the applicable container specification or appendix thereto.

5.2.3 Commercial. Tiles preserved as specified (see 5.1) shall be packed for shipment in accordance with ASTM D 3951 and herein.

5.2.3.1 Container modification. Shipping containers exceeding 200 pounds gross weight shall be provided with a minimum of two 3 by 4 inch nominal wood skids laid flat, or a skid or sill type of base that will support the material and facilitate handling by mechanical handling equipment during shipment, storage, and stowage.

5.3 Palletized unit loads When specified (see 6.2), shipping containers shall be palletized in accordance with MIL-STD-2073-1, appendix F.

5 4 Marking. In addition to any special marking required (see 6 2 and herein), unit packs, shipping containers, and palletized unit loads shall be marked in accordance with MIL-STD-2073-1, appendix F. The marking shall include lot numbers and bar coding (unit packs and shipping containers). In addition, each unit and shipping container shall be marked on two sides with the word "UP " An arrow pointing toward the top of the container shall be placed beneath each word Arrows shall be employed only to indicate or supplement the words, "This side UP " The following precautionary markings shall appear on two opposite sides of each package or packing

"FOR STORAGE DO NOT STACK MORE THAN TWO HIGH
STORE IN COOL, DRY PLACE."

"FREE OF ASBESTOS AND CERAMIC
(REFRACTORY) FIBERS."

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. This tile is intended for special use in vibration damping of metal structures and in decoupling such vibrations from adjacent water The normal weight is 5 pounds per square foot

6 2 Acquisition requirements Acquisition documents must specify the following:

(a) Title, number and date of this specification.
(b) Issue of DoDISS to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.1.1 and 2.2).
(c) Size of tile, if other than 1 by 1 foot (see 3.2).
(d) Level of preservation and level of packing required (see 5 1, 5.2 and 5.2.2)

Source: https://assist.dla.mil Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

(e) When Navy fire-retardant requirement for lumber and plywood is required (see 5.2.1.1.1.1).
(f) When container selection is not at the contractor's option (see 5.2.2).
(g) When caseliners are not required (see 5.2 2.1.1).
(h) Palletization when required (see 5.3).
(i) Special markings required (see 5.4).

6.3 Consideration of data requirements. The following data requirements should be considered when this specification is applied on a contract. The applicable Data Item Descriptions (DID's) should be reviewed in conjunction with the specific acquisition to ensure that only essential data are requested/provided and that the DID's are tailored to reflect the requirements of the specific acquisition. To ensure correct contractual application of the data requirements, a Contract Data Requirements List (DD Form 1423) must be prepared to obtain the data, except where DoD FAR Supplement 27.475-1 exempts the requirement for a DD Form 1423.

Reference Paragraph	DID Number	DID Title	Suggested Tailoring
4.2.3.1	DI-MISC-80678	Certification/data report	----

The above DID's were those cleared as of the date of this specification. The current issue of DoD 5010.12-L, Acquisition Management Systems and Data Requirements Control List (AMSDL), must be researched to ensure that only current, cleared DID's are cited on the DD Form 1423

6.4 Acceptance levels. Suggested acceptance levels for visual, dimensional and airtightness examinations are given in table III (see 4 2.2.1)

TABLE III. Suggested acceptance levels for visual, dimensional and airtightness examinations.

		Number of nonconforming or defective rubber tiles			
Lot size	Sample size	Major defects		Total defects (major plus minor)	
Number of rubber tiles	Number of rubber tiles	Acceptance number	Rejection number	Acceptance number	Rejection number
1 to 4	all	0	1	1	2
5 to 9	5	0	1	1	2
10 to 25	8	0	1	1	2
26 to 62	13	0	1	1	2
63 to 160	20	1	2	2	3
161 to 410	32	1	2	3	4
411 to 1,000	50	2	3	4	5
1,001 to 2,600	80	3	4	6	7

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

6.5 Part or Identifying Number (PIN). Rubber tile should be designated by standard part numbers as identified below:

M23074 - 1
- M23074 — Specification number
- 1 — Size

6.6 Subject term (key word) listing.

Blisters
Bonding
Decoupling
Durometer
Oscillograph
Shot

6.7 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes

Preparing activity:
Navy - SH
(Project 9320-N004)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

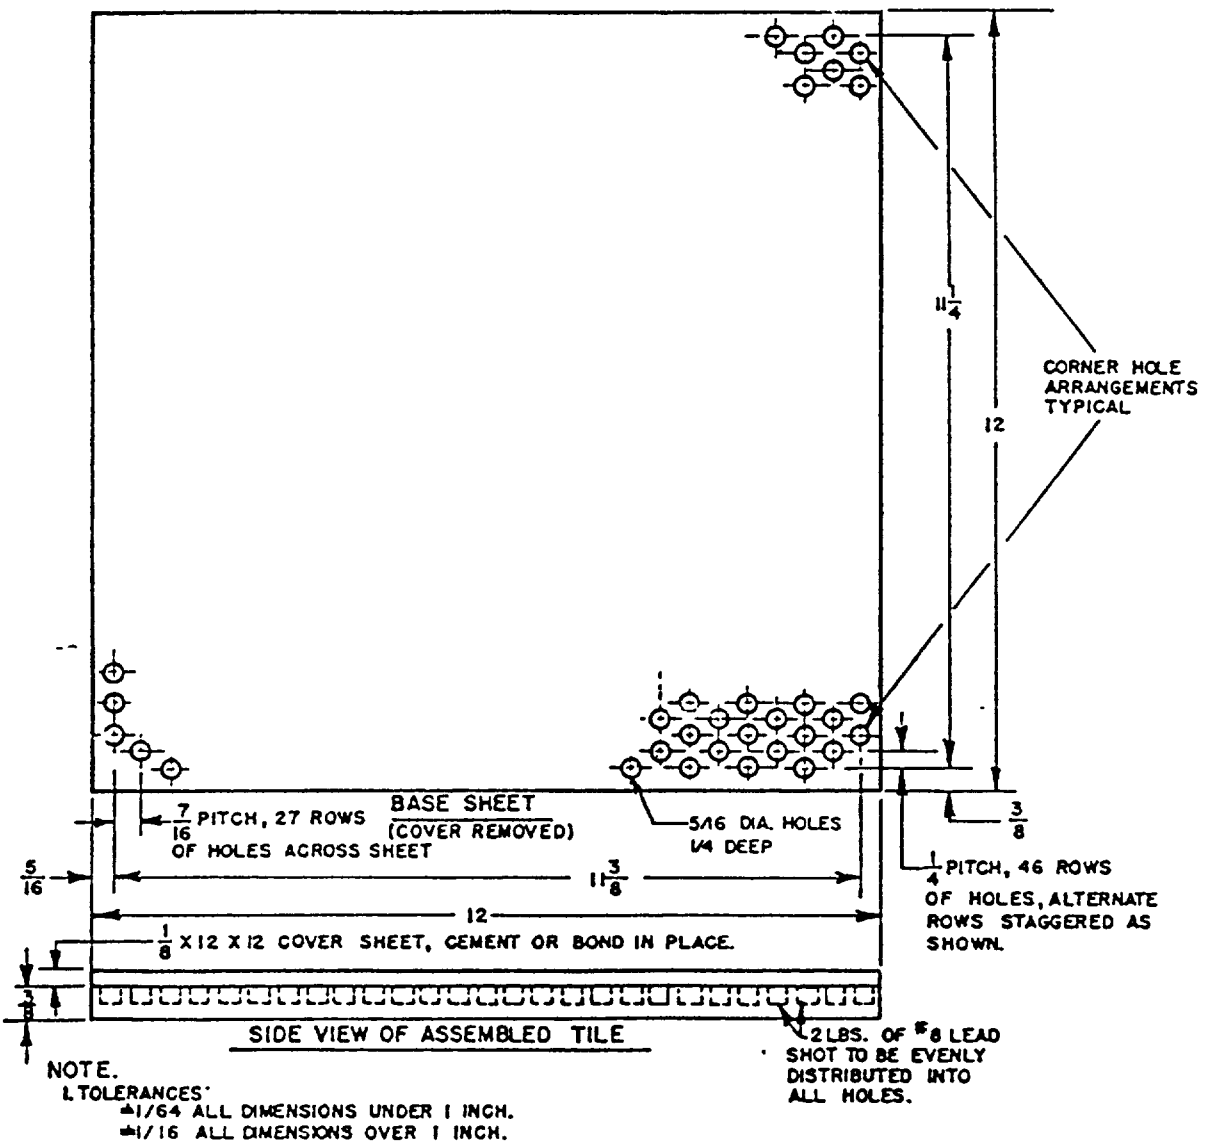


FIGURE 1. Construction of rubber tile for vibration decoupling.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER MIL-R-23074C(SH)	2. DOCUMENT DATE (YYMMDD)

3 DOCUMENT TITLE
RUBBER TILE, RUBBER-AIR-LEAD-TYPE (RAL)

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible Attach extra sheets as needed)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle Initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) (1) Commercial (2) AUTOVON (If applicable)	7. DATE SUBMITTED (YYMMDD)

8. PREPARING ACTIVITY

a NAME Technical Point of Contact (TPOC): Mr. Corbitt (SEA 05M3) PLEASE ADDRESS ALL CORRESPONDENCE AS FOLLOWS:	b TELEPHONE (Include Area Code) (1) Commercial (2) AUTOVON TPOC: 703-602-0145 332-20145
c. ADDRESS (Include Zip Code) Commander, Naval Sea Systems Command Department of the Navy (SEA 55Z3) Washington, DC 20362-5101	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 AUTOVON 289-2340

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T15:29Z
Check the source to verify that this is the current version before use.