The documentation and process conversion measures necessary to comply with this revision shall be completed by 5 November 2000.

INCH-POUND

MIL-PRF-19500/391E
5 August 2000
SUPERSEDING
MIL-PRF-19500/391D
9 December 1997

PERFORMANCE SPECIFICATION

SEMICONDUCTOR DEVICE, TRANSISTOR, NPN, SILICON, LOW-POWER
TYPES 2N3019, 2N3019S, 2N3057A, 2N3700, AND 2N3700UB
JAN, JANTX, JANTXV, AND JANS

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for NPN, silicon, low-power transistors. Four levels of product assurance is provided for each device type as specified in MIL-PRF-19500.

1.2 Physical dimensions. See figure 1, 2N3019 (TO-5), 2N3019S (similar to TO-39), figure 2 2N3057(TO-46), figure 3 2N3700 (TO-18), and figure 4 (surface mount).

1.3 Maximum ratings.

Type	P_T		V_{CBO}	V_{EBO}	V_{CEO}	I_C	T_J and T_{STG}	$R_{\theta JA}$
	T_A = +25°C	T_C = +25°C (2)						
	W	W	V dc	V dc	V dc	A dc	°C	°C/W
2N3019	0.8 (1)	5	140	7	80	1	-65 to +200	175
2N3019S	0.8 (1)	5	140	7	80	1	-65 to +200	175
2N3057A	0.5 (3)	1.8	140	7	80	1	-65 to +200	325
2N3700	0.5 (3)	1.8	140	7	80	1	-65 to +200	325
2N3700UB	0.5 (3)	1.16	140	7	80	1	-65 to +200	325

(1) Derate linearly at 5.7 mW/°C above T_A = +60°C.
(2) Derate linearly at 28.6 mW/°C for types 2N3019 and 2N3019S; 10.3 mW/°C for types 2N3057A, 2N3700, and 2N3700UB for $T_C \geq$ +25°C.
(3) Derate linearly at 3.08 mW/°C above T_A = +37.5°C.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Defense Supply Center Columbus, ATTN: DSCC-VAC, P.O. Box 3990, Columbus, OH 43216-5000, by using the Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

1.4 Primary electrical characteristics.

Limits	h_{FE1} V_{CE} = 10 V dc I_C = 150 mA dc	h_{FE2} V_{CE} = 10 V dc I_C = 0.1 mA dc	h_{FE3} (1) V_{CE} = 10 V dc I_C = 10 mA dc	$\|h_{fe}\|$ V_{CE} = 10 V dc I_C = 50 mA dc f = 20 MHz	$V_{CE(sat)1}$ (1) I_C = 150 mA dc I_B = 15 mA dc
					V dc
Min	100	50	90	5	
Max	300	200		20	0.20

(1) Pulsed (see 4.5.1).

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATION

DEPARTMENT OF DEFENSE

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

STANDARD


DEPARTMENT OF DEFENSE

MIL-STD-750 - Test Methods for Semiconductor Devices.

(Unless otherwise indicated, copies of the above specifications, standards, and handbooks are available from the Document Automation and Production Service (DAPS), Building 4D (DPM-DODSSP), 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

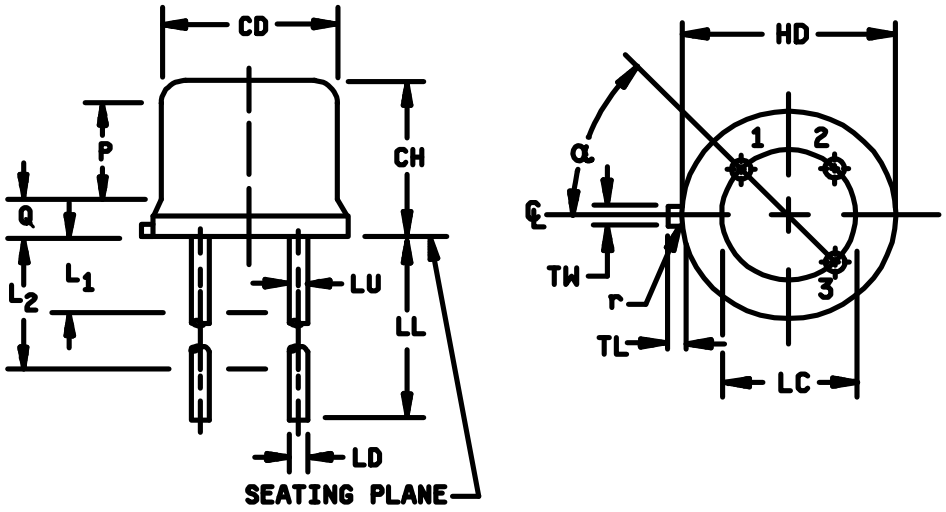

Dimensions					
Symbol	Inches		Millimeters		Notes
CD	0.305	0.335	7.75	8.51	
CH	0.240	0.260	6.10	6.60	
HD	0.335	0.370	8.51	9.40	
LC	.200 TP		5.08 TP		6
LD	0.016	0.021	0.41	0.53	7, 8
LL	See notes				7, 8, 11,12
LU	0.016	0.019	0.41	0.48	7, 8
L1		0.050		1.27	7, 8
L2	0.250		6.35		7, 8
P	0.100		2.54		5
Q		0.050		1.27	4
r		0.010		0.25	10
TL	0.029	0.045	0.74	1.14	3
TW	0.028	0.034	0.71	0.86	2
α	45° TP		45° TP		6

FIGURE 1. . Physical dimensions for device types 2N3019 (TO-5) and 2N3019S (TO-39).


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

NOTES:

1. Dimension are in inches.
2. Metric equivalents are given for general information only.
3. Beyond r (radius) maximum, TH shall be held for a minimum length of 0.011 (0.28 mm).
4. Dimension TL measured from maximum HD.
5. Body contour optional within zone defined by HD, CD, and Q.
6. Leads at gauge plane 0.054 +0.001 -0.000 inch (1.37 +0.03 -0.00 mm) below seating plane shall be within 0.007 inch (0.18 mm) radius of true position (TP) at maximum material condition (MMC) relative to tab at MMC. The device may be measured by direct methods.
7. Dimension LU applies between L_1 and L_2. Dimension LD applies between L_2 and LL minimum. Diameter is uncontrolled in L_1 and beyond LL minimum.
8. All three leads.
9. The collector shall be internally connected to the case.
10. Dimension r (radius) applies to both inside corners of tab.
11. For transistor type 2N3019, dimension LL shall be 1.5 inches (38.1) mm minimum and 1.75 inches (44.4 mm) maximum.
12. For transistor type 2N3019S, dimension LL shall be 0.5 inches (12.7) mm minimum and 0.75 inches (19.0 mm) maximum.
13. In accordance with ANSI Y14.5M, diameters are equivalent to ϕx symbology.
14. Lead 1 = emitter, lead 2 = base, lead 3 = collector.

FIGURE 1. . Physical dimensions for device types 2N3019 (TO-5) and 2N3019S (TO-39) Continued.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

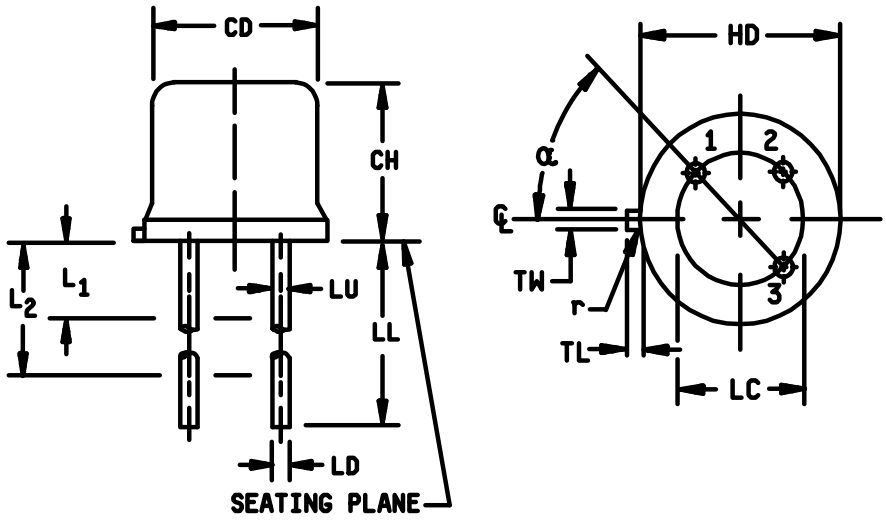


Symbol	Dimensions				Note
	Inches		Millimeters		
	Min	Max	Min	Max	
CD	0.178	0.195	4.52	4.95	
CH	0.065	0.085	1.65	2.16	
HD	0.209	0.230	5.31	5.84	
LC	0.100 TP		2.54 TP		6
LD	0.016	0.021	0.41	0.53	7
LL	0.500	1.750	12.70	44.45	7
LU	0.016	0.019	0.41	0.48	7
L1	---	0.050	---	1.27	7
L2	0.250	---	6.35	---	7
Q	---	0.040	---	1.02	4
TL	0.028	0.048	0.71	1.22	4
TW	0.036	0.046	0.91	1.17	3
r	---	0.007	---	0.18	10, 11
α	45° TP		45° TP		6

NOTES:

1. Dimension are in inches. Metric equivalents are given for general information only.
2. Beyond r (radius) maximum, TW shall be held for a minimum length of 0.011 (0.28 mm).
3. Dimension TL measured from maximum HD.
4. Leads at gauge plane 0.054 +0.001 -0.000 inch (1.37 +0.03 -0.00 mm) below seating plane shall be within 0.007 inch (0.18 mm) radius of true position (TP) at maximum material condition (MMC) relative to tab at MMC. The device may be measured by direct methods.
5. Dimension LU applies between L_1 and L_2. Dimension LD applies between L_2 and LL minimum. Diameter is uncontrolled in L_1 and beyond LL minimum.
6. All three leads.
7. The collector shall be internally connected to the case.
8. Dimension r (radius) applies to both inside corners of tab.
9. In accordance with ANSI Y14.5M, diameters are equivalent to ϕx symbology.
10. Lead 1 = emitter, lead 2 = base, lead 3 = collector.

FIGURE 2. Physical dimensions for 2N3057A (TO-46).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

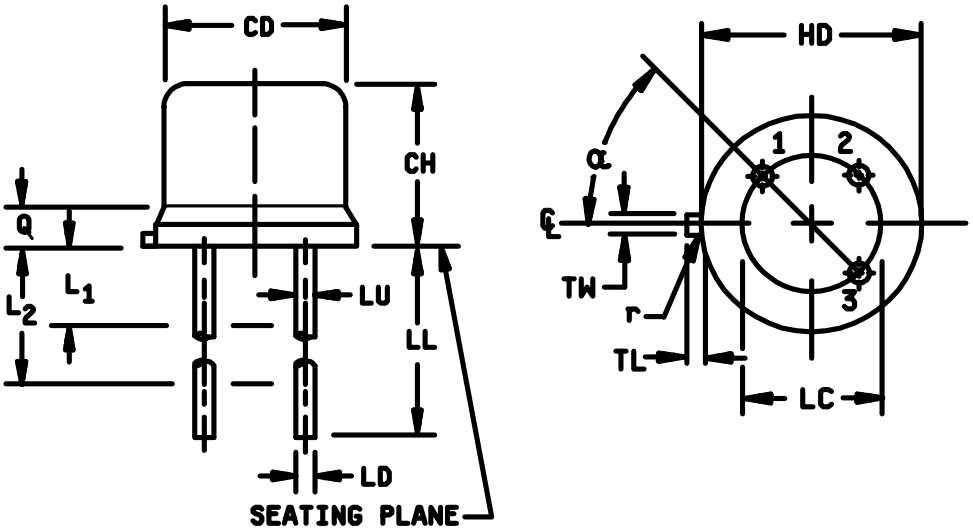

Dimensions					
Symbol	Inches		Millimeters		Notes
CD	0.178	0.195	4.52	4.95	
CH	0.170	0.210	4.32	5.33	
HD	0.209	0.230	5.31	5.84	
LC	.100 TP		2.54 TP		5
LD	0.016	0.021	0.41	0.53	6, 7
LL	.500	.750	12.70	19.05	6, 7
LU	0.016	0.019	0.41	0.48	6, 7
L1		0.050		1.27	6, 7
L2	0.250		6.35		6, 7
Q		0.040		1.02	4
r		0.010		0.25	9
TL	0.028	0.048	0.71	1.22	2, 3
TW	0.036	0.046	0.91	1.17	2
α	45° TP		45° TP		5

FIGURE 3. Physical dimensions for type 2N3700 (TO-18)..


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

NOTES:

1. Dimension are in inches. Metric equivalents are given for general information only.
2. Beyond r (radius) maximum, TH shall be held for a minimum length of 0.011 (0.28 mm).
3. Dimension TL measured from maximum HD.
4. Body contour optional within zone defined by HD, CD, and Q.
5. Leads at gauge plane 0.054 +0.001 -0.000 inch (1.37 +0.03 -0.00 mm) below seating plane shall be within 0.007 inch (0.18 mm) radius of true position (TP) at maximum material condition (MMC) relative to tab at MMC. The device may be measured by direct methods.
6. Dimension LU applies between L_1 and L_2. Dimension LD applies between L_2 and LL minimum. Diameter is uncontrolled in L_1 and beyond LL minimum.
7. All three leads.
8. The collector shall be internally connected to the case.
9. Dimension r (radius) applies to both inside corners of tab.
10. In accordance with ANSI Y14.5M, diameters are equivalent to ϕx symbology.
11. Lead 1 = emitter, lead 2 = base, lead 3 = collector.

FIGURE 3. Physical dimensions for type 2N3700 (TO-18) Continued.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

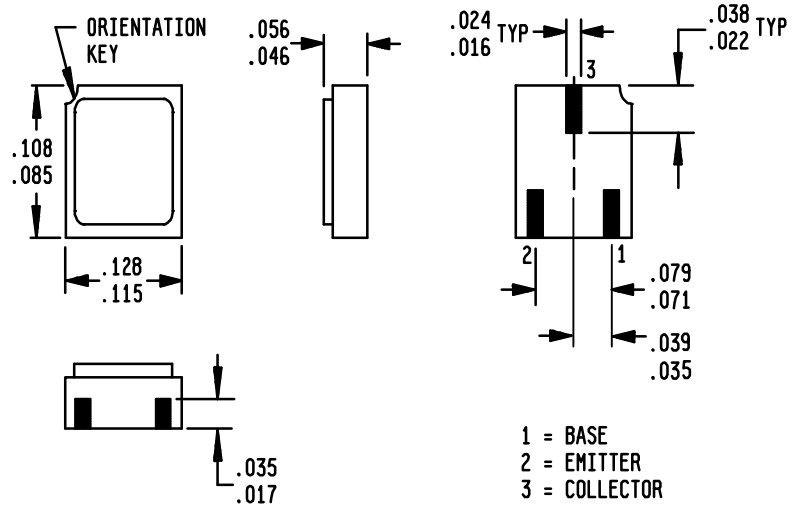

Inches	mm	Inches	mm
0.016	0.41	0.056	1.42
0.017	0.43	0.071	1.81
0.022	0.56	0.079	2.01
0.024	0.61	0.085	2.16
0.035	0.89	0.108	2.74
0.038	0.96	0.115	2.92
0.039	0.99	0.128	3.25
0.046	1.17		

NOTES:
1. Dimensions are in inches.
2. Metric equivalents are given for general information only.

FIGURE 4. Physical dimensions, surface mount (2N3700UB).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 Associated specification. The individual item requirements shall be in accordance with MIL-PRF-19500, and as specified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturer's list (QML) before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500.

3.4 Interface requirements and physical dimensions. The interface requirements and physical dimensions shall be as specified in MIL-PRF-19500, and figure 1 (2N3019, TO-5, 2N3019S, TO-39), figure 2 (2N3700, TO-18), figure 3 (2N3057, TO-46), and figure 4 (2N3700UB, surface mount) herein.

3.4.1 Lead finish. Lead finish shall be solderable in accordance with MIL-PRF-19500.

3.5 Marking. Marking shall be in accordance with MIL-PRF-19500, except for the UB suffix package. Marking on the UB package shall consist of an abbreviated part number, the date code, and the manufacturers symbol or logo. The prefixes JAN, JANTX, JANTXV, JANJ and JANS can be abbreviated as J, JX, JV, JJ and JS respectively. The "2N" prefix and the "AUB" suffix can also be omitted.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I.

3.7 Electrical test requirements. The electrical test requirements shall be the subgroups specified in 4.4.2 and 4.4.3.

4. VERIFICATION

4.1 Classification of Inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3)

c. Conformance inspection (see 4.4).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

4.3 Screening (JANTX, JANTXV, and JANS only). Screening shall be in accordance with MIL-PRF-19500 (table IV), and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen (see table IV of MIL-PRF-19500)	Measurement	
	JANS	JANTX and JANTXV levels
3c	Thermal impedance (see 4.3.2)	Thermal impedance (see 4.3.2)
9	I_{CES1} and h_{FE1}	Not applicable
10	48 hours minimum	48 hours minimum
11	I_{CES1}; h_{FE1}; ΔI_{CES1} = 100 percent of initial value or 5 nA dc, whichever is greater; Δh_{FE1} = ±15 percent.	I_{CES1} and h_{FE1}
12	See 4.3.1	See 4.3.1
13	Subgroups 2 & 3 of table I herein; ΔI_{CES1} = 100 percent of initial value or 5 nA dc, whichever is greater; Δh_{FE1} = ±15 percent.	Subgroup 2 of table I herein; ΔI_{CES1} = 100 percent of initial value or 5 nA dc, whichever is greater; Δh_{FE1} = ±15 percent.

4.3.1 Power burn-in conditions. Power burn-in conditions are as follows: T_A = Room ambient as defined in the general requirements of MIL-STD-750 (see 4.5).

V_{CB} = 10 - 30 V dc, Power shall be applied to achieve T_J = 135°C minimum and minimum power dissipation of P_D = 75 percent of maximum rated P_T as defined in 1.3.

4.3.2 Thermal impedance ($Z_{\theta JX}$ measurements). The $Z_{\theta JX}$ measurements shall be performed in accordance with MIL-STD-750, Method 3131.

a. I_M measurement current ..... 5 mA.

b. I_H forward heating current ..... 200 mA (min).

c. t_H heating time ..... 30 ms.

d. t_{md} measurement delay time ..... 60 µs max.

e. V_{CE} collector-emitter voltage ..... 10 V dc minimum

The maximum limit for $Z_{\theta JX}$ under these test conditions are $Z_{\theta JX}$ (max) = 72°C/W.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500, and as specified herein. If alternate screening is being performed in accordance with E.5.3.1d of MIL-PRF-19500, a sample of screened devices shall be submitted to and pass the requirements of group A1 and A2 inspection only (table VIb, group B, subgroup 1 is not required to be performed again if group B has already been satisfied in accordance with 4.4.2).

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with MIL-PRF-19500, and table I herein.

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VIa (JANS) of MIL-PRF-19500 and 4.4.2.1. See 4.4.2.2 for JAN, JANTX, and JANTXV group B testing. Electrical measurements (end-points) and delta requirements shall be in accordance with the steps of table II herein as specified in the notes for table II.

4.4.2.1 Group B inspection, table VIa (JANS) of MIL-PRF-19500.

Subgroup	Method	Condition
4	1037	V_{CB} = 10 V dc.
5	1027	V_{CB} = 10 V dc; T_A = +125°C ± 25°C for 96 hours with P_T adjusted according to the chosen T_A to give T_J = +275°C minimum. Optionally the test may be performed for a minimum of 216 hours with P_T adjusted to achieve T_J = +225°C minimum, sample size, n = 45, c = 0. In this case, the ambient temperature shall be adjusted such that power dissipation $P_D \geq 75$ percent of maximum rated P_T (see 1.3) is applied to the device under test. (Note: If a failure occurs, resubmission shall be at the test conditions of the original sample.)
5	2037	Test condition A.
6		Not applicable.

4.4.2.2 Group B inspection, (JAN, JANTX, and JANTXV). Separate samples may be used for each step. For rules on resubmission for failed steps, see MIL-PRF-19500 rules on resubmission of failed subgroups.

Step	Method	Condition
1	1039	Steady-state life: Test condition B, 340 hours, V_{CB} = 10 - 30 V dc. n = 45 devices, c = 0. Power shall be applied to the device to achieve a T_J = 150°C minimum and a minimum power dissipation P_D = 75 percent of max rated P_T as defined in 1.3 herein.
2	1039	Steady-state life test of step 1 shall be extended to 1,000 hours for each die design. Samples shall be selected from a wafer lot every twelve months of wafer production. Group B step 2 shall not be required more than once for any single wafer lot. n = 45 devices, c = 0
3	1032	High-Temperature life (non-operating), T_A = +200°C n = 22, c = 0

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

4.4.2.3 Group B sample selection. Samples selected from group B inspection shall meet all of the following requirements:

a. For JAN, JANTX and JANTXV samples shall be selected randomly from a minimum of three wafers (or from each wafer in the lot) from each wafer. For JANS, samples shall be selected from each inspection lot. See MIL-PRF-19500.

b. Must be chosen from an inspection lot that has been submitted to and passed group A, subgroup 2 conformance inspection. When the final lead finish is solder or any plating prone to oxidation at high temperature, the samples for life test (subgroups B4 and B5 for JANS, and group B for JAN, JANJ, JANTX and JANTXV) may be pulled prior to the application of final lead finish.

4.4.2.4 Product acceptable for delivery. The product shall be acceptable for delivery only after the successful completion of all group B testing and shall be comprised of die meeting the following requirements:

a. Manufactured on the same certified die fabrication line as the sample selected for 4.4.2.3.

4.4.3 Group C inspection, JANS. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VII of MIL-PRF-19500, and in 4.4.3.1 herein (JANS). See 4.4.3.2 for JAN, JANJ, JANTX, and JANTXV group C testing. Electrical measurements (end points) and delta requirements shall be in accordance with the steps of table II herein as specified in the notes for table II.

4.4.3.1 Group C inspection, table VII (JANS) of MIL-PRF-19500.

Subgroup	Method	Condition
C2	2036	Test condition E; not applicable for UB devices.
C6	1026	Steady-state life: Test condition B, 1,000 hours, V_{CB} = 10 - 30 V dc. n = 45 devices, c = 0. Power shall be applied to the device to achieve a T_J = 150°C minimum and a minimum power dissipation P_D = 75 percent of max rated P_T as defined in 1.3 herein.

4.4.3.2 Group C inspection, JAN, JANTX, and JANTXV. Group C inspection (JAN, JANTX, and JANTXV, package related tests) shall be as follows and shall include those package or case-related tests which are performed periodically. Group C test on each package family shall be performed on devices from each six months production of devices (based on inspection lot identification codes) for each assembly location and die attach method. Electrical measurements (end points) and delta requirements shall be in accordance with the steps of table II herein as specified in the notes for table II. The sample size for each of these subgroups is: 22 devices, c = 0. Separate samples may be used for each step. For rules on resubmission for failed steps, see MIL-PRF-19500 rules on resubmission of failed subgroups.

Step	Method	Condition
1	2066	
2	1051	Test condition C.
3	2036	Test condition E; not applicable for UB devices.
4		Not applicable

4.4.3.3 Group C sample selection. Samples for subgroups in group C shall be chosen at random from any inspection lot containing the intended package type and lead finish procured to the same specification which is submitted to and passes group A tests for conformance inspection. Testing of a subgroup using a single device type enclosed in the intended package type shall be considered as complying with the requirements for that subgroup.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

4.4.3.4 Product acceptable for delivery. The product which may be accepted for delivery based a successful completion of group C testing shall be product of the particular package type with lot inspection identification codes of the 52 successive weeks beginning with the inspection lot identification code of the successful group C sample (i.e. the inspection lot identification codes accepted for delivery based on successful group C testing will include those sealed during the approximate 10 weeks during which the sample was being screened and tested plus those sealed in the 42 weeks following successful completion of group C testing making a total of 52 successive calendar weeks.) A manufacturer shall not accept product for delivery until after successful completion of the group C testing on product of the applicable package type with an inspection lot identification code less than 51 weeks prior to the inspection identification code of the product being considered for acceptance.

4.5 Method of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows:

4.5.1 Pulse measurements. Conditions for pulse measurement shall be as specified in section 4 of MIL-STD-750.

4.5.2 Collector-base time constant. This parameter may be determined by applying an rf signal voltage of 1.0 volt (rms) across the collector-base terminals, and measuring the ac voltage drop (V_{eb}) with a high- impedance rf voltmeter across the emitter-base terminals. With f = 79.8 MHz used for the 1.0 volt signal, the following computation applies:

$$r'_b , C_{c(ps)} = 2 \text{ X } V_{eb} \text{ (millivolts)}$$

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limit		Unit
	Method	Conditions		Min	Max	
Subgroup 1						
Visual and mechanical examination	2071					
Solderability 2/ 4/	2026	15 leads, c = 0				
Resistance to solvents 2/ 3/ 4/	1022	15 devices, c = 0				
Subgroup 2						
Collector to base cutoff current	3036	Bias condition D; V_{CB} = 140 Vdc	I_{CBO1}		10	µA dc
Emitter to base cutoff current	3061	Bias condition D; V_{EB} = 7 Vdc	I_{EBO1}		10	µA dc
Collector to emitter breakdown voltage	3011	Bias condition D; I_C = 30 mA dc pulsed (see 4.5.1)	$V_{(BR)CEO}$	80		V dc
Collector to emitter cutoff current	3041	Bias condition C; V_{CE} = 90 V dc	I_{CES1}		10	nA dc
Emitter to base cutoff current	3061	Bias condition D; V_{EB} = 5 V dc	I_{EBO2}		10	nA dc
Forward current transfer ratio	3076	V_{CE} = 10 V dc; I_C = 150 mA dc; pulsed (see 4.5.1)	h_{FE1}	100	300	
Forward current transfer ratio	3076	V_{CE} = 10 V dc; I_C = 0.1 mA dc	h_{FE2}	50	200	
Forward current transfer ratio	3076	V_{CE} = 10 V dc; I_C = 10 mA dc; pulsed (see 4.5.1)	h_{FE3}	90		
Forward current transfer ratio	3076	V_{CE} = 10 V dc; I_C = 500 mA dc; pulsed (see 4.5.1)	h_{FE4}	50	200	
Forward current transfer ratio	3076	V_{CE} = 10 V dc; I_C = 1 A dc; pulsed (see 4.5.1)	h_{FE5}	15		
Collector to emitter voltage (saturated)	3071	I_C = 150 mA dc; I_B = 15 mA dc pulsed (see 4.5.1)	$V_{CE(sat)1}$		0.2	V dc

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limit		Unit
	Method	Conditions		Min	Max	
Subgroup 2 – Continued						
Collector to emitter voltage (saturated)	3071	I_C = 500 mA dc; I_B = 50 mA dc pulsed (see 4.5.1)	$V_{CE(sat)2}$		0.5	V dc
Base to emitter voltage (saturated)	3066	Test condition A; I_C = 150 mA dc; I_B = 15 mA dc; pulsed (see 4.5.1)	$V_{BE(sat)}$		1.1	V dc
Subgroup 3						
High-temperature operation		T_A = +150°C				
Collector to emitter cutoff current	3041	Bias condition C; V_{CE} = 90 V dc	I_{CES2}		10	µA dc
Low-temperature operation		T_A = -55°C				
Forward current transfer ratio	3076	V_{CE} = 10 V dc; I_C = 150 mA dc; pulsed (see 4.5.1)	h_{FE6}	40		
Subgroup 4						
Small-signal short- circuit forward-current transfer ratio	3206	V_{CE} = 5 V dc; I_C = 1 mA dc, f = 1 kHz	h_{fe}	80	400	
Magnitude of small- signal short-circuit forward-current transfer ratio	3306	V_{CE} = 10 V dc; I_C = 50 mA dc; f = 20 MHz	$\|h_{fe}\|$	5	20	
Input capacitance(output open circuited)	3240	V_{EB} = 0.5 V dc; I_C = 0; 100 kHz ≤ f ≤ 1 MHz	C_{ibo}		60	pF
Open circuit output capacitance	3236	V_{CB} = 10 V dc; I_E = 0; 100 kHz ≤ f ≤ 1 MHz	C_{obo}		12	pF
Noise figure	3246	V_{CE} = 10 V dc; I_C = 100 µA dc; R_g = 1 kΩ; Power bandwidth= 200 Hz	NF		4	dB
Collector to base time constant		V_{CB} = 10 V dc; I_C = 10 mA dc; f = 79.8 MHz(see 4.5.2)	$r'_b C_c$		400	ps
Pulse response		See figure 5	$t_{on} + t_{off}$		30	ns

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection. - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limit		Unit
	Method	Conditions		Min	Max	
Subgroup 5						
Safe operating area(continuous dc)	3051	T_C = 25°C; t = 10 ms, 1 cycle (see figure 6)				
Test 1		V_{CE} = 10 V dc;				
2N3019, 2N3019S		I_C = 500 mA dc				
2N3057A, 2N3700, 2N3700UB		I_C = 180 mA dc				
Test 2		V_{CE} = 40 V dc;				
2N3019, 2N3019S		I_C = 125 mA dc				
2N3057A, 2N3700, 2N3700UB		I_C = 45 mA dc				
Test 3		V_{CE} = 80 V dc;				
2N3019, 2N3019S		I_C = 60 mA dc				
2N3057A, 2N3700, 2N3700UB		I_C = 22.5 mA dc				
Electrical measurements		See table II, steps 2, 4, and 7.				
Subgroups 6 and 7						
Not applicable						

1/ For sampling plan, see MIL-PRF-19500.
2/ Separate samples may be used.
3/ Not required for laser marked devices.
4/ Not required for JANS devices.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

TABLE II. Groups B and C electrical measurements. 2/ 3/ 4/ 5/

Step	Inspection	MIL-STD-750		Symbol	Limits		Unit
		Method	Conditions		Min	Max	
1.	Collector to emitter cutoff current	3041	Bias condition C; V_{CE} = 90 V dc	I_{CES1}		10	nA dc
2.	Collector to emitter cutoff current	3041	Bias condition C; V_{CE} = 90 V dc	I_{CES1}		20	nA dc
3.	Emitter to base cutoff current	3061	Bias condition D; V_{EB} = 5 V dc	I_{EBO}		10	nA dc
4.	Collector to emitter voltage (saturated)	3071	I_C = 150 mA dc; I_B = 15 mA dc; pulsed (see 4.5.1)	$V_{CE(sat)1}$ 1/		0.20	V dc
5.	Base emitter voltage (saturated)	3066	Test condition A; I_C = 150 mA dc; I_B = 15 mA dc; pulsed (see 4.5.1)	$V_{BE(sat)1}$ 1/		1.1	V dc
6.	Forward-current transfer ratio	3076	V_{CE} = 10 V dc; I_C = 0.1 mA dc	h_{FE2}	50	200	
7.	Forward-current transfer ratio	3076	V_{CE} = 10 V dc; I_C = 150 mA dc	h_{FE1}	100	300	
8.	Collector-emitter cutoff current	3041	Bias condition D; V_{CE} = 90 V dc; pulsed (see 4.5.1)	ΔI_{CES1}	±100 percent of initial value or 8 nA dc, whichever is greater.		
9.	Forward-current transfer ratio	3076	V_{CE} = 10 V dc; I_C = 0.1 mA dc; pulsed (see 4.5.1)	Δh_{FE2}	±25 percent change from initial reading.		
10.	Forward-current transfer ratio	3076	V_{CE} = 10 V dc; I_C = 150 mA dc; pulsed (see 4.5.1)	Δh_{FE1}	±25 percent change from initial reading.		
11.	Collector-emitter voltage (saturated)	3071	I_C = 150 mA dc; I_B = 15 mA dc; pulsed (see 4.5.1)	$\Delta V_{CE(sat)1}$ 1/	±50 percent mV dc change from previous measured value.		

See footnotes at top of next page.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

TABLE II. Groups B and C electrical measurements - Continued. 2/ 3/ 4/ 5/

1/ Measured within 0.125 inch from the body of the device.

2/ The electrical measurements for table VIa (JANS) of MIL-PRF-19500 are as follows:

a. Subgroup 3, see table II herein, steps 1, 3, 4, 5, 6, and 7.

b. Subgroup 4, see table II herein, steps 2, 3, 4, 5, 6, 7, and 11.

c. Subgroup 5, see table II herein, steps 2, 3, 4, 5, 7, 8, and 10.

3/ The electrical measurements for group B, (JAN, JANTX, and JANTXV) 4.4.2.2 herein are as follows:

a. Steps 1, 2, and 4 of 4.4.2.2, see table II herein, steps 1, 8, 9, 10, and 11.

4/ The electrical measurements for table VII (for JANS only) of MIL-PRF-19500 are as follows:

a. Subgroup 2, see table II herein, steps 1, 3, 4, 5, 6, and 7 (JANS).


b. Subgroup 3, see table II herein, steps 1, 3, 4, 5, 6, and 7 (JANS).

c. Subgroup 6, see table II herein, steps 1, 3, 4, 5, 6, 7, 8, and 9 (JANS).

5/ The electrical measurements for group C, (JAN, JANTX, and JANTXV only) 4.4.3.2 herein are as follows:

a. Step 2 of 4.4.3.2, see table II herein, all steps.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

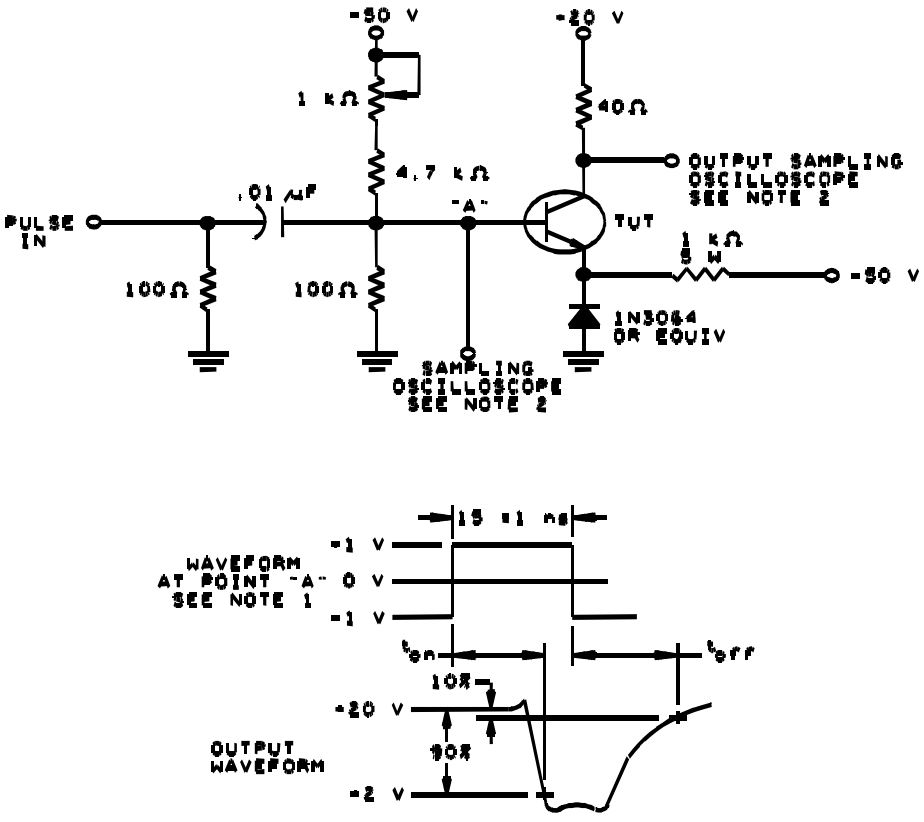

NOTES:

1. The rise time (t_r) of the applied pulse shall be ≤ 2.0 ns, duty cycle ≤ 2% and the generator source impedance shall be 50 ohms.

2. Sampling oscilloscope: Z_{IN} ≥ 100 kΩ, C_{IN} ≤ 12 pF, rise time ≤ 2.0 ns.

FIGURE 5. Nonsaturated switching-time test circuit.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

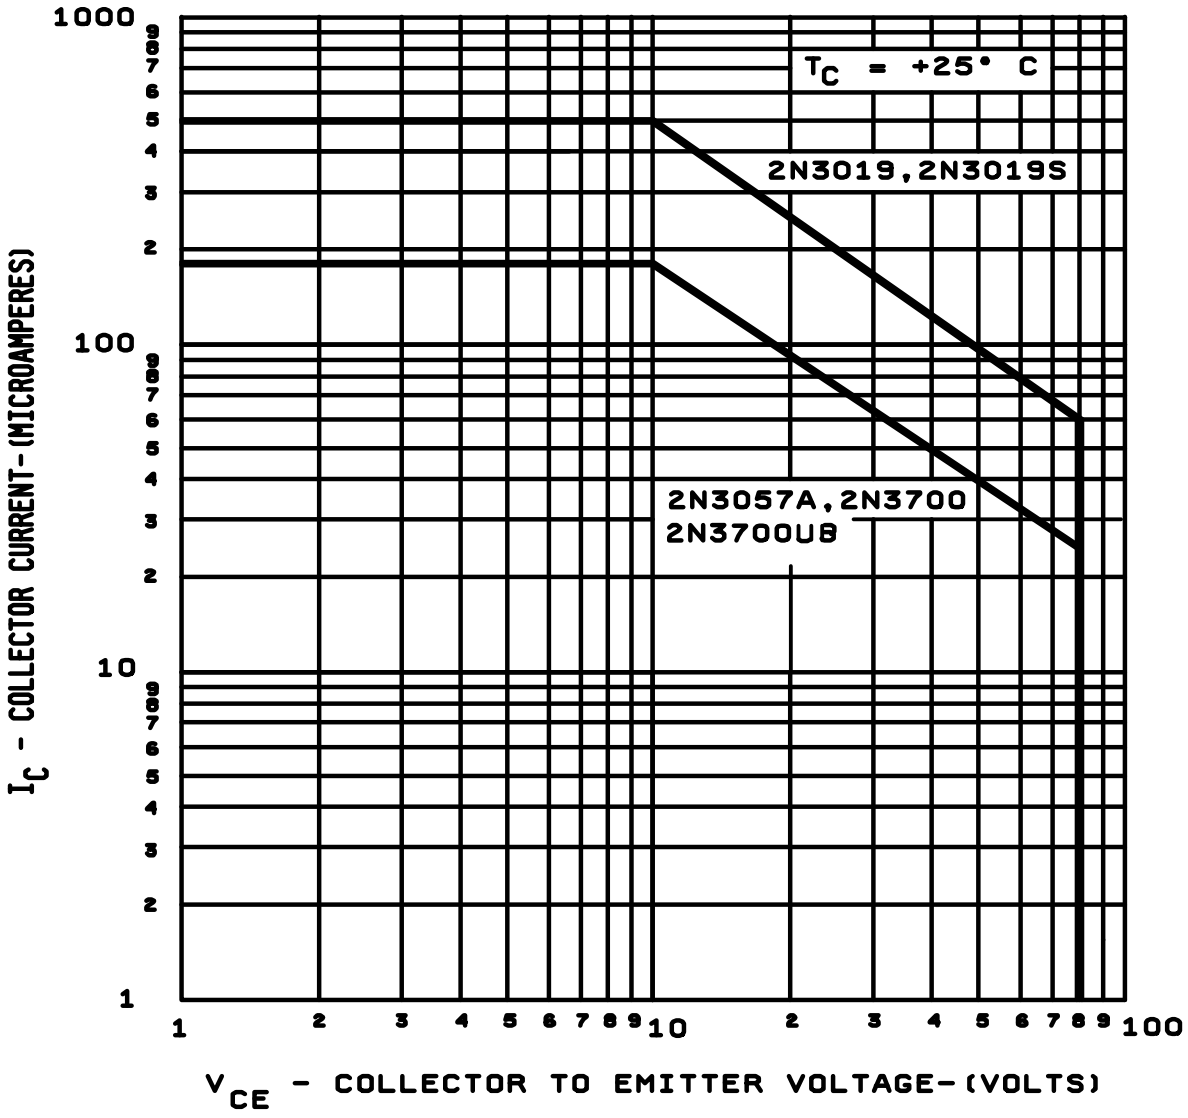


FIGURE 6. Maximum safe operating graph (DC).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When actual packaging of material is to be performed by DoD personnel, these personnel need to contact the responsible packaging activity to ascertain requisite packaging requirements. Packaging requirements are maintained by the Inventory Control Points' packaging activity within the Military Department or Defense Agency, or within the Military Departments' System Command. Packaging data retrieval is available from the managing Military Departments' or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

5.2 Marking. Unless otherwise specified (see 6.2), marking shall be in accordance with MIL-STD-129.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Notes. The notes specified in MIL-PRF-19500 are applicable to this specification.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Issue of DODISS to be cited in the solicitation and, if required, the specific issue of individual documents referenced (see 2.2.1).

b. Lead finish (see 3.4.1).

c. Type designation and product assurance level.

d. Packaging requirements (see 5.1).

6.3 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

6.4 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Products List QPL-19500 whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or purchase orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Defense Supply Center Columbus, DSCC-VQE, Columbus, OH 43216.

Custodians:
Army - CR
Navy - EC
Air Force - 11
NASA – NA
DLA – CC

Review activities:
Army - AR, MI, SM
Navy - AS, CG, MC
Air Force - 13, 19

Preparing activity:
DLA - CC

(Project 5961-2056)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.

2. The submitter of this form must complete blocks 4, 5, 6, and 7.

3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER MIL-PRF-19500/391E	2. DOCUMENT DATE 000805

3. **DOCUMENT TITLE**
SEMICONDUCTOR DEVICE, TRANSISTOR, NPN, SILICON, LOW-POWER TYPES 2N3019, 2N3019S, 2N3057A, 2N3700, AND 2N3700UB JAN, JANTX, JANTXV, AND JANS

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) COMMERCIAL DSN FAX EMAIL	7. DATE SUBMITTED

8. PREPARING ACTIVITY

a. Point of Contact Alan Barone	b. TELEPHONE Commercial: 614-692-0510 DSN: 850-0510 FAX: 614-692-6939 EMAIL: alan_barone@dscc.dla.mil
c. ADDRESS Defense Supply Center Columbus, ATTN: DSCC-VAC, 3990 East Broad Street, Columbus, OH 43216-5000	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Standardization Program Office (DLSC-LM) 8725 John J. Kingman, Suite 2533, Fort Belvoir, VA 22060-6221 Telephone (703) 767-6888 DSN 427-6888

DD Form 1426, Feb 1999 (EG) Previous editions are obsolete WHS/DIOR, Feb 99

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:20Z
Check the source to verify that this is the current version before use.