The documentation and process conversion measures necessary to comply with this document shall be completed by 18 July 2022.

INCH-POUND

MIL-PRF-19500/393M
w/AMENDMENT 2
18 April 2022
SUPERSEDING
MIL-PRF-19500/393M
w/AMENDMENT 1
23 January 2017

PERFORMANCE SPECIFICATION SHEET

TRANSISTOR, NPN, SILICON, POWER, RADIATION HARDENED, TYPES 2N3418, 2N3419, 2N3420, 2N3421, JAN, JANTX, JANTXV, JANS, JANHC AND JANKC

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-PRF-19500.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for NPN, silicon, transistors for use in medium power switching applications. Four levels of product assurance (JAN, JANTX, JANTXV, and JANS) are provided for each device type, and two levels of product assurance (JANHC and JANKC) for die (element evaluation) are provided, as specified in MIL-PRF-19500. RHA level designators “M”, “D”, “P“, “L”, “R”, “F”, “G”, and “H” are appended to the device prefix to identify devices, which have passed RHA requirements.

1.2 Package and die outlines. The device package for the encapsulated device type are as follows: TO-5 or TO-39 in accordance with figure 1, surface mount version U4 suffix in accordance with figure 2. See figure 3 for JANHC and JANKC unencapsulated die.

1.3 Maximum ratings, unless otherwise specified T_A = +25°C.

Type	P_T T_A = +25°C (1)	P_T T_C = +100°C (1)	V_{CBO}	V_{CEO}	V_{EBO}	I_C	I_C (2)	T_{STG} and T_J	$R_{\theta JA}$ (3)	$R_{\theta JC}$ (3)
	W	W	V dc	V dc	V dc	A dc	A dc	°C	°C/W	°C/W
2N3418, 2N3418S	1.0	5	85	60	8	3	5	-65 to	175	18
2N3418U4	1.0	15	85	60	8	3	5	+200	175	4.5
2N3419, 2N3419S	1.0	5	125	80	8	3	5	-65 to	175	18
2N3419U4	1.0	15	125	80	8	3	5	+200	175	4.5
2N3420, 2N3420S	1.0	5	85	60	8	3	5	-65 to	175	18
2N3420U4	1.0	15	85	60	8	3	5	+200	175	4.5
2N3421, 2N3421S	1.0	5	125	80	8	3	5	-65 to	175	18
2N3421U4	1.0	15	125	80	8	3	5	+200	175	4.5

(1) For derating, see figures 4, 5, and 6.
(2) This value applies for $t_p \leq 1$ ms, duty cycle ≤ 50 percent.
(3) For thermal impedance curves see figures 7, 8, and 9.

Comments, suggestions, or questions on this document should be addressed to DLA Land and Maritime, ATTN: VAC, P.O. Box 3990, Columbus, OH 43218-3990, or emailed to Semiconductor@dla.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A
FSC 5961

DISTRIBUTION STATEMENT A. Approved for public release. Distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

1.4 Primary electrical characteristics at T_A = +25°C.

Limits	h_{FE2} (1)	h_{FE2} (1)	h_{FE4} (1)	h_{FE4} (1)	$V_{CE(sat)}$ (1)	$V_{BE(sat)}$ (1)	$\|h_{fe}\|$	C_{obo}
	V_{CE} = 2 V dc I_C = 1 A dc	V_{CE} = 2 V dc I_C = 1 A dc	V_{CE} = 5 V dc I_C = 5 A dc	V_{CE} = 5 V dc I_C = 5 A dc	I_C = 1 A dc I_B = 0.1 A dc	I_C = 1 A dc I_B = 0.1 A dc	V_{CE} = 10 V dc I_C = 0.1 A dc f = 20 MHz	V_{CB} = 10 V dc I_E = 0 100 kHz ≤ f ≤ 1 MHz
	2N3418 2N3418S 2N3418U4 2N3419 2N3419S 2N3419U4	2N3420 2N3420S 2N3420U4 2N3421 2N3421S 2N3421U4	2N3418 2N3418S 2N3418U4 2N3419 2N3419S 2N3419U4	2N3420 2N3420S 2N3420U4 2N3421 2N3421S 2N3421U4	V dc	V dc		pF
Min	20	40	10	15		0.6	1.3	
Max	60	120			0.25	1.2	8	150

(1) Pulsed (see 4.5.1).

1.5 Part or Identifying Number (PIN). The PIN is in accordance with MIL-PRF-19500, and as specified herein. See 6.5 for PIN construction example and 6.6 for a list of possible PINs.

1.5.1 JAN certification mark and quality level for encapsulated devices. The quality level designators for encapsulated devices that are applicable for this specification sheet from the lowest to the highest level are as follows: “JAN”, “JANTX”, “JANTXV” and "JANS".

1.5.2 JAN certification mark and quality level for unencapsulated devices (die). The quality level designators for unencapsulated devices (die) that are applicable for this specification sheet from the lowest to the highest level are as follows: "JANHC" and "JANKC".

1.5.3 Radiation hardness assurance (RHA) designator. The RHA levels that are applicable for this specification sheet from lowest to highest for JANTXV and JANS quality levels are as follows: “M”, “D”, “P“, “L”, “R”, “F”, “G”, and “H”.

1.5.4 Device type. The designation system for the device types of transistors covered by this specification sheet are as follows.

1.5.4.1 First number and first letter symbols. The transistors of this specification sheet use the first number and letter symbols "2N".

1.5.4.2 Second number symbols. The second number symbols for the transistors covered by this specification sheet are as follows: "3418", “3419”, “3420” and “3421”.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

1.5.4.3 Suffix letters. The following suffix letter are incorporated in the PIN as applicable.

	A blank suffix letter indicates a through-hole mount package similar to a TO-5 metal can (see figure 1).
S	Indicates a through-hole mount package similar to a TO-39 metal can with shorter lead lengths than blank suffix letter device (see figure 1).
U4	Indicates a 4 pad surface mount package (see figure 2.).

1.5.5 Lead finish. The lead finishes applicable to this specification sheet are listed on QML 19500.

1.5.6 Die identifiers for unencapsulated devices (manufacturers and critical interface identifiers). The manufacturer die identifier that is applicable for this specification sheet is "C" (see figure 3).

* 1.6 Radiation features. The following radiation features are applicable for RHA devices supplied to this specification sheet.

* 1.6.1 Maximum total ionizing dose (TID). The maximum TID that RHA devices were tested to in accordance with condition A (dose rate = 50 to 300 rad(Si)/s) of method 1019 of MIL-STD-750 are as follows:

For device type 2N3418, 2N3418S, 2N3419, 2N3419S:..... 100 krads(Si) 1/

For device type 2N3420, 2N3420S, 2N3421, 2N3421S:..... 100 krads(Si) 1/

1/ The manufacturers supplying these device types have performed characterization testing in accordance with condition A (dose rate = 50 to 300 rad(Si)/s) of method 1019 of MIL-STD-750. The radiation end point limits are guaranteed only to a maximum TID level of 100 krads(Si).

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

DEPARTMENT OF DEFENSE STANDARDS


MIL-STD-750 - Test Methods for Semiconductor Devices.

* (Copies of these documents are available online at https://quicksearch.dla.mil).

2.3 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.


Symbol	Inches	Inches	mm	mm	Note
	Min	Max	Min	Max	
CD	.305	.335	7.75	8.51	
CH	.240	.260	6.10	6.60	
HD	.335	.370	8.51	9.40	
LC	.200	TP	5.08	TP	6
LD	.016	.021	0.41	0.53	
LL	.500	.750	12.7	19.05	7, 12, 13
LU					7
L_1		.050		1.27	7
L_2	.250		6.35		7
P	.100		2.54		5
Q		.040		1.02	4
TL	.029	.045	0.74	1.14	3,10
TW	.028	.034	0.71	.86	9,10
r		.010		0.25	11
α	45° TP		45° TP		6

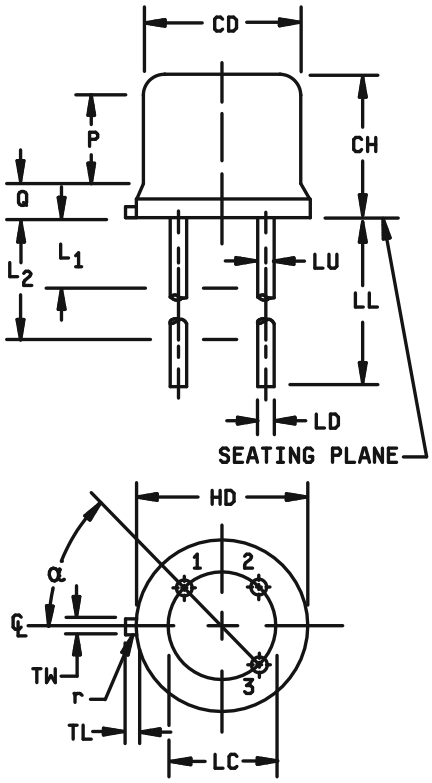

NOTES:
1. Dimensions are in inches.
2. Millimeters are given for general information only.
3. Symbol TL is measured from HD maximum.
4. Details of outline in this zone are optional.
5. Symbol CD shall not vary more than .010 inch (0.25 mm) in zone P. This zone is controlled for automatic handling.
6. Leads at gauge plane .054 inch (1.37 mm) +.001 inch (0.03 mm) -.000 inch (0.00 mm) below seating plane shall be within .007 inch (0.18 mm) radius of TP relative to tab. Device may be measured by direct methods or by gauge.
7. Symbol LU applies between L_1 and L_2. Dimension LD applies between L_2 and LL minimum. Diameter is uncontrolled in L_1 and beyond LL minimum.
8. Lead number 3 is electrically connected to case.
9. Beyond r maximum, TW shall be held for a minimum length of .021 inch (0.53 mm).
10. Lead number 4 omitted on this variation.
11. Symbol r applied to both inside corners of tab.
12. For transistor types 2N3418S, 2N3419S, 2N3420S, 2N3421S, LL is .500 (12.70 mm) minimum and .750 (19.05 mm) maximum (short leads).
13. For transistor types 2N3418, 2N3419, 2N3420, 2N3421, LL is 1.500 (38.10 mm) minimum, and 1.750 (44.45 mm) maximum (long leads).
* 14. In accordance with ASME Y14.5, diameters are equivalent to ϕx symbology.
15. Lead 1 is emitter, lead 2 is base, and lead 3 is collector.

FIGURE 1. Physical dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

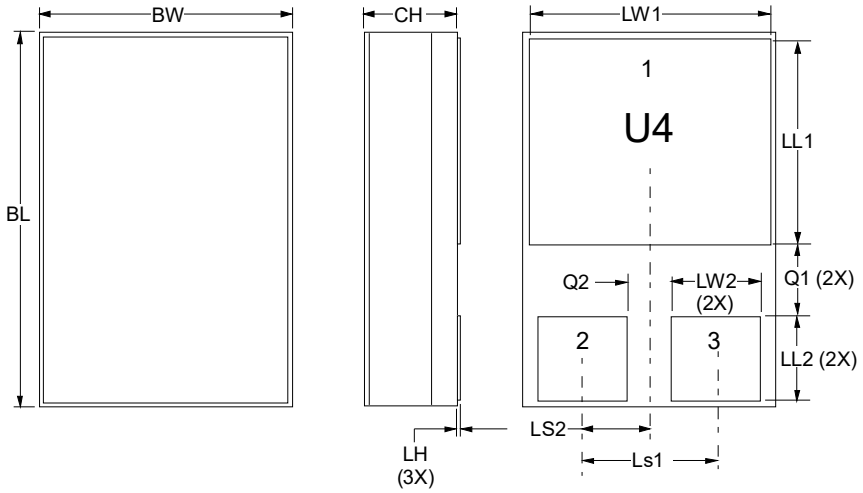


Symbol	Inches	Inches	Millimeters	Millimeters
	Min	Max	Min	Max
BL	.215	.225	5.46	5.72
BW	.145	.155	3.68	3.94
CH	.049	.075	1.24	1.91
LH		.020		0.51
LW1	.135	.145	3.43	3.68
LW2	.047	.057	1.19	1.45
LL1	.085	.125	2.16	3.17
LL2	.045	.075	1.14	1.91
LS1	.070	.095	1.78	2.41
LS2	.035	.048	0.890	1.21
Q1	.030	.070	0.76	1.78
Q2	.020	.035	0.510	0.890
Term 1	Collector			
Term 2	Base			
Term 3	Emitter			

NOTES:
1. Dimensions are in inches.
2. Millimeters are given for general information only.
* 3. In accordance with ASME Y14.5, diameters are equivalent to ϕx symbology.

FIGURE 2. Physical dimensions and configuration (U4).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

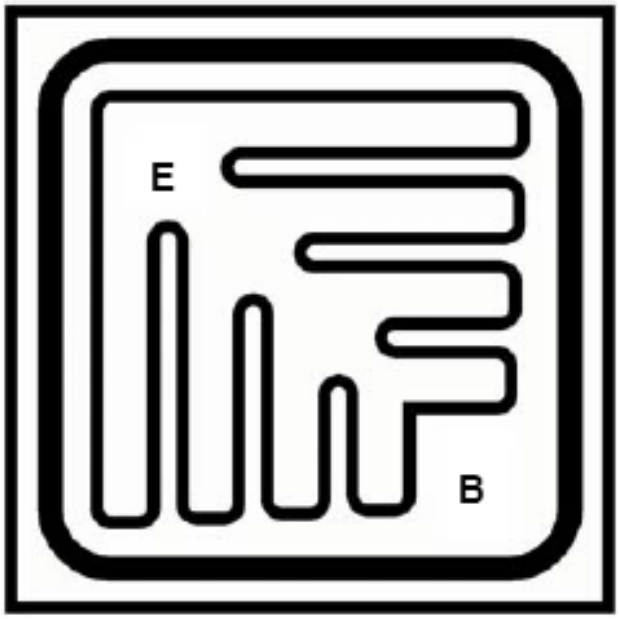

1. Chip size: .075 x .075 inch ±.002 inches (1.905 x 1.905 mm ±0.051 mm).
2. Chip thickness: .014 ±.003 inch nominal (0.356 ±0.0762 mm).
3. Top metal: Aluminum 110,000 Å minimum, 125,000 Å nominal.
4. Back metal: Al/Ti/Ni/Au 10,000 Å minimum, 12,500 Å nominal.
5. Backside: Collector.
6. Bonding pad: B = .014 x .014 inch (0.3556 x 0.3556 mm), E = .014 x .014 inch (0.3556 x 0.3556 mm).

* 7. In accordance with ASME Y14.5, diameters are equivalent to ϕx symbology.

FIGURE 3. JANHCC and JANKCC-version die dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturer's list (QML) before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500.

$R_{\theta JA}$	Thermal resistance junction to ambient.
$R_{\theta JC}$	Thermal resistance junction to case.

3.4 Interface and physical dimensions. Interface and physical dimensions shall be as specified in MIL-PRF-19500, and on figure 1, (similar to TO-5 and TO-39), figure 2 (surface mount), and figure 3 (die) herein.

3.4.1 Lead finish. Lead finish shall be solderable in accordance with MIL-PRF-19500, MIL-STD-750, and herein. Where a choice of lead finish is desired, it shall be specified in the acquisition document (see 6.2).

3.5 Radiation hardness assurance (RHA). Radiation hardness assurance requirements, PIN designators, and test levels shall be as defined in MIL-PRF-19500.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I.

3.7 Marking. Marking shall be in accordance with MIL-PRF-19500. The radiation hardened designator M, D, P, L, R, F, G, or H shall immediately precede (or replace) the device “2N” identifier (depending upon degree of abbreviation required).

3.8 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3).

c. Conformance inspection (see 4.4 and, tables I, II, and III).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.2.1 Group E qualification. Group E inspection shall be performed for qualification or re-qualification only. In case qualification was awarded to a prior revision of the specification sheet that did not request the performance of table III tests, the tests specified in table III herein that were not performed in the prior revision shall be performed on the first inspection lot of this revision to maintain qualification.

4.2.2 JANHC and JANKC qualification. JANHC and JANKC qualification inspection shall be in accordance with MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

4.3 Screening.

* 4.3.1 Screening of packaged devices (quality levels JANS, JANTX and JANTXV only). Screening of packaged devices shall be in accordance with table E-IV of MIL-PRF-19500, and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen	Measurements for JANS level	Measurements for JANTX and JANTXV levels
(1) 3c	Thermal impedance (see 4.3.3)	Thermal impedance (see 4.3.3)
9	I_{CEX1} and h_{FE2}	I_{CEX1}
11	I_{CEX1}; h_{FE2}; ΔI_{CEX1} = 100 percent or 50 nA dc, whichever is greater; Δh_{FE2} = +15, -10 percent change of initial value.	I_{CEX1} and h_{FE2}; ΔI_{CEX1} = 100 percent or 100 nA dc, whichever is greater.
12	See 4.3.2	See 4.3.2
13	Subgroups 2 and 3 of table I herein; ΔI_{CEX1} = 100 percent or 50 nA dc, whichever is greater; Δh_{FE2} = +15, -10 percent of initial value.	Subgroup 2 of table I herein; ΔI_{CEX1} = 100 percent or 100 nA dc, whichever is greater; Δh_{FE2} = +20, -10 percent of initial value.

(1) Shall be performed anytime after temperature cycling, screen 3a; JANTX and JANTXV levels do not need to be repeated in screening requirements.

* 4.3.2 Power burn-in conditions. Power burn-in conditions are as follows: V_{CB} = 10 - 30 V dc. Power shall be applied to achieve T_J = +175°C minimum and a minimum P_D = 75 percent of P_T maximum rated as defined in 1.3.

* 4.3.3 Thermal impedance. The thermal impedance measurements shall be performed in accordance with method 3131 of MIL-STD-750 using the guidelines in that method for determining I_M, I_H, t_H, t_{MD}, t_{SW} (V_C and V_H where appropriate). See table III, group E, subgroup 4 herein.

* 4.3.4 Screening of unencapsulated die (JANHC and JANKC). Screening of JANHC and JANKC unencapsulated die shall be in accordance with appendix G of MIL-PRF-19500. The burn-in duration for JANKC level shall follow the JANS requirements; the JANHC level shall follow the JANTX requirements of table E-IV of MIL-PRF-19500.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with MIL-PRF-19500 and table I herein.

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VIA (JANS) of MIL-PRF-19500 and 4.4.2.1. See 4.4.2.2 for JAN, JANTX, and JANTXV group B testing. Electrical measurements (end-points) for JAN, JANTX, and JANTXV shall be after each step in 4.4.2.2 and shall be in accordance with table I, subgroup 2 herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

4.4.2.1 Group B inspection, table E-VIA (JANS) of MIL-PRF-19500.

Subgroup	Method	Condition
B3	2037	Test condition D. All internal wires for each device shall be pulled separately.
B4	1037	V_{CB} = 5 V dc, 2,000 cycles, adjust device current, or power, to achieve a minimum ΔT_J of +100°C.
B5	1027	V_{CB} = 5 V dc, P_T adjusted to achieve T_J and time required in MIL-PRF-19500.

4.4.2.2 Group B inspection, (JAN, JANTX, and JANTXV). Separate samples may be used for each step. In the event of a lot failure, the resubmission requirements of MIL-PRF-19500 shall apply. In addition, all catastrophic failures during CI shall be analyzed to the extent possible to identify root cause and corrective action. Whenever a failure is identified as wafer lot and wafer processing related, the entire wafer lot and related devices assembled from the wafer lot shall be rejected unless an appropriate determined corrective action to eliminate the failures mode has been implemented and the devices from the wafer lot are screened to eliminate the failure mode.

Step	Method	Condition
1	1026	Steady-state life: 1,000 hours minimum, V_{CB} = 10 V dc, power shall be applied to achieve T_J = +150°C minimum using a minimum of P_D = 75 percent of maximum rated P_T as defined in 1.3. n = 45 devices, c = 0. The sample size may be increased and the test time decreased as long as the devices are stressed for a total of 45,000 device hours minimum, and the actual time of test is at least 340 hours.
2	1048	Blocking life, T_A = +150°C, V_{CB} = 80 percent of rated voltage, 48 hours minimum. n = 45 devices, c = 0.
3	1032	High-temperature life (non-operating), t = 340 hours, T_A = +200°C. n = 22, c = 0.

4.4.2.3 Group B sample selection. Samples selected from group B inspection shall meet all of the following requirements:

a. For JAN, JANTX, and JANTXV samples shall be selected randomly from a minimum of three wafers (or from each wafer in the lot) from each wafer lot. For JANS, samples shall be selected from each inspection lot. See MIL-PRF-19500.

b. Shall be chosen from an inspection lot that has been submitted to and passed table I, subgroup 2, conformance inspection. When the final lead finish is solder or any plating prone to oxidation at high temperature, the samples for life test (subgroups B4 and B5 for JANS, and group B for JAN, JANTX, and JANTXV) may be pulled prior to the application of final lead finish.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-VII of MIL-PRF-19500 and herein.

Subgroup	Method	Condition
C2	2036	Test condition E, not applicable for U4.
C5	3131	$R_{\theta JA}$ and $R_{\theta JC}$ only, as applicable (see 1.3) and in accordance with thermal impedance curves.
C6	1026	T_A = +25 ±5°C; T_J = +150°C minimum. (Not applicable to JAN, JANTX, and JANTXV). V_{CB} = 40 V dc for types 2N3418, 2N3418S, 2N3418U4, 2N3420, 2N3420S, and 2N3420U4. V_{CB} = 60 V dc for types 2N3419, 2N3419S, 2N3419U4, 2N3421, 2N3421S, and 2N3421U4.

4.4.3.2 Group C sample selection. Samples for subgroups in group C shall be chosen at random from any inspection lot containing the intended package type and lead finish procured to the same specification which is submitted to and passes table I tests for conformance inspection. When the final lead finish is solder or any plating prone to oxidation at high temperature, the samples for C6 life test may be pulled prior to the application of final lead finish. Testing of a subgroup using a single device type enclosed in the intended package type shall be considered as complying with the requirements for that subgroup.

4.4.4 Group D inspection. Conformance inspection for hardness assured JANS and JANTXV types shall include the group D tests specified in table II herein. These tests shall be performed as required in accordance with MIL-PRF-19500 and method 1019 of MIL-STD-750, for total ionizing dose or method 1017 of MIL-STD-750 for neutron fluence as applicable (see 6.2 herein), except group D, subgroup 2 may be performed separate from other subgroups. Alternate package options may also be substituted for the testing provided there is no adverse effect to the fluence profile.

4.4.5 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in appendix E, table E-IX of MIL-PRF-19500 and as specified in table III herein.

4.5 Methods of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows.

4.5.1 Pulse measurements. Conditions for pulse measurement shall be as specified in section 4 of MIL-STD-750.

* 4.5.2 Displacement damage characterization. For RHA devices, each supplier shall perform a displacement damage characterization. The characterization shall demonstrate exposure versus data and does not indicate pass or fail criteria. The exposure shall be conducted in accordance with method 1017 of MIL-STD-750. The following details shall apply:

a. Samples may be taken from any wafer of the qualification lot.

b. As a minimum, testing shall be at 2E+12 n/cm^2 plus two additional fluence levels chosen by the manufacturer.

c. If the device degrades less than 5 percent of the specification at the highest fluence level, a single data point may be sufficient.

Alternate package options may be substituted for characterization. The displacement damage characterization data shall be made available from the manufacturer.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection.

	Inspection 1/	MIL-STD-750		Symbol	Limit	Limit	Unit
		Method	Conditions		Min	Max	
	Subgroup 1 2/						
	Visual and mechanical examination 3/	2071					
	Solderability 3/ 4/	2026	n = 15 leads, c = 0				
	Resistance to solvents 3/ 4/ 5/	1022	n = 15 devices, c = 0				
*	Salt atmosphere (corrosion) (For laser marked devices only)	1041	n = 6 devices, c = 0,				
	Temp cycling 3/ 4/	1051	Test condition C, 25 cycles. n = 22 devices, c = 0				
	Hermetic seal 4/ Fine leak Gross leak	1071	n = 22 devices, c = 0				
	Electrical measurements 4/		Table I, subgroup 2				
	Bond strength 3/ 4/	2037	Precondition T_A = +250°C at t = 24 hrs or T_A = +300°C at t = 2 hrs n = 11 wires, c = 0				
	De-cap internal visual	2075	n = 4, c = 0				
	Subgroup 2						
	Thermal impedance	3131	See 4.3.3	$Z_{\theta JX}$			°C/W
	Breakdown voltage collector to emitter	3011	Bias condition D; I_C = 50 mA dc, I_B = 0, pulsed (see 4.5.1)	$V_{(BR)CEO}$			
*	2N3418, S, U4 2N3420, S, U4				60		V dc
*	2N3419, S, U4 2N3421, S, U4				80		V dc
	Collector to emitter cutoff current	3041	Bias condition A; V_{BE} = -0.5 V dc	I_{CEX1}			
*	2N3418, S, U4 2N3420, S, U4		V_{CE} = 80 V dc			0.3	µA dc
*	2N3419, S, U4 2N3421, S, U4		V_{CE} = 120 V dc			0.3	µA dc

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection - Continued.

	Inspection 1/	MIL-STD-750		Symbol	Limit	Limit	Unit
		Method	Conditions		Min	Max	
	Subgroup 2 - Continued						
	Collector to emitter cutoff current	3041	Bias condition D; I_B = 0	I_{CEO}			
*	2N3418, S, U4 2N3420, S, U4		V_{CE} = 45 V dc			5.0	µA dc
*	2N3419, S, U4 2N3421, S, U4		V_{CE} = 60 V dc			5.0	µA dc
	Emitter to base cutoff current	3061	Bias condition D; V_{EB} = 6 V dc, I_C = 0	I_{EBO1}		0.5	µA dc
	Emitter to base cutoff current	3061	Bias condition D; V_{EB} = 8 V dc, I_C = 0	I_{EBO2}		10	µA dc
	Forward current transfer ratio	3076	V_{CE} = 2 V dc; I_C = 100 mA dc, pulsed (see 4.5.1)	h_{FE1}			
*	2N3418, S, U4, 2N3419, S, U4				20		
*	2N3420, S, U4, 2N3421, S, U4				40		
	Forward current transfer ratio	3076	V_{CE} = 2 V dc; I_C = 1.0 A dc, pulsed (see 4.5.1)	h_{FE2}			
*	2N3418, S, U4, 2N3419, S, U4				20	60	
*	2N3420, S, U4, 2N3421, S, U4				40	120	
	Forward current transfer ratio	3076	V_{CE} = 2 V dc; I_C = 2 A dc, pulsed (see 4.5.1)	h_{FE3}			
*	2N3418, S, U4, 2N3419, S, U4				15		
*	2N3420, S, U4, 2N3421, S, U4				30		

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection - Continued.

	Inspection 1/	MIL-STD-750		Symbol	Limit	Limit	Unit
		Method	Conditions		Min	Max	
	Subgroup 2 - Continued						
	Forward current transfer ratio	3076	V_{CE} = 5 V dc; I_C = 5 A dc, pulsed (see 4.5.1)	h_{FE4}			
*	2N3418, S, U4, 2N3419, S, U4				10		
*	2N3420, S, U4, 2N3421, S, U4				15		
	Base-emitter voltage (saturated)	3066	Test condition A; I_C = 1.0 A dc, I_B = 0.1 A dc, pulsed (see 4.5.1)	$V_{BE(sat)1}$ 6/	0.6	1.2	V dc
	Base-emitter voltage (saturated)	3066	Test condition A; I_C = 2.0 A dc, I_B = 0.2 A dc, pulsed (see 4.5.1)	$V_{BE(sat)2}$ 6/	0.7	1.4	V dc
	Saturation voltage and resistance (collector-emitter)	3071	I_C = 1.0 A dc, I_B = 0.1 A dc, pulsed (see 4.5.1)	$V_{CE(sat)1}$ 6/		0.25	V dc
	Saturation voltage and resistance (collector-emitter)	3071	I_C = 2.0 A dc, I_B = 0.2 A dc, pulsed (see 4.5.1)	$V_{CE(sat)2}$ 6/		0.5	V dc
	Subgroup 3						
	High-temperature operation:		T_A = +150°C				
	Collector to emitter cutoff current	3041	Bias condition A; V_{BE} = -0.5 V dc	I_{CEX2}			
*	2N3418, S, U4 2N3420, S, U4		V_{CE} = 80 V dc			16	µA dc
*	2N3419, S, U4 2N3421, S, U4		V_{CE} = 120 V dc			16	µA dc
	Low-temperature operation:		T_A = -55°C				
	Forward current transfer ratio	3076	V_{CE} = 2 V dc, I_C = 1 A dc pulsed (see 4.5.1)	h_{FE5}	10		

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limit	Limit	Unit
	Method	Conditions		Min	Max	
Subgroup 4						
Small-signal short-circuit forward-current transfer ratio magnitude of common emitter	3306	V_{CE} = 10 V dc; I_C = 0.1 A dc; f = 20 MHz	$\|h_{fe}\|$	1.3	8	
Open-circuit output capacitance	3236	V_{CB} = 10 V dc, I_E = 0 , 100 kHz ≤ f ≤ 1 MHz	C_{obo}		150	pF
Switching time		I_C = 1.0 A dc, $I_{B(1)}$ = 100 mA dc, $I_{B(2)}$ = -100 mA dc $V_{BE(off)}$ = -3.7 V dc, R_L = 20 Ω, see figure 10	t_r t_d t_s t_f t_{off}		0.22 0.08 1.10 0.20 1.20	µs µs µs µs µs
Subgroup 5						
Safe operating area (continuous dc)	3051	T_C = +100°C, t ≥ 1 s, 1 cycle, see figure 11				
Test 1		I_C = 3 A dc, V_{CE} = 5 V dc				
Test 2		I_C = 0.4 A dc, V_{CE} = 37 V dc				
Test 3						
* 2N3418, S U4, 2N3420, S, U4		I_C = 0.185 A dc, V_{CE} = 60 V dc				
* 2N3419, S, U4, 2N3421, S, U4		I_C = 0.12 A dc, V_{CE} = 80 V dc				
Safe operating area (clamped switching)	3053	T_A = +25°C, I_B = 0.5 A dc, I_C = 3.0 A dc, condition B, see figure 12				
Electrical measurements		See subgroup 2 herein				
Subgroup 6 and 7						
Not applicable						

1/ For sampling plan see MIL-PRF-19500.
2/ For resubmission of failed subgroup 1, double the sample size of the failed test or sequence of tests. A failure in table I, subgroup 1 shall not require retest of the entire subgroup. Only the failed test shall be rerun upon submission.
3/ Separate samples may be used.
4/ Not required for JANS devices.
5/ Not required for laser marked devices.
6/ Measured at a point on the leads no further than .125 inch (3.18 mm) from the case.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

* TABLE II. Group D inspection.

	Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limit	Limit	Unit
		Method	Conditions		Min	Max	
	Subgroup 1 4/						
	Neutron irradiation	1017	Neutron exposure V_{CES} = 0 V				
	Breakdown voltage collector to emitter	3011	Bias condition D; I_C = 50 mA dc, I_B = 0, pulsed (see 4.5.1)	$V_{(BR)CEO}$			
*	2N3418, S, U4 2N3420, S, U4				60		V dc
*	2N3419, S, U4 2N3421, S, U4				80		V dc
	Collector to emitter cutoff current	3041	Bias condition A; V_{BE} = -0.5 V dc	I_{CEX1}			
*	2N3418, S, U4 2N3420, S, U4		V_{CE} = 80 V dc			0.6	µA dc
*	2N3419, S, U4 2N3421, S, U4		V_{CE} = 120 V dc			0.6	µA dc
	Collector to emitter cutoff current	3041	Bias condition D; I_B = 0	I_{CEO}			
*	2N3418, S, U4 2N3420, S, U4		V_{CE} = 45 V dc			10	µA dc
*	2N3419, S, U4 2N3421, S, U4		V_{CE} = 60 V dc			10	µA dc
	Emitter to base cutoff current	3061	Bias condition D; V_{EB} = 6 V dc, I_C = 0	I_{EBO1}		1.0	µA dc
	Emitter to base cutoff current	3061	Bias condition D; V_{EB} = 8 V dc, I_C = 0	I_{EBO2}		20	µA dc
	Forward current transfer ratio	3076	V_{CE} = 2 V dc; I_C = 100 mA dc, pulsed (see 4.5.1)	[h_{FE1}] 5/			
*	2N3418, S, U4, 2N3419, S, U4				[10]		
*	2N3420, S, U4, 2N3421, S, U4				[20]		

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

TABLE II. Group D inspection - Continued.

	Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limit	Limit	Unit
		Method	Conditions		Min	Max	
	Subgroup 1 4/ - Continued						
	Forward current transfer ratio	3076	V_{CE} = 2 V dc; I_C = 1.0 A dc, pulsed (see 4.5.1)	[h_{FE2}] 5/			
*	2N3418, S, U4, 2N3419, S, U4				[10]	60	
*	2N3420, S, U4, 2N3421, S, U4				[20]	120	
	Forward current transfer ratio	3076	V_{CE} = 2 V dc; I_C = 2 A dc, pulsed (see 4.5.1)	[h_{FE3}] 5/			
*	2N3418, S, U4, 2N3419, S, U4				[7.5]		
*	2N3420, S, U4, 2N3421, S, U4				[15]		
	Forward current transfer ratio	3076	V_{CE} = 5 V dc; I_C = 5 A dc, pulsed (see 4.5.1)	[h_{FE4}] 5/			
*	2N3418, S, U4, 2N3419, S, U4				[5}		
*	2N3420, S, U4, 2N3421, S, U4				[7.5]		
	Base-emitter voltage (saturated)	3066	Test condition A; I_C = 1.0 A dc, I_B = 0.1 A dc, pulsed (see 4.5.1)	$V_{BE(sat)1}$ 6/	0.69	1.38	V dc
	Base-emitter voltage (saturated)	3066	Test condition A; I_C = 2.0 A dc, I_B = 0.2 A dc, pulsed (see 4.5.1)	$V_{BE(sat)2}$ 6/	0.81	1.61	V dc
	Saturation voltage and resistance (collector-emitter)	3071	I_C = 1.0 A dc, I_B = 0.1 A dc, pulsed (see 4.5.1)	$V_{CE(sat)1}$ 6/		0.29	V dc
	Saturation voltage and resistance (collector-emitter)	3071	I_C = 2.0 A dc, I_B = 0.2 A dc, pulsed (see 4.5.1)	$V_{CE(sat)2}$ 6/		0.58	V dc

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

* TABLE II. Group D inspection - Continued.

	Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limit	Limit	Unit
		Method	Conditions		Min	Max	
	Subgroup 2						
*	Total dose irradiation	1019	Gamma exposure, Condition A for High dose rate				
	2N3418, S, U4		V_{CES} = 48 V				
*	2N3420, S, U4		V_{CES} = 48 V				
			V_{CES} = 48 V				
	2N3419, S, U4		V_{CES} = 64 V				
*	2N3421, S, U4		V_{CES} = 64 V				
			V_{CES} = 64 V				
	Breakdown voltage collector to emitter	3011	Bias condition D; I_C = 50 mA dc, I_B = 0, pulsed (see 4.5.1)	$V_{(BR)CEO}$			
	2N3418, S, U4				60		V dc
*	2N3420, S, U4						
	2N3419, S, U4				80		V dc
*	2N3421, S, U4						
	Collector to emitter cutoff current	3041	Bias condition A; V_{BE} = -0.5 V dc	I_{CEX1}			
	2N3418, S, U4		V_{CE} = 80 V dc			0.6	µA dc
*	2N3420, S, U4						
	2N3419, S, U4		V_{CE} = 120 V dc			0.6	µA dc
*	2N3421, S, U4						
	Collector to emitter cutoff current	3041	Bias condition D; I_B = 0	I_{CEO}			
	2N3418, S, U4		V_{CE} = 45 V dc			10	µA dc
*	2N3420, S, U4						
	2N3419, S, U4		V_{CE} = 60 V dc			10	µA dc
*	2N3421, S, U4						
	Emitter to base cutoff current	3061	Bias condition D; V_{EB} = 6 V dc, I_C = 0	I_{EBO1}		1.0	µA dc
	Emitter to base cutoff current	3061	Bias condition D; V_{EB} = 8 V dc, I_C = 0	I_{EBO2}		20	µA dc

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

TABLE II. Group D inspection - Continued.

	Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limit	Limit	Unit
		Method	Conditions		Min	Max	
	Subgroup 2 - Continued						
	Forward current transfer ratio	3076	V_{CE} = 2 V dc; I_C = 100 mA dc, pulsed (see 4.5.1)	[h_{FE1}] 5/			
*	2N3418, S, U4, 2N3419, S, U4				[10]		
*	2N3420, S, U4, 2N3421, S, U4				[20]		
	Forward current transfer ratio	3076	V_{CE} = 2 V dc; I_C = 1.0 A dc, pulsed (see 4.5.1)	[h_{FE2}] 5/			
*	2N3418, S, U4, 2N3419, S, U4				[10]	60	
*	2N3420, S, U4, 2N3421, S, U4				[20]	120	
	Forward current transfer ratio	3076	V_{CE} = 2 V dc; IC = 2 A dc, pulsed (see 4.5.1)	[h_{FE3}] 5/			
*	2N3418, S, U4, 2N3419, S, U4				[7.5]		
*	2N3420, S, U4, 2N3421, S, U4				[15]		
	Forward current transfer ratio	3076	V_{CE} = 5 V dc; IC = 5 A dc, pulsed (see 4.5.1)	[h_{FE4}] 5/			
*	2N3418, S, U4, 2N3419, S, U4				[5}		
*	2N3420, S, U4, 2N3421, S, U4				[7.5]		
	Base-emitter voltage (saturated)	3066	Test condition A; I_C = 1.0 A dc, I_B = 0.1 A dc, pulsed (see 4.5.1)	$V_{BE(sat)1}$ 6/	0.69	1.38	V dc
	Base-emitter voltage (saturated)	3066	Test condition A; I_C = 2.0 A dc, I_B = 0.2 A dc, pulsed (see 4.5.1)	$V_{BE(sat)2}$ 6/	0.81	1.61	V dc

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

TABLE II. Group D inspection - Continued.

Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limit	Limit	Unit
	Method	Conditions		Min	Max	
Subgroup 2 - Continued						
Saturation voltage and resistance (collector-emitter)	3071	I_C = 1.0 A dc, I_B = 0.1 A dc, pulsed (see 4.5.1)	$V_{CE(sat)1}$ 6/		0.29	V dc
Saturation voltage and resistance (collector-emitter)	3071	I_C = 2.0 A dc, I_B = 0.2 A dc, pulsed (see 4.5.1)	$V_{CE(sat)2}$ 6/		0.58	V dc


1/ Tests to be performed on all devices receiving radiation exposure.
2/ For sampling plan, see MIL-PRF-19500.
3/ Electrical characteristics apply to the corresponding U4 suffix versions unless otherwise noted.
* 4/ See 6.2.e herein.
5/ See method 1019 of MIL-STD-750 for how to determine [h_{FE}] by first calculating the delta (1/h_{FE}) from the pre- and Post-radiation h_{FE}. Notice the [h_{FE}] is not the same as h_{FE} and cannot be measured directly. The [h_{FE}] value can never exceed the pre-radiation minimum h_{FE} that it is based upon.
6/ Measured at a point on the leads no more than .125 inch (3.18 mm) from the case.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

TABLE III. Group E inspection (all quality levels) - for qualification and re-qualification only.

Inspection	MIL-STD-750		Qualification
	Method	Conditions	
Subgroup 1			45 devices c = 0
Temperature cycling (air to air)	1051	Test condition C, 500 cycles	
Hermetic seal Fine leak Gross leak	1071		
Electrical measurements		See table I, subgroup 2.	
Subgroup 2			45 devices c = 0
Intermittent life	1037	Intermittent operation life: V_{CB} = 10 V dc, 6,000 cycles. Adjust device current, or power, to achieve a minimum ΔT_J of +100°C.	
Electrical measurements		See table I, subgroup 2.	
Subgroup 4			
Thermal impedance curves		See MIL-PRF-19500, table E-IX, group E, subgroup 4.	
Subgroup 5			
Not applicable			
Subgroup 8			45 devices c = 0
Reverse stability	1033	Condition B.	
Subgroup 12			
* Neutron Irradiation	1017	See 4.5.2	

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

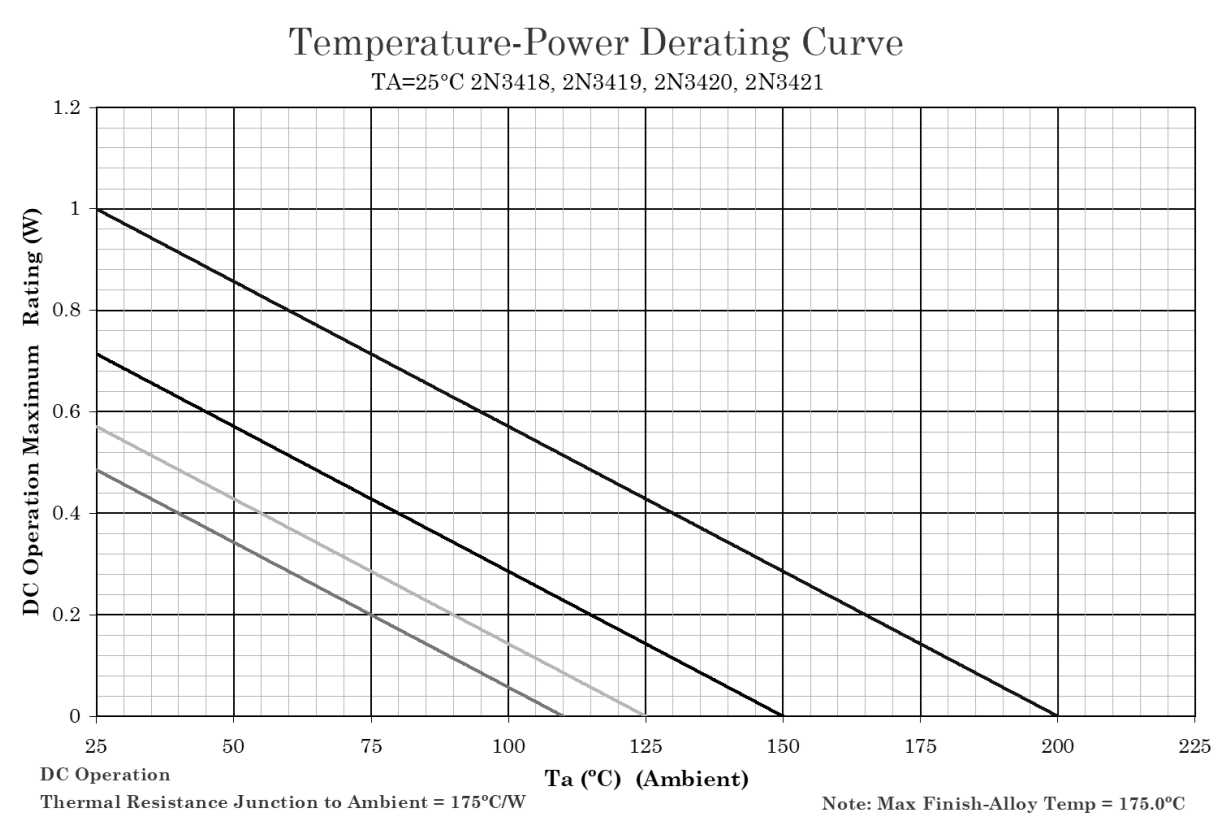


NOTES:

1. All devices are capable of operating at ≤ T_J specified on this curve. Any parallel line to this curve will intersect the appropriate power for the desired maximum T_J allowed.
2. Derate design curve constrained by the maximum junction temperatures and power rating specified. (See 1.3 herein.)
3. Derate design curve chosen at $T_J \leq 150°C$, where the maximum temperature of electrical test is performed.
4. Derate design curve chosen at $T_J \leq 125°C$, and 110°C to show power rating where most users want to limit T_J in their application.

FIGURE 4. Derating for 2N3418, 2N3418S, 2N3419, 2N3419S, 2N3420, 2N3420S, 2N3421, and 2N3421S ($R_{\theta JA}$) leads .375 inch (9.53 mm) PCB (TO-5 and TO-39).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

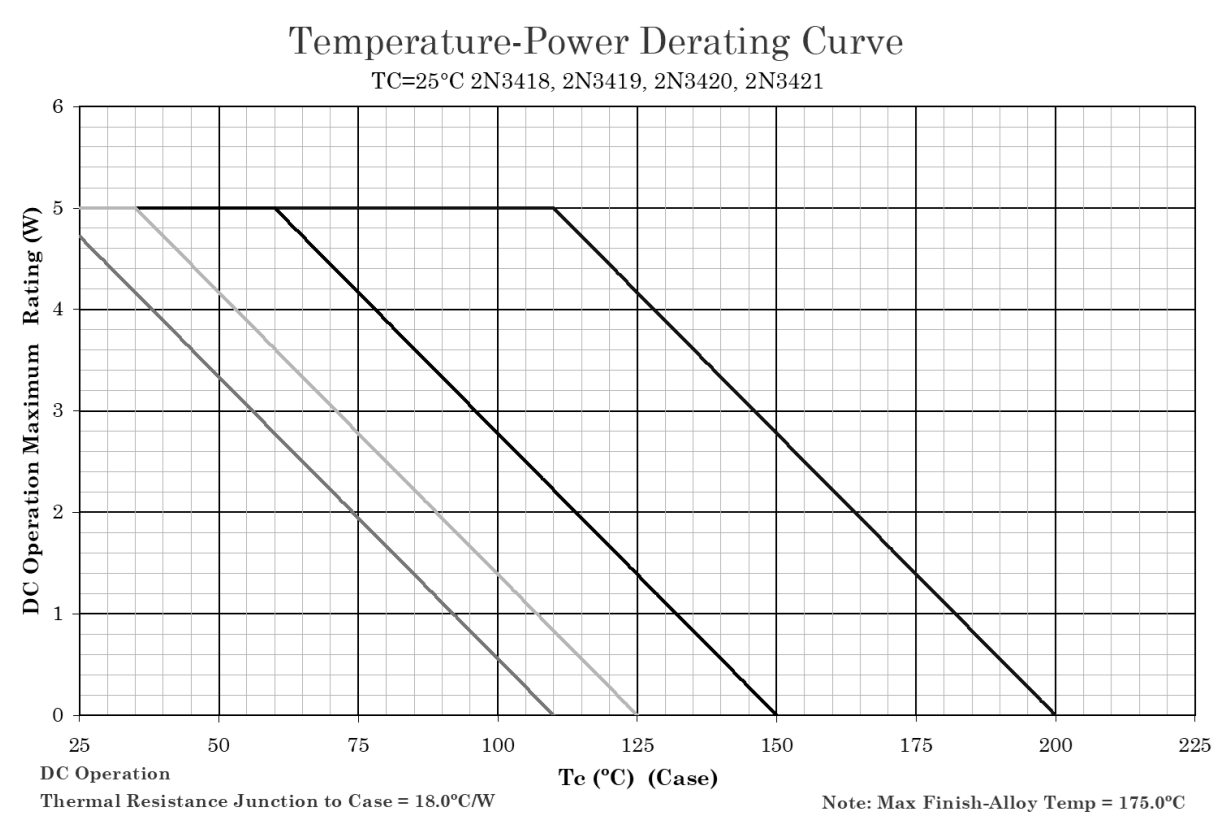


NOTES:

1. All devices are capable of operating at ≤ T_J specified on this curve. Any parallel line to this curve will intersect the appropriate power for the desired maximum T_J allowed.
2. Derate design curve constrained by the maximum junction temperatures and power rating specified. (See 1.3 herein.)
3. Derate design curve chosen at $T_J \leq 150°C$, where the maximum temperature of electrical test is performed.
4. Derate design curve chosen at $T_J \leq 125°C$, and 110°C to show power rating where most users want to limit T_J in their application.

FIGURE 5. Derating for 2N3418, 2N3418S, 2N3419, 2N3419S, 2N3420, 2N3420S, 2N3421, and 2N3421S ($R_{\theta JC}$) (TO-5 and TO-39).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

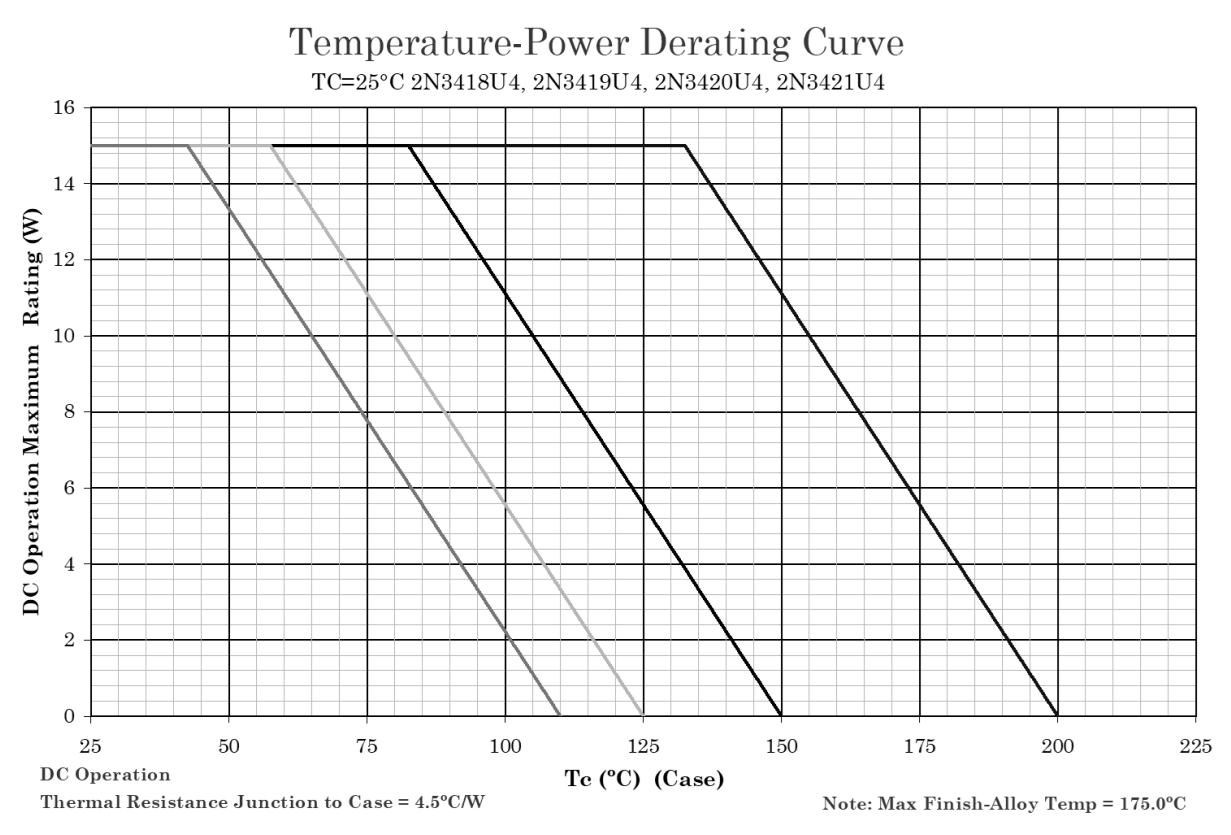


NOTES:

1. All devices are capable of operating at ≤ T_J specified on this curve. Any parallel line to this curve will intersect the appropriate power for the desired maximum T_J allowed.
2. Derate design curve constrained by the maximum junction temperatures and power rating specified. (See 1.3 herein.)
3. Derate design curve chosen at $T_J \leq 150°C$, where the maximum temperature of electrical test is performed.
4. Derate design curve chosen at $T_J \leq 125°C$, and 110°C to show power rating where most users want to limit T_J in their application.

FIGURE 6. Derating for 2N3418U4, 2N3419U4, 2N3420U4, and 2N3421U4 ($R_{\theta JC}$) (U4).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

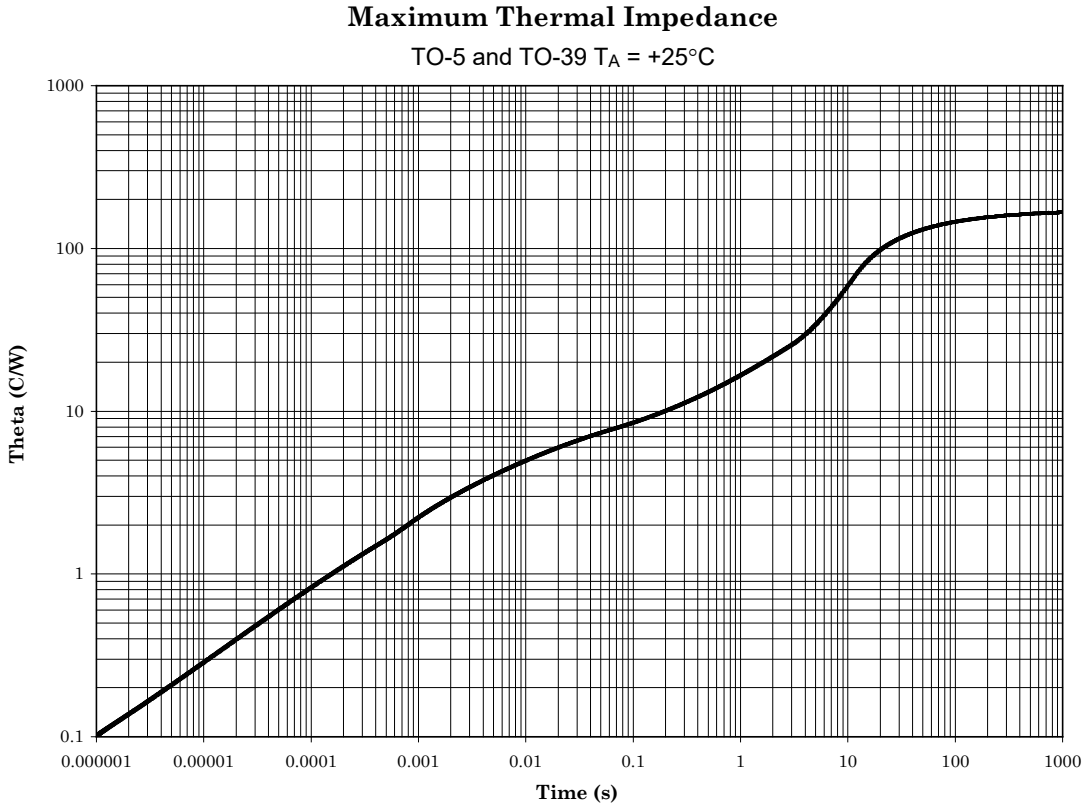


T_A = +25°C, P_{diss} = 1.0 W, Thermal Resistance $R_{\theta JA}$ = 175°C/W

FIGURE 7. Thermal impedance graph ($R_{\theta JA}$) for 2N3418, 2N3418S, 2N3419, 2N3419S, 2N3420, 2N3420S, 2N3421, and 2N3421S leads .375 inch PCB (TO-5 and TO-39).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

Maximum Thermal Impedance


TO-5 and TO-39 T_c = +25°C

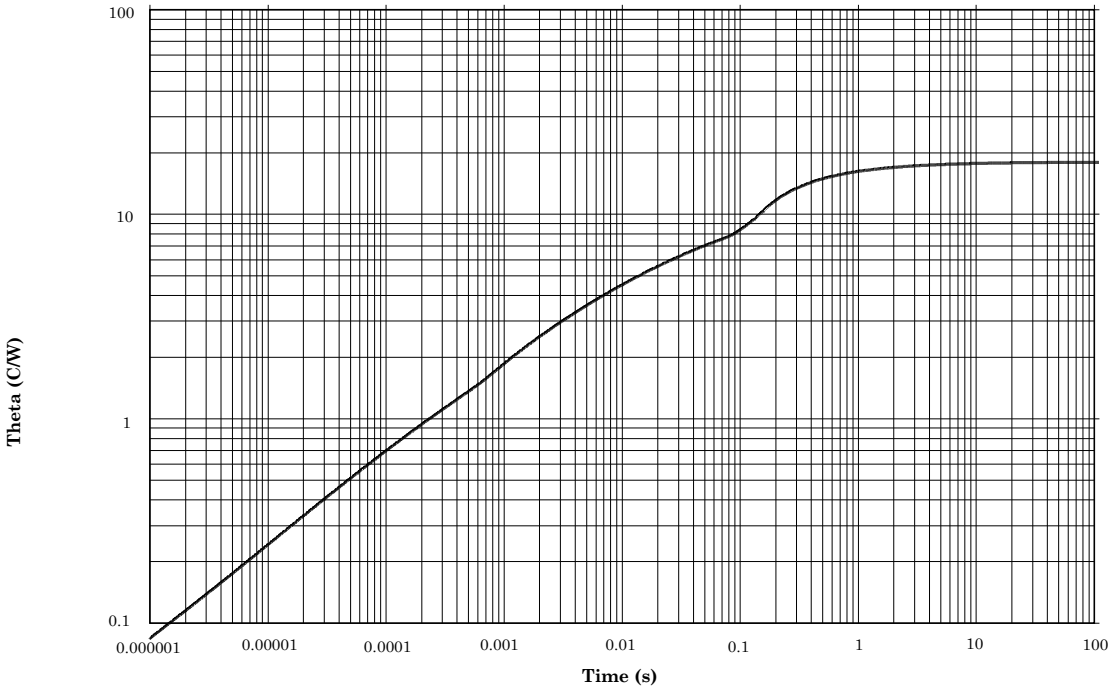

T_c = +25°C, Thermal Resistance $R_{\theta JC}$ = 18°C/W

FIGURE 8. Thermal impedance graph ($R_{\theta JC}$) for 2N3418, 2N3418S, 2N3419, 2N3419S, 2N3420, 2N3420S, 2N3421, and 2N3421S (TO-5 and TO-39).


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

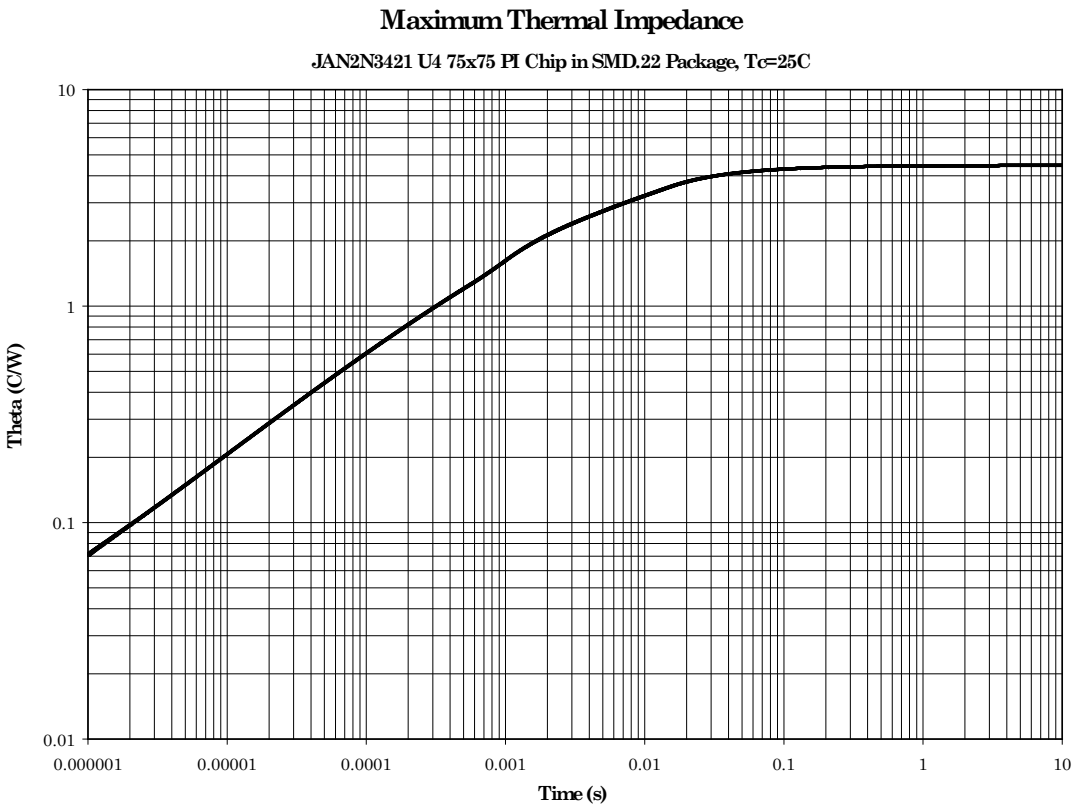

T_c = +25°C, Thermal Resistance $R_{\theta JC}$ = 4.5°C/W, $R_{\theta JX}$ =3.25°C/W at 10ms

FIGURE 9. Thermal impedance graph ($R_{\theta JC}$) for 2N3418U4, 2N3419U4, 2N3420U4 and 2N3421U4 PCB (U4).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

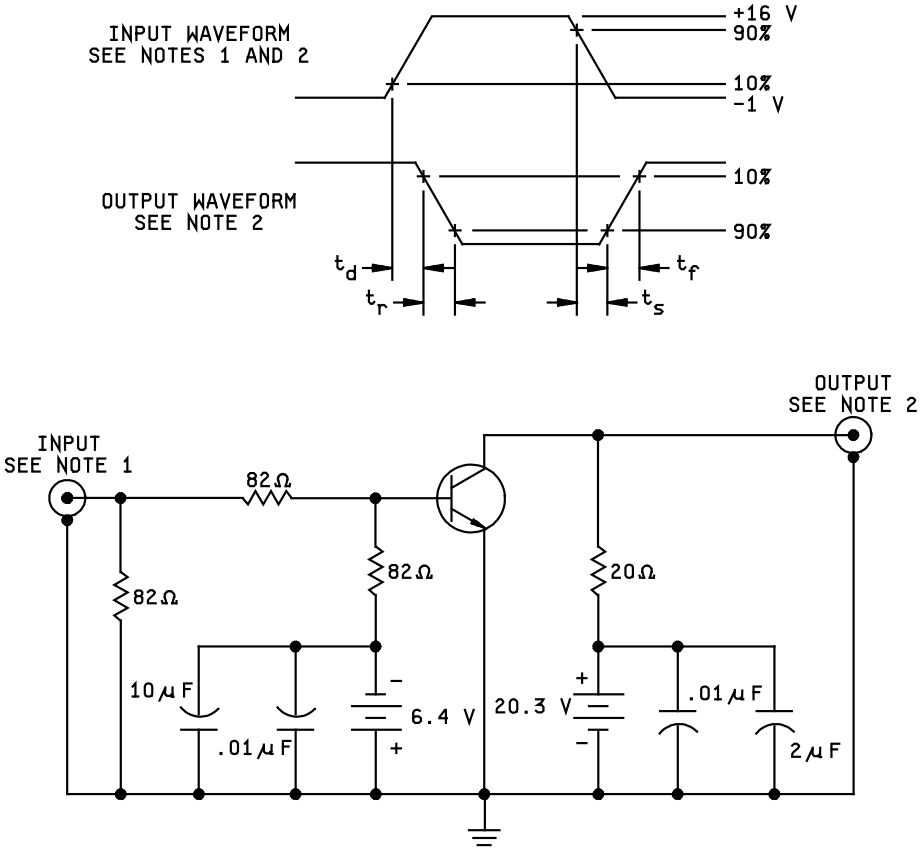


NOTES:

1. The input waveform is supplied by a pulse generator with the following characteristics: $t_r \leq 15$ ns, $t_f \leq 15$ ns, $Z_{OUT} = 50\ \Omega$, PW = 2 μs, duty cycle ≤ 2 percent.
2. Output waveforms are monitored by an oscilloscope with the following characteristics: $t_r \leq 15$ ns, $R_{in} \geq 10\ M\Omega$, $C_{in} \leq 11.5$ pF.
3. Resistors shall be noninductive types.
4. The dc power supplies may require additional by-passing in order to minimize ringing.

FIGURE 10. Pulse response test circuit.


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

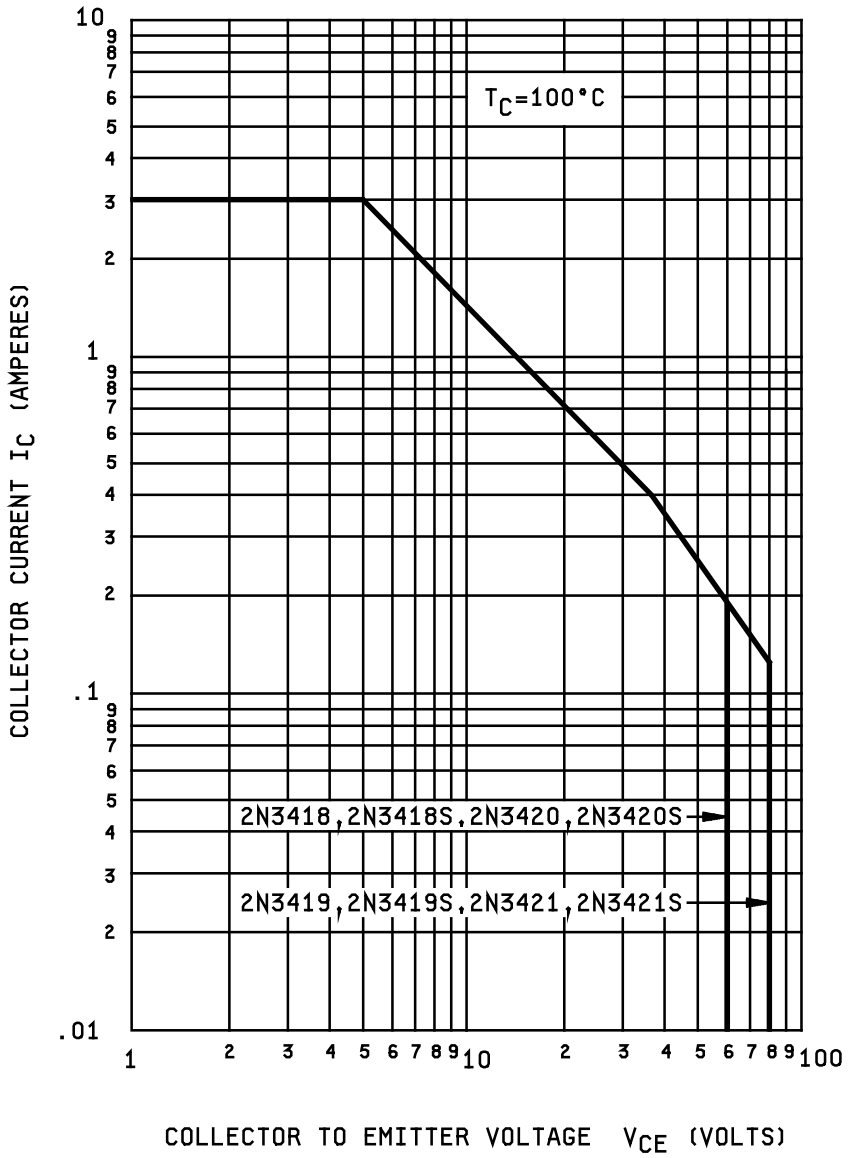

NOTES:
1. The 2N3418U4 and 2N3420U4 devices follow the 2N3418 devices.
2. The 2N3419U4 and 2N3421U4 devices follow the 2N3419 devices.

FIGURE 11. Maximum safe operating region.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

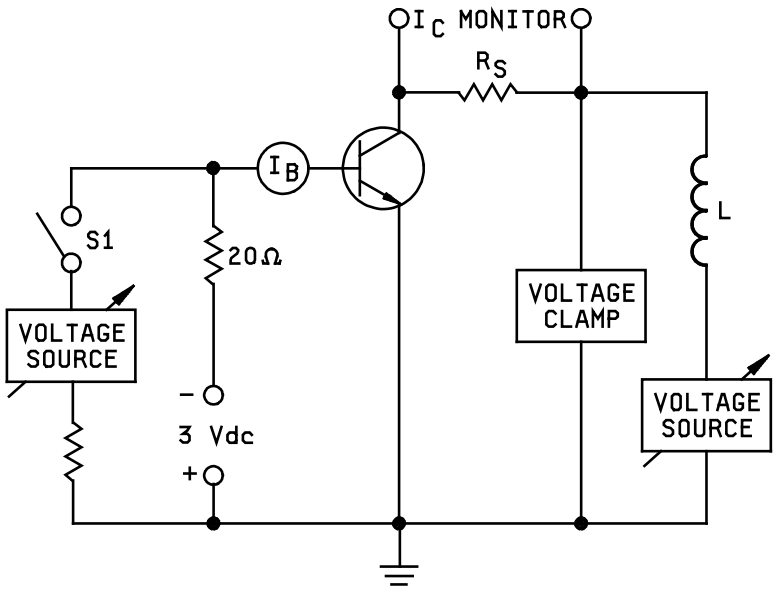

NOTES:
Voltage clamp: 2N3418, 2N2418S, 2N3418U4, 2N3420, 2N3420S, and 2N3420U4 = 85 V dc.
2N3419, 2N3419S, 2N3419U4, 2N3421, 2N3421S, and 2N3421U4 = 125 V dc.

$R_S \leq 1.0\ \Omega$ (noninductive), L = 40 mH

Procedure:
1. With switch S_1 closed, set the specified test conditions.
2. Open S_1.
3. Perform specified end-point tests.

FIGURE 12. Clamped inductive sweep test circuit diagram.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the Military Service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory. The notes specified in MIL-PRF-19500 are applicable to this specification.)

6.1 Intended use. Semiconductors conforming to this specification are intended for original equipment design applications and logistic support of existing equipment.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Packaging requirements (see 5.1).

c. Lead formation and finish (see 3.4.1).

d. The complete Part or Identifying Number (PIN), see 1.5 and 6.5.

e. For acquisition of RHA designated devices, table II, subgroup 1 testing of group D herein is optional. If subgroup 1 is desired, it should be specified in the contract.

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List (QML 19500) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from DLA Land and Maritime, ATTN: VQE, P.O. Box 3990, Columbus, OH 43218-3990 or e-mail vqe.chief@dla.mil. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://assist.dla.mil.


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

6.4. Suppliers of JANHC and JANKC die. The qualified JANHC and JANKC suppliers with the applicable letter version (example JANHCC2N3418) will be identified on the QML.

JANHC and JANKC ordering information	
PIN	Manufacturer
	43611
2N3418	JANHCC2N3418
2N3419	JANHCC2N3419
2N3420	JANHCC2N3420
2N3421	JANHCC2N3421
2N3418	JANKCC2N3418
2N3419	JANKCC2N3419
2N3420	JANKCC2N3420
2N3421	JANKCC2N3421

NOTE: The HCA and KCA die was listed in this document from June 29, 1999 (Rev B) to June 9, 2008 (Rev H), and were never qualified.
The HCB and KCB die was listed in this document from April 20, 2000 (Rev C) to June 9, 2008 (Rev H), and were never qualified.

6.5 PIN construction example. The PINs for encapsulated devices are construction using the following form.

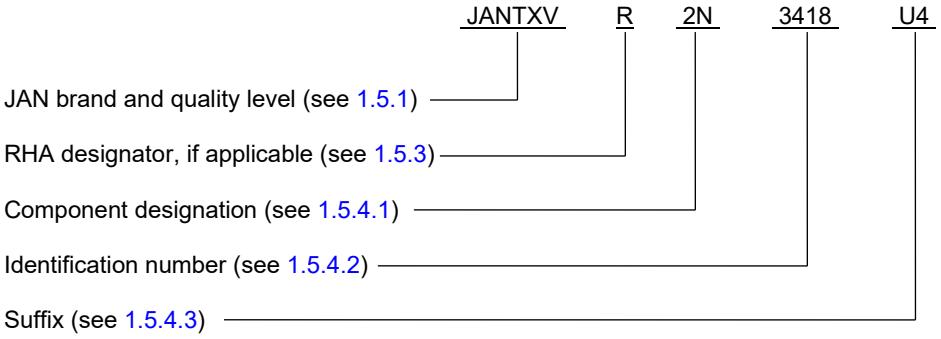

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

6.6 List of PINs.

6.6.1 PINs for encapsulated devices. The following is a list of possible PINs for encapsulated devices available on this specification sheet.

PINs for types 2N3418	PINs for types 2N3418 w/RHA (1)	PINs for types 2N3419	PINs for types 2N3419 w/RHA (1)
JAN2N3418		JAN2N3419	
JAN2N3418S		JAN2N3419S	
JAN2N3418U4		JAN2N3419U4	
JANTX2N3418		JANTX2N3419	
JANTX2N3418S		JANTX2N3419S	
JANTX2N3418U4		JANTX2N3419U4	
JANTXV2N3418	JANTXV#2N3418	JANTXV2N3419	JANTXV#2N3419
JANTXV2N3418S	JANTXV#2N3418S	JANTXV2N3419S	JANTXV#2N3419S
JANTXV2N3418U4	JANTXV#2N3418U4	JANTXV2N3419U4	JANTXV#2N3419U4
JANS2N3418	JANS#2N3418	JANS2N3419	JANS#2N3419
JANS2N3418S	JANS#2N3418S	JANS2N3419S	JANS#2N3419S
JANS2N3418U4	JANS#2N3418U4	JANS2N3419U4	JANS#2N3419U4

PINs for types 2N3420	PINs for types 2N3420 w/RHA (1)	PINs for types 2N3421	PINs for types 2N3421 w/RHA (1)
JAN2N3420		JAN2N3421	
JAN2N3420S		JAN2N3421S	
JAN2N3420U4		JAN2N3421U4	
JANTX2N3420		JANTX2N3421	
JANTX2N3420S		JANTX2N3421S	
JANTX2N3420U4		JANTX2N3421U4	
JANTXV2N3420	JANTXV#2N3420	JANTXV2N3421	JANTXV#2N3421
JANTXV2N3420S	JANTXV#2N3420S	JANTXV2N3421S	JANTXV#2N3421S
JANTXV2N3420U4	JANTXV#2N3420U4	JANTXV2N3421U4	JANTXV#2N3421U4
JANS2N3420	JANS#2N3420	JANS2N3421	JANS#2N3421
JANS2N3420S	JANS#2N3420S	JANS2N3421S	JANS#2N3421S
JANS2N3420U4	JANS#2N3420U4	JANS2N3421U4	JANS#2N3421U4

(1) The number sign (#) represent one of eight RHA designators available (M, D, P, L, R, F, G, or H).

6.6.2 PINs for unencapsulated devices (die). The following is a list of possible PINs for unencapsulated devices available on this specification sheet.

Quality level HC	Quality level HC w/ RHA	Quality level KC	Quality level KC w/ RHA
JANHCC2N3418	JANHCC#2N3418	JANKCC2N3418	JANKCC#2N3418
JANHCC2N3419	JANHCC#2N3419	JANKCC2N3419	JANKCC#2N3419
JANHCC2N3420	JANHCC#2N3420	JANKCC2N3420	JANKCC#2N3420
JANHCC2N3421	JANHCC#2N3421	JANKCC2N3421	JANKCC#2N3421

(1) The number sign (#) represent one of eight RHA designators available (M, D, P, L, R, F, G, or H).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.

6.7 Amendment notations. The margins of this specification are marked with asterisks to indicate modifications generated by this amendment. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the previous issue.

Custodians:
Army - CR
* Navy - SH
Air Force - 85
NASA - NA
DLA - CC

Review activities:
Army - AR, AV, MI
Navy - AS, MC
* Air Force - 19

Preparing activity:
DLA - CC

(Project 5961-2022-029)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:22Z
Check the source to verify that this is the current version before use.