The documentation and process conversion measures necessary to comply with this document shall be completed by 11 August 2026.

INCH-POUND

MIL-PRF-19500/394R
w/AMENDMENT 2
11 May 2026
SUPERSEDING
MIL-PRF-19500/394R
w/AMENDMENT 1
1 August 2022

PERFORMANCE SPECIFICATION SHEET

* TRANSISTOR, RADIATION AND NON-RADIATION HARDENED, NPN, SILICON, POWER SWITCHING, TYPES: 2N4150, 2N5237, 2N5238, THROUGH-HOLE, SURFACE MOUNT, AND UNENCAPSULATED DIE, QUALITY LEVELS JAN, JANTX, JANTXV, JANS, JANHC, AND JANKC

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-PRF-19500.

1. SCOPE

* 1.1 Scope. This specification covers the performance requirements for NPN, silicon, low-power, high voltage radiation hardened transistors. Four levels of product assurance (JAN, JANTX, JANTXV, and JANS) are provided for each encapsulated device type as specified in MIL-PRF-19500. Two levels of product assurance are provided for each unencapsulated device type (JANHC and JANKC). RHA level designators “M”, “D”, “P”, “L”, “R”, “F”, “G”, and “H” are appended to the device prefix to identify devices, which have passed RHA requirements.

* 1.2 Package outlines. The device package outlines are as follows: (TO-5 and TO-39) in accordance with figure 1 and U3 in accordance with figure 2 for all encapsulated device types. See figures 3, 4, and 5 for unencapsulated devices.

1.3 Maximum ratings unless otherwise specified T_A = +25°C.

Types	P_T (1) T_C = +25°C	P_T (2) T_A = +25°C	$R_{\theta JA}$ (max) (3)	$R_{\theta JC}$ (max) (4)	V_{CBO}	V_{CEO}	V_{EBO}	I_C	T_{STG} and T_J
	W	W	°C/W	°C/W	V dc	V dc	V dc	A dc	°C
2N4150, S	15	1.0	175	10	100	70	10	10	-65 to
2N5237, S	15	1.0	175	10	150	120	10	10	+200
2N5238, S	15	1.0	175	10	200	170	10	10	

(1) For derating see figure 6.
(2) For derating see figure 7.
(3) For thermal impedance curve see figure 8.
(4) For thermal impedance curve see figure 9.

Comments, suggestions, or questions on this document should be addressed to DLA Weapons Support, ATTN: VAC, P.O. Box 3990, Columbus, OH 43218-3990, or emailed to Semiconductor@dla.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil/.

AMSC N/A
DISTRIBUTION STATEMENT A. Approved for public release. Distribution is unlimited.

FSC 5961

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

1.4 Primary electrical characteristics unless otherwise specified T_A = +25°C.

Limits	h_{FE2} (1)	h_{FE3} (1)	C_{obo}	$\|h_{fe}\|$	$V_{BE(sat)}$ (1)	$V_{CE(sat)1}$
	I_C = 5 A dc V_{CE} = 5 V dc	I_C = 10 A dc V_{CE} = 5 V dc	I_E = 0 V_{CB} = 10 V dc 100 kHz ≤ f ≤ 1 MHz	I_C = 0.2 A dc V_{CE} = 10 V dc f = 10 MHz	I_C = 5 A dc I_B = 0.5 A dc	I_C = 5 A dc I_B = 0.5 A dc
			pF		V dc	V dc
Min	40	10		1.5		
Max	120		350	7.5	1.5	0.6

(1) Pulsed, (see 4.5.1).

1.5 Part or Identifying Number (PIN). The PIN is in accordance with MIL-PRF-19500, and as specified herein. See 6.4 for PIN construction example and 6.5 for a list of available PINs.

1.5.1 JAN certification mark and quality level for encapsulated devices. The quality level designators for encapsulated devices that are applicable for this specification sheet from the lowest to the highest level are as follows: “JAN”, “JANTX”, “JANTXV” and "JANS".

1.5.2 JAN certification mark and quality level for unencapsulated devices (die). The quality level designators for unencapsulated devices (die) that are applicable for this specification sheet from the lowest to the highest level are as follows: "JANHC" and "JANKC".

1.5.3 Radiation hardness assurance (RHA) designator. The RHA levels that are applicable for this specification sheet from lowest to highest are as follows: "M", "D", "P", "L", "R", "F", "G", and "H".

1.5.4 Device type. The designation system for the device types of transistors covered by this specification sheet are as follows.

1.5.4.1 First number and first letter symbols. The transistors of this specification sheet use the first number and letter symbols "2N".

1.5.4.2 Second number symbols. The second number symbols for the transistors covered by this specification sheet are as follows: "4150", "5237", and "5238".

* 1.5.4.3 Suffix symbols. The following suffix symbols are incorporated in the PIN as applicable.

	A blank first suffix symbol indicates a 3 lead metal can package with lead dimension LL = 1.5 inches (38.10 mm) min and 1.75 inches (44.45 mm) max. (see figure 1, TO-5)
S	Indicates a 3 lead metal can package with lead dimension LL = .5 inches (12.70 mm) min and .750 inch (19.05 mm) max. (see figure 1, TO-39).
U3	Indicates a 3 pad surface mount package, (see figure 2)

1.5.5 Lead finish. The lead finishes applicable to this specification sheet are listed on QPDSIS-19500.

1.5.6 Die identifiers for unencapsulated devices (manufacturers and critical interface identifiers). The manufacturer die identifiers that are applicable for this specification sheet are "A", “B”, "C", and “D” (see figures 3, 4, 5 and 6.5.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

1.6 Radiation features. The following radiation features are applicable for RHA devices supplied to this specification sheet.


* 1.6.1 Maximum total ionizing dose (TID). The maximum TID that RHA devices were tested to in accordance with condition A (dose rate = 50 to 300 rad(Si)/s) of method 1019 of MIL-STD-750 are as follows:


For device type 2N4150S:..... 100 krad(Si) 1/

1/ The manufacturers supplying these device types have performed characterization testing in accordance with condition A (dose rate = 50 to 300 rad(Si)/s) of method 1019 of MIL-STD-750. The radiation end point limits are guaranteed only to a maximum TID level of 100 krad(Si).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

Symbol	Inches	Inches	mm	mm	Notes
	Min	Max	Min	Max	
CD	.305	.335	7.75	8.51	
CH	.240	.260	6.10	6.60	
HD	.335	.370	8.51	9.40	
LC	.200 TP		5.08 TP		6
LD	.016	.021	0.41	0.53	7, 8
LL	See notes				7, 8, 11,12
LU	.016	.019	0.41	0.48	7, 8
L_1		.050		1.27	7, 8
L_2	.250		6.35		7, 8
P	.100		2.54		5
Q		.050		1.27	5
r		.010		0.25	10
TL	.029	.045	0.74	1.14	3, 4
TW	.028	.034	0.71	0.86	3
α	45° TP		45° TP		6

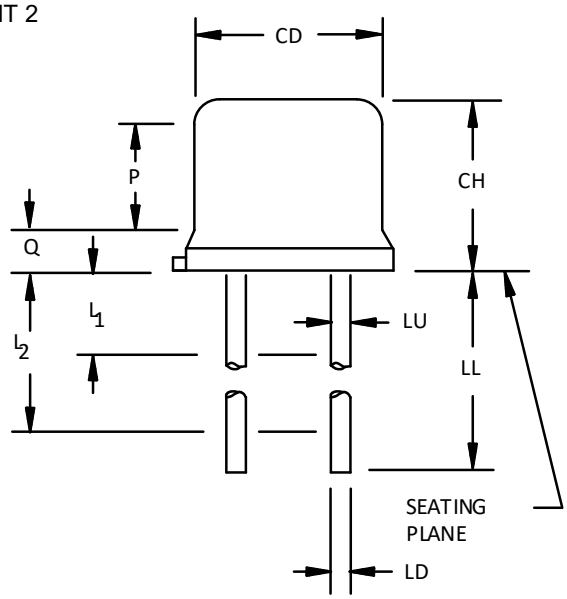


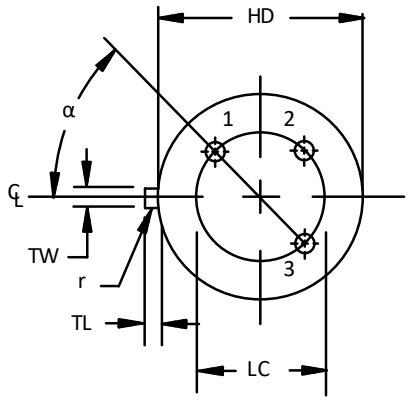


* NOTES:
1. Dimensions are in inches.
2. Millimeters are given for general information only.
3. Beyond r (radius) maximum, TW shall be held for a minimum length of .011 (0.28 mm).
4. Dimension TL measured from maximum HD.
5. Body contour optional within zone defined by HD, CD, and Q.
6. Leads at gauge plane .054 +.001 -.000 inch (1.37 +0.03 -0.00 mm) below seating plane shall be within .007 inch (0.18 mm) radius of true position (TP) at maximum material condition (MMC) relative to tab at MMC.
7. Dimension LU applies between L_1 and L_2. Dimension LD applies between L_2 and LL minimum. Diameter is uncontrolled in L_1 and beyond LL minimum.
8. All three leads.
9. The collector shall be internally connected to the case.
10. Dimension r (radius) applies to both inside corners of tab.
11. For 2N4150, 2N5237, and 2N5238 dimension LL shall be 1.5 inches (38.1 mm) minimum and 1.75 inches (44.4 mm) maximum.
12. For 2N4150S, 2N5237S, and 2N5238S, dimension LL shall be .5 inch (12.7 mm) minimum and .75 inch (19.0 mm) maximum.
13. Lead 1 = emitter, lead 2 = base, lead 3 = collector.

FIGURE 1. Physical dimensions (TO-5 and TO-39).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

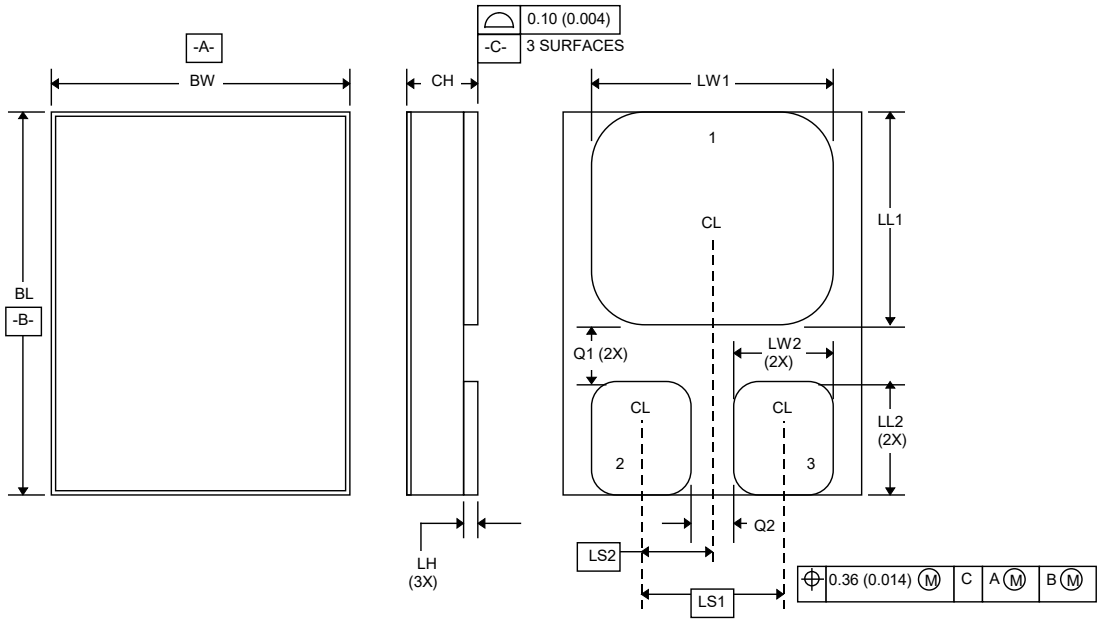

SCHEMATIC




Symbol	Inches	Inches	Millimeters	Millimeters
	Min	Max	Min	Max
BL	.395	.405	10.03	10.29
BW	.291	.301	7.40	7.65
CH	.1085	.1205	2.76	3.06
LH	.010	.020	0.25	0.51
LW1	.281	.291	7.14	7.39
LW2	.090	.100	2.29	2.54
LL1	.220	.230	5.59	5.84
LL2	.115	.125	2.92	3.18
LS1	.150 BSC		3.81 BSC	
LS2	.075 BSC		1.91 BSC	
Q1	.030		0.762	
Q2	.030		0.762	

* NOTES:
1. Dimensions are in inches. Millimeters are given for general information only.
2. Terminal 1 - collector, terminal 2 -base, terminal 3 - emitter.

FIGURE 2. Physical dimensions and configuration (U3) (SMD 5) (TO-276AA).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

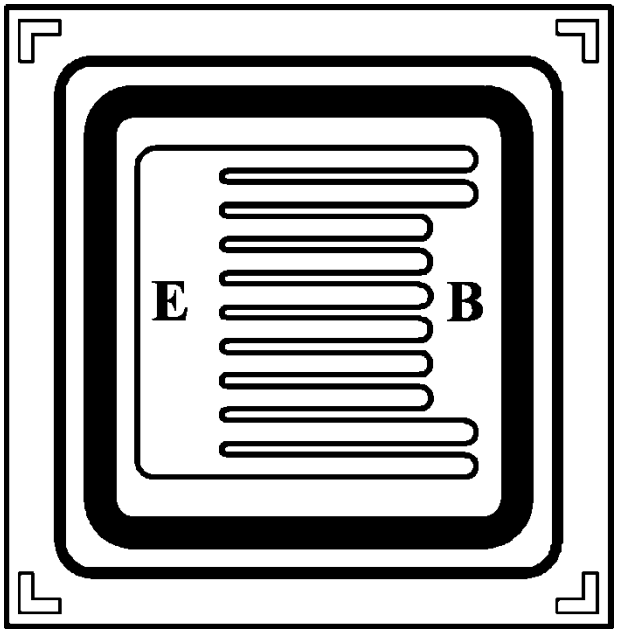


NOTES:

1. Chip size: .128 x .128 inch ±.002 inch (3.25 x 3.25 ±0.051 mm).
2. Chip thickness: .015 inch (0.381 mm) nominal.
3. Top metal: Aluminum 30,000Å minimum, 33,000Å nominal.
4. Back metal: Gold 3,500Å minimum, 5,000Å nominal.
5. Backside: Collector.
6. Bonding pad: B = .052 x .012 inch (1.321 x 0.305 mm), E = .084 x .012 inch (2.134 x 0.305 mm).

FIGURE 3. Physical dimensions for JANHC and JANKC (A-version) die.


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

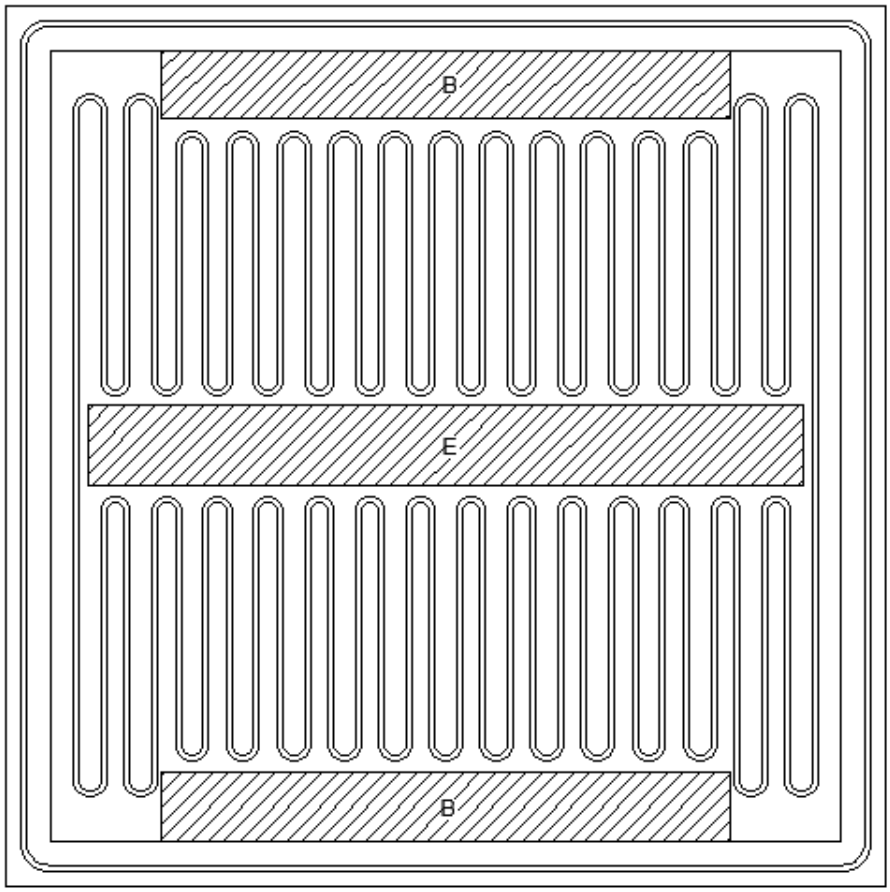

NOTES:
1. Die size: .155 x .155 inch (3.937 x 3.937 mm).
2. Die thickness: .008 ±.0016 inch (0.2032 ±0.04064 mm).
3. Base pad: .012 x .090 inch (0.3048 x 2.286 mm).
4. Emitter pad: .012 x .090 inch.
5. Back metal: Gold, 2,400 ±720 Å.
6. Top metal: Aluminum, 37,500 ±7,500 Å.
7. Back side: Collector.
8. Glassivation: SiO_2, 7,500 ±1,500 Å.

FIGURE 4. Physical dimensions for JANHC and JANKC (B-version) die.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

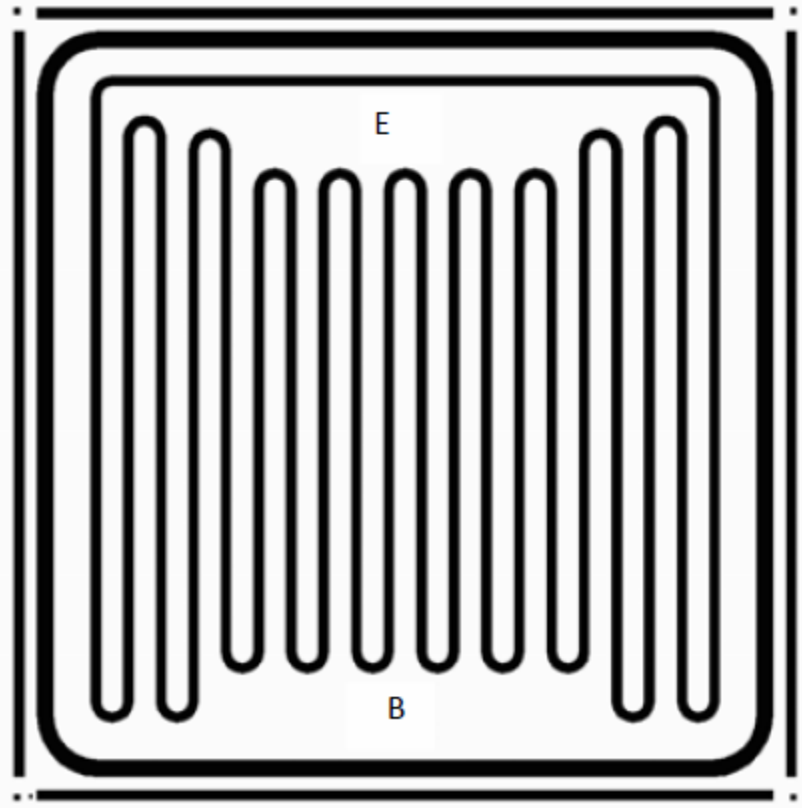

NOTES:

1. Chip size: .120 x .120 inch ±.002 inch (3.05 x 3.05 ±0.05 mm).
2. Chip thickness: .014 ±.0015 inch (0.35 ±0.04 mm) nominal.
3. Top metal: Aluminum 54,000Å minimum, 60,000Å nominal.
4. Back metal: JANHCC/JANKCC Gold 6,400Å minimum, 8,000Å nominal.
   JANHCD/JANKCD Al/Ti/Ni/Au, 10,000 Å minimum, 12,000 Å nominal.
5. Backside: Collector.
6. Bonding pad: B = .060 x .012 inch (1.50 x 0.30 mm), E = .050 x .012 inch (1.27 x 0.30 mm).

FIGURE 5. Physical dimensions for JANHC and JANKC (C-version and D-version) die.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

* 2. APPLICABLE PUBLICATIONS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-750 - Test Methods for Semiconductor Devices.

(Copies of these documents are available online at https://quicksearch.dla.mil).

2.3 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturers list before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500 and as follows.

PCB	Printed circuit board.
$R_{\theta JA}$	Thermal resistance junction to ambient.
$R_{\theta JC}$	Thermal resistance junction to case.

* 3.4 Interface and physical dimensions. Interface and physical dimensions shall be as specified in MIL-PRF-19500, and on figure 1 (TO-5 and TO-39), figure 2 (U3) and on figures 3, 4, and 5 (JANHC and JANKC) herein.

3.4.1 Lead finish. Lead finish shall be solderable in accordance with MIL-PRF-19500, MIL-STD-750, and herein. Where a choice of lead finish is desired, it shall be specified in the acquisition document (see 6.2).

3.4.2 Construction. These devices shall be constructed in a manner and using materials which enable the devices to meet the applicable requirements of MIL-PRF-19500 and this document.

3.5 Radiation hardness assurance (RHA). Radiation hardness assurance requirements, PIN designators, and test levels shall be as defined in MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I.

3.7 Electrical test requirements. The electrical test requirements shall be as specified in table I.

3.8 Marking. Marking shall be in accordance with MIL-PRF-19500. The radiation hardened designator M, D, P, L, R, F, G, or H shall immediately precede (or replace) the device "2N" identifier (depending upon degree of abbreviation required).

3.9 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3).

c. Conformance inspection (see 4.4 and tables I, II, and III).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.2.1 Group E qualification. Group E inspection shall be performed for qualification or re-qualification only. In case qualification was awarded to a prior revision of the specification sheet that did not request the performance of table III tests, the tests specified in table III herein that were not performed in the prior revision shall be performed on the first inspection lot of this revision to maintain qualification.

4.2.2 JANHC and JANKC qualification. JANHC and JANKC qualification inspection shall be in accordance with MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

4.3 Screening (JANS, JANTXV, and JANTX levels only). Screening shall be in accordance with table E-IV of MIL-PRF-19500 and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen	Measurements for JANS level	Measurements for JANTX and JANTXV levels
(1) 3c	Thermal impedance, method 3131 of MIL-STD-750, (see 4.3.2).	Thermal impedance, method 3131 of MIL-STD-750, (see 4.3.2).
9	I_{CBO2} and h_{FE1}	Not applicable
10	48 hours minimum	48 hours minimum
11	I_{CBO2}; h_{FE1}; ΔI_{CB02} = 100 percent of initial value or 50 nA dc, whichever is greater; Δh_{FE1} = ±15 percent of initial value.	I_{CBO2} and h_{FE1}
12	See 4.3.1	See 4.3.1
13	Subgroups 2 and 3 of table I herein; ΔI_{CB02} = 100 percent of initial value or 50 nA dc, whichever is greater; Δh_{FE1} = ±15 percent of initial value.	Subgroup 2 of table I herein; ΔI_{CB02} = 100 percent of initial value or 50 nA dc, whichever is greater; Δh_{FE1} = ±15 percent of initial value.

(1) Shall be performed anytime after temperature cycling, screen 3a; JANTX and JANTXV levels do not need to be repeated in screening requirements.

* 4.3.1 Power burn-in conditions. Power burn-in conditions are as follows: V_{CB} = 10 - 30 Vdc. Power shall be applied to achieve T_J = +135°C minimum using a minimum P_D = 75 percent of P_T maximum rated as defined in 1.3. With approval of the qualifying activity and preparing activity, alternate burn-in criteria (hours, bias conditions, T_J, and mounting conditions) may be used for JANTX and JANTXV quality levels. A justification demonstrating equivalence is required. In addition, the manufacturing site's burn-in data and performance history will be essential criteria for burn-in modification approval.

* 4.3.2 Thermal impedance. The thermal impedance measurements shall be performed in accordance with method 3131 of MIL-STD-750 using the guidelines in that method for determining I_M, I_H, t_H, t_{MD} (and V_C where appropriate). See table III, subgroup 4 herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500 and as specified herein. If alternate screening is being performed in accordance with MIL-PRF-19500, a sample of screened devices shall be submitted to and pass the requirements of group A1 and A2 inspection only (table E-VIB, group B, subgroup 1 is not required to be performed again if group B has already been satisfied in accordance with 4.4.2).

4.4.1 Group A inspection. Group A inspection shall be conducted with MIL-PRF-19500, and table I herein.

* 4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the tests and conditions specified for subgroup testing in table E-VIA (JANS) of MIL-PRF-19500 and 4.4.2.1. Delta measurements shall be in accordance with 4.5.2 herein and only apply to subgroups B4 and B5. See 4.4.2.2 for JAN, JANTX, and JANTXV group B testing. Delta measurements for JAN, JANTX, and JANTXV shall be after each step in 4.4.2.2 and shall be in accordance with 4.5.2 herein.

4.4.2.1 Quality level JANS, table E-VIA of MIL-PRF-19500.

Subgroup	Method	Condition
B4	1037	V_{CB} = 10 V dc, 2,000 cycles, adjust device current, or power, to achieve a minimum ΔT_J of +100°C.
B5	1027	V_{CB} = 10 V dc; $P_D \geq$ 100 percent of maximum rated P_T (see 1.3). (NOTE: If a failure occurs, resubmission shall be at the test conditions of the original sample.) Option 1: 96 hours minimum sample size in accordance with MIL-PRF-19500, table E-VIa, adjust T_A or P_D to achieve T_J = +275°C minimum. Option 2: 216 hours minimum, sample size = 45, c = 0; adjust T_A or P_D to achieve a T_J = +225°C minimum.
B5	2037	Test condition D.

4.4.2.2 Quality levels JAN, JANTX and JANTXV, table E-VIB (JAN, JANTX, and JANTXV) of MIL-PRF-19500. Separate samples may be used for each step. In the event of a lot failure, the resubmission requirements of MIL-PRF-19500 shall apply. In addition, all catastrophic failures during CI, (conformance inspection), shall be analyzed to the extent possible to identify root cause and corrective action. Whenever a failure is identified as wafer lot or wafer processing related, the entire wafer lot and related devices assembled from the wafer lot shall be rejected unless an appropriate determined corrective action to eliminate the failures mode has been implemented and the devices from the wafer lot are screened to eliminate the failure mode.

Step	Method	Condition
1	1026	Steady-state life: 1,000 hours minimum, V_{CB} = 10 V dc, power shall be applied to achieve T_J = +150°C minimum using a minimum of P_D = 75 percent of maximum rated P_T as defined in 1.3. n = 45 devices, c = 0. The sample size may be increased and the test time decreased as long as the devices are stressed for a total of 45,000 device hours minimum, and the actual time of test is at least 340 hours.
2	1048	Blocking life, T_A = +150°C, V_{CB} = 80 percent of rated voltage, 48 hours minimum. n = 45 devices, c = 0.
3	1032	High-temperature life (non-operating), t = 340 hours, T_A = +200°C. n = 22, c = 0.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

4.4.2.3 Group B sample selection. Samples selected from group B inspection shall meet all of the following requirements:

a. For JAN, JANTX, and JANTXV samples shall be selected randomly from a minimum of three wafers (or from each wafer in the lot) from each wafer lot. For JANS, samples shall be selected from each inspection lot. See MIL-PRF-19500.

b. Shall be chosen from an inspection lot that has been submitted to and passed table I, subgroup 2, conformance inspection. When the final lead finish is solder or any plating prone to oxidation at high temperature, the samples for life test (subgroups B4 and B5 for JANS, and group B for JAN, JANTX, and JANTXV) may be pulled prior to the application of final lead finish.

* 4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the tests and conditions specified for subgroup testing in table E-VII of MIL-PRF-19500, and 4.4.3.1 (JANS), and 4.4.3.2 (JAN, JANTX, and JANTXV) herein for group C testing. Delta measurements shall be in accordance with 4.5.2 herein and apply to subgroup C6.

4.4.3.1 Quality level JANS (see table E-VII of MIL-PRF-19500).

Subgroup	Method	Condition
C2	2036	Test condition E, not applicable for U3.
C5	3131	$R_{\theta JA}$ and $R_{\theta JC}$ only, as applicable (see 1.3) and in accordance with thermal impedance curves.
C6	1026	1,000 hours at V_{CB} = 10 V dc; power shall be applied to achieve T_J = +150°C minimum and a minimum of P_D = 75 percent of maximum rated P_T as defined in 1.3, n = 45, c = 0. The sample size may be increased and the test time decreased as long as the devices are stressed for a total of 45,000 device hours minimum, and the actual time of test is at least 340 hours.

4.4.3.2 Quality levels JAN, JANTX and JANTXV (see table E-VII of MIL-PRF-19500).

Subgroup	Method	Condition
C2	2036	Test condition E, not applicable for U3.
C5	3131	$R_{\theta JA}$ and $R_{\theta JC}$ only, as applicable (see 1.3 and 4.3.2) and in accordance with thermal impedance curves.
C6		Not applicable.

4.4.3.3 Group C sample selection. Samples for subgroups in group C shall be chosen at random from any inspection lot containing the intended package type and lead finish procured to the same specification which is submitted to and passes table I tests herein for conformance inspection. When the final lead finish is solder or any plating prone to oxidation at high temperature, the samples for C6 life test may be pulled prior to the application of final lead finish. Testing of a subgroup using a single device type enclosed in the intended package type shall be considered as complying with the requirements for that subgroup.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

4.4.4 Group D inspection. Conformance inspection for hardness assured JANS and JANKC types shall include the group D tests specified in table II herein. These tests shall be performed as required in accordance with MIL-PRF-19500 and method 1019 of MIL-STD-750, for total ionizing dose or method 1017 of MIL-STD-750 for neutron fluence as applicable (see 6.2 herein), except group D, subgroup 2 may be performed separate from other subgroups. Alternate package options may also be substituted for the testing provided there is no adverse effect to the fluence profile.

4.4.5 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-IX of MIL-PRF-19500 and as specified in table III herein. Electrical measurements (end-points) shall be in accordance with table I, subgroup 2 herein; delta measurements shall be in accordance with the applicable steps of 4.5.2.

4.5 Methods of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows.

4.5.1 Pulse measurements. Conditions for pulse measurement shall be as specified in section 4 of MIL-STD-750.

* 4.5.2 Delta measurements. Delta measurements shall be as specified below:

Step	Inspection	MIL-STD-750		Symbol	Limit
		Method	Conditions		
1	Collector-base cutoff current	3036	Bias condition D, V_{CB} = 80 V dc	ΔI_{CB02} (1)	100 percent of initial value or 50 nA dc, whichever is greater.
2	Forward current transfer ratio	3076	V_{CE} = 5 V dc; I_C = 5 A dc; pulsed see 4.5.1 (see figure 10).	Δh_{FE2} (1)	±20 percent change from initial reading.

(1) Devices which exceed the table I limits for this test shall not be accepted.

* 4.6 Element evaluation. Element evaluation of unencapsulated die. The element evaluation of unencapsulated die shall be in accordance with appendix G of MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limit	Limit	Unit
	Method	Conditions		Min	Max	
Subgroup 1 2/						
Visual and mechanical examination 3/	2071					
Solderability 3/ 4/	2026	n = 15 leads, c = 0				
Resistance to solvents 3/ 4/ 5/	1022	n = 15 devices, c = 0				
Salt atmosphere (corrosion) 4/	1041	(Laser marked devices only) n = 6 devices, c = 0				
Temp cycling 3/ 4/	1051	Test condition C, 25 cycles. n = 22 devices, c = 0				
Electrical measurements 4/		Table I, subgroup 2				
Hermetic seal 4/ 6/ Fine leak Gross leak	1071	n = 22 devices, c = 0				
Bond strength 3/ 4/	2037	Precondition T_A = +250°C at t = 24 hours or T_A = +300°C at t = 2 hours, n = 11 wires, c = 0				
Decap internal visual (design verification) 4/	2075	n = 4 devices, c = 0				
Subgroup 2						
Thermal impedance	3131	See 4.3.2	$Z_{\theta JX}$			°C/W
Collector to base cutoff current	3036	Bias condition D;	I_{CBO1}		10	µA dc
2N4150, 2N4150S		V_{CB} = 100 V dc				
2N5237, 2N5237S		V_{CB} = 150 V dc				
2N5238, 2N5238S		V_{CB} = 200 V dc				
Breakdown voltage, collector to emitter	3011	Bias condition D, I_C = 0.1 A dc, pulsed (see 4.5.1).	$V_{(BR)CEO}$			
2N4150, 2N4150S				70		V dc
2N5237, 2N5237S				120		V dc
2N5238, 2N5238S				170		V dc
Emitter to base cutoff current	3061	Bias condition D; V_{EB} = 7 V dc	I_{EBO1}		10	µA dc
Collector to emitter cutoff current	3041	Bias condition D	I_{CEO1}			
2N4150, 2N4150S		V_{CE} = 60 V dc			10	µA dc
2N5237, 2N5237S		V_{CE} = 110 V dc			10	µA dc
2N5238, 2N5238S		V_{CE} = 160 V dc			10	µA dc

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limit	Limit	Unit
	Method	Conditions		Min	Max	
Subgroup 2 - Continued.						
Collector to emitter cutoff current	3041	Bias condition A, V_{BE} = -0.5 V dc.	I_{CEX1}			
2N4150, 2N4150S		V_{CE} = 60 V dc			10	µA dc
2N5237, 2N5237S		V_{CE} = 110 V dc			10	µA dc
2N5238, 2N5238S		V_{CE} = 160 V dc			10	µA dc
Emitter to base cutoff current	3061	Bias condition D, V_{EB} = 5 V dc	I_{EBO2}		0.1	µA dc
Collector to base cutoff current	3036	Bias condition D, V_{CB} = 80 V dc	I_{CBO2}		0.1	µA dc
Forward-current transfer ratio	3076	V_{CE} = 5 V dc, I_C = 1 A dc, pulsed (see 4.5.1)	h_{FE1}			
2N4150, 2N4150S				50	200	
2N5237, 2N5237S				50	225	
2N5238, 2N5238S				50	225	
Forward-current transfer ratio	3076	V_{CE} = 5 V dc, I_C = 5 A dc, pulsed (see 4.5.1)	h_{FE2}	40	120	
Collector to emitter voltage (saturated)	3071	I_C = 5 A dc, I_B = 0.5 A dc, pulsed (see 4.5.1)	$V_{CE(sat)1}$		0.6	V dc
Collector to emitter voltage (saturated)	3071	I_C = 10 A dc, I_B = 1 A dc, pulsed (see 4.5.1)	$V_{CE(sat)2}$		2.5	V dc
Base emitter voltage saturation	3066	Test condition A, I_C = 5 A dc, I_B = 0.5 A dc, pulsed (see 4.5.1)	$V_{BE(sat)1}$		1.5	V dc
Base emitter voltage saturation	3066	Test condition A, I_C = 10 A dc, I_B = 1 A dc, pulsed (see 4.5.1)	$V_{BE(sat)2}$		2.5	V dc
Forward-current transfer ratio	3076	V_{CE} = 5 V dc, I_C = 10 A dc, pulsed (see 4.5.1)	h_{FE3}	10		
Subgroup 3						
High temperature operation:		T_A = +150°C				
Collector to emitter cutoff current	3041	Bias condition A, V_{BE} = -0.5 V dc	I_{CEX2}		100	µA dc
2N4150, 2N4150S		V_{CE} = 60 V dc				
2N5237, 2N5237S		V_{CE} = 110 V dc				
2N5238, 2N5238S		V_{CE} = 160 V dc				
Low temperature operation:		T_A = -55°C				
Forward-current transfer ratio	3076	V_{CE} = 5 V dc, I_C = 5 A dc, pulsed (see 4.5.1)	h_{FE4}	20		

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limit	Limit	Unit
	Method	Conditions		Min	Max	
Subgroup 4						
Magnitude of common-emitter small-signal short-circuit forward-current transfer ratio	3306	V_{CE} = 10 V dc, I_C = 0.2 A dc, f = 10 MHz	$\|h_{fe}\|$	1.5	7.5	
Small-signal short-circuit forward-current transfer ratio	3206	V_{CE} = 5 V dc, I_C = 50 mA dc, f = 1 kHz	h_{fe}			
2N4150, 2N4150S				40	160	
2N5237, 2N5237S				40	160	
2N5238, 2N5238S		figure 10		40	250	
Open circuit output capacitance	3236	V_{CB} = 10 V dc, I_E = 0, 100 kHz ≤ f ≤ 1 MHz	C_{obo}		350	pF
Pulse response	3251	Test condition A				
Delay time		See figure 11	t_d		50	ns
Rise time		See figure 11	t_r		500	ns
Storage time		See figure 11	t_s		1.5	µs
Fall time		See figure 11	t_f		500	ns
Subgroup 5						
Safe operating area (continuous dc)	3051	T_C = +25°C, t = 1.0 s,				
Test 1		V_{CE} = 40 V dc, I_C = 0.22 A dc				
Test 2		V_{CE} = 70 V dc, I_C = 90 mA dc				
Test 3						
2N5237, 2N5237S only		V_{CE} = 120 V dc, I_C = 15 mA dc				
2N5238, 2N5238S only		V_{CE} = 170 V dc, I_C = 3.5 mA dc				
Clamped inductive sweep	3053	T_C = +100°C minimum, I_B = 0.5 A dc, I_C = 5 A dc, (see figure 12)				
Electrical measurements		See 4.5.2 herein.				

1/ For sampling plan see MIL-PRF-19500.
2/ For resubmission of failed test in subgroup 1 of table I, double the sample size of the failed test or sequence of tests. A failure in table I, subgroup 1 shall not require retest of the entire subgroup. Only the failed test shall be rerun upon submission.
3/ Separate samples may be used.
4/ Not required for JANS devices.
5/ Not required for laser marked devices.
6/ This hermetic seal test is an end-point to temp-cycling in addition to electrical measurements.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

TABLE II. Group D inspection

Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limits	Limits	Unit
	Method	Conditions		Min	Max	
Subgroup 1 4/						
Neutron Irradiation	1017	Neutron exposure, V_{CES} = 0V				
Collector to base cutoff current	3036	Bias condition D	I_{CBO1}		20	µA dc
2N4150, 2N4150S		V_{CB} = 100 V dc				
2N5237, 2N5237S		V_{CB} = 150 V dc				
2N5238, 2N5238S		V_{CB} = 200 V dc				
Breakdown voltage, collector to emitter	3011	Bias condition D, I_C = 0.1 A dc, pulsed (see 4.5.1).	$V_{(BR)CEO}$			
2N4150, 2N4150S				70		V dc
2N5237, 2N5237S				120		V dc
2N5238, 2N5238S				170		V dc
Emitter to base cutoff current	3061	Bias condition D, V_{EB} = 7 V dc	I_{EBO1}		20	µA dc
Collector to emitter cutoff current	3041	Bias condition D	I_{CEO1}			
2N4150, 2N4150S		V_{CE} = 60 V dc			20	µA dc
2N5237, 2N5237S		V_{CE} = 110 V dc			20	µA dc
2N5238, 2N5238S		V_{CE} = 160 V dc			20	µA dc
Collector to emitter cutoff current	3041	Bias condition A, V_{BE} = 0.5 V dc.	I_{CEX1}			
2N4150, 2N4150S		V_{CE} = 60 V dc			20	µA dc
2N5237, 2N5237S		V_{CE} = 110 V dc			20	µA dc
2N5238, 2N5238S		V_{CE} = 160 V dc			20	µA dc
Emitter to base cutoff current	3061	Bias condition D, V_{EB} = 5 V dc	I_{EBO2}		0.2	µA dc
Collector to base cutoff current	3036	Bias condition D, V_{CB} = 80 V dc	I_{CBO2}		0.2	µA dc
Forward-current transfer ratio	3076	V_{CE} = 5 V dc, I_C = 1 A dc, pulsed (see 4.5.1)	[h_{FE1}] 5/			
2N4150, 2N4150S				[25]	200	
2N5237, 2N5237S				[25]	225	
2N5238, 2N5238S				[25]	225	
Forward-current transfer ratio	3076	V_{CE} = 5 V dc, I_C = 5 A dc, pulsed (see 4.5.1)	[h_{FE2}] 5/	[20]	120	
Collector to emitter voltage (saturated)	3071	I_C = 5 A dc, I_B = 0.5 A dc, pulsed (see 4.5.1)	$V_{CE(sat)1}$		0.69	V dc
Collector to emitter voltage (saturated)	3071	I_C = 10 A dc, I_B = 1 A dc, pulsed (see 4.5.1)	$V_{CE(sat)2}$		2.88	V dc
Base emitter voltage saturation	3066	Test condition A, I_C = 5 A dc, I_B = 0.5 A dc, pulsed (see 4.5.1)	$V_{BE(sat)1}$		1.73	V dc
Base emitter voltage saturation	3066	Test condition A, I_C = 10 A dc, I_B = 1 A dc, pulsed (see 4.5.1)	$V_{BE(sat)2}$		2.88	V dc
Forward-current transfer ratio	3076	V_{CE} = 5 V dc, I_C = 10 A dc, pulsed (see 4.5.1)	[h_{FE3}] 5/	[5]		

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

TABLE II. Group D inspection - Continued

Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limits	Limits	Unit
	Method	Conditions		Min	Max	
Subgroup 2						
Total Dose Irradiation	1019	Gamma Exposure, Condition A				
2N4150, 2N4150S		Vces = 56V				
2N5237, 2N5237S		Vces = 96V				
2N5238, 2N5238S		Vces = 136V				
Collector to base cutoff current	3036	Bias condition D	I_{CBO1}			
2N4150, 2N4150S		V_{CB} = 100 V dc			20	µA dc
2N5237, 2N5237S		V_{CB} = 150 V dc			20	µA dc
2N5238, 2N5238S		V_{CB} = 200 V dc			20	µA dc
Breakdown voltage, collector to emitter	3011	Bias condition D, I_C = 0.1 A dc, pulsed (see 4.5.1).	$V_{(BR)CEO}$			
2N4150, 2N4150S				70		V dc
2N5237, 2N5237S				120		V dc
2N5238, 2N5238S				170		V dc
Emitter to base cutoff current	3061	Bias condition D, V_{EB} = 7V dc	I_{EBO1}		20	µA dc
Collector to emitter cutoff current	3041	Bias condition D	I_{CEO1}			
2N4150, 2N4150S		V_{CE} = 60 V dc			20	µA dc
2N5237, 2N5237S		V_{CE} = 110 V dc			20	µA dc
2N5238, 2N5238S		V_{CE} = 160 V dc			20	µA dc
Collector to emitter cutoff current	3041	Bias condition A, V_{BE} = 0.5 V dc.	I_{CEX1}			
2N4150, 2N4150S		V_{CE} = 60 V dc			20	µA dc
2N5237, 2N5237S		V_{CE} = 110 V dc			20	µA dc
2N5238, 2N5238S		V_{CE} = 160 V dc			20	µA dc
Emitter to base cutoff current	3061	Bias condition D, V_{EB} = 5 V dc	I_{EBO2}		0.2	µA dc
Collector to base cutoff current	3036	Bias condition D, V_{CB} = 80 V dc	I_{CBO2}		0.2	µA dc
Forward-current transfer ratio	3076	V_{CE} = 5 V dc, I_C = 1 A dc, pulsed (see 4.5.1)	[h_{FE1}] 5/			
2N4150, 2N4150S				[25]	200	
2N5237, 2N5237S				[25]	225	
2N5238, 2N5238S				[25]	225	
Forward-current transfer ratio	3076	V_{CE} = 5 V dc, I_C = 5 A dc, pulsed (see 4.5.1)	[h_{FE2}] 5/	[20]	120	

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

TABLE II. Group D inspection - Continued

Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Limits	Limits	Unit
	Method	Conditions		Min	Max	
Subgroup 2 - Continued						
Collector to emitter voltage (saturated)	3071	I_C = 5 A dc, I_B = 0.5 A dc, pulsed (see 4.5.1)	$V_{CE(sat)1}$		0.69	V dc
Collector to emitter voltage (saturated)	3071	I_C = 10 A dc, I_B = 1 A dc, pulsed (see 4.5.1)	$V_{CE(sat)2}$		2.88	V dc
Base emitter voltage saturation	3066	Test condition A, I_C = 5 A dc, I_B = 0.5 A dc, pulsed (see 4.5.1)	$V_{BE(sat)1}$		1.73	V dc
Base emitter voltage saturation	3066	Test condition A, I_C = 10 A dc, I_B = 1 A dc, pulsed (see 4.5.1)	$V_{BE(sat)2}$		2.88	V dc
Forward-current transfer ratio	3076	V_{CE} = 5 V dc, I_C = 10 A dc, pulsed (see 4.5.1)	$[h_{FE3}]$ 5/	[5]		


1/ Tests to be performed on all devices receiving radiation exposure.
2/ For sampling plan, see MIL-PRF-19500.
3/ Electrical characteristics apply to all device types unless otherwise noted.
4/ See 6.2.e herein.
5/ See method 1019 of MIL-STD-750, for how to determine $[h_{FE}]$ by first calculating the delta($1/h_{FE}$) from the pre and post radiation h_{FE}. Notice that $[h_{FE}]$ is not the same as h_{FE} and cannot be measured directly. The $[h_{FE}]$ value can never exceed the pre-radiation minimum h_{FE} that it is based upon.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

TABLE III. Group E inspection (all quality levels) - for qualification or re-qualification only.

Inspection	MIL-STD-750		Qualification
	Method	Conditions	
Subgroup 1			45 devices c = 0
Temperature cycling (air to air)	1051	Test condition C, 500 cycles.	
Hermetic seal	1071		
Fine leak Gross leak			
Electrical measurements		See table I, subgroup 2 and 4.5.2 herein.	
Subgroup 2			45 devices c = 0
Intermittent life	1037	Intermittent operation life: V_{CB} = 10 V dc, 6,000 cycles. Adjust device current, or power, to achieve a minimum ΔT_J of +100°C.	
Electrical measurements		See table I, subgroup 2 and 4.5.2 herein.	
Subgroup 4			
Thermal impedance curves		See MIL-PRF-19500.	
Subgroup 5			
Not applicable			
Subgroup 8			45 devices c = 0
Reverse stability	1033	Condition B	

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

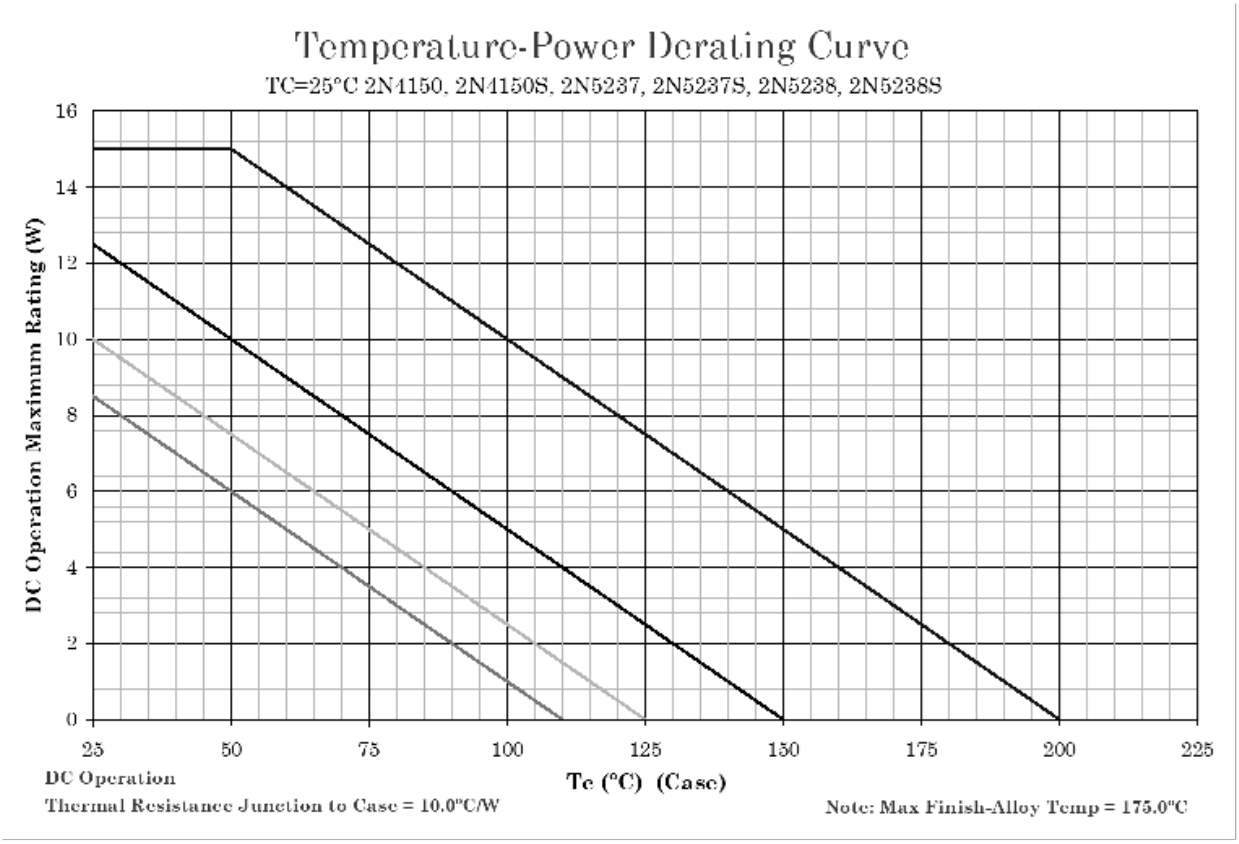


NOTES:

1. All devices are capable of operating at $\leq T_J$ specified on this curve. Any parallel line to this curve will intersect the appropriate power for the desired maximum T_J allowed.
2. Derate design curve constrained by the maximum junction temperature ($T_J \leq +200°C$) and power rating specified. (See 1.3 herein.)
3. Derate design curve chosen at $T_J \leq +150°C$, where the maximum temperature of electrical test is performed.
4. Derate design curves chosen at $T_J \leq$, +125°C, and +110°C to show power rating where most users want to limit T_J in their application.

* FIGURE 6. Derating for 2N4150, 2N5237, 2N5238, 2N4150S, 2N5237S, and 2N5238S ($R_{\theta JC}$) (TO-5 and TO-39).


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

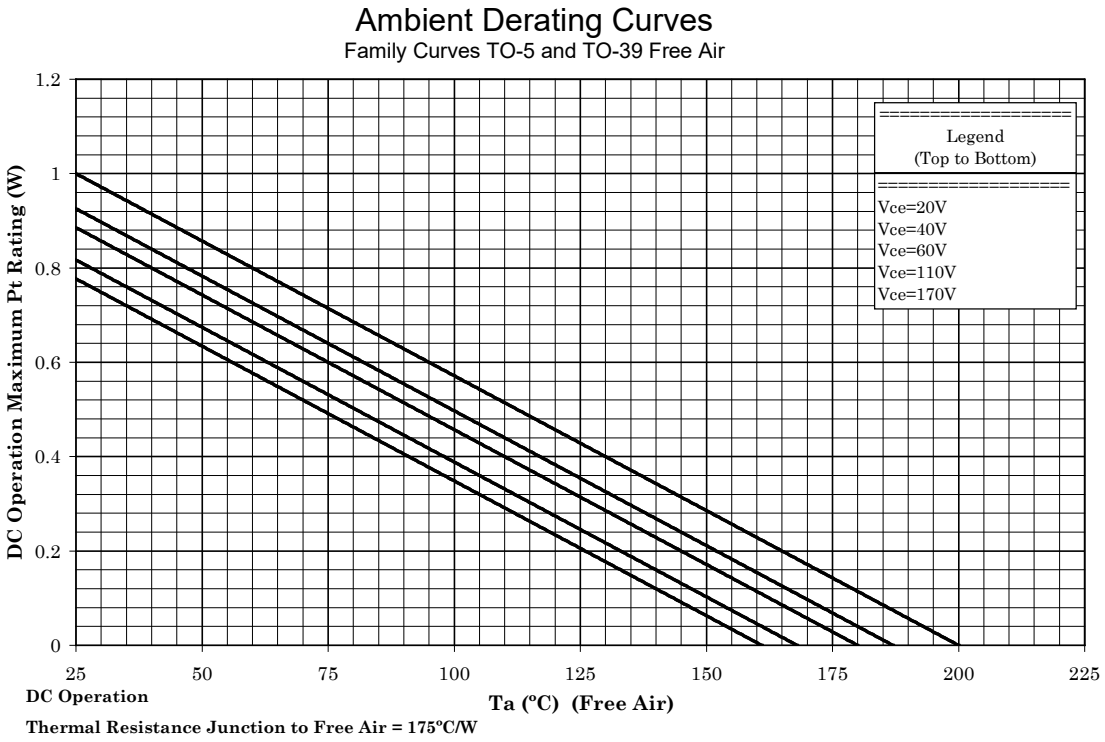

* FIGURE 7. Derating for 2N4150, 2N5237, 2N5238, 2N4150S, 2N5237S, and 2N5238S ($R_{\theta JA}$) (TO-5 and TO-39).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

Maximum Thermal Impedance

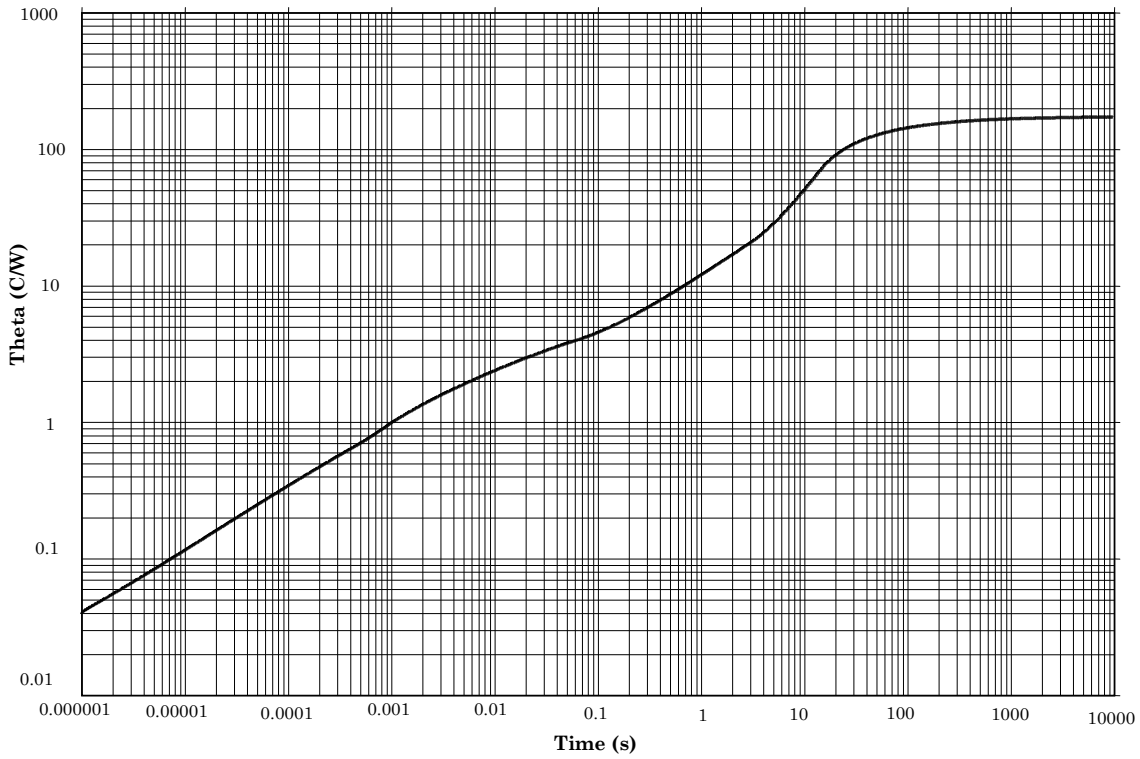


T_A = +25°C, 1W, thermal resistance $R_{\theta JA}$ = 175°C/W.

* FIGURE 8. Thermal impedance graph ($R_{\theta JA}$) for all 2N4150, 2N5237, 2N5238, 2N4150S, 2N5237S, and 2N5238S devices (TO-5 and TO-39).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.


Maximum Thermal Impedance

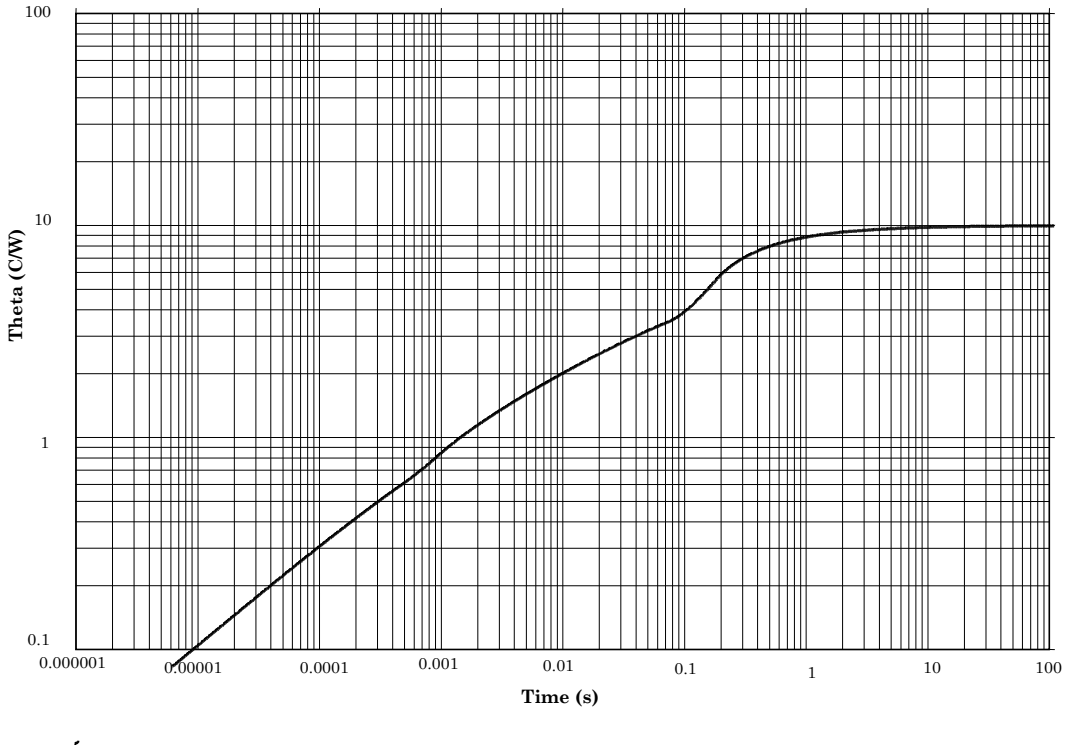

T_C = +25°C, thermal resistance $R_{\theta JC}$ = 10°C/W.


* FIGURE 9 Thermal impedance graph ($R_{\theta JC}$) for all 2N4150, 2N5237, 2N5238, 2N4150S, 2N5237S, and 2N5238S devices (TO-5 and TO-39) Kovar.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

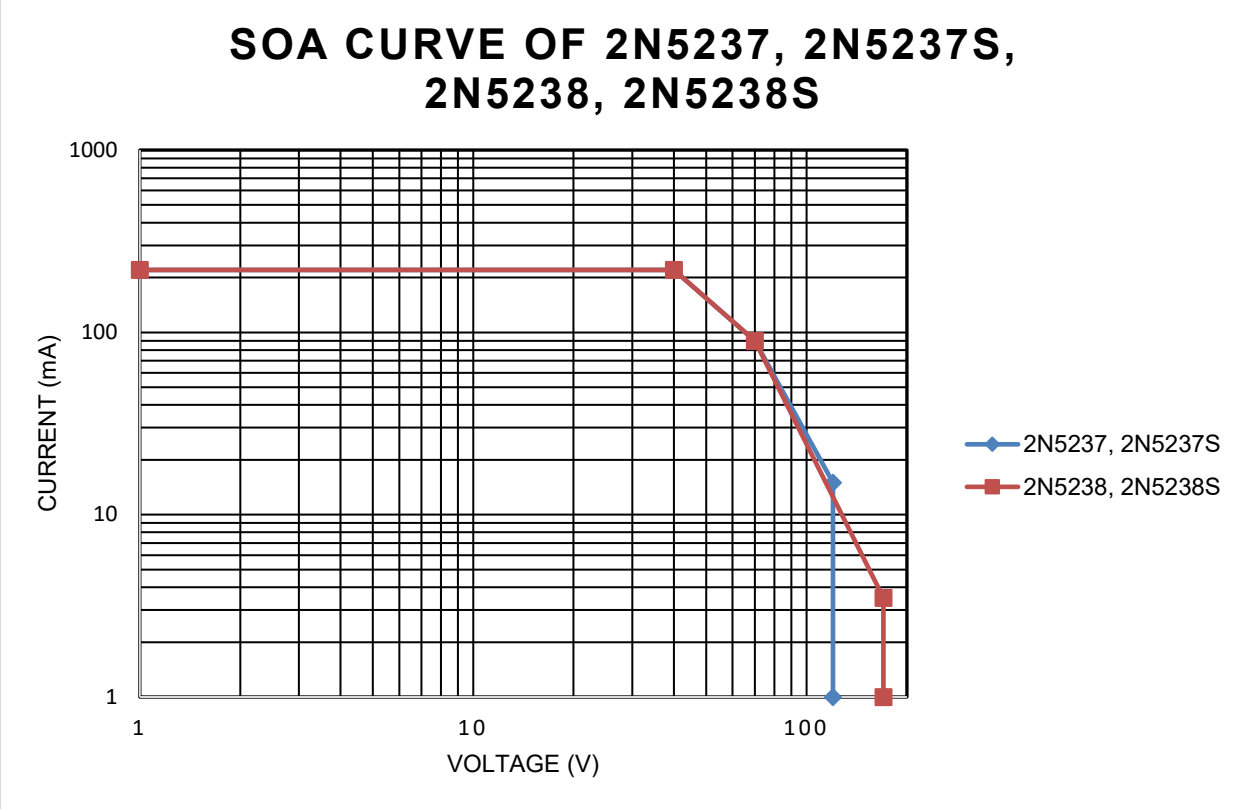


* FIGURE 10. Maximum operating conditions - dc forward biased mode.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

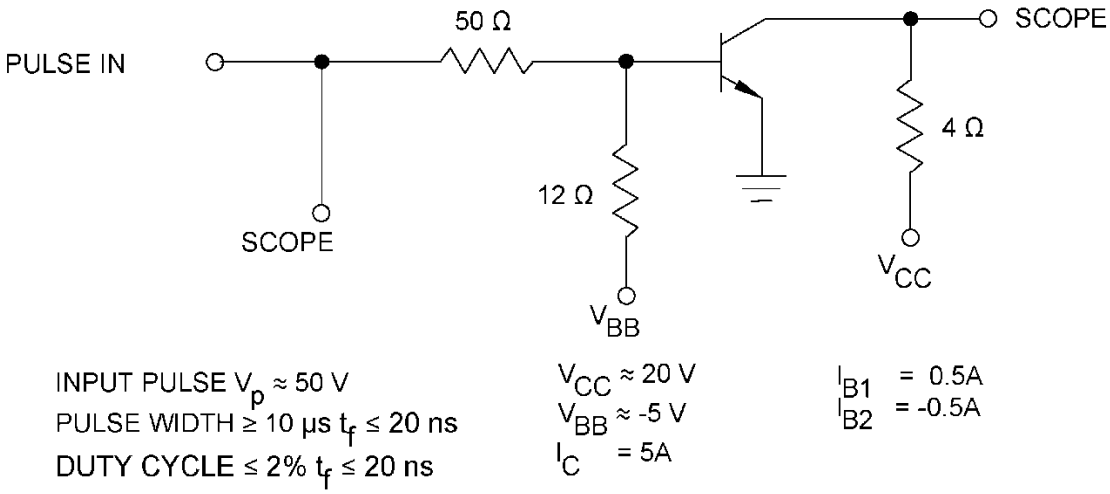

* FIGURE 11. Speed of response test circuit.

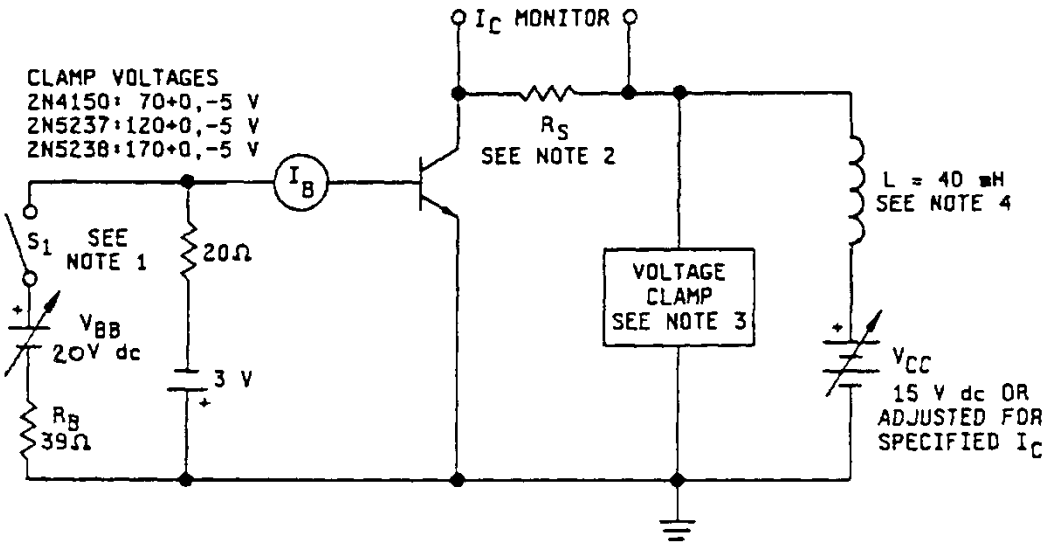

NOTES:
1. An appropriate pulse generator may be substituted.
2. $R_S \leq 1.0\ \Omega$ noninductive.
3. Clamp voltage: 2N4150: 70 V dc +0 V dc, -5 V dc; 2N5237: 120 V dc +0 V dc, -5 V dc; 2N5238: 170 V dc +0 V dc, -5 V dc.
4. STANCOR C-2691 or equivalent; 2 in series.

FIGURE 12. Clamped inductive sweep test circuit.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the Military Service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory. The notes specified in MIL-PRF-19500 are applicable to this specification.)

6.1 Intended use. Semiconductors conforming to this specification are intended for original equipment design applications and logistic support of existing equipment.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Packaging requirements (see 5.1).

c. Lead finish (see 3.4.1).

d. The complete PIN, see 1.5 and 6.5.


e. For acquisition of RHA designated devices, table II, subgroup 1 testing of group D is optional. If subgroup 1 testing is desired, it should be specified in the contract.

* 6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List (QML-19500) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from DLA Weapons Support, ATTN: VQE, P.O. Box 3990, Columbus, OH 43218-3990 or e-mail vqe.chief@dla.mil. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://qpldocs.dla.mil.


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

6.4 PIN construction example.

6.4.1 Encapsulated devices The PINs for encapsulated devices are constructed using the following form.

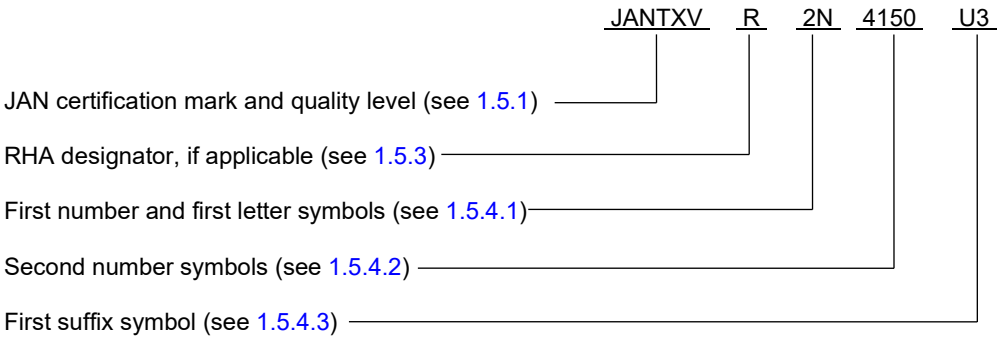

6.4.2 Unencapsulated devices. The PINs for unencapsulated devices are constructed using the following form.

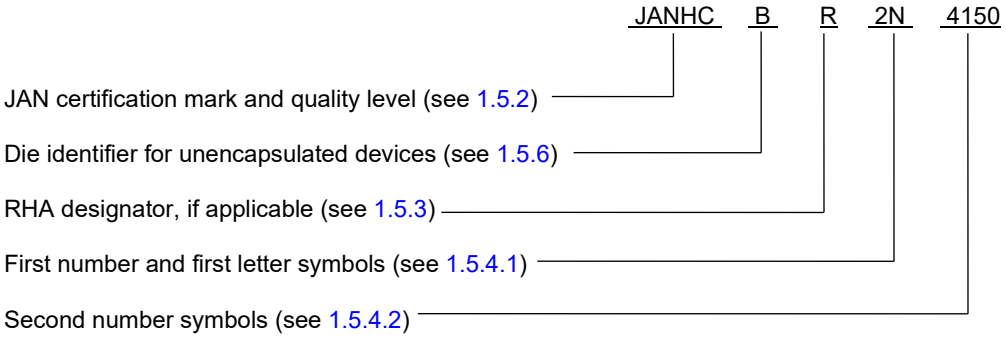

6.5 List of PINs.

6.5.1 List of PINs for encapsulated devices. The following is a list of possible PINs for encapsulated devices available on this specification sheet.

PINs for devices of the base quality level	PINs for devices of the "TX" quality level	PINs for devices of the "TXV" quality level	PINs for devices of the "S" quality level
JAN2N4150	JANTX2N4150	JANTXV#2N4150	JANS#2N4150
JAN2N4150S	JANTX2N4150S	JANTXV#2N4150S	JANS#2N4150S
JAN2N4150U3	JANTX2N4150U3	JANTXV#2N4150U3	JANS#2N4150U3
JAN2N5237	JANTX2N5237	JANTXV#2N5237	JANS#2N5237
JAN2N5237S	JANTX2N5237S	JANTXV#2N5237S	JANS#2N5237S
JAN2N5237U3	JANTX2N5237U3	JANTXV#2N5237U3	JANS#2N5237U3
JAN2N5238	JANTX2N5238	JANTXV#2N5238	JANS#2N5238
JAN2N5238S	JANTX2N5238S	JANTXV#2N5238S	JANS#2N5238S
JAN2N5238U3	JANTX2N5238U3	JANTXV#2N5238U3	JANS#2N5238U3

(1) The number sign (#) represent one of eight RHA designators available (M, D, P, L, R, F, G, or H) if desired. Remove for no RHA.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.

6.5.2 List of PINs for unencapsulated devices. The following is a list of possible PINs for unencapsulated devices available on this specification sheet. The qualified die suppliers with the applicable letter version (e.g., JANHCA2N4150) will be identified on the Qualified Manufacturers List (QML-19500).

PIN (1)	Manufacturer	Manufacturer	Manufacturer	Manufacturer
	43611	34156	52GC4	52GC4
2N4150	JANHCA#2N4150 JANKCA#2N4150	JANHCB#2N4150 JANKCB#2N4150	JANHCC#2N4150 JANKCC#2N4150	JANHCD#2N4150 JANKCD#2N4150
2N5237	JANHCA#2N5237 JANKCA#2N5237	JANHCB#2N5237 JANKCB#2N5237		
2N5238	JANHCA#2N5238 JANKCA#2N5238	JANHCB#2N5238 JANKCB#2N5238		

(1) The number sign (#) represent one of eight RHA designators available (M, D, P, L, R, F, G, or H) if desired. Remove for no RHA.

6.6 Amendment notations. The margins of this specification are marked with asterisks to indicate modifications generated by this amendment. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

CONCLUDING MATERIAL

Custodians:
Army - CR
Navy - SH
Air Force - 85
NASA - NA
DLA - CC

Review activities:
Army - AR, MI, SM
Air Force - 19, 71

Preparing activity:
DLA - CC

(Project 5961-2026-028)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil/.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:24Z
Check the source to verify that this is the current version before use.