INCH - POUND

MIL-P-40619B(MI)
18 October 1991
SUPERSEDING
MIL-P-40619A(MI)
9 December 1968

MILITARY SPECIFICATION
PLASTIC MATERIAL, CELLULAR, POLYSTYRENE
(FOR BUOYANCY APPLICATIONS)

This specification is approved for use by the U.S. Army Missile Command, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers cellular polystyrene, of two classes and two grades, that is intended primarily for buoyancy applications where a rigid material is required.

1.2 Classification. Cellular (foamed) polystyrene shall be furnished in the following classes and grades, as specified (see 6.2):

Class 1 - Non-self-extinguishing
Grade A - Low density
Grade B - High density

Class 2 - Self-extinguishing
Grade A - Low density
Grade B - High density

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, U.S. Army Missile Command, ATTN: AMSMI-RD-SE-TD-ST, Redstone Arsenal, AL 35898-5270 by using the Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 9330

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATIONS

FEDERAL

A-A-907	-	Candle, Illuminating 8 Hour
PPP-B-636	-	Boxes, Shipping, Fiberboard
PPP-B-640	-	Boxes, Fiberboard, Corrugated, Triple-wall

MILITARY

MIL-P-116	-	Preservation, Methods of

STANDARDS

MILITARY

MIL-STD-129	-	Marking for Shipment and Storage

(Unless otherwise indicated, copies of the federal and military specifications, standards, and handbooks are available from the Standardization Documents Order Desk, Bldg. 4D, 700 Robbins Ave., Philadelphia, PA 19111-5094.)

2.2 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DoD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the documents cited in the solicitation (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

C 203	-	Breaking Load and Flexural Properties of Block-Type Thermal Insulation, Standard Test Methods for
D 471	-	Rubber Property - Effect of Liquids, Standard Test Method for
D 1621	-	Compression Properties of Rigid Cellular Plastics, Standard Test Method for
D 1622	-	Apparent Density of Rigid Cellular Plastics, Standard Test Method for
D 1667	-	Flexible Cellular Materials - Vinyl Chloride Polymers and Copolymers (Closed-Cell Foam), Standard Specification for

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 First article. When specified (see 6.2), a sample shall be subjected to first article inspection (see 6.3) in accordance with 4.3.

3.2 Materials. Cellular polystyrene shall be of an essentially closed cell rigid form. It shall be formed by the expansion and fusion of polystyrene beads in a mold or by mixing polystyrene under heat and pressure with a vaporizable substance with subsequent expansion during an extrusion process.

3.3 Uniformity. The foamed material shall be of a uniform texture and density throughout its mass. Repairs of any kind to the expanded material shall not be permitted.

3.4 Color. The color of class 1 material shall be white or the natural color of the product. Class 2 material shall be of solid color other than white or marked "SELF EXTINGUISHING" in such a manner as prescribed by the

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

procuring activity (see 6.2). Marking shall not degrade the physical properties of the subject material.

3.5 Odor. The material shall be free of objectionable odor.

3.6 Form. The materials shall be in the form of boards, rough planks or billets. Unless otherwise specified (see 6.2), boards shall be furnished. Edges of boards shall be square within 0.125 inch per foot.

3.7 Dimensions and tolerances. Length, width, and thickness dimensions and tolerances shall be as specified in table 1 (see 6.2).

TABLE I. Tolerances (for boards only).

Dimensions	Tolerances (Inches)
Length	
up to 48 inches	± 0.25
above 48 inches	+ 2, -0.5
Width	± 0.0625
Thickness	± 0.0625

3.8 Physical properties. The cellular polystyrene shall meet the requirements listed in table II when tested as specified herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

TABLE II. Physical properties.

Property	Test method reference	Requirement Classes 1 and 2 Grade A	Grade B
Density, kilogram per cubic meter	4.6.2		
Maximum		4.0	10.4
Minimum		2.4	9.6
Compressive strength, kiloPascal (kPa)	4.6.3		
Minimum		124	689
Flexural strength, kPa	4.6.9		
Minimum		137.9	689
Water absorption, Pascal (Pa)	4.6.4		
of skinless surface, maximum		0.0574	0.0479
Volume change on heat aging,	4.6.5		
percent, maximum		3.5	3.5
Flame retardance (class 2 only)	4.6.6	Self extinguishing	Self extinguishing
Oil resistance	4.6.7	No softening, visible volume change or deterioration	
Resistance against crushing (falling ball)	4.6.8		
Depth of depression, inches, maximum		0.24	0.21
Cracking beyond depression		No cracks	No cracks

3.9 Adhesives. If required by the procuring activity (see 6.2), the contractor shall recommend water resistant, air drying adhesives for joining cellular polystyrene. The resulting jointed foam shall meet all the applicable requirements of this specifications.

3.10 Identification marking. One face of the foamed polystyrene planks, boards, or billets shall be marked permanently and legibly at recurrent intervals of not greater than 2 feet with the manufacturer's

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

identification, specification number, class, and grade. The National Stock number, if any, may be used in lieu of the specification number.

3.11 Workmanship. Workmanship shall be uniform and shall conform to best commercial practice.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in this specification where such inspections are deemed necessary to ensure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items shall meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to accept defective material.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3)

b. Quality conformance inspection (see 4.5).

4.3 First article inspection. When specified in the contract or order (see 6.2), a first article sample shall be subjected to first article inspection. Subsequent units shall not be considered for acceptance until Government approval of the first article sample has been obtained.

4.4 Sampling.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

4.4.1 Lot. For purpose of sampling, examinations, and tests, a lot shall consist of all the material of the same class and grade produced under essentially the same conditions, and offered for delivery at one time.

4.4.2 Unit for examination of preparation of delivery. The sample unit of examination of material (see 4.5.1) shall be one of full length of board, plank, or billet. The sample unit for examination of preparation for delivery (see 4.5.2) shall be one pack, fully prepared for delivery.

4.4.3 Sampling for examination. For the examinations of 4.5.1 and 4.5.2, random samples shall be taken in accordance with table III. Inspection for all major defects shall be 100 percent.

TABLE III. Sampling plan.

Lot Size	Sample Size
2 to 3	All
4 to 25	3
26 to 50	5
51 to 90	6
91 to 150	7
151 to 280	10
281 to 500	11
501 to 1200	15
1201 to 3200	18
3201 to 10,000	22
10,001 and over	29
Note: The acceptance number in all cases is ZERO. The rejection number in all cases is ONE.	

4.4.4 Sampling for tests. Representative samples for testing shall be taken at random from those which passed the examination of 4.5.1. These samples shall be used for the tests of 4.5.5 and 4.5.6.

4.5 Quality conformance inspection and tests.

4.5.1 Examination for defects of material. Samples shall be taken from each lot in accordance with table III and shall be examined for conformance with the requirements for uniformity (see 3.3), color (see 3.4), odor (see

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

3.5), form (see 3.6), dimensions and tolerances (see 3.7 and 6.2), and workmanship (see 3.11). Material defects are listed in table IV.

TABLE IV. Material defects.

Categories	Defect	Method of inspection	Sampling plan (table)
Critical:	None defined		
Major:			
101	Texture not uniform; surface not continuous over entire area; repairs to foam	Visual	III
102	Color of class 1 not white or natural; class 2 not colored or not distinguished from class 1.	Visual	III
103	Objectionable odor	Scent	III
104	Form not as specified; edges not square within 0.125 inch per foot (for boards only)	Visual/gage	III
105	Dimensions not as specified; tolerances exceeded	Gage	III
106	Marking not as specified Marking is not permanent, legible or at recurrent intervals	Visual	III
107	Workmanship not uniform; largest dimension of voids greater than 0.125 inch; presence of resin accumulations; presence of foreign inclusions; crushed surface areas greater than 10 percent of original thickness; tears, cracks extending a distance larger than 0.5 inch from edges; defects detracting from serviceability; repairs	Visual/gage	III

4.5.2 Examination for defects in preparation for delivery. Samples shall be taken from each lot in accordance with table III and shall be examined for conformance with Section 5 of this specification. Defects are listed in table V.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

TABLE V. Defects in preparation for delivery.

Categories	Defect	Method of inspection	Sampling plan (table)
Critical:	None defined		
Major:			
101	Packing not specified level; shipping container not as specified; number of boards, planks, or billets per pack as specified	Visual	III
102	Marking not indicating class and grade; illegible, incorrect; not conforming to carrier regulations	Visual	III

4.5.3 Production check tests. Production check tests shall be conducted on samples taken in accordance with 4.4.4 from or representing the first lot of material offered for delivery and from one out of every five lots thereafter, but not later than one year after delivery of the first lot, which ever is the shorter period. All the tests specified in 4.4 shall be performed.

4.5.4 Quality conformance tests. Quality conformance tests shall be conducted on samples taken in accordance with 4.4.4 from all lots on which production check tests were not conducted. The tests for density (see 4.6.2), water absorption (see 4.6.4), and flame retardance (see 4.6.6) shall be performed, the latter for Class 2 only.

4.5.5 Action in case of nonconformance. If any of the sample in the production check tests or quality conformance tests are found not be in conformance with the requirements of this specification, the lot which it represents shall be rejected. Furthermore, additional samples shall be taken or provided from each subsequent lot and shall be subjected to the test or tests wherein the failure occurred. Each lot shall then be accepted only after satisfactory results are obtained on the test or tests by all samples taken or provided to represent the lot. This additional testing shall be discontinued after four successive lots have passed the test or tests.

4.6 Test procedures.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

4.6.1 General conditions. The specimens shall be conditioned and tested at 23 ± 5° Celsius (C) and 50 ± 4 percent relative humidity. In cases of dispute, the conditions 23 ± 1° C and 50 ± 2 percent relative humidity shall apply. Unless otherwise specified, not less than 2 specimens per sample unit shall be tested.

4.6.2 Density. The density shall be determined by ASTM D 1622.

4.6.3 Compressive strength. The compressive strength shall be determined by procedure A of ASTM D 1621. The pressure shall be applied until failure or until the specimen has been compressed 5 percent of the original thickness, whichever occurs first.

4.6.4 Water absorption. The water absorption shall be determined by ASTM D 1667.

4.6.5 Volume change on heat aging. The volume before and after heat aging shall be determined by the displacement method. The confining medium shall be a free flowing, non-dusting solid of small particle size. Clean flax or rape seed is suitable. The specimens shall be of suitable size to fit into a 200 milliliter (ml) cylinder with 1 ml graduations, and shall allow covering the specimen by the confining medium within the graduated section of the cylinder. The specimen shall be placed in the cylinder, surrounded by the measuring medium and the total volume shall be determined. The difference between this total volume and that of the measuring medium only, is the volume of the specimen. The specimen shall then be heated in an oven for 48 hours ± 30 minutes at 60° C. After conditioning, the volume of the specimen shall be determined as described above. The volume change after aging expressed in percent of the initial volume shall be calculated using the following expression:

$$V = \frac{v_i - v_a}{v_i} \times 100$$

Where: V = Volume change in percent of initial
v_i = Initial volume
v_a = Volume after aging

4.6.6 Flame retardance.

4.6.6.1 Specimens. The specimens shall be one inch wide and 0.25 inch thick with a tolerance of 0.0625 inch. The length shall be 12 inches with a tolerance of ± 0.0625 inch.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

4.6.6.2 Test equipment. The equipment shall include a means of supporting and positioning the specimen. A laboratory ring stand and burette clamp are suitable. A candle conforming to A-A-907 and a timing device permitting measurement of time intervals of 0.2 second are required.

4.6.6.3 Test procedure. The test shall be conducted in a location free from drafts. The specimen shall be clamped at the upper end with the length dimension positioned downward at a 45° angle from the horizontal and the width dimension vertical. The skinless 0.25 inch face shall be in a downward position facing the flame. The candle (see 4.6.6.2) shall be prepared for use by allowing it to burn until the conical top is completely consumed and until the wick has assumed a bent shape. The wick shall not be trimmed. The flame shall be extinguished and the clamp holding the specimen adjusted to provide a vertical clearance of 0.25 inch between the highest point of the bent wick and the lowest point on the specimen. The candle shall be removed, lighted and permitted to burn until molten wax fills the crater forming the top of the candle. The burning candle shall then be replaced under the specimen. If the burning portion of the specimen melts or shrinks from the flame, the candle shall be moved along the 45 degree angle so as to keep the specimen in the flame. At the end of 15 ± 0.2 seconds the candle shall be removed. The burning plus glowing times of the specimen after withdrawal of the candle shall be measured. Ten specimens shall be used in one test. The average of the burning plus glowing times shall be not greater than ten seconds after removal of the flame in order for the material to be rated self-extinguishing by this test. If any specimen is completely consumed during the 15 second exposure period, a new specimen shall be substituted and if that specimen is also consumed, the material shall be rated "non-self-extinguishing". If more than one of the ten specimens used in the test is completely consumed, the material shall be rated "non-self-extinguishing".

4.6.7 Oil resistance. Specimens of suitable size shall be immersed for 70 hours ± 30 minutes in No. 2 oil conforming to ASTM D 471. The specimen shall then be removed, blotted gently with filter paper and compared with an untreated specimen of similar size for visible volume change, softening or deterioration.

4.6.8 Resistance against crushing.

4.6.8.1 Specimens. Specimens shall be 4 x 4 x 1 inches. If the exterior of the finished article is intended to have a skin (see 6.2) one of the 4 x 4 inch surfaces of the specimens shall be completely covered by an integral skin. Otherwise the presence of a skin on the test face of the specimen shall be optional.

4.6.8.2 Test procedure. A specimen with surface skin up, if present, shall be placed on a hard flat surface, such as metal or concrete. A steel

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

ball, 2.14 inches in diameter weighing 1.44 pounds, shall be dropped once vertically from a height of 4 feet, measured from the hard surface, on the center of the specimen. The ball shall be removed and after a recovery period of 15 minutes the depth of the formed depression shall be measured to the nearest 0.01 inch.

4.6.9 Flexural strength. The flexural strength shall be determined by ASTM C 203.

4.7 Inspection of packaging. Except when commercial packaging is specified, the sampling and inspection of the preservation and interior package marking shall be in accordance with groups A and B quality conformance inspection requirements of MIL-P-116. The sampling and inspection of the packing for shipment and storage shall be in accordance with the quality assurance provisions of the applicable container specification shown in section 5. The inspection of marking for shipment and storage shall be in accordance with MIL-STD-129. The inspection of commercial packaging shall be as specified in the contract (see 6.2).

5. PACKAGING

5.1 Packing. Packing shall be level A, B, or C, as specified (see 6.2).

5.1.1 Level A. Packing shall be in fiberboard boxes conforming to PPP-B-636, Type CF, class weather-resistant, grade V3c, or PPP-B-640, class 2, style A. All center and edge seams and the manufacturer's joint of the boxes shall be waterproofed in accordance with the applicable box specification or appendix thereto. Box closure and reinforcing shall be in accordance with the appendix to the applicable box specification except reinforcing shall be by pressure sensitive, reinforced filament tape. The gross weight of shipping containers shall not exceed the weight limitations of the applicable box specification. Dimensional limits shall be waived.

5.1.2 Level B. Packing shall be in fiberboard boxes conforming to PPP-B-636, class domestic or PPP-B-640, class 2, except that dimensional limits shall be waived. Box closures shall be as specified in the applicable box specification or appendix thereto. Gross weight of shipping containers shall not exceed the weight limitations of the applicable box specification.

5.1.3 Level C. Packing shall be accomplished in a manner which will ensure acceptance by a carrier at the lowest rate, and will afford protection against physical or mechanical damage during direct shipment from the supply source to the using activity for early material use. The shipping containers

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

or method of packing shall conform to carrier regulations as applicable to the mode of transportation.

5.2 Marking. Shipment marking information shall be provided on shipping containers in accordance with the requirements of MIL-STD-129. The information shall include nomenclature, National Stock number or manufacturer's part number, lot number, data (month and year) of manufacture, size, contract or order number, contractor's name, and designation. Special markings shall be provided if specified (see 6.2).

5.3 Sub-contracted material and parts. The preparation for delivery requirements of referenced documents listed in Section 2 do not apply when material and parts are procured by the supplier for incorporation into equipment and lose their separate identity when the equipment is shipped.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. This cellular, polystyrene plastic material is intended to be used for buoyancy applications for flotation purposes.

6.2 Acquisition requirements. Acquisition documents must specify the following:

a. Title, number, and date of the specification

b. Class and grade required (see 1.2)

c. Issue of DODISS to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.1.1)

d. Manner in which "self extinguishing" shall be marked (see 3.4)

e. Form, if other than board (see 3.6)

f. Dimensions (see 3.7)

g. Recommendations for adhesives, if required (see 3.9)

h. If exterior surface of finished article shall have a skin (see 4.6.8.1)

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

for seal strength in accordance with ASTM F 88, except pouches shall be tested

i. Number of items per pack, if required

j. Level of packing (see 5.1)

k. Special markings, if required (see 5.2).


6.3 First article. When first article inspection is required, the contracting officer should provide specific guidance to offerers whether the item(s) should be a first article sample, a first production item, or a number of items to be tested as specified in 4.3. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examinations, approval of first article test results and disposition of first articles. Invitations for bids should provide that the Government reserves the right to waive the requirement for samples for first article inspection to those bidders offering a product which has been previously acquired or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending contract.

6.4 Definition of defects. A major defect is likely to prevent or to reduce materially the usability of the unit of product for its intended purpose.

6.5 Flame retardance. The term "self-extinguishing" denotes solely that burning class 2 material will self-extinguish, when an external fuel source is removed. Class 2 material represents a lesser fire hazard than does Class 1 material, but the term "self-extinguishing" should not be considered a fire hazard classification.

6.6 Metrication. Metric equivalents in accordance with FED-STD-376 are acceptable for use in this specification.

6.7 Part or identifying number (PIN). The PIN to be used for material acquired to this specification are created as follows:

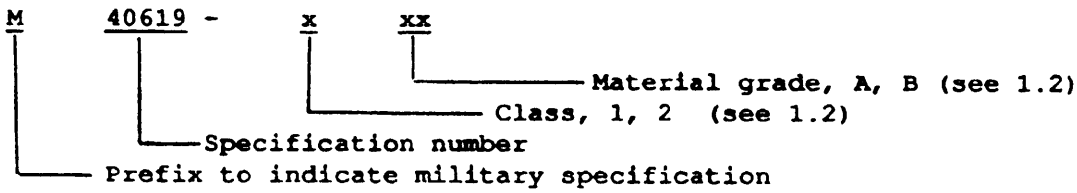

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

6.8 Subject term (keyword) listing.

Foam
Flotation material
Plastics

6.9 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

Custodian:
Army-MI

Preparing Activity:
Army-MI

Project No. 9330-1154

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T19:26Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER MIL-P-40619B (MI)	2. DOCUMENT DATE (YYMMDD)

3. DOCUMENT TITLE
Plastic Material, Cellular, Polystyrene (For Bouyancy Applications)

4. NATURE OF CHANGE (*Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.*)

5. REASON FOR RECOMMENDATION

6. SUBMITTER		
a. NAME (Last, First, Middle Initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) (1) Commercial (2) AUTOVON (If applicable)	e. DATE SUBMITTED (YYMMDD)

8. PREPARING ACTIVITY

a. NAME	b. TELEPHONE (Include Area Code)	
Commander U.S. Army Missile Command	(1) Commercial (205) 876-6980	(2) AUTOVON 746-6980
ADDRESS (Include Zip Code) ATTN: AMSMI-RD-SE-TD-ST Redstone ARsenal, AL 35898-5270	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 AUTOVON 289-2340	

DD FORM 1426

Source: https://assist.dla.mil -- Downloaded: 202640-21T19:26Z
Check the source to verify that this is the current version before use.