MIL-N-85353/2A
23 June 1986
SUPERSEDING
MIL-N-85353/2
1 November 1985

MILITARY SPECIFICATION SHEET

NUT, PRELOAD LOCKING, EXTENDED WASHER, HEXAGON, REDUCED HEIGHT, CRES, 125 KSI, 450°F AND 1200°F

This specification sheet is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the nuts described herein shall consist of this specification and the latest issue of MIL-N-85353.

This specification sheet covers preload locking nuts. It will meet the requirements of MIL-N-85353 only when seated to the torque values specified in Table I.

This nut shall be used in accordance with the reliability and maintainability requirements of MS14194.

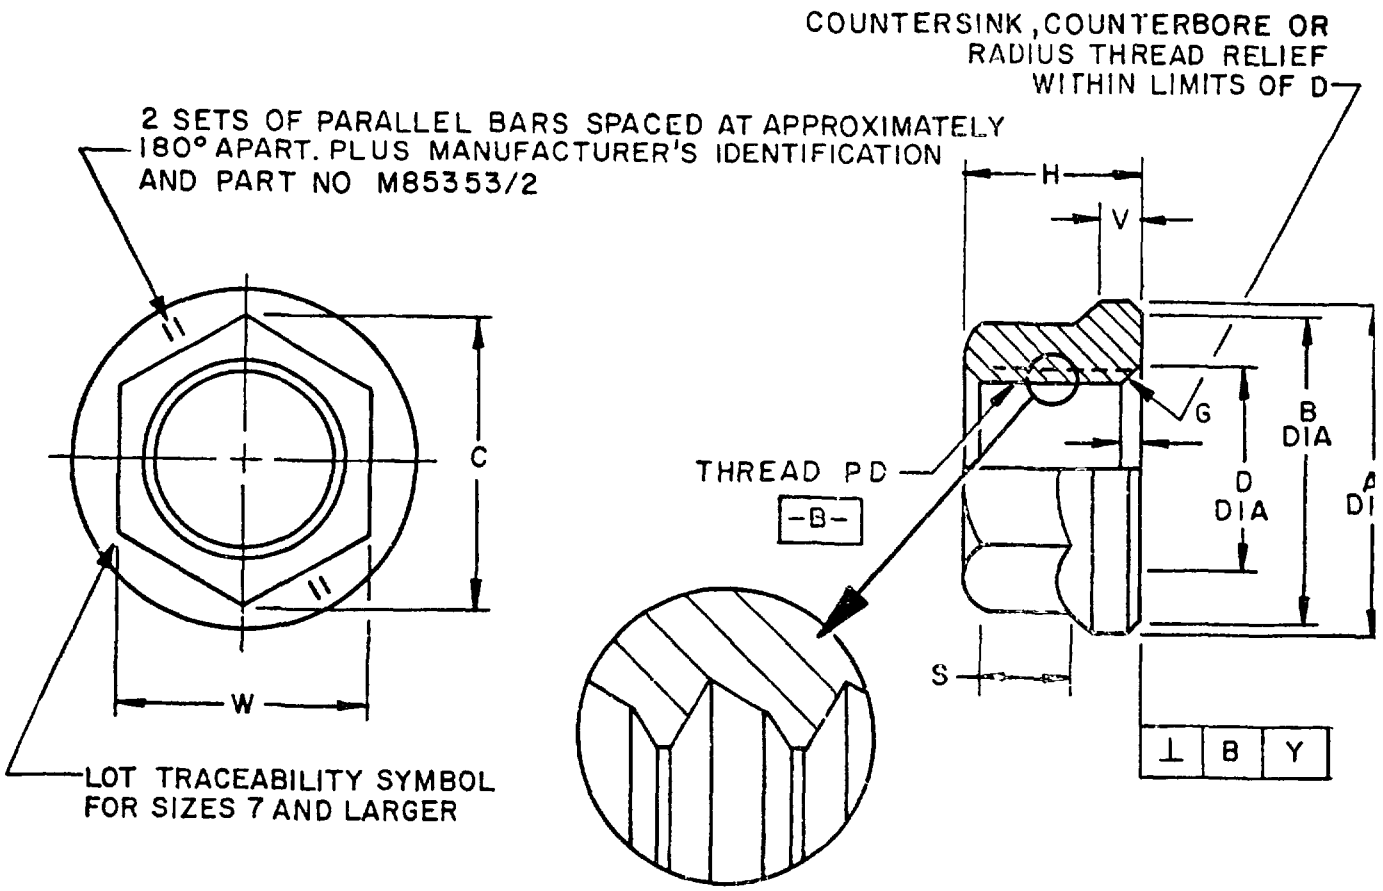


FIGURE 1. Preload locking fastener.

AMSC N/A
FSC 53

DISTRIBUTION STATEMENT A: Approved for public release; distribution is unlimite

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:43Z
Check the source to verify that this is the current version before use.

TABLE I. Dimensions and characteristics.

Part Size	Threads Designation UNJS-3B	A Max	B Min	C Min	D +0 -.030	G +.010 -0	H Max	S Min	V Ref	W Max	W Min	Y FIM	Axial Tensile Strength Lb Min	Seating Torque In.-Lbs Min	Approx Weight Lbs/100
-02	.0860-56	.167	.137	.138	.096	.015	.095	.045	.020	.127	.122	.003	440	2.5	.02
-04	.1120-40	.206	.176	.171	.127	.015	.125	.050	.025	.158	.150	.003	750	7	.04
-06	.1380-32	.244	.214	.207	.168	.025	.141	.055	.032	.190	.181	.003	1,130	15	.07
-08	.1640-32	.290	.260	.244	.194	.025	.170	.060	.035	.221	.213	.003	1,720	30	.11
-3	.1900-32	.330	.292	.277	.220	.025	.188	.065	.035	.252	.243	.003	2,460	40	.18
-4	.2500-28	.420	.386	.347	.280	.025	.219	.090	.045	.316	.304	.003	4,580	95	.30
-5	.3125-24	.520	.482	.419	.342	.025	.266	.120	.050	.378	.367	.003	7,390	175	.55
-6	.3750-24	.620	.575	.491	.405	.025	.282	.125	.060	.440	.430	.003	11,450	325	.76
-7	.4375-20	.720	.690	.562	.468	.025	.328	.160	.070	.504	.494	.005	15,450	600	1.26
-8	.5000-20	.820	.786	.633	.530	.030	.480	.220	.080	.566	.556	.005	21,110	1000	2.07
-9	.5625-18	.922	.877	.775	.592	.035	.540	.240	.090	.692	.680	.005	26,810	1400	3.26
-10	.6250-18	1.027	.982	.846	.655	.035	.600	.250	.105	.755	.743	.006	34,130	1900	4.15

REQUIREMENTS:

1. Material: A286 corrosion-resistant steel in accordance with AMS5732 or AMS5737 except heat treat shall be in accordance with MIL-H-6875 to 160 KSI tensile strength level, minimum.

2. Threads: Threads shall be in accordance with MIL-S-8879 modified per MIL-N-85353/1.

3. Finish: Passivate in accordance with QQ-P-35.

4. Plating: Silver plate in accordance with AMS 2410 (for 1200°F nuts).

5. Lubrication: Dry film lubricant in accordance with MIL-L-8937 or equivalent (for 450°F nuts).

6. Surface texture: In accordance with ANSI B46.1, shall be not greater than 125 roughness height rating (R_a); bearing surface shall be not greater than 32 R_a.

7. Concentricity: Diameters A and B shall be concentric to thread ramp within .012 TIR.

8. Bearing surface: Shall be perpendicular to thread ramp within Y values.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:43Z
Check the source to verify that this is the current version before use.

NOTES:

1. These nuts are intended for use in applications with bolts heat treated to the same heat treat level as the mating nut, with threads conforming to MIL-S-8879.


2. Dimensions are in inches. Interpret in accordance with ANSI Y14.5M-1982.

3. Unless otherwise specified, tolerances are ±.010 for decimals.

4. All sharp edges shall be broken and all burrs and slivers shall be removed.

5. The nut is manufactured under patent number 4023914 which expires in 1995. The Government does not have a royalty-free license.

Example of a part number:

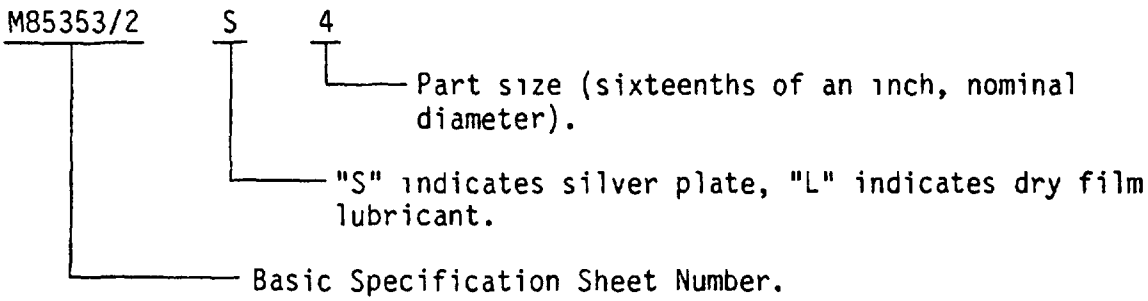

Custodians:
Navy - AS
Air Force - 11
Army - AV

Review Activities:
DLA - IS
Air Force - 99
Army - AR

User Activity:
Air Force - 82

Preparing Activity:
Navy - AS
(Project No. 5310-1529)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:43Z
Check the source to verify that this is the current version before use.

INCH-POUND

MIL-N-85353/2A
AMENDMENT 1
14 December 1994

MILITARY SPECIFICATION SHEET

NUT, PRELOAD LOCKING, EXTENDED WASHER, HEXAGON, REDUCED HEIGHT, CRES 125 KSI 450°F AND 1200°F

This amendment forms a part of MIL-N-85353/2A, dated 23 June 1986, and is approved for use by all Departments and Agencies of the Department of Defense.

PAGE 2

Requirements:

Delete:

6. Lubrication: Dry film lubricant in accordance with MIL-L-8937 or equivalent (for 450°F nuts).

Substitute with:

6. Lubrication: Dry film lubricant in accordance with MIL-L-46010, Type I or equivalent (for 450°F nuts).

Custodians:
Navy - AS
Air Force - 11
Army - AV

Preparing Activity:
DLA-IS
(Project No. 5310-2033)

Review Activities.
Air Force - 99
Army - AR

AMSC N/A 1 of 1 FSC 5310

DISTRIBUTION STATEMENT A. Approved for public release, distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:43Z
Check the source to verify that this is the current version before use.