INCH POUND

MIL-DTL-7726L (USAF)
23 September 2019

SUPERSEDING
MIL-PRF-7726K
20 February 2007

DETAIL SPECIFICATION

RETREAD TIRES, RIBBED TREAD, PNEUMATIC, AIRCRAFT

This specification is approved for use by all Departments and Agencies of the Department of Defense.

AMSC: N/A

FSC: 2620

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

FOREWORD

1. This detail specification is approved for use by the AF70 Hill AF Base, AFMC 417 SCMS/GUEA Landing Gear/Aircraft Tires Program Office Department of the Air Force, and is available for use by all Departments and Agencies of the Department of Defense.

2. This specification covers the requirements for a retreaded bias ply or radial ply aircraft tire, which has had a worn casing restored by renewing the tread material or the tread and sidewall material. A rebuilt aircraft pneumatic tire may be a tube-type or tubeless ribbed and is intended for use on military aircraft wheels.

3. Comments, suggestions, or questions on this document should be addressed to Landing Gear/Aircraft Tires Program Office, 417th SCMS, 6040 Gum Lane, Bldg. 1216, Hill AFB, UT 84056-5825 or 748SCMG.Workflow@us.af.mil attn: 417th Landing Gear/Aircraft Tires Program Office. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

SUMMARY OF CHANGES

PAGE	MODIFICATIONS
Page I – Title	Changed
Page ii – Forward	Added
Page iii – Summary of changes	Added
Page iv – vii Table of contents	Added

PARAGRAPH/SECTION	MODIFICATIONS
2.1	Changed
2.2.1	Changed
2.2.2	Added
2.3	Changed
3.1	Changed
3.1.1 – 3.1.2	Changed
3.2	Changed
3.2.1 – 3.2.3	Changed
3.2.3.1 – 3.2.3.2	Changed
3.3 – 3.4	Changed
3.5.1 – 3.5.9	Changed
3.5.9.1 – 3.5.9.4	Changed
3.5.10 – 3.5.13	Changed
3.6 – 3.8	Changed
3.9	Added
4.1.1 – 4.1.2	Changed
4.2 – 4.6.12	Changed
4.7 – 4.7.10	Added
5.1	Changed
5.2 – 5.2.2	Added
6.1	Changed
6.2 – 6.2.13	Changed
6.3 – 6.5	Changed
6.7	Added
Table I	Changed
Table II	Changed
Figure 1	Changed
Figure 2	Added
Appendix A (entire)	Added
Concluding Material	Changed

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

CONTENTS

PARAGRAPH		PAGE
	FORWARD	ii
	SUMMARY OF CHANGES	iii
	CONTENTS	v
1.	SCOPE	1
1.1	Scope	1
2.	APPLICABLE DOCUMENTS	1
2.1	General	1
2.2	Government Document	1
2.2.1	Specifications, standards, and handbooks	1
2.2.2	Other Government Documents, drawings, and publications	1
2.3	Non-Government Publications	2
2.4	Order of Precedence	2
3.	REQUIREMENTS	2
3.1	Specification sheets	2
3.1.1	Tire and Rima Association Aircraft Yearbook	3
3.2	Qualification	3
3.2.1	Qualification casing requirements	3
3.2.2	Retread level escalation	3
3.3	General requirements	3
3.3.1	Ambient temperature range	3
3.3.2	Tire sizing and classification	3
3.4	Materials	3
3.5	Performance	4
3.5.1	Basic tire performance	4
3.5.2	Tire speeds	4
3.5.3	Burst pressure	4
3.5.4	Dynamic durability	4
3.5.4.1	Cord fraying	4
3.5.4.2	Tread chunking	4
3.5.4.3	Groove cracking	4
3.5.4.4	Bead separation	4
3.5.4.5	Cable bruise	4
3.5.5	Wheel/tire slippage	4
3.5.6	Inflation pressure retention – tubeless tire	4
3.5.7	Balance	5
3.5.8	Tread adhesion	5
3.6	Design and construction	5
3.6.1	Tire dimension and weight	5
3.6.2	Tire dimensions for helicopters	5
3.6.3	Tread	5
3.6.3.1	Tread pattern	5

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

3.6.3.2	Underskid thickness	5
3.6.3.3	Maximum Wear Limit (MWL) indicator	5
3.6.3.4	Retread Buff Line (RBL)	5
3.6.4	Sidewall	5
3.6.5	Venting	5
3.6.6	Rim dimensions	5
3.6.7	Cut limit dimensions	6
3.7	Product identification and marking	6
3.7.1	Original tire identification data	6
3.7.2	Retreaded tire identification data	6
3.7.3	Markings not required	7
3.8	Interchangeability	7
3.9	Age	7
4.	VERIFICATION	7
4.1	Classification requirements	7
4.2	Responsibility for inspection	8
4.3	Qualification inspection	8
4.3.1	Qualification Test Report (QTR)	8
4.3.1.1	Bead-seating	8
4.3.1.2	Mold skid depth	8
4.3.1.3	Load deflection curves	8
4.3.1.4	Footprints	9
4.3.1.5	Navy QTR inflated profiles	9
4.3.1.6	Cross-section image	9
4.3.2	Qualification tests	9
4.3.3	Dynamic test inspection	10
4.4	Conformance inspection	10
4.4.1	Individual tests	10
4.4.2	Sample tests	10
4.5	Test conditions	10
4.6	Requirements cross-reference matrix	10
4.7	Test methods	10
4.7.1	Air injection test	10
4.7.2	Pre-tested inspection test	10
4.7.3	Examination of product test	10
4.7.4	Balance test	11
4.7.5	Tire dimensions, weight, and rim interface test	11
4.7.6	Balance pad adhesion test	11
4.7.7	Dynamic durability test	11
4.7.7.1	Dynamic durability test temperature	11
4.7.7.2	Cable bruise test (carrier based aircraft tires only)	11
4.7.7.3	Post-test inspection	11
4.7.7.4	Bead separation test	11
4.7.8	Low temperature test	11
4.7.9	Inflation pressure retention test - tubeless tires	12
4.7.10	Burst pressure test	12

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

5	PACKAGING	12
5.1	General	12
5.2	Marking for shipment	12
5.2.1	National Stock Number (NSN)	12
5.2.2	Color coding, age identification	12
6	NOTES	12
6.1	Intended use	12
6.2	Acquisition requirements	12
6.3	Qualified Parts List (QPL)	13
6.4	Additional Information	13
6.4.1	Use of tubeless tire in tube type application	13
6.5	Definitions	13
6.5.1	Bead bundle	13
6.5.2	Casing	13
6.5.3	Casing ply	13
6.5.4	Escalation	13
6.5.5	Fabric-reinforced tread	13
6.5.6	Fabric tread	13
6.5.7	Julian date	14
6.5.8	Liner	14
6.5.9	Ply rating	14
6.5.10	Rated inflation pressure	14
6.5.11	Rated load	14
6.5.12	Retread Buff Line (RBL)	14
6.5.13	Retread level marking	14
6.5.14	Retread tire	14
6.5.15	Ribbed tire	14
6.5.16	Rubber tread	14
6.5.17	Skid depth	14
6.6	Subject term (key word) listing	14
6.7	Changes from previous issue	15
	TABLES	
Table I	Tire drawing matrix	16
Table II	Paragraph cross-reference matrix	17
	FIGURES	
Figure 1	Part marking	18
Figure 2	Cut-limit dimensions and maximum wear limit identification	19
A.	APPENDIX A	20
A.1	Header section	20
A.2	Title page section	20
A.3	Table of contents section	21
A.4	Compliance section	22
A.5	Static test requirements/results sections	22
A.5.1	Contact areas section	24
A.6	Dynamic test requirements section	25

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

A.7 Dynamic test results section 26
A.8 Other pertinent data 28

CONCLUDING MATERIAL 29

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

1. SCOPE

1.1 Scope. This specification covers the requirements for a retreaded bias ply or radial ply aircraft tire, which has had a worn casing restored by renewing the tread material or the tread and sidewall material. A rebuilt aircraft pneumatic tire may be a tube-type or tubeless ribbed and is intended for use on military aircraft wheels. The drawing and slash sheet matrix (see Table I) identifies these retreaded tires by size and ply rating.

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does ***not*** include documents in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections three (3) and four (4) of this specification, whether or ***not*** they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS AND STANDARDS

MIL-DTL-5041	Tires, Ribbed Tread, Pneumatic, Aircraft
SD-6	Standardization Document – Provisions Governing Qualification - Qualified Products Lists and Qualified Manufacturers Lists
MIL-STD-129	Military Marking for Shipment and Storage
MS14113	Tape, Identification, Color Coded, for Aircraft Tires
QPL-5041	Tires, Ribbed Tread, Pneumatic, Aircraft
Other Specifications	Weapon-system specific – see Table I

(Copies of these documents are available online at https://assist.dla.mil.)

2.2.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

Drawings	Weapon-system specific – see Table I

(Copies of these drawings are available at https://www.jedmics.net/index.jsp, https://assist.dla.mil, or contact Landing Gear/Aircraft Tires Program Office, 417th SCMS, 6040 Gum Lane, Bldg 1216, Hill AFB, UT 84056-5825, or email at 748SCMG.Workflow@us.af.mil attn: 417th Landing Gear/Aircraft Tires Program Office)

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

FEDERAL AVIATION ADMINISTRATION (FAA) PUBLICATION

TSO-C62	Technical Standard Order – Aircraft Tires
AC 145-4A	Inspection, Retread, Repair, and Alterations of Aircraft Tires

(Copies of these documents are available online at https://www.faa.gov/.)

2.3 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

SOCIETY OF AUTOMOTIVE ENGINEERS INTERNATIONAL (SAE)

SAE AS4834	Aircraft Tire Retreading Practice – Bias and Radial
SAE ARP6404	Aircraft Tire Electrical Resistance Test

(Copies of these documents are available online at www.sae.org.)

AMERICAN SOCIETY FOR QUALITY (ASQ)

ASQ/ANSI Z1.4	Sampling Procedures and Tables for Inspection by Attributes

(A copy of this document is available online at www.asq.org/.)

AMERICAN SOCIETY FOR TESTING & MATERIALS (ASTM)

ASTM D413	Standard Test Methods for Rubber Property – Adhesion to Flexible Substrate
ASTM D746	Standard Test Methods for Brittleness Temperature of Plastics and Elastomers by Impact

(Copies of these documents are available online at www.astm.org.)

THE TIRE AND RIM ASSOCIATION, Inc. (TRA)

Aircraft Year Book	TRA Standards and related information approved by the Associate for tires, rims and allied parts for aircraft

(A copy of this document is available online at www.us-tra.org)

2.4 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein (except for related specification sheets), the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

3.1 Specification sheets. The individual item requirements shall be as specified herein and in accordance with the applicable specification sheet. In the event of any conflict between the requirements of this specification and the specification sheet, the latter shall govern. Some specification sheets are listed in Table I, but the list is ***not*** exhaustive.

3.1.1 Tire and Rim Association Aircraft Yearbook. In the event that no specification sheet exists, the TRA Aircraft Yearbook shall be the authority for tire dimensions.

3.2 Qualification. The retreaded tires furnished under this specification shall be products authorized by the qualifying activity for listing on the applicable Qualified Products List (QPL) before contract award (see 4.3 and 6.2) in accordance with Standardization Document (SD)-6. Changes in plants, construction, materials or processes require notification of the cognizant engineering authority to determine if the change will affect performance of the tire. If performance is affected, requalification requirements will be determined by the cognizant engineering authority. Qualification testing is only required with the first (R-1) application of a new tread or as otherwise specified in this document. Design and construction differences between radial tires of different manufacturers dictate that retread qualification testing (in accordance with 4.7 of this document) be conducted on each radial tire manufacturer's casing. Qualification of bias tire retreads on a single manufacturer's casing qualifies the retread on other manufacturers' compatible casings of the same size, ply rating, speed rating and National Stock Number (NSN). Commercial source retread tires used in military application may ***not*** comply with specific requirements cited herein and will be authorized by the cognizant engineering authority.

3.2.1 Qualification casing requirements. Unless otherwise specified, maximum damage (e.g. cuts, fatigue, casing ply exposure, etc.) to candidate tire casing (see 6.5) used for retread qualification shall be in accordance with FAA publication AC 145-4A. Each retread manufacturer shall provide a "Process Specification" document detailing the maximum permissible repairs that have been validated by tests, or analysis, or both for approval by the qualifying activity prior to being applied in service. The process specification shall also include preliminary inspection methods (such as non-destructive inspection (NDI)), escalation plan, and quality control processes. The casings selected for qualification testing shall have no less than 80 % (percent) of their new molded skid depth removed by wear (i.e. worn by aircraft usage).

3.2.2 Retread level escalation. Following successful qualification of retreaded tires at the first retreaded level, each part number shall be escalated in accordance with AC 145-4A. The escalation plan shall be submitted to the cognizant engineering authority as part of the process specification. The qualification test requirements of this document take precedence over those specified by AC 145-4A.

3.3 General requirements. Unless otherwise specified, tires shall be suitable for use on military aircraft, on all types of improved and unimproved runways, including ships (usually aircraft carrier decks), under all weather conditions. For retread tires ***not*** found in Table I, the procuring activity will provide the performance and interface requirements.

3.3.1 Ambient temperature range. The ambient temperature range, which a retread tire is required to operate, is: -58° to 125° F (-50° to 52° C). All retreaded tire compounds shall maintain their fracture toughness and strength characteristic with this temperature range.

3.3.2 Tire sizing and classification. Tire shall be sized and classified in accordance with either the TRA Aircraft Yearbook or the applicable specification sheet.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

3.4 Materials. Materials shall be of a quality shall meet the performance requirements specified in the applicable specification sheet. The use of toxic chemicals, hazardous substances, and ozone depleting chemicals shall be avoided, whenever possible. All aircraft tires shall be constructed of materials that meets electrical resistance requirements per SAE ARP6404. Reclaimed rubber/materials shall ***not*** be used without approval of the cognizant engineering authority.

3.5 Performance.

3.5.1 Basic tire performance. Unless otherwise specified, the basic performance of the tire shall be as specified in the applicable specification sheet.

3.5.2 Tire speeds. Unless otherwise specified, the retreaded tire shall have a minimum velocity capability of 120 miles per hour (mph) at the rated load and rated inflation pressure.

3.5.3 Burst pressure. The retreaded tire shall be designed to withstand a minimum burst pressure as specified in the applicable specification sheet. If burst pressure is ***not*** specified it shall be 3.5 times the rated pressure for land-based aircraft, and four (4) times rated pressure for carrier-based aircraft.

3.5.4 Dynamic durability. Unless otherwise specified, excluding wear, retreaded tires for fighters, attack, and trainer aircraft shall withstand a minimum of 50 cycles of taxi, takeoff, and landing; and retreaded tires for other aircraft shall withstand a minimum of 100 cycles of taxi, takeoff, and landing. In addition, the Department of Navy aircraft with carrier based requirements; retreaded tires shall withstand normal catapults, landing arrestments, and cable strikes without failure.

3.5.4.1 Cord fraying. During the dynamic life of the retreaded tire, cord fraying, if present in the groove of the tire, shall be only of the outer layer or cord.

3.5.4.2 Tread chunking. During the dynamic life of the retreaded tire, the tread chunk shall ***not*** exceed one (1) square inch in area or 75% of the skid; there shall be no more than three (3) chunks, each ½ to one (1) inch in area; and there shall be no more than 10 chunks totaling more than four (4) square inches in area. There shall be no rib undercutting.

3.5.4.3 Groove cracking. During the dynamic life of the retreaded tire, there shall be no groove cracking in retreaded tires having rubber or reinforced fabric tread. In retreaded tires with fabric tread, any void in the bottom of the groove shall be no deeper than a void caused by the outer layer of cord being pulled through the rubber stock in bottom of the groove. There shall be no rib undercutting.

3.5.4.4 Bead separation. During dynamic life of the retreaded tire, the walls of the bead bundle shall ***not*** show evidence of separating from the casing plies. If bead wires are used, individual wires shall ***not*** show evidence of separating from each other, or kinked, broken, or exposed.

3.5.4.5 Cable bruise (carrier based tires only). A tire to be used on carrier based aircraft shall withstand the minimum cable bruise load specified in the applicable specification sheet without pressure loss.

3.5.5 Wheel/tire slippage. A mounted retreaded tire inflated to rated inflation pressure shall ***not*** slip on the wheel rim to such an extent that would damage the tube or valve in a tube type tire or the inflation seal of a tubeless tire.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

3.5.6 Inflation pressure retention – tubeless tire. After an initial 12-hour stretch starting at rated inflation pressure, the pressure loss from rated inflation pressure in a tubeless retreaded tire assembly during the subsequent 24-hour period shall ***not*** exceed five (5) % of rated inflation pressure specified in the applicable specification sheet. The retreaded tire shall ***not*** show evidence of appearance defects such as sidewall blisters, tread separation, etc.

3.5.7 Balance. Retreaded tires shall be balanced, when ***not*** inflated, within tolerances specified in the applicable specification sheet. Out-of-tolerance conditions may be corrected by utilizing balance pads affixed to the inside of the tire. In tube type retreaded tires, the pads shall ***not*** chafe the tubes. Balance pad adhesion values shall be as follows: eight (8)-pound force per inch-width minimum for tubeless retreaded tires and 1.5 pounds force per inch-width minimum for tube type retreaded tires.

3.5.8 Tread adhesion. Retreaded tires shall have a minimum of 30-pounds force per inch-width adhesion at the interface between the tread or under tread and the outermost structural ply (casing, breaker, or belt ply).

3.6 Design and construction. Design and construction shall conform to the requirements specified in the applicable specification sheet.

3.6.1 Tire dimensions and weight. Dimensions and weight of the retreaded tire shall be as specified in the applicable specification sheet. All lettering and decorative ribs and designs shall be included in the dimensions. Dimension definitions are found in the TRA Aircraft Yearbook or the specification sheet.

3.6.2 Tire dimensions for helicopters. Helicopter retreaded tire dimensions shall be in accordance with the applicable specification sheet.

3.6.3 Tread. Retreaded tire tread may be manufactured using fabric-reinforced tread, fabric tread, or rubber.

3.6.3.1 Tread pattern. The tread shall be a ribbed tread pattern having a minimum of three (3) grooves for tires with a cross-sectional width greater than 6.0 inches, and minimum of two (2) grooves for tires with a cross-sectional width of 6.0 inches or less. The grooves shall be continuous and circumferential.

3.6.3.2 Underskid thickness. The material between bottom of the groove and first fabric layer shall be of sufficient thickness to minimize groove cracking. This requirement does ***not*** apply to fabric tread tires.

3.6.3.3 Maximum Wear Limit (MWL) indicator. If a colored indicator is used, it shall be visible when observing a cross-sectional cut.

3.6.3.4 Retread Buff Line (RBL). The RBL shall be a definitive, continuous, circumferential layer of uninterrupted rubber 0.060 inch minimum thickness extending shoulder to shoulder. The RBL shall be adjacent to and above the carcass or breaker plies in the finished tire. The retreader uses the RBL rubber stock location as a reference indicator to removal of old tread. The removal process shall not affect adhesion properties between the casing and tread rubber.

3.6.4 Sidewall. The sidewall shall protect the casing against abrasion and weathering.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

3.6.5 Venting. Means shall be provided to vent any trapped gases from the casing. If vent holes are used, the retreader shall verify sufficient venting in the casing. If vent holes are not providing sufficient venting, then reventing is required. Vent holes for tubeless tires shall not penetrate the liner of the tire, but may penetrate the liner of the tire for tube type tires.

3.6.6 Rim dimensions. Retreaded tires shall be designed and constructed to fit the rims as specified in the applicable specification sheet. If no specification sheet exists, the rim shall conform to the specification control drawing or to the rim profile recommended by the TRA Aircraft Yearbook.

3.6.7 Cut limit dimension. The cut limit is the allowable depth for cuts as measured from the bottom of the nearest groove in the vicinity of the cut. The cut limit shall be determined by the manufacturer. It shall be determined by calculating the number of structural cords that can be cut to allow continued safe operation of the tire.

3.7 Product identification and marking. Unless otherwise specified, the following information, as applicable, shall be marked legibly and permanently on the retreaded tire sidewall for the life of the casing. Markings on the retreaded tire sidewall shall be located so that they can ***not*** be removed during buffing for retreading. See Figure 1.

3.7.1 Original tire identification data. Unless otherwise specified the following identification data, required of the original tire manufacturer, are required to remain on the tire, and shall be remarked legibly and permanently on the tire sidewall if removed during retread manufacture. See MIL-DTL-5041 for details.

3.7.1.1 Date of manufacture and serial number. The lettering shall be a minimum of 3/16 inch in height.

3.7.1.2 Manufacturer’s name or trademark, or both.

3.7.1.3 The original MWL marking shall remain on the tire sidewall only if the limit for the retreaded tire is identical.

3.7.1.4 Size

3.7.1.5 On tube type tires include “TUBE TYPE.”

3.7.1.6 Ply rating (PR is permissible)

3.7.1.7 Original cut limit dimension shall remain on the tire only if the limit for the retreaded tire is identical.

3.7.1.8 National Stock Number (NSN)

3.7.1.9 The casing manufacturer’s original qualification test report (QTR) number, prefixed by “QTR.”

3.7.1.10 Tires shall be marked with appropriate type of tread construction if other than rubber tread only if the retreaded tread type is identical.

3.7.1.11 Part number – ensures traceability of casing.

3.7.1.12 Additional markings as required by the applicable specification sheets.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

3.7.2 Retreaded tire identification data. Unless otherwise specified the following information shall be marked legibly on the retreaded tire and shall be placed on the sidewall area such that the identification becomes a portion of the retreading compound. Markings on the tire sidewall shall be located so they ensure the markings are not be removed during buffing for retreading or during normal operation

3.7.2.1 The letter "R" followed by an Arabic number "1", "2", "3", etc., to signify the first, second, third and so on retreading of the casing. This is known as the retread level marking.

3.7.2.2 Date of manufacture shall be marked on the tire using either Julian date (see 6.5.7) or month and year (i.e. MM/YY). This marking shall be placed near but not adjacent to the retread level marking. At least 0.5 inch shall separate the retread date from the retread level marking.

3.7.2.3 Retread manufacturer's name and plant identifier.

3.7.2.4 Maximum Wear Limit. The MWL marking shall be either "MWL-RC" for tires with a colored indicator or "MWL #" for tires with a ply count indicator to be shown in a separate molded box (See Figure 2). For tires with an outside diameter greater than 26 inches, the MWL marking shall be molded in a minimum of two (2) places equally spaced on each sidewall of the tire. For tires with an outside diameter less than or equal to 26 inches, the MWL marking shall be molded once on each sidewall, 180-degrees from the cut limit marking, as shown in Figure 2. The lettering shall be a minimum of 3/8 inch high and the dimensions of the rectangle shall be a minimum of ½ inch by 1¼ inch in height. Department of the Navy retreaded tires do not require MWL indicator.

3.7.2.5 Cut limit dimension. The cut-limit dimension shall be expressed as increments of 1/32 inch and shall be rounded to the next smaller increment of 1/32 inch when a fraction of 1/32 inch is involved. The lettering shall be a minimum of ¼ inch in height and the diameter of the circle shall be a minimum of one (1) inch.

3.7.2.6 The retread manufacturer's QTR number prefixed by: "QTR."

3.7.2.7 Retreaded tires with a fabric tread shall be marked: "FABRIC TREAD."

3.7.2.8 Retread mold identification number.

3.7.3 Markings not required. For military tires with equivalent commercial applications, the following markings are not required: MWL, cut limit dimension, NSN, and QTR.

3.8 Interchangeability. All parts having the same manufacturer's part number shall be functionally and dimensionally interchangeable.

3.9 Age. The tire shall ***not*** be more than 36-months old from the date of manufacture to the initial date of delivery.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

4.1.1 Qualification Inspection (see 4.3)

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

4.1.1 Conformance Inspection (see 4.4)

4.2 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements specified herein. Except as otherwise specified in the contract or order, the supplier may use their own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.3 Qualification inspection. Qualification inspections shall be performed on tires when qualification is required (see 3.2 and 6.3). The qualification test sample shall include all the tests listed in paragraph 4.7. The qualification test samples shall consist of at least one tire of each construction, size, and type. The tire(s) shall be identified and marked as specified in paragraph 3.7. A waiver may be granted for the marking requirements on tires supplied for qualification test, when agreed between the qualifying activity and the manufacturer.

4.3.1 Qualification Test Report (QTR). The manufacturer shall prepare test reports in the general format shown in Appendix A, and shall furnish electronically to the Government Approving activity.

4.3.1.1 Bead-seating. When conducting bead-seating pressure tests on steel or non-aircraft wheels, results shall be specified in the QTR.

4.3.1.2 Mold skid depth. The mold skid depth shall meet the minimum requirements of the applicable specification sheet unless otherwise specified by the procuring activity. The molded tire skid depth in a groove closest to center of the tread shall be reported on the QTR.

4.3.1.3 Load deflection curves. A chart shall be included with the QTR showing load-deflection curves. The deflection shall be plotted on the y-axis, and the load on the x-axis. To include:

4.3.1.3.1 Seven (7) inflation pressure curves on the chart. One (1) curve shall be rated inflation pressure. Three (3) curves shall be less than the rated inflation pressure curve at approximately 85%, 70%, and 55% of the rated inflation pressure. Three (3) curves shall be greater than the rated inflation pressure at approximately 115%, 130%, and 160% of the rated inflation pressure. Department of the Navy tires shall include a load deflection curve at carrier inflation pressure.

4.3.1.3.2 All inflation pressure curves shown on the chart shall have a range from 16% deflection to the tire bottoming point.

4.3.1.3.3 The following percent deflection lines shall be plotted across the inflation pressure curves based on dimensions at rated inflation pressure: 16, 20, 24, 28, 32, 35, 37, 40, 44, and 48.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

4.3.1.3.4 The following data shall be listed in the lower right-hand corner of the load deflection chart:

Size_____ PR
Manufacturer
QTR Number
Rated Static Load (lb) _____ at _____ psi
Rated Speed (mph)
Rim Dia (in) _____Flange Ht (in)_____
Flat Tire Radius (in) _____
Data at Rated Static Load or Inflation (or both)
OD (in) _____ Section width (in)
Shoulder Dia (in)
Shoulder Width (in)
Loaded Radius (in)
Contact Area (sq in)
Bottomed Pressure (psi)
Bottomed Load (lb)

4.3.1.4 Footprints. Images indicating the actual shape, total gross contact area, and net contact area in square inches at rated static load and inflation, shall be submitted electronically with each QTR. The footprints shall include data at rated load, at increments of approximately 15%, 30%, and 45% above rated load, and at increments of approximately 15%, 30%, and 60% below rated load. For tires used by the Department of the Navy on carrier-based aircraft, a footprint at bottomed condition at carrier inflation pressure shall be submitted.

4.3.1.4.1 Tire size

4.3.1.4.2 Ply rating

4.3.1.4.3 Rated load and inflation

4.3.1.4.4 Net and gross contact area

4.3.1.4.5 Date

4.3.1.4.6 Manufacturer’s name

4.3.1.4.7 QTR number

4.3.1.5 Navy QTR inflated profiles. Inflated profiles indicating actual inflated shape of the tire at rated and carrier inflation pressures shall be submitted with each Navy QTR.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

4.3.1.6 Cross-section image. The supplier shall submit an 8 by 10-inch digital photograph taken perpendicular to and showing clearly the complete cross section of the tire with adequate contrast between the ends and body of the carcass, breaker and tread reinforcement cords, and the remainder of the tire section. The tire section shall be photographed with the beads spread so that the distance from heel-to-heel is the same as the flange-to-flange distance for the tire. A steel tape or ruler shall be laid at the base of the beads of the tire to show the distance between the bead heals. The photographs shall be submitted along with the QTR to the approving activity.

4.3.2 Qualification tests. The qualification tests shall consist of all the tests specified in paragraph 4.7 Qualification approval shall apply to a specific construction, size, and materials as defined in the manufacturer's QTR. The construction shall be identified by the manufacturer's QTR number.

4.3.3 Dynamic test inspection. When tires are dynamically tested, a section of the tire shall be submitted to the Government approving activity to determine any evidence of failure. The section shall be approximately two (2) inches in width and representative of the worst area. When the approving activity tests the tire, that activity reserves the right to section the tire in any manner necessary for the examination. The manufacturer shall submit an image taken perpendicular to and showing clearly the complete cross-section of the tire with adequate contrast between the ends and body of the casing, breaker, and tread reinforcement cords and the remainder of the tire section. The beads of the cross-section shall be spread so that the distance from heel-to-heel is the same as the flange-to-flange distance for the tire. A steel tape or ruler shall be laid at the base of the beads of the tire to show the distance between the bead heals. All images shall be submitted along with the QTR to the Government approving activity.

4.4 Conformance inspection. Conformance inspection shall include individual tests and sample tests.

4.4.1 Individual tests. Each retreaded tire shall be subject to the following tests:

4.4.1.1 Air injection test (see 4.7.1)

4.4.1.2 Pre-tested inspection test (see 4.7.2)

4.4.1.3 Examination of product test (see 4.7.3)

4.4.1.4 Balance test (see 4.7.4)

4.4.2 Sample tests. Unless otherwise specified, retreaded tires shall be sampled in accordance with ASQ/ANSI Z1.4 at initial inspection level of the normal, and the tread adhesion tests shall be performed.

4.4.2.1 Tire dimensions, weight, and rim interface (see 4.7.5)

4.4.2.2 Mold dimensions

4.5 Test conditions. Unless otherwise specified in the individual test description (see 4.7), all tests shall be conducted at ambient temperature and pressure as specified in applicable paragraphs below.

4.6 Requirement cross-reference matrix. Table II provides a cross-reference matrix of the Section three (3) requirements tested or verified in the paragraphs below.

4.7 Test methods.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

4.7.1 Air injection test. The air injection procedure and test for checking all tubeless tires shall be performed.

4.7.2 Pre-tested inspection test. All tire casings covered by this specification shall be inspected before retreading to determine compliance with the requirements for acceptable casing conditions.

4.7.3 Examination of product test. The tire and associated documentation shall be examined to determine compliance with size, materials, dimensions, weight, bead width, tread pattern, sidewall, venting, identification, interchangeability, and age requirements. Non-Destructive Inspection (NDI) techniques (shearography, or other method approved by cognizant engineer), other than visual, shall be utilized to check all casings for separations or other damage.

4.7.4 Balance test. The tire shall be balance checked to determine that the moment required to static balance the tire does not exceed the limits specified in the applicable specification sheet.

4.7.5 Tire dimensions, weight, and rim interface test. The retreaded tire shall be mounted on its rim, inflated to rated inflation pressure specified in the applicable specification sheet, allowed to stand for 12-hours minimum at room temperature, and then re-adjusted to rated inflation pressure. The tire dimensions and weight shall then be determined and compared to values the applicable specification sheet. The tire weight may be measured unmounted. Manufacturers are responsible for ensuring that the new tire inflated dimensions are properly correlated to the grown dimensions to ensure conformance to the grown tire envelope.

4.7.6 Balance pad adhesion test. Balance pad adhesion shall be tested in accordance with ASTM D413 to determine compliance with the balance pad adhesion requirement.

4.7.7 Dynamic durability test. A dynamic durability test shall demonstrate satisfactory retread tire performance during the taxi, takeoff, and landing cycles. Unless otherwise specified, test parameters for taxi, takeoff, and landing are specified in the applicable specification sheet. Suggested test methods for tire speeds at 120 mph and provided in SAE AS4834.

4.7.7.1 Dynamic durability test temperature. Unless otherwise specified, the contained air temperature or highest casing temperature at the start of 80% of the taxi, takeoff, and landing cycles shall be no less than 105° ± -5° F (41° ± 3° C).

4.7.7.2 Cable bruise test (carrier based aircraft tires only). Unless otherwise specified, the tire shall be inflated to carrier pressure, and vertically loaded against a 1.625-inch diameter length of plain round steel stock or equivalent diameter arresting gear cable to the specified vertical load in the applicable specification sheet. Unless otherwise specified, immediately following the release of this load, the tire shall be subjected to the same loading conditions 180-degrees from the application of the first load.

4.7.7.3 Post-test inspection. At the conclusion of the dynamic durability test, the examination of product test (see 4.7.3) shall be performed with the retreaded tire at rated inflation pressure. In addition, the retreaded tire and associated documentation shall be examined to determine compliance with the fabric material, chafing resistance, MWL indicator (if applicable), tread chunking, groove cracking, cord fraying, bead separation, cable bruise (for carrier-based aircraft tires), RBL, and wheel/tire slippage requirements. Non-destructive inspection techniques, other than visual or air injection, shall be utilized to verify the retread tire has met specification requirements. The post-test inspection shall include examination of a cross-sectional cut.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

4.7.7.4 Bead separation test. If bead bundle or wire separation is found in the cross-sectional cut, the material around the bead bundle shall be stripped back at least one (1) inch to determine if the separation was caused by the cross-sectional cut of the post-test inspection or during the dynamic durability test. If no separation is found in the stripped area, the bead construction shall be considered satisfactory.

4.7.8 Low temperature test. Samples of the tread, casing, and liner compounds shall be tested in accordance with ASTM D746 at -58° F (-50° C). Alternate test method may be used, providing the data is submitted substantiating an equivalent test method and the alternate method and approved by the responsible qualifying activity.

4.7.9 Inflation pressure retention test – tubeless tires. The retreaded tire shall be inflated to rated inflation pressure specified in the applicable specification sheet and allowed to stand for a minimum of 12-hours, at which time the pressure loss due to stretch shall be replaced. The retreaded tire shall then stand for an additional 24-hours, at which time the pressure shall be recorded. Ambient temperature shall be measured at the start and finish of the test to assure that any pressure change was ***not*** caused by ambient temperature change. At no time shall the retreaded tire be inflated above rated inflation pressure.

4.7.10 Burst pressure test. The minimum burst pressure specified in the applicable specification sheet shall be applied to the mounted tire and held to a minimum of three (3) seconds. The tire shall ***not*** fail under this pressure. The burst pressure test of a tubeless tire may be conducted with a tube in the same manner as for tube type tires. The tire pressure shall then be increased until the tire bursts or the limit of the equipment is reached, provided the limit of the equipment is over the minimum burst pressure. The testing agency shall report whether failure was a casing or a bead failure.

5. PACKAGING

5.1 General. For acquisition purposes, the packaging requirements shall be specified in the contract or purchase order. When actual packaging of materiel is to be performed by DoD personnel, these personnel will contact the responsible packaging activity to ascertain requisite packaging requirements. Packaging requirements will be maintained by the Inventory Control Point packaging activity with the Military Department or Defense Agency, or within the Military Department or Defense Agency automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

5.2 Marking for shipment. Each retreaded tire shall be labeled in accordance with MIL-STD-129. The identification shall consist of the following information listed in the order shown:

5.2.1 National Stock Number (NSN). Tire, Pneumatic, Aircraft Specification MIL-DTL-5041

5.2.2 Color coding, age identification. The retreaded tire shall be color-code taped for age identification using the color of tape in accordance with MS14113. Color used shall reflect year of casing manufacture, with the date of year superimposed on the tape.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. Retreaded tires covered by this specification are intended for use on all military aircraft.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

6.2 Acquisition requirements. Acquisition documents specifically include, but are not limited to the following, unless specified in this specification:

6.2.1 Title, number, and date of this specification

6.2.2 The referenced applicable documents

6.2.3 Operational environment

6.2.4 Performance or interface requirements

6.2.5 Basic tire performance requirements

6.2.6 Retreadability requirements

6.2.7 Taxi, takeoff, and landing cycle conditions to be met

6.2.8 Tire identification data

6.2.9 Initial inspection level or sample tests

6.2.10 Test conditions

6.2.11 Dynamic durability test requirements

6.2.12 Packaging requirements

6.2.13 Data required

6.3 Qualified Parts List (QPL). With respect to products requiring qualification, contract award will only be made for products qualified for inclusion in the QPL at the time of contract award, and whether or not such products have been listed by that date. Contractors are urged to study these requirements. Manufacturers are advised to have their products in order they propose to offer to the Federal Government to be tested for qualification, to assist in eligibility for contract awards or for product orders covered by this specification. Product qualification information may be obtained from the Landing Gear Program Office, 417th SCMS, 6040 Gum Lane, Bldg. 1216, Hill AFB, UT 84056-5825 or email 748SCMG.Workflow@us.af.mil, attn: 417th Landing Gear. The online listing of products qualified to this specification are found in the Qualified Products Database (QPD) at https://assist.dla.mil. Product qualification procedures are found in the SD-6 at https://assist.dla.mil. Additional QPD information found at https://qpd.dla.mil/qpd/.

6.4 Additional information.

6.4.1 Use of tubeless tire in tube type application. In tube type applications, tubeless tires (with a tube installed) may be used in lieu of tube type tires.

6.5 Definitions.

6.5.1 Bead bundle. High tensile strength steel wires embedded in rubber. The beads anchor the casing plies and provide a firm-mounting surface on the wheel.

6.5.2 Casing. The casing consists of the beads, cord body, and sidewall of a tire intact.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

6.5.3 Casing ply. One (1) or more strips or layers of fabric found in the casing.

6.5.4 Escalation. To verify that a population of retread tires is suitable for another life and determine the control/verification plan to put into place for individual tires.

6.5.5 Fabric-reinforced tread. A fabric reinforced tread is at one with a fabric ply or plies constructed in the material between the outer casing ply and the bottom of the tread grooves.

6.5.6 Fabric tread. A fabric tread is at one with a fabric ply or plies constructed in the tread ribs above the bottom of the tread grooves.

6.5.7 Julian date. The Julian date is a five (5) digit alphanumeric code indicating the year and number of the day of the year. For example, the Julian date for May 23, 1996 – the *number of the day* is 143 of 1996, and appears as 96143. An acceptable variation of the Julian date is a decade identifier, and may be used and assigned by the manufacturer. This variation is also a five (5) digit alphanumeric code indicating the year, the number of the day of the year, and a decade identifier. For example, the Julian date May 23, 1996 would state the *number of the day* as 143 of 1996, and would appear as 6143J, "J" being the decade identifier.

6.5.8 Liner. The inner layer of low permeability rubber in a tubeless tire, which acts as a built-in tube and prevents gas from seeping through the casing plies.

6.5.9 Ply Rating. The term *ply rating* (PR) is used to identify a given tire with its maximum recommended load when used in a specific type of service. It is an index of the tire strength and does ***not*** necessarily represent the number of cord plies. The ply rating is ***not*** to be interpreted as limiting the number of plies that may be used in a given tire construction.

6.5.10 Rated inflation pressure. The rated inflation pressure is the specified inflation pressure corresponding to the rated load for the tire.

6.5.11 Rated load. Rated load is the maximum permissible load at the specified inflation pressure. Rated loads are established and standardized by Tire and Rim Association (TRA) or a specification sheet. The rated load combined with the rated inflation pressure is utilized when selecting tires for application to an aircraft and for testing to the performance requirements of this document.

6.5.12 Retread Buff Line (RBL). The RBL is a definitive, continuous, circumferential layer of uninterrupted rubber, 0.060 inch minimum thick, extending shoulder to shoulder. The RBL is located adjacent to and above the carcass or breaker plies in the finished tire.

6.5.13 Retread level marking. Reflects the number of retreading operations the tire has undergone (e.g. first retread is represented with a "1" and second retread is represented with a "2," etc.).

6.5.14 Retread tire. A retread aircraft tire has had the worn casing restored by renewing the tread material or the tread and sidewall material. Retreaded tires are sometimes referred to as "rebuilt," "recapped," or "remanufactured" tires.

6.5.15 Ribbed Tread. A ribbed-type tread pattern is one having continuous circumferential ribs and grooves

6.5.16 Rubber tread. A rubber tread is at one with no reinforcing plies in the tread material.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

6.5.17 Skid depth. Skid depth is the radial distance, measured along the centerline of the tire mold, from the line enveloping the outer cross section of the tread to the line enveloping the outer cross section of the under tread of the deepest groove.

6.6 Subject term (key word) listing.

Packaging
Qualification requirements
Retread
Verification

6.7 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes. A *Summary of Changes* page was added on page iii.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

TABLE I.
Tire drawing matrix.

WHEEL TYPE	SIZE	PLY RATING	DRAWING or MS NUMBER 2/
TL	12.50 – 16	12	MS22080
TL	20.00 – 20	26	MS27823
TL	20 X 5.5	14	MS3380
TL	24 X 5.5	16	MS3381
TL	28 X 7.7	14	MS3384
TL	36X11	22	66D32270
TL	36X11	22	855955
TL	36X11	24	MS14186
TL	38X11	14	MS27818
TL	40 X 14	28	MS3387
TL	44X16	28	MS27815
TL	46X16	28	TSO-C62 3/
TL	49X17	26	MS27811
TL	49/11	26	71204
TL	56X16	38	MS27811
TL	22X6.75 – 10	18	MS14185
TL	30X11.5 – 14.5	26	MS14172
TL	34.5X9.75 – 18	26	855854
TL	50X21.0 – 20	30	PS 17026

Key:
1/ TL Tubeless
2/ The above listed Air Force and Navy drawings and MS (slash) sheets contain only performance data and do not contain detail drawings.
3/ TSO-C62 is a technical standard order that prescribes the minimum performance standards for certain tires.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

TABLE II.
Paragraph cross-reference matrix.

Section 3 – Requirement Paragraphs	Section 4 – Qualification Test Method
3.2 Qualification	4.7
3.2.1 Qualification casing requirement	4.7.2 and 4.7.3
3.2.2 Retread level escalation	4.7 and 4.7.2
3.3 General requirements	4.7
3.3.1 Ambient temperature range	4.5, 4.7.7.3, and 4.7.8
3.3.2 Tire sizing and classification	4.7.3
3.4 Materials	4.7.3 and 4.7.7.3
3.5.1 Basic tire performance	4.7
3.5.2 Tire speeds	4.7.7
3.5.3 Burst pressure	4.7.10
3.5.4 Dynamic durability	4.7.7
3.5.5 Wheel/tire slippage	4.7.7.3
3.5.6 Inflation pressure retention	4.7.9
3.5.7 Balance	4.7.4 and 4.7.6
3.5.8 Tread adhesion	4.7.7
3.6.1 Time dimensions and weight	4.7.3 and 4.7.7.3
3.6.2 Tire dimensions and weight for helicopters	4.7.3 and 4.7.7.3
3.6.3.1 Tread pattern	4.7.3
3.6.3.2 Underskid thickness	4.7.7.3
3.6.3.3 Maximum Wear Limit (MWL) indicator	4.7.7.3
3.6.3.4 Retread Buff Line (RBL)	4.7.7.3
3.6.4 Sidewall	4.7.3
3.6.5 Venting	4.7.2 and 4.7.3
3.6.6 Rim dimensions	4.7.5
3.6.7 Cut Limit Dimensions	2/
3.7 Product Identification and Marking	4.7.3
3.8 Interchangeability	4.7.3
3.9 Age	4.7.3

Key:
1/ Determined in Process Specification provided by manufacturer
2/ Determined by manufacturer – no reportable test requirement

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

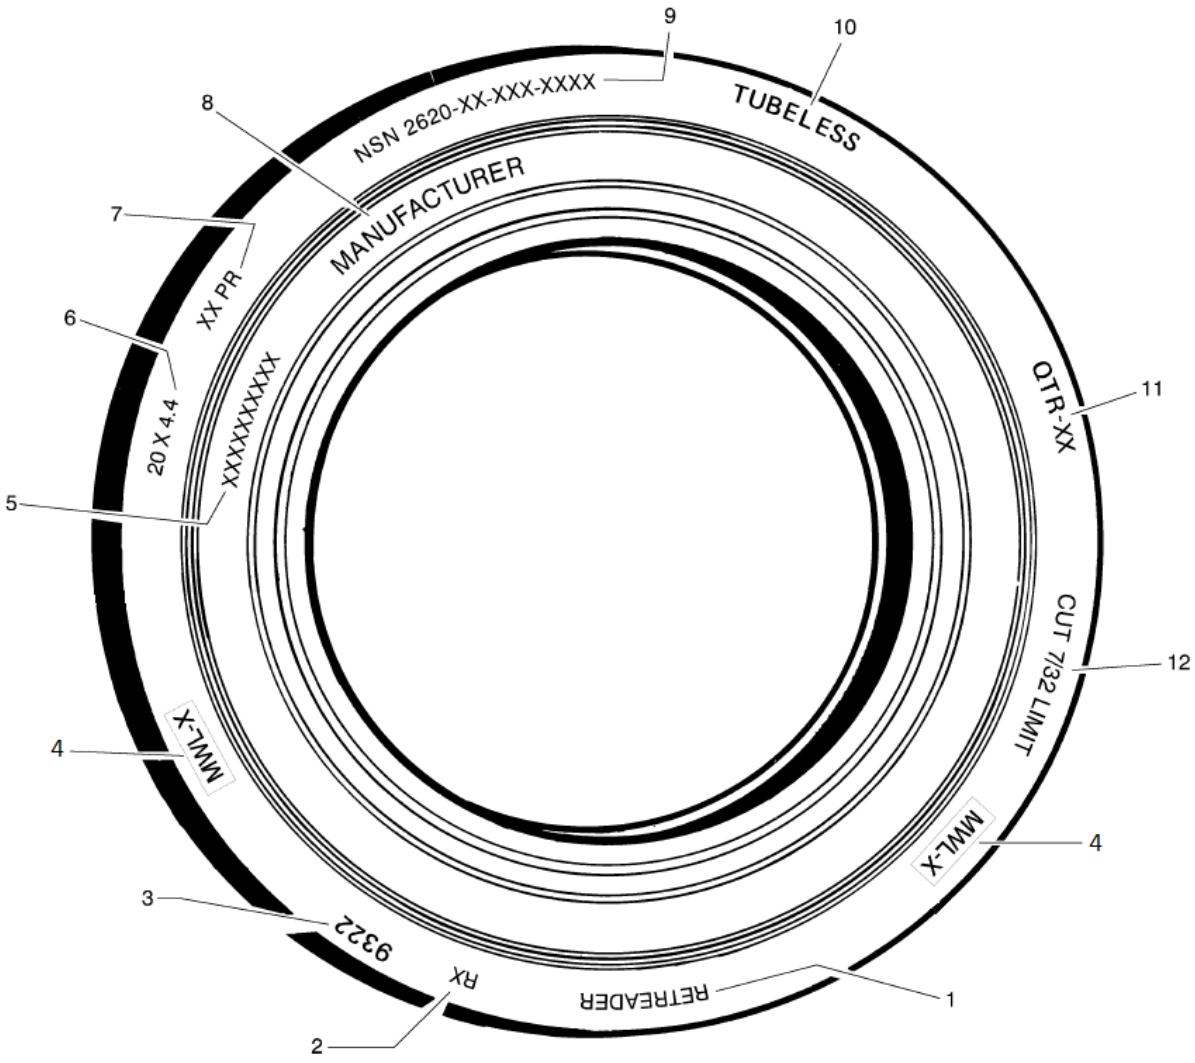


FIGURE 1. Part marking

Key:
1. Retreader name and plant identifier
2. Retread level marking
3. Date of retread manufacture
4. Maximum wear limit
5. Date of manufacture and serial number
6. Size
7. Ply rating
8. Manufacturer's name or trademark, or both
9. National Stock Number (NSN)
10. Type (tube type or tubeless)
11. QTR number (new and retread)
12. Cut-limit dimension identification

NOTE – Exact location is ***not*** required.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

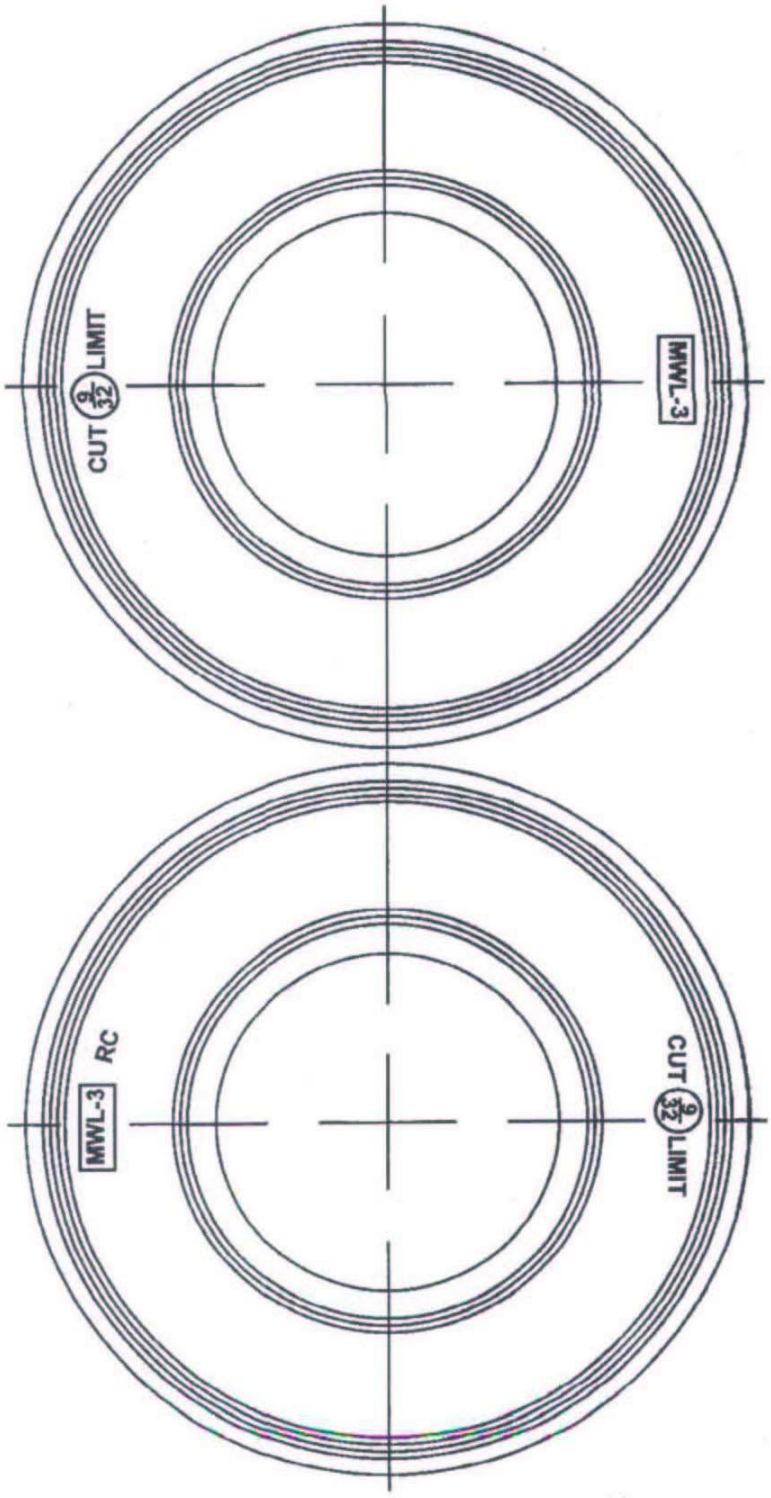


FIGURE 2. Cut-limit dimensions and maximum wear limit identification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

QUALIFICATION TEST REPORT (QTR) FORMAT

A.1 HEADER SECTION

The header for each page, (except the title page) shall be as follows:

[Manufacturer] QTR:
DATE:
PAGE:

A.2 TITLE PAGE SECTION

[Company Name] [Location]

[Date]

Qualification Test Report #_____

To

[Customer]

For [Weapon System]

[New or Rebuilt, Bias or Radial, NLG or MLG Tire] [Size]

[NSN]

[P/N (if other than QTR#)]

References: [OEM/military specification], MIL-DTL-5041

Prepared by: _____
Design Engineer

Reviewed by: _____
Design Engineering

Approved by: _____
R&D, QA

Reviewed by: _____
Government Representative

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

A.3 TABLE OF CONTENTS SECTION.

TABLE OF CONTENTS

ITEM PAGE

QUALITY TEST REPORT TITLE

COMPLIANCE

STATIC TEST REQUIREMENTS / RESULTS
- Measurements
- Load Deflection Curves
  - Static
  - Dynamic / Impact (if applicable)
  - Impact Energy (if applicable)
  - Contact Area (if applicable)
- Tire Contact Areas
- Inflated Tire Profile
- [Other static data required by specification]

DYNAMIC TEST REQUIREMENTS

DYNAMIC TEST RESULTS
- Tire #1
- Tire #2
- Tire #3
- Grown Profile (if applicable)
- Thrown and Grown Profile (if applicable
- [Other dynamic data required by specification]

OTHER PERTINENT DATA
- Torsion Recovery at Low Temperature
- Low Temperature Brittleness Qualification
- High Temperature Compliance (if applicable)
- Quality Control
- Product Identification and Marking
- Photograph
- Cut Limit
- Colored Wear Indicator (if applicable)
- [Other data required by specification]

APPENDICES
- APPENDIX A. FOOT PRINTS
- APPENDIX B. LOAD-SPEED-TIME CURVES
- APPENDIX C. LOW TEMPERATURE APPROVALS
- APPENDIX D. PHOTOGRAPH

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

A.4 COMPLIANCE SECTION.

COMPLIANCE
The [specific aircraft, N/MLG tire, size] has successfully completed the requirements of [OEM/military specification, revision no., revision date] and MIL-DTL-5041. Test results were obtained on tires manufactured on production equipment at [facility/location] and are representative of future production tires. [Include any general comments concerning test results or post-test condition of tires.]

A.5 STATIC TEST REQUIREMENTS / RESULTS SECTION.

STATIC TEST REQUIREMENTS / RESULTS		
Size_____	No. carcass plies_____	Cord material_____
Ply rating_____		
Low temperature approval:		
A) Tread / Carcass: [Identification, Approving Authority, Approval Date]		
B) Inner lining: [Identification, Approving Authority, Approval Date]		
Speed rating_____knots	Rated load_____lbs	Rated pressure_____psi

ITEM		**REQUIREMENTS**	**QUALIFICATION RESULTS**
(A)	Balance	Max _____ in-oz	_____ in-oz
(B)	Bead Seat Pressure	Max _____ psi	_____ psi
		Min _____ psi	_____ psi
(C)	Bead Width	Max _____ in	_____ in
(D)	Burst Pressure	Min _____ psi	_____ psi
(E)	Loaded Radius	Nominal _____ in	_____ in
	Tolerance @ Rated Load And Pressure: _____ to _____ in		
(F)	Dimensions		
	Outside Diameter	Max ____ in	_____ in
		Min ____ in	
	Section Width	Max ____ in	_____ in
		Min ____ in	
	Shoulder Diameter	Max ____ in	_____ in
		Min ____ in	
	Shoulder Width	Max ____ in	_____ in
		Min ____ in	

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

A.5. STATIC TEST REQUIREMENTS / RESULTS SECTION – Continued.

ITEM		REQUIREMENTS	QUALIFICATION RESULTS
(G)	Mold Skid Depth	Min_____ in	_____ in
(H)	Total Tread Thickness	Min _____ in	_____ in
(I)	Weight	Max _____ lbs	_____ lbs
(J)	Retread buff line (if applicable)	Min 0.06 inch	_____ in
(K)	Air retention (tubeless)	Max loss 5%	_____ %
	@ Rated inflation pressure and constant ambient temperature		
(L)	Number of wires per bead bundle	(as determined)	_____ 1st
		(as determined	_____ 2nd
		(as determined	_____ 3rd
		(as determined	_____ 4th
(M)	Chafing strips	(as determined)	_____ each
(N)	Bead tie-in:		
	Heel ply turn-ups	(as determined)	_____ each
	Toe ply turn-ups	(as determined)	_____ each
	Flippers/Bead bundle	(as determined)	_____ each
(O)	Minimum load capacity of cord	(as determined)	_____ lbs
(P)	Cord count in crown	(as determined)	Plies___ Count____ Each
	Measured at 90º angle to cord axis		Plies___ Count____ Each
			Plies___ Count____ Each
(Q)	Total crown thickness	(as determined)	_____ in
(R)	Number of breaker plies	(as determined)	_____ each
(S)	Number of tread reinforcing plies	(as determined)	_____ each
(T)	Sidewall vents per sidewall	(as determined)	_____ each
(U)	Durometer hardness	(as determined)	_____ Shore
(V)	Balance pad adhesion	Min 8 lb tubeless	_____ lbs
		Min 1-1/2 lb tubetyle	_____ lbs

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

A.5.1 CONTACT AREAS SECTION.

CONTACT AREAS

The contact areas for the applicable load and inflation conditions are summarized below per [OEM/military specification] and MIL-DTL-5041. Footprints are located in this document see 4.3.1.4.

Percent of Rated Load	Actual Load (lbs)	Inflation (psi)	Gross Contact Area ($inch^2$)	Net Contact Area ($inch^2$)
40				
55				
70				
85				
100 (Rated)				
115				
130				
145				
Bottomed				

[**Size/Ply Rating/Speed Rating**]

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

A.6 DYNAMIC TEST REQUIREMENTS SECTION.

DYNAMIC TEST REQUIREMENTS
[**Loads and Inflation Pressures**]
[**Test Sequence Requirements**]
Tire #1:
Tire #2:
Tire #3:
[**Cycle Destinations (including references to LST curves)**]
Taxi - Take-off
Extended taxi - Take-off
Taxi – High-speed take-off
Landing – Taxi
Taxi-out – Turn
Taxi-in – Turn
Taxi – Aborted take-off, Stop, Taxi
Envelope compliance
[**Special Requirements**]
Cable bruise
Step load obstruction

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

A.7 DYNAMIC TEST RESULTS SECTION.

DYNAMIC TIRE #1		
Test completion date:		
Test specification:		
Size, Ply rating, Type:		
Serial number:		
Actual tire weight (lbs):		
Bead seating pressure (psi):		
Dimensions	After 12-hours minimum growth	
Rated inflation (psi)		
Outside diameter (inch)		
Section width (inch)		
Shoulder diameter (inch}		
Shoulder width (inch)		
Flat plate deflection at rated load/pressure	Before break-in	After Break-In
(inch)		
(%)		
Curved surface inflation before break-in (psi)		
[**Name of test cycle**] [LST Curve No. or Figure No.]	Taxi	Take-off
Flywheel outside diameter (inch)		
Test inflation (psi)		
Acceleration (ft/sec^2)		
Speed range (knots)		
Roll distance (ft)		
Taxi time (sec}		
Time programmed take-off (sec)		
Load range (lbs)		
Average peak carcass air temp (°F)		
Number of test cycles		
Remarks: [Tire condition following completion of test cycles shall be described in this section.]		

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

A7. DYNAMIC TEST RESULTS SECTION. DYNAMIC TIRE #1 (Continued)

[**Name of Test Cycle**] [LST Curve No. or Figure No.]	LANDING	TAXI
Flywheel outside diameter (inch)		
Test inflation (psi)		
Deceleration rate (ft/sec^2)		
Speed range (knots)		
Roll distance (ft)		
Taxi time (sec)		
Time programmed landing (sec)		
Load range (lbs)		
Average peak carcass temp (°F)		
Number of test cycles		
Remarks: [Tire condition following completion of test cycles shall be described in section]		
[**Name of Test Cycle**] [LST Curve No. or Figure No.]	TAXI	TAKE-OFF
Flywheel outside diameter (inch)		
Test inflation (psi)		
Deceleration rate (ft/sec^2)		
Speed range (knots)		
Roll distance (ft)		
Taxi time (sec)		
Time programmed landing (sec)		
Load range (lbs)		
Average peak carcass temp (°F)		
Number of test cycles		
Remarks: [Summary of all test results shall be provided in this section. Any evidence of tread chunking or groove cracking shall be noted. Refer to submitted cut section or photo as necessary.]		

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

A.8 OTHER PERTINENT DATA SECTION

Low Temperature Brittleness Qualification (Tubeless Tire Liner Compound Only)

Aircraft tire liner compound construction [#] has met the low temperature requirement in accordance with paragraphs 3.3.1 and 4.7.7 of MIL-DTL-5041. The brittleness temperature of construction [#], as defined by ASTM D746, is _____ degrees° F. A copy of the USAF approval letter is located in [appendix].

High Temperature Compliance

Quality Control

Preproduction acceptance criteria are established for control of raw material to be used in all aircraft tires (qualification test tires and production tires) manufactured at [facility location]. This then assures material used in production tires meets the same control limit as that used in the qualification tires. Dynamic testing assures these materials with the established limits are adequate.

Qualification test tires represented in this QTR were manufactured in the [name] facility under the same quality assurance criteria and test procedures that are applicable production tires.

Product Identification And Marking

The identification markings on the tire conform to paragraph 3.7 of MIL-DTL-5041 [and to section _____of OEM/military specification].

Photograph Cross-Section

A photograph, which clearly depicts (adequate contrast) the cross-sectional design of the subject tire (i.e. number of tread plies, number of tread reinforcing plies, number of breaker plies, number of carcass plies, colored wear indicator), is located in [appendix].

Cut Limit

A cut limit of [X/32] is recommended.

Colored Wear Indicator (If Applicable)

Per [OEM/military specification], a [color] colored wear indicator ply is located [just below or just above] the first carcass ply.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.

CONCLUDING MATERIAL

Custodians:
Army – AV
Navy – AS
DLA – GS
Air Force – 70

Preparing Activity:
Air Force – 70

Review Activities:
United States Marine Corps – MC

Project 2620-2018-001

NOTE: The activities listed above were interested in this document as of the date of this document. Some organizations and responsibilities can change verification of this currency of the information above by using ASSIST Online database or https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T08:46Z
Check the source to verify that this is the current version before use.