MILITARY SPECIFICATION

DELAY COMPOSITION, TUNGSTEN-FLUOROCARBON COPOLYMER

This specification is approved for use by the Naval Sea Systems Command, Department of the Navy, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers one type of Tungsten-Fluorocarbon copolymer delay composition.

1.2 Classification. This type of delay composition shall be of three classes depending upon the burning time ranges, as follows:

Class I 2.5 to 7.5 sec/in at 24 ± 4°C.
Class II 7.5 to 12.5 sec/in at 24 ± 4°C.
Class III 12.5 to 32.5 sec/in at 24 ± 4°C.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. Unless otherwise specified, the following specifications and standards of the issue listed in that issue of the Department of Defense Index of Specifications and Standards (DODISS) specified in the solici tation form a part of this specification to the extent specified herein.

SPECIFICATIONS

Federal

O-A-51	Acetone, Technical
PPP-B-601	Boxes, Wood, Cleated Plywood
PPP-B-621	Box, Wood, Nailed and Lock Corner

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commanding Officer, Naval Ordnance Station, (524), Indian Head, MD 20640-5000, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

Military

MIL-P-116	Preservation - Packaging, Methods of
MIL-P-217	Potassium Perchlorate
MIL-B-550	Barium Chromate
MIL-P-22264	Powders, Ignition, Gasless, AlA

Naval Sea Systems Command

OS 8990	Diatomaceous Earth
OS 9765	Boron-Potassium Nitrate
WS 7682	Copolymer, Vinylidene Difluoride and Hexafluoropropylene
WS 7692	n-Hexane

Naval Air Systems Command

AS 2686	Tungsten Metal Powder, Pyrotechnic

STANDARDS

Military

MIL-STD-129	Marking for Shipment and Storage
MIL-STD-1218	ACS Grade Chemical
MIL-STD-1234	Pyrotechnics: Sampling, Inspection and Testing

2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this specification to the extent specified herein.

DRAWINGS

Naval Sea Systems Command

NAVORD	2249362	Test Element Loading Assembly
NAVORD	2249363	Delay Body
NAVORD	2249365	Output Charge Holder Loading Assembly
NAVORD	LD 518765	Test Element

PUBLICATIONS

Naval Air Systems Command

AD 1014	Operating Procedures for Pyrotechnic Delay Timing Apparatus

Code of Federal Regulations

49 CFR 100-177	Transportation
49 CFR 178-199	Transportation

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

(Application for copies of the Code of Federal Regulations should be addressed to the Superintendent of Documents, Government Printing Office, Washington, D.C. 20404. Orders for this publication should cite "the latest edition and Supplements thereto.")

(Copies of specifications, standards, drawings and publications required by suppliers in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. The issue of the documents which are indicated as DoD adopted shall be the issue listed in the current DODISS and the supplement thereto, if applicable.

NATIONAL MOTOR FREIGHT CLASSIFICATION RULES

(Application for copies should be addressed to the American Trucking Association, Inc., Traffic Department, 1616 P Street, NW, Washington, DC 20036.)

UNIFORM FREIGHT CLASSIFICATION RULES

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza Chicago, IL 60606).

(Industry association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence.

3. REQUIREMENTS

3.1 Description. The tungsten-fluorocarbon copolymer delay compositions shall be homogeneous mixtures of tungsten, barium chromate, potassium perchlorate, diatomaceous earth, and a fluorocarbon copolymer.

3.2 Materials. The materials used in the manufacture of the tungsten fluorocarbon copolymer delay composition shall conform to the following:

3.2.1 Tungsten. The tungsten shall conform to AS 2686, Type II. These tungsten particle size ranges are considered most useful for the given burning time series. With proper adjustment of composition tungsten percentage, any particle size close to the suggested range may be used to achieve the desired burning time.

Class	AS 2686, Type II
I	Class 2
II	Class 3
III	Class 4

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

3.2.2 Barium chromate. The barium chromate shall conform to MIL-B-550, Grade A.

3.2.3 Potassium perchlorate. The potassium perchlorate shall conform to MIL-P-217, grade A, class 3.

3.2.4 Diatomaceous earth. The diatomaceous earth shall conform to OS 8990.

3.2.5 Flourocarbon copolymer. The vinylidene difluoride and hexafluoropropylene copolymer shall conform to WS 7682.

3.2.6 Acetone. The acetone solvent shall conform to O-A-51.

3.2.7 Hexane. The hexane non-solvent shall conform to WS-7692.

3.3 Formulation. The material components of the tungsten fluorocarbon copolymer delay composition shall be homogeneously mixed. Advisory formulation shall be as follows:

Ingredient	Percentage ranges	Nominal percentages
Tungsten	25 - 75%	
Barium chromate (As required)	12 - 62%	
Potassium perchlorate		7%
Diatomaceous		5%
Fluorocarbon copolymer		1%

In order to meet the specific burning time characteristics required, the percentage composition by weight of tungsten can be determined by pilot mixture (see 6.3.6) Figure 1 shows the effect of percentage tungsten on burning time. The composition which conforms to the performance requirements of 3.4, 3.5, and 3.6 shall be considered in compliance with the formulation requirements.

3.4 Burning time at 24 ± 4°C. The burning time of the tungsten-fluorocarbon copolymer delay composition shall conform to the basic time and tolerance specified (see 6.2.1). The burning time of the tungsten-fluorocarbon copolymer delay composition is an average value ascertained under the provisions of 4.3.2. The percent coefficient of variation (CV) of the observed burning times shall not be greater than shown below for the ranges indicated.

Class	Burning time, sec/in	CV, %
I	2.5 to 7.5	10.0
II	7.5 to 12.5	7.0
III	12.5 to 32.5	5.0

3.5 Burning time at -54 ± 20°C. The burning time shall not be increased by more than 15.0 percent when the initial temperature is changed to -54 ± 2°C. The provisions of 4.3.3 shall be applicable in determination of low-temperature functioning. The percent coefficient of variation of observed burning time shall be as specified in 3.4 at all required temperatures.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

3.6 Delay performance. There shall be no delay failures at room temperature or at the low temperature specified above. A delay failure shall be a condition where ignition powder ignites but the delay column does not burn through. Satisfactory performance of 4.3.2 and 4.3.3 tests with no delay failures shall constitute conformance to this requirement.

3.7 Moisture content. The moisture content of the delay composition shall not exceed 0.05 percent maximum when tested in accordance with 4.3.4.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in this specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Lot. A lot of tungsten-fluorocarbon copolymer delay composition shall consist either of a manufacturer's batch which has been mixed as a unit from the ingredients or a blend of one or more such batches offered for acceptance at one time.

4.1.2 Sampling. Sampling of the tungsten-fluorocarbon copolymer delay compositions for test purposes shall be performed following the last mixing operation and screening of the dried powder. Each lot (4.1.1) to be tested shall be divided into 20 equal parts so that 20 delay bodies may be so loaded that each delay body contains a representative sample from one of the 20 parts without duplication (see 4.3.2). A second representative pooled sample of the delay composition is selected of a sufficient quantity tc load a minimum of 10 test elements according to 4.3.2.1 for the low-temperature functioning test (4.3.3). All sampling prior to test loading or loading in delay assemblies shall be carried out in areas having a relative humidity below 60 percent. The samples shall be stored in hermetically sealed containers and correctly labeled to show the following information:

(a) Name of item
(b) Weight of sample
(c) Lot number of delay composition
(d) Manufacturer
(e) Date of manufacture

4.2 Quality conformance inspection. The material shall be subjected to all the following inspections and tests for acceptance. When specified in the contract (see 6.2), the contractor shall prepare a report giving the results obtained for all inspections and tests performed. Unless otherwise specified, all chemicals shall be ACS grade in accordance with MIL-STD-1218 and distilled water shall be used. Where applicable, blank determination shall be run and corrections applied where significant.

4.3 Test procedures.

4.3.1 Ingredient testing. All ingredients shall be tested in accordance with the applicable specifications and the exceptions taken in Section 3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

4.3.2 Burning time test for delay compositions. Conduct the test on the basis of each lot as provided in 4.1.1. The sample for test shall consist of 20 test elements as provided in 4.3.2.1. The lot shall be divided into 20 equal parts, and 20 delay bodies shall be loaded so that each delay body contains a representative sample from one of the 20 parts without duplication.

4.3.2.1 Loading of the test element. The delay body shown in Drawing 2249363 shall be loaded in accordance with Drawing 2249362. The tools required for loading appear in drawings under LD 518765. The ignition increment P shall consist of approximately 160 milligrams (mg) of A-1A ignition powder conforming to MIL-P-22264 or 160 mg of a composition consisting of 80 percent A-1A ignition powder (MIL-P-22264) and 20 percent BKNO3 ignition powder conforming to OS9765, type II, class 3 and shall be adjusted to be within the drawing limits (0.060 ± 0.002 inch) for increment length when pressed at 30,000 ± 500 pounds per square inch. Each increment may be measured volumetrically by means of a scoop of such size as to give six approximately equal increments. After the last increment, D6 is pressed, the loading funnel cap shall be loosened and tightened again. The D6 increment shall then be re-pressed to improve compaction and to minimize the danger of loss of powder by fallout. The surface of the delay column shall be flush with the end of the delay element in which it is contained. Excess powder may be removed by sliding the end of the test element over a hard cloth. The output charge holder containing the P2 charge shall be loaded in accordance with Drawing 2249365.

4.3.2.2 Timing of test elements. Suggested directions for mounting components into the delay body holder and assembling the test adapter are given in AD 1014. The temperature of the test elements for room temperature firing shall be 24° ± 4°C. If detailed directions for testing at low and high temperatures are not specified for acceptance of the powder, the following procedure shall be followed: The testadapters shall be conditioned continuously for at least 2 hours at the required temperature before firing.

4.3.2.3 Procedure for operating test apparatus. It is recommended that AD 1014 be used for operating instructions of the test apparatus.

4.3.2.4 Computation of burning time and percent coefficient of variation. Compute the burning time which is the average (X) of the time observations obtained in 4.3.2.2. Compute the standard deviation (S) of the time observations. The symbols and the method of computation shall be in accordance with Appendix A. Compute the percent coefficient of variation by dividing (100) times (S) by $\bar{X}$. Disposition of the lot shall be governed by 3.4 and 3.6. Where lot rejection is on the basis of the percent coefficient of variation, or 3.6, the lot may be remixed and resubmitted for acceptance under all provisions of 4.3.

4.3.2.5 Testing after shipment or prolonged storage. After the tungsten-fluorocarbon copolymer delay composition has been properly mixed, it is possible for the fuel and oxidants to segregate under conditions of storage and transportation. Segregation appears to occur near the surface when a delay composition is subjected to prolonged agitation, particularly during shipment by rail. The surface layer is then nonhomogeneous and not representative of the composition of the lot. After shipment of a lot of the delay composition or after storage of the lot for longer than 3 months, the lot should be reevaluated according to test procedures outlined in 4.3.2. If the lot fails to meet the requirements of 3.4 then the lot shall be remixed to restore uniformity prior to test and use. In all testing, the provisions of 4.3.2 shall be followed to ensure representative sampling of the lot.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

4.3.3 Low-temperature functioning test. Sampling shall be conducted after the last mixing operation (4.3.2.5). Select and prepare a representative pooled sample of delay mixture from the lot in accordance with 4.3.2 by preparing 10 test elements as provided by 4.3.2.1. Determine the burning time at low temperature by the procedures of 4.3.2.2 and 4.3.2.4 with the exception that the temperature at the time of firing and for at least 2.0 hours before firing shall be -54 ± 2°C. Determine average burning time according to 4.3.2.4. Compute the percentage change in burning time on the basis of change from the buring time determined under 4.3.2.4 at room temperature (24 ± 4°C). The lot is acceptable if the increase in burning time is less than 15.0 percent as required by 3.5 and meets the requirement of 3.6. A lot rejected for not conforming to 3.5 or 3.6 may be remixed and resubmitted for acceptance under 4.2. Failure of the lot to conform to 3.5 and 3.6 on resubmission shall result in rejection of the lot.

4.3.4 Moisture content inspection. Randomly select two samples from each lot of delay composition to be inspection. Determine moisture content in accordance with MIL-STD-1234, Method 101.2.1. If the moisture content for each sample does not exceed 0.05 percent, then the inspected lot of delay composition shall be accepted as regards to moisture content; otherwise, the inspected lot shall be dried 16 hours minimum at 60 ± 5°C and resubmitted for moisture content inspection.

5. PACKAGING

5.1 Preservation and packaging.

5.1.1 Level A. In addition to the following , level A packaging shall be in accordance with 49 CFR 173.154.

5.1.1.1 Unit packaging. Unit packaging of the delay composition shall be in accordance with MIL-P-116, method 1A5.

5.2 Packing. Packing shall be level A, B, or C as specified in the contract. (See 6.2.1)

5.2.1 Level A. In addition to the following, level A packing shall be in accordance with 49 CFR 173.154.

5.2.1.1 Exterior containers. The delay composition packaged as described in 5.1.1.1 shall be packed in an overseas-type wood box conforming to PPP-B-601 or PPP-B-621.

5.2.2 Level B. In addition to the following, level B packing shall be in accordance with 49 CFR 173.154.

5.2.2.1 Exterior containers. The delay composition packaged as described in 5.1.1.1 shall be packed in a domestic-type box conforming to PPP-B-601 or PPP-B-621.

5.2.3 Level C. The delay composition packaged in accordance with 5.1.1.1 shall be packed to afford protection against damage during direct shipment from the supply source to the first receiving activity for immediate use. Containers used shall comply with National Motor Freight Classification Rules and other Uniform Freight Classification Rules or regulations of other carriers applicable to the mode of transportation and 49 CFR 173.154.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

5.3 Marking.

5.3.1 Special markings. Marking of exterior containers shall be in accordance with 49 CFR 173.154.

5.3.2 Normal markings. In addition to the markings required by contract, unit packages and shipping containers shall be marked in accordance with the requirements of MIL-STD-129, including lot numbers, burning time at room temperature and standard deviation, percentage composition and class.

5.4 Test reports. Copies of the test report shall be furnished with each lot; one to the procuring activity, one to the consignee, and one to be packed in each box (see 6.2).

6. NOTES

6.1 Intended use. Tungsten-fluorocarbon copolymer delay compositions are intended for use as delay-time-determining elements in fuze explosive trains and cartridge actuated devices. Application of this powder is restricted to hermetically sealed assemblies.

6.2 Ordering data.

6.2.1 Acquisition requirements. Acquisition documents should specify the following:

(a) Title, number, and date of this specification
(b) Class and specific burning time (see 3.4)
(c) A Government inspector shall observe all tests and inspections
(d) That test reports are required (see 4.2 & 5.4)
(e) Level of packing (see 5.2)
(f) That the safety precaution requirements of the Contractor's Safety Manual for Ammunition, Explosives and Related Dangerous Material, DOD 4145.26M, are applicable. Note: When this specification is used as part of the describtion of work to be accomplished by a Government activity the safety precaution requirements of Ammunition and Explosives Ashore, OP 5, shall be made applicable.

6.2.2 Data requirements.6. When this specification is used in an acquisition which incorporates a DD Form 1423, Contract Data Requirements List (CDRL), the data requirements identified below shall be developed as specified by an approved Data Item Description (DD Form 1664) and delivered in accordance with the approved CDRL incorporated into the contract. When the provisions of 27.410-6 of the DOD FAR Supplement are invoked and the DD Form 1423 is not used the data specified below shall be delivered by the contractor in accordance with the contract or purchase order requirements. Deliverable data required by this specification is cited in the followiing paragraph.

Paragraph No.	Data requirement title	Applicable DID No.
4.2	Test Report	DI-T-2072

The report shall include the last number and date of manufacture for the delay composition and the manufacturer and lot number for each ingredient.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

(Copies of data item descriptions required by the contractors in connection with specific acquisition functions should be obtained from the Naval Publications and Forms Center or as directed by the contracting officer.)

6.2.3 The attention of the contracting officer is invited to the quality assurance provisions and options contained in MIL-P-116 and 5.3.2 of this specification.

6.3 Advisory procedures for formulation. (2,000 gram batch).

6.3.1 Equipment.

6.3.1.1 Balance 4 kg capacity, one gram sensitivity.

6.3.1.2 Sieves U.S. Standard No. 20, No. 100

6.3.1.3 Air-Driven Stirrer, with Cowles Dissolver Blade Attachment.

6.3.1.4 Siphon

6.3.1.5 Jar Rolling Mill

6.3.1.6 Stokes Granulator, mfd. by Penwalt Co.

6.3.2 Chemical processing.

6.3.2.1 Prior to use, tungsten metal powder shall pass 100% thru a U.S. Standard No. 100 mesh sieve.

6.3.2.2 Prior to use, barium chromate shall pass 100% thru a U.S. Standard No. 20 mesh sieve and shall be dried at 88°C for a minimum of 16 hrs.

6.3.2.3 Prior to use, the potassium perchlorate shall pass 100% thru a U.S. Standard No. 100 mesh sieve and shall be dried at 88°C for a minimum of 16 hrs.

6.3.2.4 Prior to use, the diatomaceous earth shall pass 100% thru a U.S. Standard No. 20 mesh sieve and shall be dried at 88°C for a minimum of 16 hrs.

6.3.2.5 Prior to use, the fluorocarbon copolymer shall be cut up into pieces no larger than 1 inch so as to facilitate dissolving of the copolymer in acetone solvent.

6.3.3 Mixing instructions.

6.3.3.1 Prepare fluorocarbon copolymer solution. To 20 grams of fluorocarbon copolymer add 250 ml acetone in a polyethylene bottle. Seal bottle and roll on jar rolling mill until copolymer is completely dissolved.

6.3.3.2 Prepare premix. To a mixing bowl add 1500 ml acetone and 1080 ml hexane. Mix 2 minutes. Add fluorocarbon solution to mixing bowl. Rinse the fluorocarbon container with 130 ml. additional acetone.

6.3.3.3 Mix. To mixing bowl, add these preweighed ingredients, a little at a time to ensure proper blending, in this order: (1) diatomaceous earth (2) potassium perchlorate and (3) barium chromate, mix 10 minutes. Add tungsten and mix 10 more minutes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

6.3.3.4 Drown. Add 2170 ml hexane for drown cycle. Mix 3 minutes. Stop mixer.

6.3.3.5 1st Decant. Allow mix to stand for 20 minutes, or until mix settles out. Decant excess solvent using a siphon.

6.3.3.6 Wash. Add 3000 ml hexane for wash cycle and mix 3 minutes.

6.3.3.7 2nd Decant. Repeat step 6.3.3.5.

6.3.4 Drying instructions.

6.3.4.1 Transfer. Transfer wet mix to shallow drying pans and allow mix to further settle. Decant excess solvent.

6.3.4.2 First dry. Transfer mix to vented drying oven, maintained at 60 ± 5°C. Let dry for 3 hours or until a damp earth consistency is reached.

6.3.4.3 Screen. Transfer partially dried mix to remotely operated Stokes Granulator and screen thru a U.S. Standard 30 mesh screen.

6.3.4.4 Final dry. Transfer screened mix to vented drying oven, maintained at 60 ± 5°C. Let dry 16 hours minimum.

6.3.5 Packaging. Package in accordance with 5.1.1.1.

6.3.5 Pilot mixture. Since the particle size distribution and chemical purity of the tungsten, barium chromate, potassium perchlorate, diatomaceous earth, and fluorocarbon copolymer will vary from lot to lot, the burntime of delay compositions made from different ingredient lots may vary. A pilot mixture technique is recommended to define the compositon vs. burntime curve for the new components. A composition on the curve within the range of burntime of interest should be prepared and its burntime determined according to 4.3.2. These data are used to construct a curve parallel to that shwon in Figure 1 from which the composition for any desired burntime may be determined.

Preparing Activity
Navy - OS

Project No. 1376-N246

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

Computation of mean and standard deviation of a sample.

A-1 Take the sum of individual measurements (ΣX).

A-2 Compute the mean value ($\overline{X}$) by dividing the result of A-1 by the number of measurements. (N). Thus $\overline{X} = \Sigma X/N$.

A-3 Square each individual measurement (X^2).

A-4 Take the sum of the squared measurements (ΣX^2).

A-5 Multiply A-4 by the number of measurements (N). This gives $N(\Sigma X^2)$.

A-6 Square the result of A-1 $(\Sigma X)^2$.

A-7 Subtract A-6 from A-5. This gives $N\Sigma X^2 - (\Sigma X)^2$.

A-8 Multiply the number of measurements (N) by the number of measurements less one (N - 1).

A-9 Divide A-7 by A-8. This gives $N\Sigma X^2 - (\Sigma X)^2 / (N)(N - 1)$.

A-10 The standard deviation (S) is the square root of A-9 Thus,

$$S = \left[\frac{N\Sigma X^2 - (\Sigma X)^2}{N(N - 1)}\right]^{\frac{1}{2}}$$

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

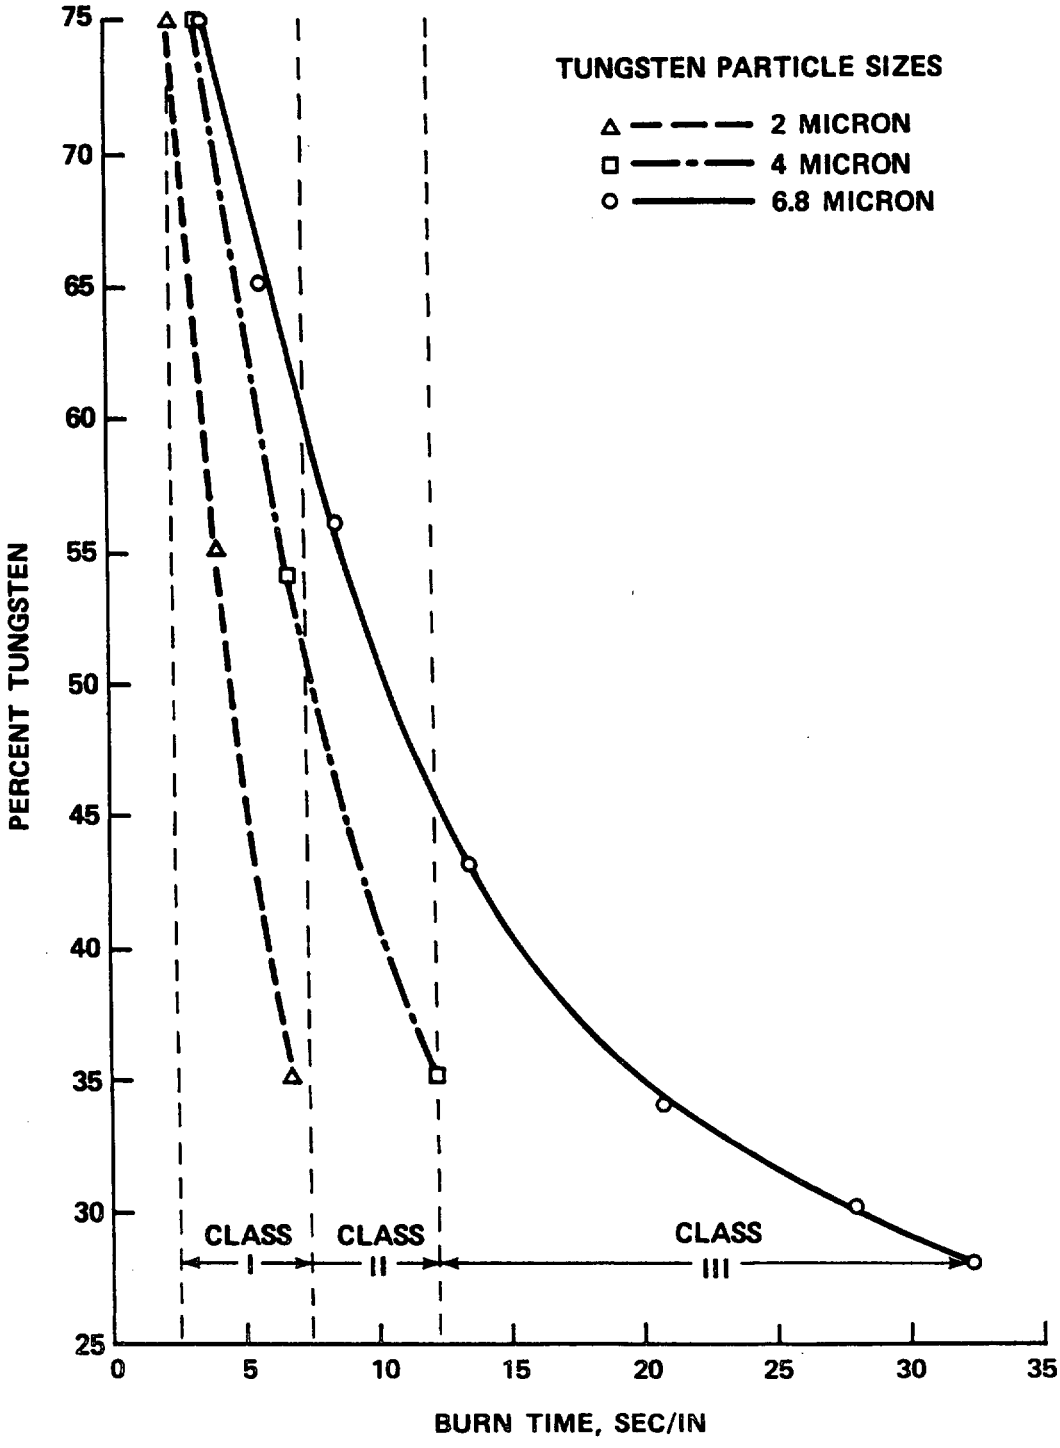


FIGURE 1. BURNING CHARACTERISTICS OF TUNGSTEN FLUOROCARBON COPOLYMER DELAY

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE NAVY
Commanding Officer
Naval Ordnance Station
Standardization/Documentation Div. (524)
Indian Head, MD 20640-5000

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12503 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

Commanding Officer
Naval Ordnance Station
Standardization/Documentation Div. (524)
Indian Head, MD 20640-5000

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-D-82710(OS)	Delay Composition, Tungsten-Fluorocarbon Copolymer

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR ☐ USER ☐ MANUFACTURER ☐ OTHER *(Specify)*: _____
b. ADDRESS *(Street, City, State, ZIP Code)*	

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

(TO DETACH THIS FORM, CUT ALONG THIS LINE.)

DD FORM 1426 MAR 92 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:22Z
Check the source to verify that this is the current version before use.

F1