INCH-POUND

MIL-B-55252B(CR)
14 February 1992
SUPERSEDING
MIL-B-55252A(EL)
12 April 1971

MILITARY SPECIFICATION
BATTERIES, NON-RECHARGEABLE, MAGNESIUM

This specification is approved for use by Communications-Electronics Command, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers non-rechargeable batteries composed of electrochemical cells utilizing a magnesium anode with a manganese dioxide depolarizer and magnesium perchlorate electrolyte.

1.2 Classification.

1.2.1 Type designation. The type designation of magnesium dry batteries shall be in the following form, (See 3.1 and 6.1).

BA-	4270/U
Component (1.2.1.1)	Battery Type number (1.2.1.2)

1.2.1.1 Component. Non-rechargeable batteries are identified by the two-letter symbol "BA" followed by a hyphen.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, US Army CECOM, ATTN: AMSEL-ED-TM, Fort Monmouth, New Jersey 07703-5023 by using the Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 6135

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

1.2.1.2 Battery type number. The battery type number identifies the basic design of the battery (see 3.1) and consists of a four digit number in the 4000 through 4999 series.

2. APPLICABLE DOCUMENTS

2.1 Government Documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.1).

SPECIFICATIONS

FEDERAL

FF-N-836D	Nut, Square, Hexagon, Cap, Slotted, Castle, Knurled, Welding and Single Ball Seat
FF-S-92	Screw, Machine, Slotted, or Hexagon Head
L-P-390	Plastic, Molding Material, Polyethylene, Low and Medium Density
L-P-513	Plastic Sheet, Laminated, Thermosetting, Paper-Base, Phenolic-Resin
QQ-N-290	Nickel Plating (Electrodeposited)
QQ-P-416E	Plating, Cadmium (Electrodeposited)
QQ-S-571	Solder: Lead Alloy, Tin Lead Alloy, and Tin Alloy; Flux Cored Ribbon and Wire, and Solid Form
PPP-T-60E	Tape: Packaging, Waterproof

MILITARY

MIL-M-14	Molding Plastics and Molded Plastic Parts, Thermo-setting
MIL-W-76	Wire and Cable, Hook-up, Electrical Insulated
MIL-W-530H	Webbing, Textile, Cotton, General Purpose, Natural or in Colors
MIL-F-14256	Flux, Soldering, Liquid (Resin Base)
MIL-S-1222	Bolts, Nuts and Studs.

STANDARDS

FEDERAL

FED-STD-595B	Colors used in Government Procurement

MILITARY

MIL-STD-105	Sampling Procedures and Tables for Inspection by Attributes

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

MIL-STD-970 Standards and Specifications, Order of Preference for the Selection of

(Unless otherwise indicated, copies of Federal and Military specifications and standards are available from the Standardization Document Order Desk, 700 Robbins Ave, Bldg No. 4, Section D, Philadelphia, PA. 19111-5094.)

2.2 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DoD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the documents cited in the solicitation (see 6.2).

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

ASTM B36 Standard Specification for Brass Plate, Sheet, Strip, and Rolled Bar

ASTM B16E1 Standard Specification for Free-Cutting Brass Rod, Bar and Shapes for Use in Screw Machines

ASTM B16M Standard Specification for Free-Cutting Brass Rod, Bar, and Shapes for Use in Screw Machines (Metric)

ASTM B121 Standard Specification for Leaded Brass Plate, Sheet, Strip, and Rolled Bar

ASTM B122 Standard Specification for Copper-Nickel-Tin Alloy, Copper-Nickel-Zinc Alloy (Nickel Silver), and Copper-Nickel Alloy Plate, Sheet, Strip, and Rolled Bar

ASTM B124 Standard Specification for Copper and Copper-Alloy Forging Rod, Bar, and Shapes

ASTM B139 Standard Specification for Phosphor Bronze Rod, Bar, and Shapes

ASTM B152 Standard Specification for Copper Sheet, Strip, Plate, and Rolled Bar

ASTM B152M Standard Specification for Copper Sheet, Strip, Plate, and Rolled Bar (Metric)

ASTM B194E1 Standard Specification for Copper-Beryllium Alloy Plate, Sheet, Strip, and Rolled Bar

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

ASTM B196 Standard Specification for Copper-Beryllium Alloy Rod and Bar

ASTM B196M Standard Specification for Copper-Beryllium Alloy Rod and Bar (Metric)

ASTM B197 Standard Specification for Copper-Beryllium Alloy Wire

ASTM B272 Standard Specification for Copper Flat Products with Finished (Rolled or Drawn) Edges (Flat Wire and Strip)

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103-1187.)

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents. These documents also may be available in or through libraries or other informational services).

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein (except for related associated detail specifications, specification sheets, or MS standards), the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Specification sheets. The individual item requirements shall be as specified herein and in accordance with the applicable specification sheet. In the event of any conflict between the requirements of this specification and the specification sheet, the latter shall govern.

3.2 Selection of specification and standards. Specifications and standards for necessary commodities and services not specified herein shall be selected in accordance with MIL-STD-970 and shall be approved by the procuring activity. Classification of Requirements shall as listed in the Appendix.

3.3 First article. When specified (see 6.1), a sample shall be subjected to first article inspection (see 6.4) in accordance with 4.5.

3.4 Materials and components. When a definite material or component is specified, it shall be in accordance with the applicable specification or requirement listed in Table I. When deemed necessary by the Government, certification from the source of the material or component be required. In the absence of certification from the source, a certificate of analysis or certified inspection data will be required. (See 4.4 and 4.4.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

3.4.1 Metals. All metals which do not enter into the basic electrochemical reaction of the cell shall resist or be treated to resist corrosion.

TABLE I. - Materials and Components

Material or components	Applicable specifications or requirements (See 4.4)	Methods of test (See 4.4.1)
Solder 1/.....	QQ-S-571	
Soldering Flux 2/.....	MIL-F-14256	
Metals.....	3.5.1	
Brass.....	ASTM B36	
Copper.....	ASTM B133, ASTM B152, ASTM B272	
Beryllium copper.....	ASTM B196, ASTM B197	
Phosphor bronze.....	ASTM B139	
Cadmium plating.....	QQ-P-416E	
Nickel plating.....	QQ-N-290	
Wire.....	MIL-W-76	
Bolts, Nuts and Studs....	MIL-S-122	
Plastic, laminated.....	L-P-513, type PBE	
Plastic, Molded.....	MIL-M-14, type MPE	
Plastic polyethylene.....	L-P-390, type I	
Webbing, Cotton.....	MIL-W-530H	
Tape: Packaging, Waterproof.....	PPP-T-60E	
Insulating, impregnating potting and sealing compounds.....	3.6.2	4.7.1.1.1
Filler or padding.....	3.6.3	4.7.1
Cell-block-container material.....	3.6.4, 3.7 and 3.8	4.7.2 and 4.7.3
Intercell separation.....	3.6.5	4.7.2 and 4.7.3
Terminals.....	3.6.8.1, 3.6.8.2, 3.6.8.3 3.6.8.4, 3.6.8.5, 3.6.8.6 and 3.6.8.7	4.7.4.1.1, 4.7.4.2.1
Jackets, metallic 3/.....	3.6.10.1	
Jackets, nonmetallic.....	3.6.10.2	4.7.2 and 4.7.3
Terminal mounting plate..	3.7 and 3.8	4.7.2 and 4.7.3
Strap handle 4/.....	3.6.9	

NOTES

1/ For electrical connections, type Sn40 or higher tin content shall be used.
2/ If other fluxes are used, they shall not affect the performance of the battery or reduce its shelf life.
3/ Test method 4.7.2 is applicable only for metallic jackets of material other than terneplate.
4/ Applicable to batteries with metallic jackets only.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

3.4.1.1 Dissimilar metals. When dissimilar metals which would adversely affect battery performance are used in intimate contact with each other, protection against electrolysis and corrosion shall be provided.

3.6 Design and construction. Batteries shall be of the design, construction, physical dimensions, and polarity specified in 3.1.

3.6.1 Battery voltages.

3.6.1.1 Open-circuit voltage. The open-circuit voltage shall not exceed the maximum voltage specified (see 3.1 and 4.7.8.1).

3.6.1.2 Closed-circuit voltage. The closed-circuit voltage shall be not less than the minimum voltage specified (see 3.1 and 4.7.8.2).

3.6.2 Insulating, impregnating, potting and sealing compounds. The insulating, impregnating, potting, and sealing compounds shall exclude moisture from insulating material without impairing its electrical characteristics. When tested as specified in 4.7.1.1.1 the potting and sealing compounds shall not flow at high temperature, nor crack or draw away from the sides of a container at low temperature sufficiently to impair electrical connections. Voids within the potted battery, except the socket well, shall be adequately filled with microcrystalline wax, asphalt, wood blocks, or wax-impregnated chipboard, or equivalent material.

3.6.3 Filler or padding. Filler or padding shall be a cushioning electrically nonconducting material which maintains its insulating characteristics under adverse environmental conditions. If adverse environmental conditions affect this material, then it shall be isolated from the electrical components by and insulating material that maintains its electrical characteristics.

3.6.4 Cell-block container. Cell-block container shall be an insulating material surrounding a group or a stack of individual cells.

3.6.5 Intercell separation. A separator shall be placed between cells in series connected multicell batteries. The separator shall be an insulating material.

3.6.6 Intercell connections. Connections between cell blocks and between cell block and terminal shall be so insulated or positioned as to avoid contact with other conducting material and/or the jacket of the battery. When insulated wire is soldered to terminal lugs, it shall not be bared more than 3/32 inch from the lug nor shall it extend more than 3/32 inch beyond the lug.

3.6.7 Age of cells. The minimum age of cells, from the time of their fabrication to the time of their presentation for acceptance inspection as batteries, shall be 5 days. The maximum age of cells, from the time of their fabrication to the time of their shipping date, shall be 120 days. Batteries

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

shall be submitted for acceptance inspection not more than 45 days prior to the shipping date.

3.6.8 Terminals. The type, dimensions, location, and mounting of terminals shall be as specified herein (see 3.1).

3.6.8.1 Stud and nut. Stud and nut terminals shall be as shown in figure 1 and shall be made of brass with a brass nut, except when otherwise specified. When specified, the nut shall be made of insulated material with a brass insert (see 3.1). A bronze or brass plated steel external tooth lockwasher shall be provided for each terminal.

3.6.8.1.1 Mounting. It shall be possible to screw the nut down by hand to make a firm seat with the shoulder of the stud, without turning of the stud.

3.6.8.2 Spring clip. Spring clip terminals shall be of the Fahnestock type made of spring brass or phosphor bronze, and shall be large enough to accommodate a wire having a cross-sectional area of 4,200 circular mils.

3.6.8.2.1 Mounting. Each clip shall be mounted in such a manner that the entire contact surface of the clip will be located above the surface adjacent to the clip.

3.6.8.3 Wire leads. Wire-lead terminals shall be hook up wire, type MW-C18(16)U or larger of MIL-W-76.


3.6.8.3.1 Mounting. The external length of each wire lead shall be 6 1/2 + 1/2 inches. The wire leads shall be color coded as follows: Positive - red, negative - black, intermediate as specified (see 3.1). The free end of each wire shall be bared for a distance of 1/2 + 1/8 inch. The strands of each lead, so bared, shall be twisted together and soldered, and then covered with an adherent insulating waterproof material, or an equivalent method shall be used to prevent short circuits during storage and handling.

3.6.8.4 Snap-on. Snap-on terminals shall consist of two parts: stud (nonresilient member) for positive terminal, and socket (resilient member) for negative terminal as shown in figure 2.

3.6.8.4.1 Mounting. Each member shall be securely mounted. Mating member engagements and disengagements shall be made without dislocating the terminals or distorting the battery beyond the specified limits during or after any tests performed on the battery (see 3.1). Each member shall be mounted so that the battery jacket does not interface with the proper mating of terminals.

3.6.8.4.2 Contact resistance. The contact resistance between the plug gage and socket when tested in accordance with 4.7.4.1.1 shall not exceed .005 ohm.


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

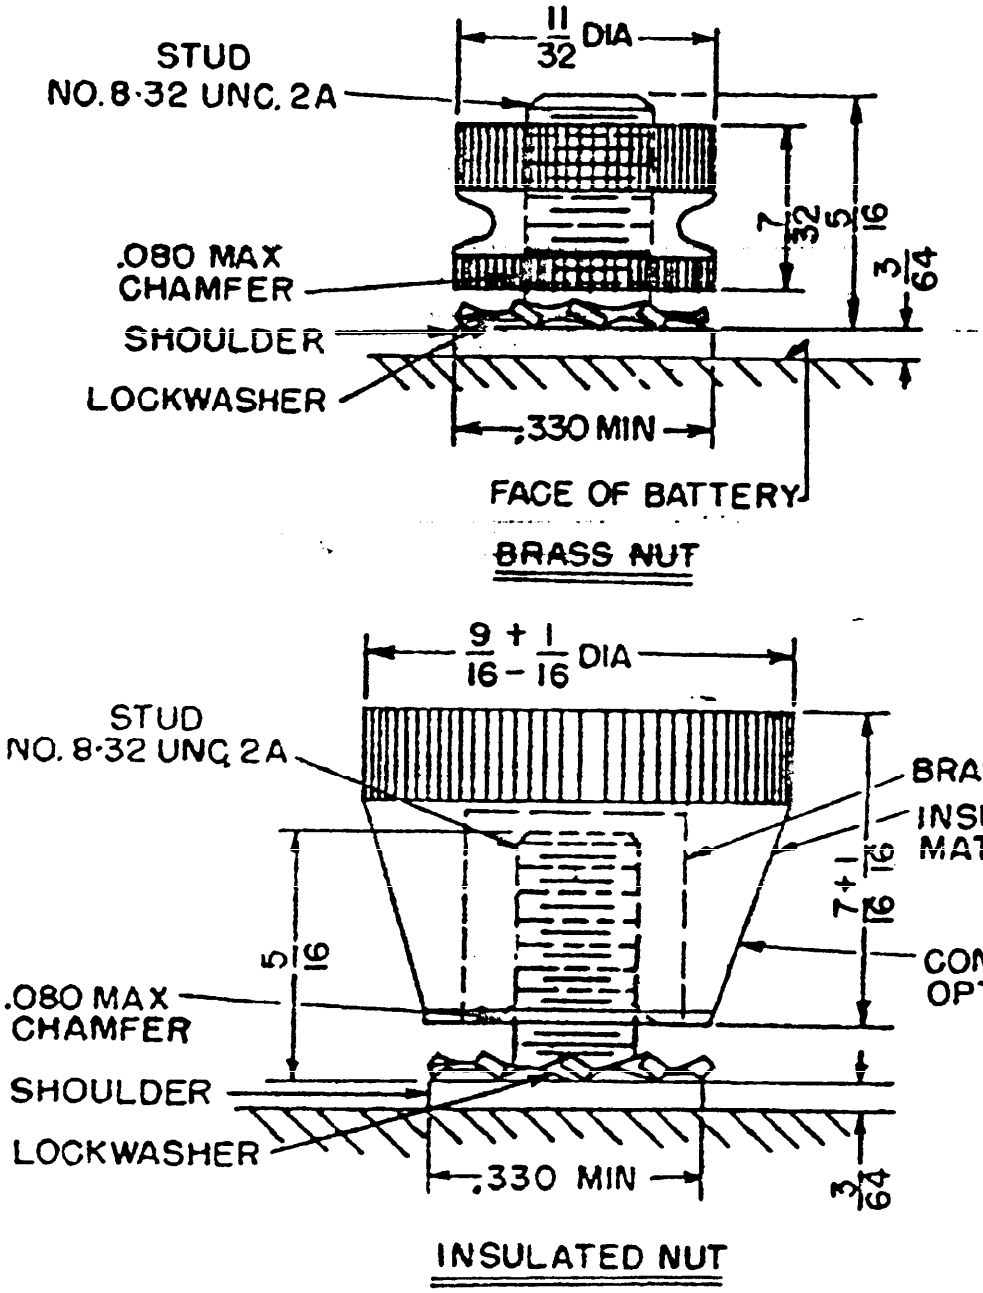

1—ALL DIMENSIONS IN INCHES
2—UNLESS OTHERWISE SPECIFIED
TOLERENCES ARE ±1/32

FIGURE 1. *Stud and nut terminal.*

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

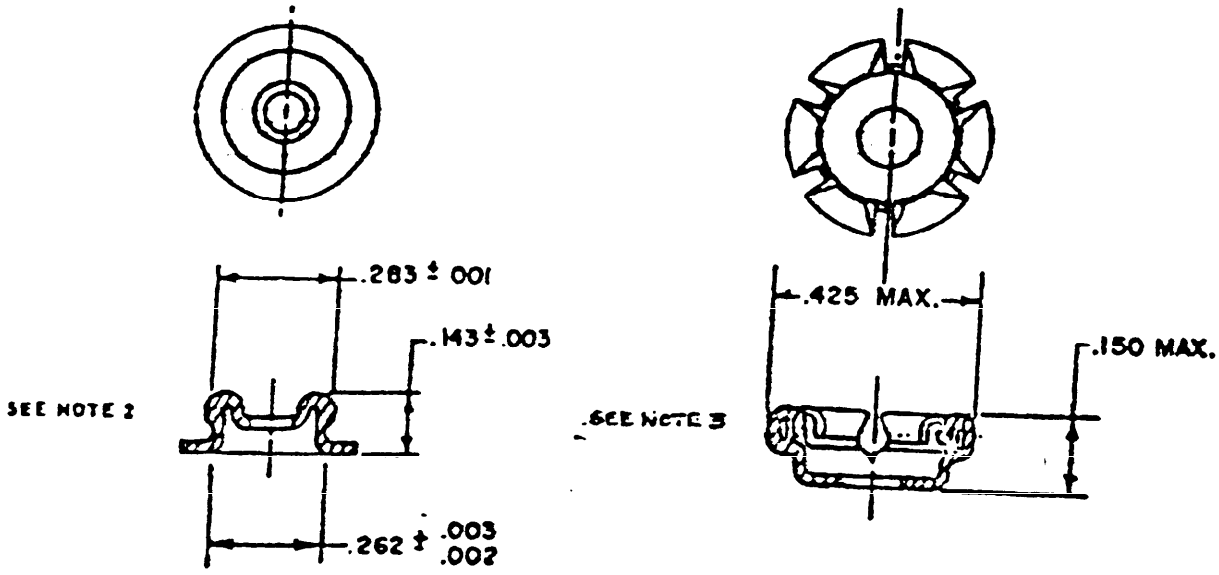

STUD, POSITIVE TERMINAL

SOCKET, NEGATIVE TERMINAL

NOTES:

1. ALL DIMENSIONS IN INCHES
2. STUDSHALL BE OF PLATED SOFT BRASS NOT LESS THAN 0.015 IN THICKNESS
3. SOCKET SHALL BE PLATED SPRING BRASS

FIGURE 2. *Snap-on terminals.*

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:15Z
Check the source to verify that this is the currentversion before use.

3.6.8.5 Socket. Socket terminals shall be as specified in 3.1. When the following types are specified they shall be as shown in figure 3, as applicable:

Type	No. of holes
I	2
IV	2
VIII	3
XIII	4
IX	5
A	8
B	8

Contact components of socket terminal shall be made of phosphor bronze, beryllium copper, or plated spring brass. Sockets shall be so designed and constructed that there will not be contact of any of the pins of the mating plug to any socket terminal other than those for which such pins are intended without using undue force. Insulating material shall be of plastic. The pinholespacing tolerances shall be +0.005 inch.


3.6.8.5.1 Mounting. The socket shall be so supported and mounted that the top surface of the socket shall not protrude above the adjacent surface of the jacket and shall not be more than 1/16 inch below the surface of the jacket or socket dome, when used, initially, during, and after subsequent insertions of the mating plug. The socket pin-circle center shall be located as specified, and the jacket opening shall be positioned so that its center is within 3/32 inch diameter circle whose center coincides with the socket pin-circle center, initially, during and after insertions of the mating plug. The angular orientation of the socket shall be within 5o of the battery centerlines or other lines of orientation as specified. Socket well depth, when measured from the top surface of the jacket or socket dome, shall be specified (see 3.1).

3.6.8.5.2 Contact resistance. Contact resistance between each socket insert and the applicable pin of the mating-plug when tested in accordance with 4.7.4.2.1 shall not exceed .005 ohm.

3.6.8.6 Flat surface. Flat surface terminals shall be a flat plate of brass or other approved metal, the center of which may be level, have a raised or a recessed portion, or a punched or drilled hole, as specified. When one terminal is the bottom of the can housing the battery, it shall be smooth and not injured as a result of cleaning or polishing. When the positive terminal is the carbon rod of a cell, it shall have a tight-fitting cap of brass or other approved metal. The cap shall be coated with solder, tin, cadmium, or nickel. The cap and the raised center portion of a flat plate may be provided with a centered outward projecting point not to exceed 0.020 inch (see 3.1).


Source: https://assist.dla.mil -- Downloaded: 2026l0-26T04:15Z
Check the source to verify that this is the currentversion before use.

TYPE I

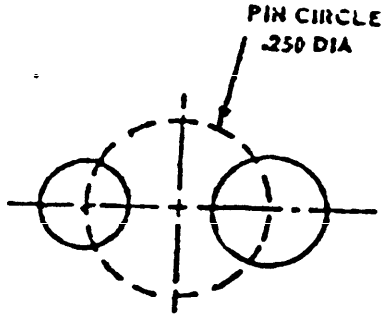


SOCKETS FOR
1 PIN 1/8 DIA(0.125 ± 0.002)
1 PIN 5/32 DIA (0.156 ± 0.002)

TYPE IV

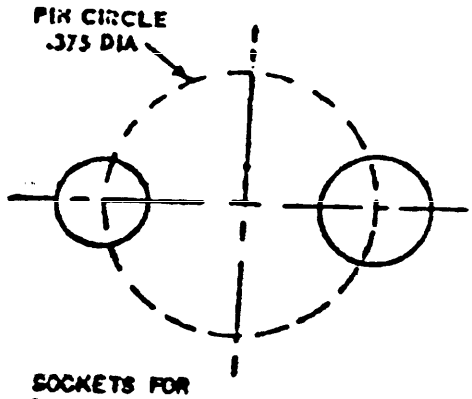


SOCKETS FOR
1 PIN 1/8 DIA(0.125 ± .002)
1 PIN 5/32 DIA(0.156 ± .002)

TYPE VIII

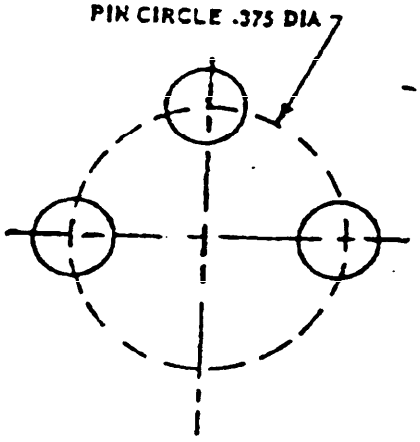

SOCKETS FOR
3 PINS 3/32 DIA(0.093 ± .002)

TYPE XIII

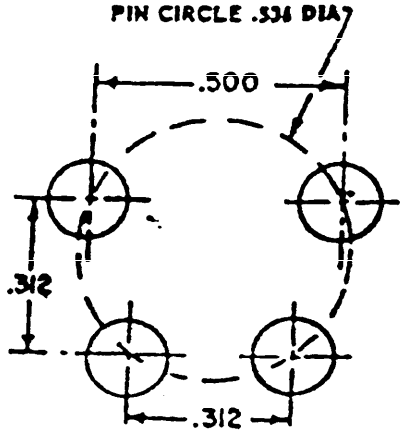


SOCKETS FOR
4 PINS 1/8 DIA(0.125 ± .002)


FIGURE 3. *Socket terminals (top views).*

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:15Z
Check the source to verify that this is the current version before use.


TYPE IX

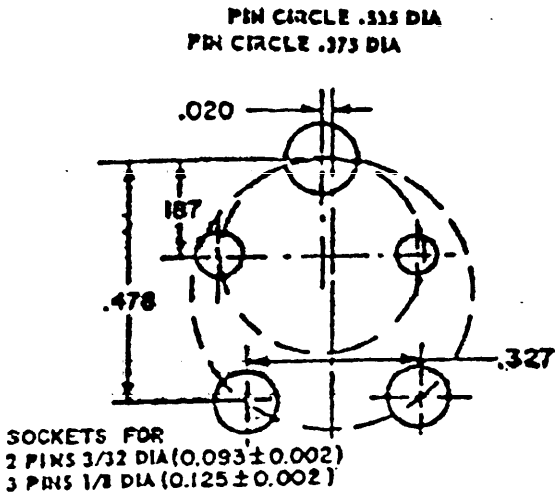

TYPE A

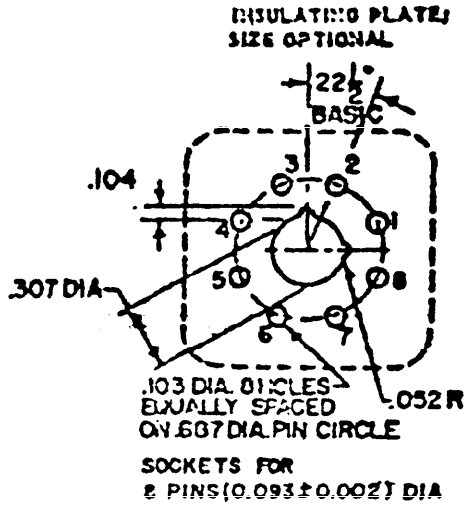

TYPE B

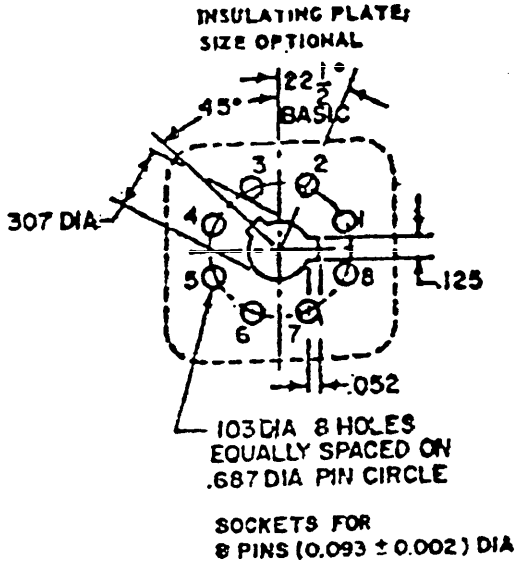

1. ALL DIMENSIONS IN INCHES
2. TOLERANCES ARE ± 1/64 ON FRACTIONS AND ± .003 ON DECIMALS EXCEPT AS OTHERWISE SPECIFIED.

FIGURE 3—Continued.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

3.6.8.7 Coil and flat spring. Coil and flat spring terminals shall be made of beryllium copper, spring brass, or phosphor bronze, and shall be as specified (see 3.1).

3.6.8.8 Protection of terminals. When flash dip microcrystalline wax or equal is used to waterproof the jacket, the terminals shall be covered with a removable tape or cap. Markings shall be legible after removal of the tape or cap. The wax dip shall be applied after the application of the tape or cap.

3.6.9 Strap handle. Strap handle shall be of webbing, using natural or synthetic fiber, or of plastic material. The width of the strap shall be 7/16 inch minimum. The effective length of the strap shall be at least one inch longer than the distance between its anchorages. The strap shall withstand the test specified in 4.7.5 without breaking or separating from its anchorages.

3.6.10 Jackets. The jackets may consist of either metallic or nonmetallic material. The contents of multicell batteries shall fit snugly enough in the jackets to minimize movement of the cells. Jackets covering one or more cylindrical cells stacked end on end, and having open top and open bottom, shall be so attached to the cells as to prevent them from slipping out when held or shaken vertically. The bottom opening of the jacket shall be of the size specified (see 3.1).

3.6.10.1 Metallic jackets.

3.6.10.1.1 Prior to battery fabrication. The inside of the jacket, when other than terneplate, shall be coated or lined with an electrolyte corrosion resistant material.

3.6.10.1.2 As a fabricated battery. The outside of the battery shall have a coating to protect the jacket from corrosion during or at the conclusion of any of the tests specified herein. The contents of the jacket shall be completely insulated from the metal unless otherwise specified. The jacket shall not become permanently distorted nor open at any of its seams after being subjected to the test specified in 4.7.6.1. The test of 4.7.6.1 shall be applicable to batteries weighing 5 pounds or more.

3.6.10.2 Nonmetallic jacket. When wax coating a nonmetallic jacket, microcrystalline wax or equal shall be used. All excess wax shall be removed from the external surfaces of the jacket.

3.6.10.3 Waterproofing of jackets (WOJ). Metallic jackets shall show no evidence of water penetration and nonmetallic jackets shall not fall apart and the seams shall remain intact when tested as specified in 4.7.6.2. The WOJ requirement shall not apply to single cell batteries with metallic or plastic jackets.

3.6.10.4 Color of jackets. The color of exposed surfaces of jackets shall match one of the following lusterless greens 34079, 34086, 34087, 34096,

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

34102, 34127, and 34128 per Federal Standard No. 595.

3.6.11 Closure. The closure is defined as the seal of the cell or battery.

3.6.11.1 Sealing compound. When sealing compound is used for closures in batteries containing cells whose seals are exposed, the outer edge of the sealing compounds of such cells shall be approximately level with the top of the container or the top of the jacket, and the inner edge of the sealing compound shall be approximately level with the lower edge of the cap on the carbon element. On multicell batteries, the exposed sealing compound shall be approximately level with the edge of the jacket and shall not obstruct the contact surfaces of the terminals (see 4.7.1.1.1).

3.6.11.2 Metal or plastic covers. Metal or plastic covers for tops of cells or batteries may be used in lieu of sealing compound provided such covers and accessory parts are not adversely affected by leakage, corrosion, or deformation during any of the tests specified herein. Construction shall be such that it will be impossible for one cell to be short-circuited by coming in contact with another cell of the same type when placed end to end.

3.7 Electrolyte penetration. When applicable materials are tested as specified in 4.7.2, the millimeter deflection shall be less than 0.225 ma during the entire test period.

3.8 Dielectric strength. When applicable materials are tested as specified in 4.7.3, there shall be no voltage breakdown during the entire test period.

3.9 Capacity. When the battery is tested for capacity as specified in 4.7.9 the time require to terminate the discharge as specified in 4.7.9.5 shall be not less than the minimum time specified (see 3.1).

3.10 Delayed voltage. When the battery is tested for capacity, the time required for the battery units to reach end voltage after the applicable specified load is applied shall be not more than the time specified (see 3.1).

3.11 Insulation resistance. The insulation resistance between any two terminal not electrically connected, and between all ungrounded terminals and the jacket of the batter, shall be not less than five megohms, when tested as specified in 4.7.10.

3.12 Vibration. After the batteries have been tested as specified in 4.7.11 they shall meet the visual and mechanical and battery voltage requirements (see 3.6 through 3.6.1.2 and 3.6.8 through 3.6.8.5). There shall be no voltage fluctuations during the test.

3.13 Mechanical shock. After the batteries have been tested as specified in 4.7.12 they shall meet the visual and mechanical and battery voltage requirements (see 3.6 through 3.6.1.2 and 3.6.8 through 3.6.8.5).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

3.14 Battery venting. After the batteries have been tested as specified in 4.7.13, they shall not exhibit any dimensional change in excess of 1/16 inch.

3.15 Direct short. After the batteries have been tested as specified in 4.7.14, they shall not have any pieces or parts expelled or ejected from it.

3.16 Socket breakage. After the batteries have been tested as specified in 4.7.15, they shall not have any socket plate break or drop more than 1/16 inch below the top surface of the battery.

3.17 Cell corrosion. After the cells have been tested as specified in 4.7.16, they shall not show any evidence of corrosion, i.e. a mass of white powder. The evidence of corrosion can be on the inner or outer wall of the cell can.

3.18 Labeling and marking. All labeling and marking shall be clear and legible throughout all of the tests specified herein. Labeling and marking shall be black. Metallic and plastic jackets may have the labeling and marking embossed or die depressed, in which case it may be the same color as the background.

3.18.1 Labels. Each battery shall have a label positioned as specified in 3.1. If there is insufficient space to show all required information on the face of the battery, it shall be continued on another face. There shall be no information on the label other than the following:

BATTERY, DRY
Type Designation
(Contract Number)---
(Code) ---
Manufacturer's name
(Trade name may also be used)
Manufacturer's plant

EXAMPLE:

BATTERY, DRY
BA-4270/U
DAAB05-71-C-1243
0371
John Doe Company
JODOCO
Batteryville, NJ

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

NOTE: The code may be place on the bottom of single-cell batteries.

3.18.1.1 Code. The code shown shall indicate the month and year of manufacture of the battery by means of a four-digit number in which the first two digits shall indicate the number of the month and the last two digits shall indicate the year. Months earlier than the tenth month shall be a single digit preceded by "0".

EXAMPLES:

A battery manufactured in March 1971 will bear the code "0371".

A battery manufactured November 1972 will bear the code "1172".

When a battery is completed during the last three working days of a month, or the first three working days of the subsequent month, the manufacturer is permitted to use either month as the date to be coded.

3.18.2 Special marking. A black band, extending around approximately one third (1/3) of the battery length, shall be provided on each jacket. The term "Magnesium Battery" shall appear in bold lusterless green lettering (same as jacket color) on the black portion of the jacket in the locations indicated on the applicable specification sheet (see 3.1).

3.18.3 Terminal marking. On batteries having socket-type terminals, all markings required to indicate polarity by a + or - sign, voltage, and the voltage leg of the battery (A, B, C, etc.) shall appear on the face of the battery bearing the socket. On other type terminals, the terminal markings may appear on the surface with the terminal or the side of the battery, or both. Markings shall indicate clearly the terminals to which they refer.

3.19 Workmanship. Batteries shall be processed in such a manner as to be uniform in quality and shall be fee from defects that will affect its life, serviceability, or appearance.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. - Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified here in. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:15Z
Check the source to verify that this is the currentversion before use.

4.1.1 Test equipment and inspection facilities. - Test equipment and inspection facilities shall be of sufficient accuracy, quality and quantity to permit performance of the required inspection. The supplier shall establish calibration of inspection equipment to the satisfaction of the Government. Inspection equipment furnished by the Government, for performing certain inspection at supplier's plant, will be calibrated by the supplier and maintained by the Government.

4.1.1.1 Instrument accuracy.

4.1.1.1.1. Voltmeters and ammeters. - All voltmeters and ammeters used in testing the batteries shall be accurate within 1 percent of the full-scale value. The voltmeter and ammeter ranges shall be such that all readings are taken on the upper half of the scale. The sensitivity of voltmeters shall be not less than 10,000 ohms per volt.

4.1.1.1.2 Resistor tolerance. - During all tests involving discharge through a resistance, such resistance shall be accurate within the following percentages:

	Percent
Up to and including 25,000 ohms.....	0.5
From above 25,000 ohms to and including 1 megohm.....	1.0
Above 1 megohm.....	5.0

In determining the resistance used as a test load, the resistance of all continuously operating voltmeters shall be considered as part of the specified load.

4.1.1.1.3 Timing. - Timing equipment shall be accurate within 0.5 percent.

4.2 Classification of inspection. - The examination and testing of batteries shall be classified as follows:

(a) Materials and components inspection. (See 4.4)

(b) First article inspection. (See 4.5)

(c) Quality conformance inspection of equipment before packaging (see 4.6).

4.3 Inspection conditions. - Except as otherwise specified herein, all examinations and tests shall be performed at a temperature of $80^{\circ} \pm 20^{\circ}$ F. ($26.7^{\circ} \pm 11.1^{\circ}$ C), ambient atmospheric pressure, and relative humidity.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

4.4 Materials and components inspection. - Materials and components inspection shall consist of verification by certification from the source that the materials and components used in fabricating the batteries are in accordance with applicable requirements prior to such fabrication. In the absence of certification from the source a certificate of analysis or certified inspection data shall be required as proof of conformance to applicable requirements. Materials and components involved are listed in table I.

4.4.1 Samples of materials and components. - For those items listed in table I for which the specification requirement does not reference a subsidiary specification; eight samples of materials or components, treated and processed as they would be in the finished batteries shall be inspected.

4.5 First article. - After award of contract first article inspection shall be performed by the supplier as specified in 4.5.1 through 4.5.1.3.

4.5.1 Sample batteries. - The supplier at no additional cost to the Government shall make 46 batteries and 80 cells constituting a first article inspection lot.

4.5.1.1 Inspection Routing. - First article inspection shall consist of Groups I, II, III, IV, V, VI & VII per table II. Group VIII shall consist of one sample battery, untested, to remain at the supplier's plant to be available as a standard of comparative purposes.

4.5.1.2 First Article Inspection Report. - Contractor shall furnish four legible copies of complete test data for all tests performed by contractor on the first article inspection lot samples for approval within 10 calendar days of completion of testing. Reports shall be sent at contractor's expense to the activity designated in the contract.

4.5.1.3 Failure. - If one or more sample batteries fail to meet any of the first article examinations and tests, the supplier shall immediately make the remedial changes. The supplier at no additional cost to the government shall be required to submit additional first article samples for reinspection. A description of the corrective action taken or to be taken shall be included in the first article inspection report (See 4.5.1.2). Official approval to begin production will be give upon successful completion of first article inspection.

4.5.2 Start of production. - Any production prior to materials and components inspection and approval of the first article samples shall be at the supplier's risk. (See 4.4 and 4.5)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

Table II - First Article Inspection

Group	No. of Batteries	Examination & Test	Req. Par.	Method of Test Para.
I	10	Visual-Mechanical (External)	3.6	4.7.1
		Battery voltage	3.6.1 3.6.1.1 & 3.6.1.2	4.7.8,4.7.8.1& 4.7.8.2
		Dimensions and weight	3.6	4.7.7 and 4.7.7.1
		Vibration	3.12	4.7.11
		Mechanical Shock	3.13	4.7.12
		Insulation Resistance	3.11	4.7.10
		Capacity Discharge I	3.9	4.7.9.1.1, 4.7.9.2 - 4.7.9.5
		Socket Breakage	3.16	4.7.15
II	5	(2) Visual-Mechanical (Internal)	3.6	4.7.1
		(3) WQJ	3.6.10.3	4.7.6.2
III	10	Visual-Mechanical (External)	3.6	4.7.1
		Battery Voltage	3.6.1, 3.6.1.1 & 3.6.1.2	4.7.8,4.7.8.1 & 4.7.8.2
		Capacity Discharge HT(1) (when specified)	3.9	4.7.9.1.2, 4.7.9.2 through 4.7.9.5
		Capacity Discharge HT(3) (when specified)		
		Delayed Voltage	3.10	4.7.9.6
IV	10	Visual-Mechanical (External)	3.6	4.7.1
		Battery Voltage	3.6.1, 3.6.1.1 & 3.6.1.2	4.7.8,4.7.8.1 & 4.7.8.2
		Capacity Discharge LT (when specified)	3.9	4.7.9.1.4, 4.7.9.2 - 4.7.9.5
V	10	Battery Venting	3.14	4.7.13
VI	10	Direct Short	3.15	4.7.14
VII	80 cells	Cell Corrosion	3.17	4.7.16
VIII	1	Untested-referenced sample	-	4.5.1.1.

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:15Z
Check the source to verify that this is the currentversion before use.

4.6 Quality conformance inspection.

4.6.1 Inspection of product for delivery. - The contractor shall perform the inspection specified in 4.4 and 4.6.1.2 through 4.6.1.4.1. This does not relieve the contractor of his responsibility for performing any additional inspection which is necessary to control the quality of the product and to assure compliance with all specification requirements. The government will review and evaluate the contractor's inspection procedures and examine the contractor's inspection records. In addition, the Government, at its discretion, may perform all or any part of the specified inspection, to verify the contractor's compliance with specified requirements. (See 6.3) Test equipment for Government verification inspection shall be made available by the contractor.

4.6.1.1 A lot shall be defined as the quantity of batteries of any one type, of any one code, and produced at any one place of manufacture on any one contract, submitted at one time to quality conformance inspection.

4.6.1.1.1 Shipment lot. - The shipment lot (Ns) is the quantity of batteries (exclusive of the number of batteries required as samples) manufacture on any one contract.

4.6.1.1.2 Contract lot. - The contract lot (N) is the total of all batteries (exclusive of the number of batteries required as samples) of any one type, delivered in one or more shipment lots, under the terms of any one contract.

4.6.1.2 Group A Inspection. - Each unit of each lot of batteries shall be inspected for conformance to all the examination and test requirements of Table III. Each lot will then be subject to verification, utilizing the procedures of Military Standard MIL-STD-105, and AQL's indicated in Table III. Group A inspection shall be performed in any order which is satisfactory to the Government.

Table III - Group A inspection

Examination and Test	Requirement Paragraph	Method of Test Para.	AQL (percent defective) Major	Minor	Insp Level
Visual-Mechanical (External)	3.6	4.7.1	1.0%	4.0	II
Battery Voltage	3.6.1,3.6.1.1 & 3.6.1.2	4.7.8 4.7.8.1 & 4.7.8.2	1.0%	-	II

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

4.6.1.3 Group B Inspection. - This inspection, including sampling, shall conform to Table IV and to special procedures for small-sample inspection of MIL-STD-105. Group B1 inspection shall be performed in the order listed in Table IV on the same sample batteries an shall normally be performed on inspection lots that have passed group A inspection and on samples selected from units that have been subjected to an met the group A inspection with the exception that the WOJ test can at the option of the manufacturer be performed on any batteries representing the inspection lot. (See 4.6.1.1)

Table IV - Group B1 Inspection

Test	Requirement Paragraph	Method of Test Para.	AQL	Inspection Level
Dimensions & Weight	3.6	4.7.7 & 4.7.7.1	1.0%	S-1
Insulation Resistance 1/	3.11	4.7.10	1.0%	S-1
Vibration	3.12	4.7.11	2.5%	S-1
Mechanical shock	3.13	4.7.12	2.5%	S-1
Battery Voltage	3.6.1,3.6.1.1 & 3.6.1.2	4.7.8, 4.7.8.1 & 4.7.8.2	2.5%	S-1
Visual-Mechanical (External)	3.6	4.7.1	2.5%	S-1
WOJ	3.6.10.3	4.7.6.2	2.5%	S-1

1/ When Applicable

4.6.1.4 Group B2 inspection. - Group B2 inspection shall consist of (a) HT(2) capacity discharge test at 70° F including delayed voltage test, (see 3.1) after one week storage at 160° F.

4.6.1.4.1 Sampling plan. - Ten samples each shall be taken at random form the first five-hundred (500) batteries produced in each monthly shipment lot.

More than one failure per sample group of ten constitutes a failure of the monthly production lot and corrective action must be taken; such as determining cause reporting same to Government, obtaining permission from Government to reinitiate production and repeating monthly production lot evaluation.

A failure is any sample having one or more of the following deficiencies:

(1) Insufficient service
(2) Excessive voltage delay (where applicable)
(3) Electrolyte leakage
(4) Battery exceeds dimensional tolerances

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:15Z
Check the source to verify that this is the currentversion before use.

4.6.1.5 Group C inspection. - Group C inspection shall be performed at the Government inspection facility (see 6.1(e)) on sample batteries subjected to the examination and tests specified in table V in the order shown. Shipment of the lot represented by the sample batteries shall not be held up pending the results of group C inspection.

4.6.1.5.1 Sampling plan. - Nineteen sample batteries shall be selected at random from each monthly shipment lot. For HT(3) and T testing (a total of 38 batteries).

Table V Group C Inspection

Examination and tests	Requirement paragraph	Method of Test paragraph
Subgroup I: (Adjustment Purposes)		
Capacity T.....	3.9	4.7.9
HT(3).....	3.9	4.7.9
Subgroup II: (Design Control)		
Cell Corrosion Test.....	3.17	4.7.16

4.6.1.5.2 Determination of compliance.

4.6.1.5.2.1 The monthly shipment lot shall be considered as complying upon successful completion of both T and HT(3) tests.

4.6.1.5.2.1.1 To determine whether the monthly shipment lot conforms to the T and HT3 requirements the best 16 samples must meet 100 percent of the required performance requirements, i.e., for a 52-hour requirement, the required performance would be 832 hours. No credit will be given to batteries exceeding 52 hours. If the actual performance of the best 16 samples is less than 832 hours, the monthly shipment lot will be subject to the adjustment provision specified elsewhere in he contract.

4.6.1.5.3 Noncompliance.

4.6.1.5.3.1 Subgroup I. - If the capacity test results do not show compliance with requirements as defined in 4.6.1.5.2. the monthly shipment lot shall be considered as not complying with the requirements of this specification and an adjustment shall be made.

4.6.1.5.3.2 Subgroup II. - If the number of cells showing evidence of corrosion exceeds the acceptance number of one, the government shall have cause to refuse to accept subsequent shipment lots until it has been proven, to the satisfaction of the government, that faults revealed by the test have been corrected.

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:15Z
Check the source to verify that this is the currentversion before use.

4.6.1.5.4 Shipment. - when the inspection lot passes group A, B1 and B2 inspection, as applicable, all sample batteries selected as specified in 4.6.1.5.1 shall be shipped to the Government inspection facility (see 6.1(e)) at no additional cost to the Government.

4.6.1.5.5 Marking. - Sample batteries allocated to tests specified in 4.6.1.5 shall be marked "(*) TEST SAMPLE." (The asterisk(*) shall be replaced by "T" or MT(3), as applicable.) The marking shall be rubber stamped or placed on a label securely attached to each battery. However, on batteries weighing eight ounces less, the above marking shall be placed on the outside of each unit package.

4.7 Methods of examination and tests. -

4.7.1 Visual and mechanical examination. - Batteries shall be examined to determine compliance with all applicable requirements and characteristics listed in table VII. When internal examination is necessary it shall be performed either during fabrication of the battery, or by dismantling the finished battery.

4.7.1.1 Potting. - The manufacturer shall determine the minimum weight of an adequately potted battery, and shall not present for acceptance any batteries failing to meet this minimum weight requirement. This shall be done by determining the minimum weight of a battery filled with a sufficient quantity of potting material to withstand the vibration and mechanical-shock test specified. (See 3.1)

Table VII Visual and Mechanical Examination

Requirement	Reference paragraph
External	
Design and construction 1/	3.6
Terminals	3.6.8
Jackets	3.6.10
Closure	3.6.11
Strap handle (when applicable)	3.6.9
Internal	
Dissimilar metals	3.4.1.1
Filler or padding	3.6.3
Cell-Block container	3.6.4
Intercell separation	3.6.5
Intercell Connections	3.6.6
Age of cells	3.6.7
Metallic Jackets	3.6.10.1
Insulating, impregnating Potting and sealing compounds	3.6.2

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:15Z
Check the source to verify that this is the current version before use.

1/ With exception of dimensions and weight which shall be performed in group B1 inspection. (See 4.6.1.3)

4.7.1.1.1 Flow or shrinking. - Potting and sealing compounds, when used, shall be placed in a container , approximately 3 inches, wide by 6 inches long by 3/4 inch high, to within 1/4 inch of the top. The temperature of the compound within the container shall be raised to $160^{\circ} \pm 5^{\circ}$ F ($71.1^{\circ} \pm 2.8$ C.) and the container shall be held in an inverted position for 24 hours. Then the temperature of the compound shall be lowered to $0^{\circ} \pm 5^{\circ}$ F($-17.8^{\circ} \pm 2.8^{\circ}$ C.) The flow or cracking or shrinking of the compound from the sides of the container shall be noted. If flow is noted at $160^{\circ} \pm 5^{\circ}$ F ($71.1^{\circ} \pm 2.8^{\circ}$ C) five batteries of type involved shall be exposed to $160^{\circ} \pm 5^{\circ}$ F($71.1^{\circ} \pm 2.8^{\circ}$ C) storage for 24 hours with terminals resting in lowest possible position. At the end of this exposure period batteries shall be examined to determine that there is no impairment of electrical contact. (See 3.6.2)

4.7.2 Electrolyte penetration. - Applicable specimens of materials and components shall be placed on a metal plate, and a cylindrical plastic tube two inches high with an internal diameter of 1 1/2 inches shall be clamped over the material. The tube shall then be filled to a depth of one inch with a solution of approximately 34 percent Mg $(ClO_4)_2$ by weight or the specified electrolyte to be used in the batteries. A metal electrode shall be inserted into this solution to a depth of approximately 1/2 inch. A direct-current potential of 22.5 volts shall be applied between this electrode and the metal plate with a millimeter of proper range in the circuit. The test shall continue for a period of 72 hours, but may be terminated if failure occurs sooner.

4.7.3 Dielectric strength. - Applicable specimens of material and components shall be conditioned for 48 hours at $160^{\circ} \pm 2^{\circ}$ F ($71.1^{\circ} \pm 1.1^{\circ}$ C) and a relative humidity of 50 ± 15 percent, then for one hour at $70^{\circ} \pm 5^{\circ}$ F ($21.1^{\circ} \pm 2.8^{\circ}$ C) and a relative humidity of 50 ± 15 percent. Each specimen that the electrodes will make contact with both sides of the specimen being tested. Each electrode shall have a diameter of two inches with the edge rounded to a radius of 1/4 inch, so that the contact surface is a circle 1 1/2 inches in diameter. The specimen shall extend at least 1/2 inch beyond the electrode surfaces around the entire circumference of the electrode to prevent flas-over at the edge of the specimen. The specimens of material shall be subjected to a potential of 1,000 volts root mean square, alternating current, at commercial frequency, for a period of one minute. The transformer used shall be rated not less than 1/2 kilovoltampere and shall be capable of delivering up0 to 10,000 volts root mean square, 60-cycle alternating current, to the electrodes. The applied voltage shall be increased, starting at zero voltage, at an approximate rate of 500 volts per second.

4.7.4 Terminals.

4.7.4.1 Snap-on terminals.

4.7.4.1.1 Contact resistance. - Contact resistance between the stud and

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

REQUIREMENTS:

socket shall be measured during engagement nos. 1, 5, 6 and 10 when a current of five amperes is flowing through the point of contact. (See 3.6.8.4.2)

4.7.4.2 Socket terminals.

4.7.4.2.1 Contact resistance. - contact resistance between each socket insert and the applicable pin of the mating-plug shall be measured after insertion No. 1, 10, 11, and 20, while a current of five amperes is flowing through the point of contact. (See 3.6.8.5.2)

4.7.5 Strap handle strength. - The sample battery, or a strap handle attached to a metal plate (mockup) shall be supported by the strap handle. The battery or the mockup shall be conditioned for six hours at a temperature of $160^{\circ} \pm 5^{\circ}$ F ($71.1^{\circ} \pm 2.8^{\circ}$ C) and ambient relative humidity. Immediately following the conditioning a weight shall be added gradually in such a manner that the total weight (including the weight of the battery, if used) applied to the strap handle and its anchorages shall be at least 80 pounds; and it shall be maintained at inspection conditions specified in 4.3 for at least one minute. This test shall be repeated again after conditioning the battery or the mockup at a temperature of $-40^{\circ} \pm 5^{\circ}$ F ($-40^{\circ} \pm 2.8^{\circ}$ C) for six hours. Condition of the strap handle as a whole and of the strap at its anchorages shall be observed.

4.7.6 Jackets.

4.7.6.1 Metallic jackets. - Metallic jacketed batteries weighing five pounds or more shall be loaded by applying weights totalling 100 pounds evenly distributed over the top of the battery and shall remain so loaded at least one minute. The condition of the jacket shall be observed. (See 3.6.10.1.2)

4.7.6.2 Waterproofing of jackets (WOJ). - All multicell batteries and paper jacketed single cell batteries shall be immersed to within 1/4 inch of the top of the jacket in water maintained at a temperature of $160^{\circ} \pm 5^{\circ}$ F ($71.1^{\circ} \pm 2.8^{\circ}$ C) for a period of 48 hours. In case of multicell metallic jacketed batteries the metal containers without covers may be subjected to this test in place of assembled batteries. in the case of nonmetallic jacketed batteries the jackets may be applied to dummy batteries in place of actual batteries. Condition of the jacket and its seams shall be observed. (See 3.6.10.3)

4.7.7 Dimensions and weight. - Batteries shall be examined by gaging or measuring the by weighing to determine conformance.

4.7.7.1 Dimensions. - All dimensions shall include any casting which may be used, and shall remain within the specified tolerances throughout the required tests. When box gages are used, batteries, loaded with the following weights, shall pass freely through the applicable gage openings:

(a) Batteries weighing less than five pounds - loading weight of five pounds.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

(b) Batteries weighing five pounds or more - loading weight equal to the weight of the battery.

The inside dimensions of the box gage shall be the specified maximum outside dimension of the battery.

4.7.8 Battery Voltage.

4.7.8.1 Open-circuit voltage. - A direct current voltmeter of proper range and sensitivity shall be used to measure the open-circuit voltage.

4.7.8.2 Closed-circuit voltage. - A direct current voltmeter of proper range and sensitivity shall be used to measure the closed circuit voltage utilizing resistance specified. (See 3.1)

4.7.9 Capacity.

4.7.9.1 Capacity Tests. - Sample batteries selected for capacity tests specified in the individual battery specification sheet (See 3.1) shall be stored and discharged, as applicable, in accordance with 4.7.9.1.1 through 4.7.9.5.

4.7.9.1.1 Capacity Test I. - Discharge at 70° F without previous storage specified in 4.7.9.3.

4.7.9.1.2 Capacity Test HT(1). - When specified discharge at 70° F after four weeks storage at 160° F (See 3.1).

4.7.9.1.3 Capacity Test HT(2). - When specified discharge at 70° F after one week storage at 160° F (See 3.1).

4.7.9.1.4 Capacity Test LT. - When specified discharge at 40° F after storage at 40° F for a minimum of 16 hours (See 3.1).

4.7.9.1.5 Capacity Test T. - Discharge at 70° F after 13 weeks storage at 130° F.

4.7.9.1.6 Capacity Test D. - Discharge at 70° F after 52 weeks storage at 70° F and/or 113° F.

4.7.9.1.7 Capacity Test HT(3). - When specified discharge at 70° F of A2 section after four weeks storage at 160° F (See 3.1).

4.7.9.1.8 Capacity Test HT(4). - When specified discharge at 70° F of A2 section after one week storage at 160° F (See 3.1).

4.7.9.2 Ambient storage and discharge conditions. - The ambient conditions specified in table VIII shall prevail during storage and discharge periods. Normal conditions shall be maintained insofar as possible. Deviations from normal conditions are permitted, provided that: (1) The extreme conditions

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

specified in table VIII do not exist for more than ten percent (cumulative) of the specified storage or discharge periods; and (2) that at no time are the extreme conditions exceeded.

4.7.9.3 Storage. - Sample batteries (packaged per contract) shall be stored at applicable storage conditions for the specified period. (See 3.1) The storage period shall be considered to have started from the date the batteries are actually placed in storage. At the conclusion of the storage period the outside of the battery container shall be examined for corrosion. (See 3.6.10)

4.7.9.4 Stabilization preceding discharge. - Following storage, and conditioning, when applicable, the batteries shall be further stored for 48 hours at ambient discharge conditions specified in table VIII. Prior to initiation of discharge, LT samples shall be stored at 40° F for a minimum of 16 hours.

4.7.9.5 Discharge. - Following stabilization the batteries shall be discharge at the ambient discharge conditions specified in table VIII. The discharge shall be terminated when any one of the following conditions occur:

(a) The battery voltage or the voltage of any one unit falls below the specified test and voltage. (For batteries requiring discharge alternately through two resistance, the voltage shall be read during the final minute of the heavier-load period).

(b) The battery dimensions exceeds the maximum specified. (See 3.1).

(c) Electrolyte leakages becomes apparent on the exterior surface of the battery.

4.7.9.6 Delayed voltage. - During the performance of the capacity discharge test, batteries will be monitored to determine the time required for battery units to reach and voltage after the applicable specified load is applied for the discharge cycles stipulated in the individual specification sheets. (See 3.1)

4.7.10 Insulation resistance. - Insulation-resistance test shall be performed, except as otherwise specified. (See 3.1) Batteries shall be stored for a period of 48 hours at 70° ±5° F (21.1° ± 2.8° C) and a relative humidity of 50 ± 15 percent. After storage and while at these conditions, the insulation resistance shall be measured by applying a direct-current potential off 500 ± 20 volts between any two terminals not electrically connected and between all ungrounded terminals and the container of the battery. The insulation resistance of batteries having a nonmetallic container shall be measured by the use of a one inch-square copper plate making physical contact with the container. The plate shall be placed with the broad surface against any area of any surface of the jacket other than that on which the battery terminals are located. (See 3.11)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

TABLE VIII. AMBIENT STORAGE AND DISCHARGE CONDITIONS

Kind of Storage or Discharge	Normal Conditions		Extreme Conditions	
	Temperature	Relative Humidity (per cent)	Temperature	Relative Humidity (per cent)
T Storage	130 + 3° F - 4° F (54.4 +1.7° C) (-2.2° C)	NA	108° F(42.2° C)thru 126° F(52.2° C) and 133° F(56.1° C)thru 135° F(57.2° C)	NA
D Storage	113° +2° F -8° F (45° +1.1° C) (-4.4° C)	50 ± 20	88° F(31.1° C) thru 105° F(40.6° C) and 115° F(46.1° C)thru 118° F(47.8° C)	10 - 30 and 70 - 90
	70° ±5° C (21.1° ± 2.8° C)	50 ± 20	60° F(15.6° C)thru 65° F(18.3° C) and 75° F(23.9° C)thru 80° F(26.7° C)	10 - 30 and 70 - 90
HT Storage	160° +3° F -7° F (71.1° +1.7° C) (-3.9° C)	NA	140° F(60° C) thru 153° F(67.2° C) and 163° F(72.8° C)thru 165° F(73.9° C)	NA
70 Discharge	70° ±20° F (21.1° ± 1.1° C)	50 ± 20	65° F(18.3° C)thru 68° F(20.0° C)thru and 72° F(22.2° C)thru 80° F(26.7° C)	10 - 30 and 70 - 90
LT Storage and discharge (See 4.7.6.3)	40° ± 3° F (4.4° C ± 1.7° C)	NA	34° F(1.1° C)thru 37° F(2.8° C) and 43° F(6.1° C)thru 46° F(7.8° C)	NA

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

4.7.11 Vibration. - Only multi-cell batteries shall be subjected to vibration. Each battery shall be rigidly clamped to the platform of a vibration machine in a manner approximating ads closely as practicable the manner in which the batteries are clamped when in use. (See 3.1) A simple harmonic motion shall be applied having an amplitude of 0.03 inch (0.06 - inch total maximum excursion). The frequency shall be varied at the rate of one cycle per second per minute between the limits of 10 and 55 cycles per second. The entire range of frequencies and return shall be traversed in 95 ± 5 minutes for each mounting position, (direction of vibration) of the battery. The batteries shall be vibrated in three equal periods in mutually perpendicular directions, one of which shall be perpendicular to the terminal face of the battery. Open-circuit voltage shall be observed for 30 seconds during the last quarter of each of the three vibration periods.

4.7.12 Mechanical shock. - Only multi-cell batteries shall be subjected to mechanical shock. Each battery shall be secured to the testing machine by means of a rigid mount which will support all mounting surfaces of the battery. Each battery shall be subjected to a total of three shocks of equal magnitude. The shocks shall be applied in each of three mutually perpendicular directions. Each shock shall be supplied in a direction normal to a face of the battery. The faces of the battery are identified by their position in relation to the front face (the face which bears the label.) For each shock, the battery shall be accelerated in such a manner that during the first three milliseconds the minimum average acceleration is 75 gravity units (G). The peak acceleration shall be between 125 to 175 G.

4.7.13 Battery venting. - The battery's A2 section shall be subjected to a five ohm discharge for two minutes followed by a discharge through 100 ohms for four minutes. This duty cycle shall be repeated continuously until the battery voltage reached 10 volts (See 3.14)

4.7.14 Direct short. - The battery shall be subjected to a direct short, i.e., less than 0.30 ohms for two hours (see 3.15)

4.7.15 Socket breakage. - The socket plate in the battery shall be subjected to a force of 20 pounds by 1 1/4 inch diameter rod at any point on the top surface of the battery socket plate (see 3.16)

4.7.16 Cell Corrosion. - The 80 cells selected for test shall be stored at 130° F for 12 weeks after each is given a serial number. Then a visual inspection of the group of 80 cells shall be mad weekly during the 12 weeks storage. In addition, four cells from the group shall be drawn at random every two weeks and inspected internally. (See 3.17)

5. PACKAGING

5.1 Packaging requirements. - The packaging requirements for the desired level(s) of protection shall be as specified by the acquisition activity.

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:15Z
Check the source to verify that this is the currentversion before use.

6. NOTES

6.1 Acquisition requirements. - Acquisition document must specify the following:

(a) Title, number, and date of this specification.

(b) Complete battery type designation and the title, number and date of the applicable specification sheet. (See 1.2.1 and 3.1)

(c) Date for notice of availability for shipment.

(d) Government inspection facility performing Group C inspection.

(e) Number of first article samples to be submitted if other than specified in 4.5.

(f) Issue of DODISS to be cited in the solicitation, and, if required, the specific issue of document referenced (see 2.1.1 and 2.2).

6.1.1 Indirect shipments. - The packaging, packing and marking specified in section five apply only to direct purchases by or direct shipment to the Government and are not intended to apply to contracts or orders between the supplier and prime contractor.

6.2 Awarding of contract. - Contracts will be awarded only to suppliers who guarantee to meet the requirements of this specification. No combining of performance requirements should be undertaken. Bids that offer to guarantee higher capacities will receive no special consideration in awarding a contract. Contracts will be awarded to the lowest bidder on a cost-per-unit battery basis provided that all performance requirements are guaranteed. Failure on a prior contract, of a manufacturer's particular battery type to meet any of the performance requirements of this specification, will be adequate cause for rejection of bids on that particular type until the supplier submits certified data proving that:

(a) Action has been taken to eliminate the cause of failure; and

(b) The battery meets all the performance requirements of this specification.

6.3 Verification inspection. - Verification by the Government will be limited to the amount deemed necessary to determine compliance with the contract and will be limited in severity to the definitive quality assurance provisions established in this specification and the contract. The amount of verification inspection by the Government will be adjusted to make maximum utilization of the contractor's quality control system and the quality history of the product.

6.4 First article. When first article inspection is required, the

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

contracting officer should provide specific guidance to offerors whether the item(s) should be a preproduction sample, a first article sample, a first production item, a sample selected from the first production items, a standard production item from the contractor's current inventory (see 3.3), and the number of items to be tested as specified in 4.5. The contracting officer should also include specific instructions in acquisition documents regarding arrangments for examinations, approval of first article test results, and that the government reserves the right to waive the requirement for product which has been previously acquired or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending contract. Bidders should not submit alternate bids unless specifically requested to do so in the solication.

6.5 Subject term (key word) listing.

Batteries, magnesium
Batteries, non-rechargeable
BA-4000/U thru
BA-4999/U
Electrochemical cells

Custodians:
Army - CR

Preparing Activity
Army - CR

(Project 6135-A243)

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:15Z
Check the source to verify that this is the currentversion before use.

APPENDIX

Classification of requirements. - The requirements for the product are classified herein as follows:

Requirement	Paragraph
Selection of specifications and standards	3.2
First article	3.3
Materials and components	3.4
Design and construction	3.6
Electrolyte penetration	3.7
Dielectric strength	3.8
Capacity	3.9
Delayed voltage	3.10
Insulation resistance	3.11
Vibration	3.12
Mechanical shock	3.13
Battery venting	3.14
Direct short	3.15
Socket Breakage	3.16
Cell Corrosion	3.17
Labeling and marking	3.18
Workmanship	3.19

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revisio letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification o requirements on current contracts. Comments submitted on this form do not constitute or imply authorization t waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER	2. DOCUMENT DATE (YYMMDD)
	MIL-B-55252B(CR)	14 February 1992

3. DOCUMENT TITLE BATTERIES, NON-RECHARGEABLE, MAGNESIUM

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle Initial)	b. ORGANIZATION
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) (1) Commercial (2) AUTOVON (If applicable)	7. DATE SUBMITTED (YYMMDD)

8. PREPARING ACTIVITY

a. NAME	b. TELEPHONE (Include Area Code)
U.S. ARMY COMMUNICATIONS-ELECTRONICS COMMAND	(1) Commercial 908-532-5851 (2) AUTOVON 992-5851
c. ADDRESS (Include Zip Code) ATTN: AMSEL-ED-TM FORT MONMOUTH, NJ 07703-5023	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340. AUTOVON 289-2340

DD Form 1426, OCT 89 *Previous editions are obsolete.*

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:15Z
Check the source to verify that this is the current version before use.