MILITARY SPECIFICATION

CLAMP ASSEMBLY, SADDLE-TYPE, CUSHION, GENERAL
SPECIFICATION FOR

This amendment forms a part of Military Specification MIL-C-85449, dated 6 March 1981, and is approved for use by all Departments and Agencies of the Department of Defense.

PAGE 5

Paragraphs "3.5.1.2 and 3.5.1.3", delete and substitute the following:

"3.5.1.2 Compression set. The average compression set value of three cushion material specimens shall not exceed the value specified in the applicable specification sheet (see 4.5.3.2)."

"3.5.1.3 Flammability. The cushion material shall be tested for flammability in accordance with the applicable specification sheet and as specified herein (see 4.5.3.3)."

PAGE 10

Paragraphs "4.5.3.2, 4.5.3.3, 4.5.3.3.1 and 4.5.3.3.2," delete and substitute the following:

"4.5.3.2 Compression set test. Three cushion material test samples shall be air aged at the temperature specified on the applicable specification sheet for 70 hours and tested in accordance with ASTM D395 Method "B". Cushion material samples shall meet the requirements specified in the applicable specification sheet (see 3.5.1.2)."

"4.5.3.3 Flammability test. The flammability tests shall be performed as specified below. The flame source shall be a Bunsen Burner or similar burner having a nominal tube internal diameter of 3/8 inch. The burner shall be adjusted to provide a 1-1/2 inch high flame of blue intensity. Verify flame temperature to be a minimum of 1550°F, at the center of the flame, with the use of a thermocouple."

FSC 5340

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:52Z
Check the source to verify that this is the current version before use.

"4.5.3.3.1 Preconditioning. All specimens shall be preconditioned at 70° ± 5°F and 50 ± 5 percent relative humidity for a period of 24 hours prior to testing. Clamps used for vertical burn test shall be uncurled until straight (strap section) before being placed in the preconditioning chamber. The cushion shall not be removed from the clamp band."

"4.5.3.3.2 Vertical burn test. Three size dash 16 clamps shall be used for the vertical burn test (see 4.5.3.3.1). Remove the specimens one at a time from the preconditioning chamber immediately before performing test. Slide the cushion to one end of the clamp band. Position the specimen in the vertical position with the centerline of the cushion material 3/4 inch above the top edge of the burner tube. Apply flame for 12 seconds and then remove. Testing shall be performed in a draft free environment. The average burn time of the three samples after removal of flame shall not exceed 15 seconds. The average burn length shall be less than the length of one of the specimens (cushion). Drippings from the burning specimens shall not continue to flame for more than 5 seconds after falling (see Figure 2)."

"4.5.3.3.3 Horizontal burn test. Three specimens fabricated in accordance with ASTM D3182 shall be used for the horizontal burn test. The specimens shall be removed one at a time from the preconditioning chamber and positioned so that the centerline of the edge being burned shall be 3/4 inch above the top edge of the burner tube. The flame shall be applied for 15 seconds and then removed. Permit a minimum of 1-1/2 inches to burn to calculate the burn rate. The burn rate shall not exceed 2-1/2 inches per minute. Record burn rate (see Figure 2)."

Custodians:
Navy - AS
Air Force - 99
Army - AV

Review activities:
Air Force - 11
DLA - IS

Preparing activity:
Navy - AS
(Project No. 5340-1608)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:52Z
Check the source to verify that this is the current version before use.

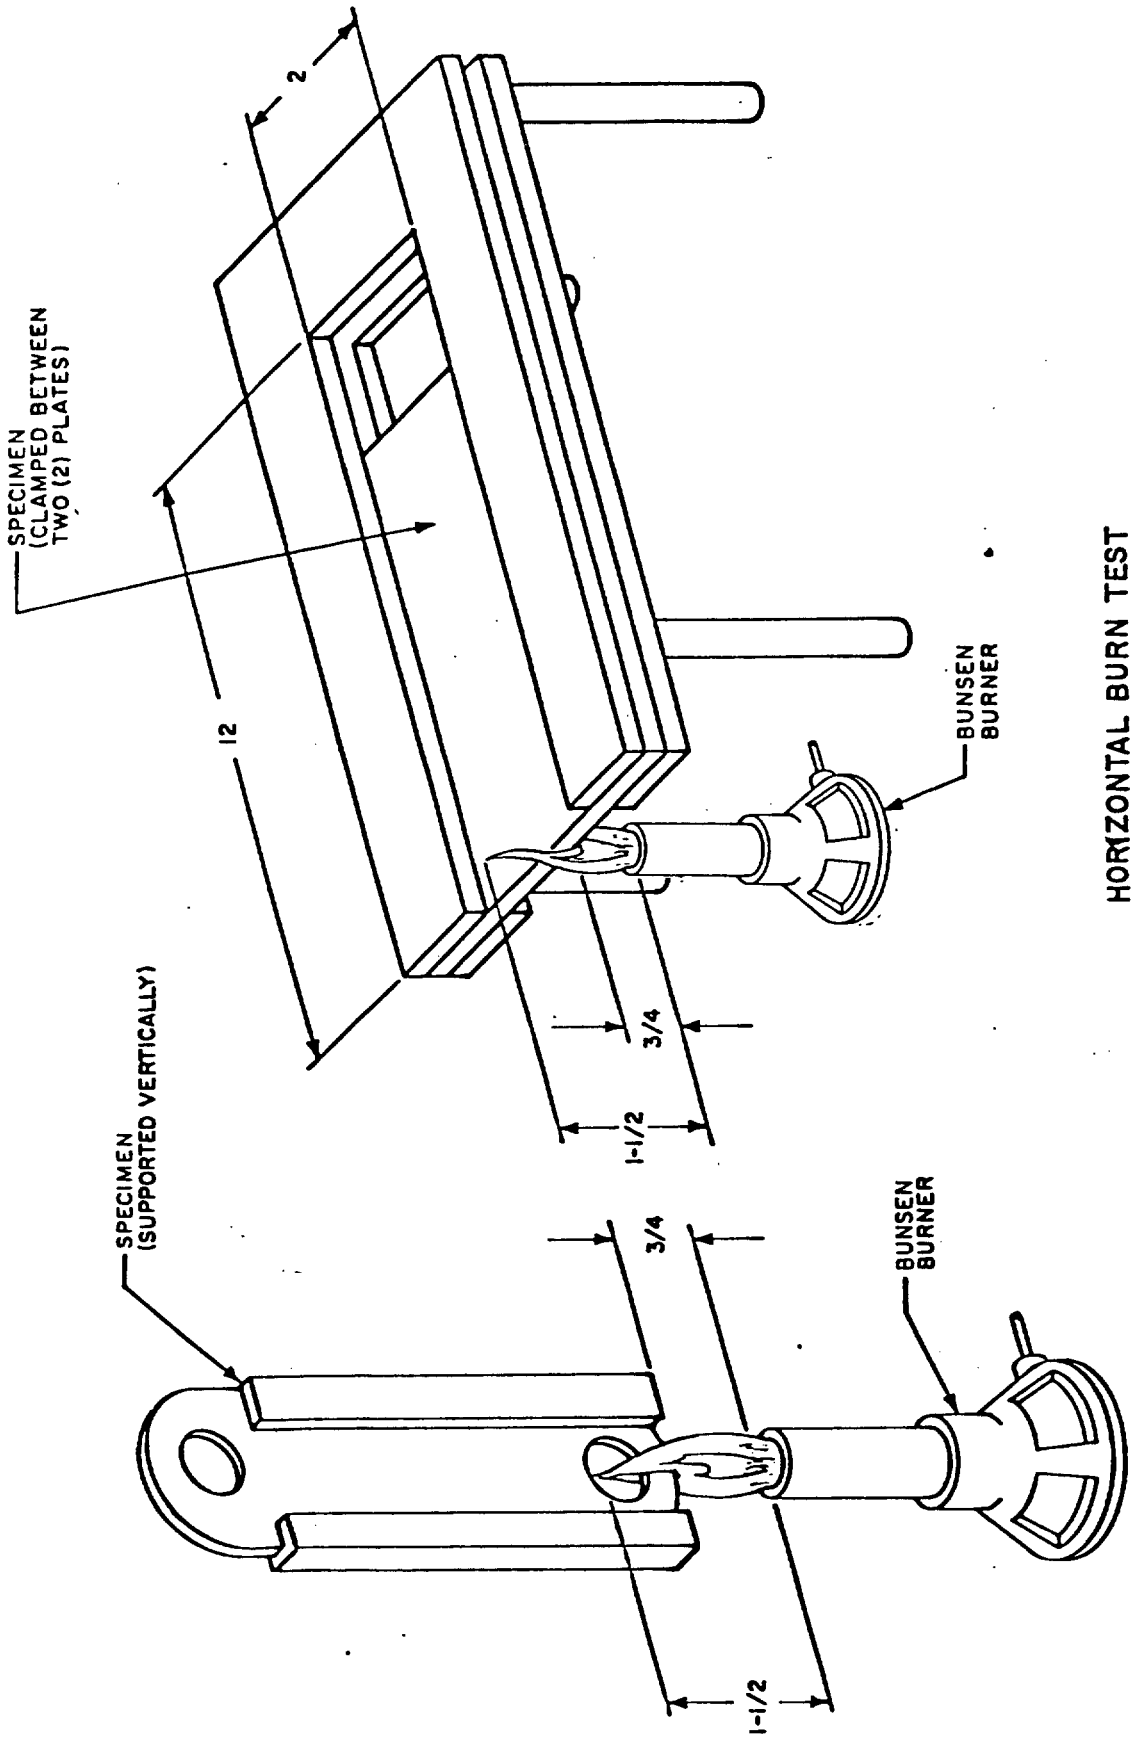


FIGURE 2. Flammability test set-up (typical).

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T10:52Z
Check the source to verify that this is the current version before use.