METRIC
MIL-PRF-23236D
w/AMENDMENT 1
20 March 2023
SUPERSEDING
MIL-PRF-23236D
15 September 2009

# PERFORMANCE SPECIFICATION

# COATING SYSTEMS FOR SHIP STRUCTURES

This specification is approved for use by the Naval Sea Systems Command (NAVSEA) and is available for use by all Departments and Agencies of the Department of Defense.

## 1. SCOPE

1.1 Scope. This specification covers four types of air pollution regulated ship and structure coatings that comply with the National Emission Standards for Hazardous Air Pollutants (NESHAP) for shipbuilding for state and Federal regulations. There are five types, twelve classes, and four grades of coating systems based on temperature of application and cure. In addition to tanks, all paint systems qualified to this specification are suitable for use on any ship structure, interior or exterior, for corrosion control. Except for trace levels, all types are free of lead, chromium, cadmium, and asbestos (see 3.2.3.1). All types have levels of hazardous air pollutants (HAP) that do not exceed applicable NESHAP levels (see 3.2.2.3). Dry type V, VI, VII, and VIII coating residues and debris are non-hazardous waste under U.S. Environmental Protection Agency (USEPA) regulations in effect on the date of this specification. Type VII coatings will not have any solvent added to either the base resin component or the hardener component.

1.2 Classification.

1.2.1 Types. The types of coating systems are as follows (see 6.2):

Type V - A coating system having a maximum volatile organic compound (VOC) content of 340 grams per liter (2.83 pounds per gallon) of coating. HAPs in the solvent will not exceed VOC levels (see 3.2.2.3). Use of pigments that are hazardous to workers or create hazardous waste is restricted to trace levels (see 3.2.3.1). May be used in any air quality management district regulating VOC. Dry coating is not a hazardous waste under USEPA regulations.

Type VI - A coating system having a maximum VOC of 250 grams per liter (2.08 pounds per gallon) of coating. HAPs in the solvent will not exceed VOC levels (see 3.2.2.3). Use of pigments that are hazardous to workers or create hazardous waste is restricted (see 3.2.3.1). Dry coating is not a hazardous waste under USEPA regulations.

Type VII - A coating system having a maximum VOC of 150 grams per liter (1.25 pounds per gallon) of coating. HAPs in the solvent will not exceed VOC levels (see 3.2.2.3). Use of pigments that are hazardous to workers or create hazardous waste is restricted to trace levels (see 3.2.3.1). Dry coating is not a hazardous waste under USEPA regulations. Coatings proposed for qualification testing to this type have no solvent added to either the base resin component or the hardener component.

Comments, suggestions, or questions on this document should be addressed to Commander, Naval Sea Systems Command, ATTN: SEA 05S, 1333 Isaac Hull Avenue, SE, Stop 5160, Washington Navy Yard DC 20376-5160 or emailed to CommandStandards@navy.mil, with the subject line "Document Comment". Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A FSC 8010

DISTRIBUTION STATEMENT A. Approved for public release. Distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

Type VIII - Non-metallic functional powder coating system for severe marine service having a maximum VOC of 75 grams of solvent per 4.54 kilograms (0.17 pounds of solvent per 10 pounds) of powder.

Type VIIIa - Functional powder coating system with two coats which may contain zinc for severe marine service with a maximum VOC of 75 grams of solvent per 4.54 kilograms (0.17 pounds of solvent per 10 pounds) of powder.

1.2.2 Classes. The classes of coating systems are as follows:

Class 5 - A coating system for use in fuel tanks, seawater ballasted fuel tanks, seawater tanks, bilges, and other ship structures, interior and exterior. Class 5 coatings are not for use in tanks that may be used for fresh or potable water.

Class 6 - Class 6 coatings are no longer used.

Class 7 - A coating system for use in dedicated seawater ballast tanks. Class 7 coatings are not for use in tanks that may be used for freshwater, potable water, fuels, or other hydrocarbons.

Class 8 - Class 8 coatings are no longer used.

Class 9 - A coating system for use in dedicated potable or freshwater tanks. Class 9 coatings are not for use in tanks that may be used for seawater, fuels, or other hydrocarbons.

Class 10 - Class 10 coatings are no longer used.

Class 11 - A coating system for use in dedicated boiler feedwater (pure water) tanks. Class 11 coatings may not be used for seawater, potable water, freshwater, fuels, or other hydrocarbons.

Class 12 - Class 12 coatings are no longer used.

Class 13 - A coating system for use in dedicated collection, holding, and transfer (CHT) tanks. Class 13 coatings may not be used for seawater, potable water, freshwater, fuels, or other hydrocarbons.

Class 14 - Class 14 coatings are no longer used.

Class 15a - A coating system intended as a repair or touch-up coating for use over oily surfaces that are prepared to bare metal surfaces where paint has been removed to the bare metal substrate.

Class 15b - A coating system intended as a repair or touch-up coating for use over wet surfaces that are prepared to bare metal surfaces where the paint has been removed to the bare metal substrate.

Class 15c - A coating system intended as a repair or touch-up coating for application and cure under (salt) water.

Class 16 - Class 16 coatings are no longer used.

Class 17a - A depot-level or intermediate-level coating system intended for use on properly cleaned and prepared bilge surfaces.

Class 17b - An organizational-level maintenance coating system intended for use on properly cleaned and prepared bilge surfaces by brush or roller application.

Class 18 - A single coat coating system. (Class 18 products are not a standalone class and are designated as class X/18, where X is another service class such as 5, 7, 9, 11, 13, 17, or 19.)

Class 19 - A coating system intended for use on well deck overhead areas of Landing Craft Air Cushion (LCAC) capable ships.

1.2.3 Grades. The grades of coating systems are as follows:

Grade A - A coating system which can be applied down to a temperature of 0 ºC (32 ºF) and cured down to a temperature of -4 ºC (25 ºF).

Grade B - A coating system which is to be applied and cured at temperatures from 0 ºC (32 ºF) to 10 ºC (49 ºF).

Grade C - A coating system which is to be applied and cured at or above a temperature of 11 ºC (50 ºF).



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

Grade D - Powder coatings cured at a high temperature in accordance with manufacturer's instructions in order to meet all performance requirements of this specification.

1.3 Part or identifying number (PIN). DELETED

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

FEDERAL STANDARDS

FED-STD-141 - Paint, Varnish, Lacquer and Related Materials: Methods of Inspection, Sampling and Testing

DELETED

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-DTL-5624 - Turbine Fuel, Aviation, Grades JP-4 and JP-5

MIL-DTL-24441 - Paint, Epoxy-Polyamide, General Specification for

MIL-DTL-24441/29 - Paint, Epoxy-Polyamide, Green Primer, Formula 150, Type IV

MIL-DTL-24441/35 - Paint, Epoxy-Polyamide, Red, Formula 156, Type IV

(Copies of these documents are available online at https://quicksearch.dla.mil.)

2.2.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

FEDERAL REGULATIONS

29 CFR 1910 - Occupational Safety and Health Standards

29 CFR 1910.1200 - Hazard Communication

29 CFR 1915 - Occupational Safety and Health Standards for Shipyard Employment

29 CFR 1917 - Marine Terminals

29 CFR 1918 - Safety and Health Regulations for Longshoring

29 CFR 1926 - Safety and Health Regulations for Construction

29 CFR 1928 - Occupational Safety and Health Standards for Agriculture

DELETED



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

40 CFR 60, Appendix A, Method 24 - Determination of Volatile Matter Content, Water Content, Density, Volume Solids, and Weight Solids of Surface Coatings

40 CFR Part 63, Appendix A, Method 311 - Hazardous Air Pollutant Compounds in Paints and Coatings

DELETED

40 CFR 261, Appendix II, Method 1311 - Toxicity Characteristic Leaching Procedure (TCLP)

DELETED

DELETED

40 CFR 372.65 - Specific Toxic Chemical Listings

(Copies of these documents are available online at https://www.ecfr.gov.)

NATIONAL INSTITUTE OF ENVIRONMENTAL HEALTH SCIENCES (NIEHS)

DELETED

NATIONAL INSTITUTE FOR OCCUPATIONAL SAFETY AND HEALTH (NIOSH)

NIOSH Manual of Analytical Methods (NMAM)

Method 7500 - Silica, Crystalline, by XRD (Filter Redeposition)

(Copies of these documents are available online at https://www.cdc.gov/niosh.)

OCCUPATIONAL SAFETY AND HEALTH ADMINISTRATION (OSHA)

ID-191 - Polarized Light Microscopy of Asbestos

(Copies of this document are available online at https://www.osha.gov.)

U.S. ENVIRONMENTAL PROTECTION AGENCY (EPA)

EPA SW-846 - Test Methods for Evaluating Solid Waste: Physical/Chemical Methods

EPA 600/4-79/020 - Methods for Chemical Analysis of Water and Wastes

(Copies of these documents are available online at www.epa.gov.)



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

2.3 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

AMERICAN CONFERENCE OF GOVERNMENTAL INDUSTRIAL HYGIENISTS (ACGIH)

DELETED

AMERICAN NATIONAL STANDARDS INSTITUTE (ANSI)

ANSI Z400.1 - Hazardous Workplace Chemicals - Hazard Evaluation and Safety Data Sheet and Precautionary Labeling Preparation

(Copies of this document are available online at https://webstore.ansi.org/.)

AMERICAN PUBLIC HEALTH ASSOCIATION (APHA)

Standard Methods for the Examination of Water and Wastewater

APHA 2120B - Visual Comparison Method

APHA 2150B - Threshold Odor Test

APHA 2160B - Flavor Threshold Test (FTT)

APHA 4500Cl-F - DPD Colorimetric Method

APHA 5530C - Chloroform Extraction Method

APHA 5530D - Direct Photometric Method

(Copies of these documents are available online at https://www.apha.org.)

ASTM INTERNATIONAL

ASTM B117 - Standard Practice for Operating Salt Spray (Fog) Apparatus

ASTM D93 - Standard Test Methods for FlashPoint by Pensky-Martens Closed Cup Tester

ASTM D130 - Standard Method for Corrosiveness to Copper from Petroleum Products by Copper Strip Test

ASTM D156 - Standard Test Method for Saybolt Color of Petroleum Products (Saybolt Chromometer Method)

ASTM D381 - Standard Test Method for Gum Content in Fuels by Jet Evaporation

ASTM D523 - Standard Test Method for Specular Gloss

ASTM D562 - Standard Test Method for Consistency of Paints Measuring Krebs Unit (KU) Viscosity Using a Stormer-Type Viscometer

ASTM D714 - Standard Test Method for Evaluating Degree of Blistering of Paints

ASTM D823 - Standard Practices for Producing Films of Uniform Thickness of Paint, Coatings and Related Products on Test Panels

ASTM D910 - Standard Specification for Leaded Aviation Gasolines

ASTM D1141 - Standard Practice for the Preparation of Substitute Ocean Water

ASTM D1193 - Standard Specification for Reagent Water



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

ASTM D1655 - Standard Specification for Aviation Turbine Fuels

ASTM D1729 - Standard Practice for Visual Appraisal of Colors and Color Differences of Diffusely-Illuminated Opaque Materials

ASTM D3278 - Standard Test Methods for Flash Point of Liquids by Small Scale Closed-Cup Apparatus

DELETED

ASTM D4400 - Standard Test Method for Sag Resistance of Paints Using a Multinotch Applicator

ASTM D4417 - Standard Test Methods for Field Measurement of Surface Profile of Blast Cleaned Steel

ASTM D4541 - Standard Test Method for Pull-Off Strength of Coatings Using Portable Adhesion Testers

DELETED

ASTM D4585 - Standard Practice for Testing Water Resistance of Coatings Using Controlled Condensation

ASTM D5150 - Standard Test Method for Hiding Power of Architectural Paints Applied by Roller

ASTM E260 - Standard Practice for Packed Column Gas Chromatography

ASTM E1252 - Standard Practice for General Techniques for Obtaining Infrared Spectra for Qualitative Analysis

ASTM F718 - Standard Specification for Shipbuilders and Marine Paints and Coatings Product/Procedure Data Sheet

ASTM G8 - Standard Test Methods for Cathodic Disbonding of Pipeline Coatings

ASTM and Other Specifications and Classifications for Petroleum Products and Lubricants: Fuels and Oils, Bituminous Materials, Solvents

(Copies of these documents are available online at https://www.astm.org and https://amazon.com.)

NSF INTERNATIONAL

NSF Standard 61 - Drinking Water System Components - Health Effects

(Copies of this document are available online at https://www.nsf.org.)

SAE INTERNATIONAL

SAE AMS-STD-595 - Colors Used in Government Procurement

SAE AMS-STD-595/20109 - Brown, Semi-Gloss, Red Brown

SAE AMS-STD-595/20152 - Brown, Semi-Gloss

SAE AMS-STD-595/22563 - Orange, Semi-Gloss

SAE AMS-STD-595/23695 - Yellow, Semi-Gloss

SAE AMS-STD-595/24272 - Green, Semi-Gloss

SAE AMS-STD-595/24585 - Green, Semi-Gloss



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

SAE AMS-STD-595/25526 - Blue, Semi-Gloss

SAE AMS-STD-595/26081 - Gray, Semi-Gloss

SAE AMS-STD-595/26270 - Gray, Semi-Gloss, Haze Gray

SAE AMS-STD-595/26307 - Gray, Semi-Gloss, Bulkhead Equipment Gray

SAE AMS-STD-595/26622 - Gray, Semi-Gloss

SAE AMS-STD-595/27038 - Miscellaneous, Semi-Gloss, ANA 514

SAE AMS-STD-595/27880 - Miscellaneous, Semi-Gloss

SAE AMS-STD-595/27886 - Miscellaneous, Semi-Gloss

(Copies of this document are available online at https://www.sae.org.)

THE SOCIETY FOR PROTECTIVE COATINGS (SSPC)

SSPC-SP 2 - Hand Tool Cleaning

SSPC-SP 10 - Near-White Metal Blast Cleaning

SSPC-SP 11 - Power-Tool Cleaning to Bare Metal

SSPC-SP 15 - Commercial Grade Power-Tool Cleaning

(Copies of these documents are available online at https://www.sspc.org.)

2.4 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Qualification. Coating systems furnished under this specification shall be products that are authorized by the qualifying activity for listing on the applicable qualified products list before contract award (see 4.2 and 6.3).

3.1.1 Description of coatings. At the time of qualification submittal, manufacturer shall identify all coatings and coating component constituents of the coating system being qualified by the following;

a. Type, class, and grade for which qualification is sought; and

b. Unique product nomenclature.

At a minimum, this unique product nomenclature shall consist of component name, alpha-numeric identifier, and color. Nomenclature shall be as specific as necessary to uniquely identify each total system component.

3.2 Materials. Each individual component and mixed final coating of the total coating system qualified to this specification shall, when mixed and applied in accordance with the manufacturer's instructions, be in accordance with the appropriate requirements. The composition of the coating furnished to this specification shall be the responsibility of the manufacturer, except as limited by this specification.

3.2.1 Description. Where coatings are composed of components to be mixed at the time of application, the proportions for the ratio of resin component to hardener shall be 4:1, 3:1, 2:1, or 1:1, by volume. With the exception of type VIII (all classes) and class 18 (all types) coatings, the coating system shall consist of at least two full coats (see 6.6.3 and 6.6.4).

3.2.2 Component chemistry (except types VIII and VIIIa). All coatings shall be composed of two components:

a. One component shall contain chemically cross-linking resins (base) (see 6.6.2); and

b. A second component which shall contain a curing agent (converter).



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

3.2.2.1 Powder coatings. Type VIII and VIIIa powders are single component materials and shall be applied and cured using industry accepted application procedures in accordance with the manufacturer's instructions. The resulting cured film shall be tested for compliance with the requirements in this specification.

3.2.2.2 VOC limits. When tested as specified in 4.5.5, the VOC of types V, VI, VII, VIII, and VIIIa shall be less than that allowed for the type being qualified.

3.2.2.3 HAP content of types V, VI, VII, VIII, and VIIIa coatings. When evaluated as specified in 4.5.6, the content of HAP in each individual coatings of types V, VI, VII, VIII, and VIIIa shall be less than the VOC limit prescribed for the specific types. Within this limitation and the requirement that the finished coating meet all requirements of this specification, type V, VI, and VII coating systems solvent selection is the responsibility of the manufacturer.

3.2.3 Hazardous pigments and additives.

3.2.3.1 Types V, VI, VII, VIII, and VIIIa. When tested as specified in 4.5.10, the content of each soluble metal and the total content of each metal of the coating shall be less than the values listed in tables I and II. In addition, asbestos and asbestiform pigments shall be less than 0.5 percent by weight (wt%) of the dry paint film. Crystalline silica shall not exceed 0.1 wt%. If the total metal content for an individual metal is less than the allowed soluble metal content for that metal, the total metal value may be submitted for the soluble metal value and the actual test for soluble metal need not be performed.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE I. Soluble metals content for type V, VI, VII, VIII, and VIIIa coatings.

| **Soluble metal and its compound in each individual dry paint** | **Maximum, mg/L** |
|---|---|
| Antimony | 15 |
| Arsenic | 5 |
| Barium (excluding barite) | 100 |
| Beryllium | 0.75 |
| Cadmium | 1 |
| Chromium (VI) | 1 |
| Chromium and chromium (III) | 560 |
| Cobalt | 50 |
| Copper | 25 |
| Fluoride salts | 180 |
| Lead | 5 |
| Mercury | 0.2 |
| Molybdenum | 350 |
| Nickel | 20 |
| Selenium | 1 |
| Silver | 5 |
| Tantalum | 100 |
| Thallium | 7 |
| Tungsten | 100 |
| Vanadium | 24 |
| Zinc | 250 |
| NOTE:<br>1. Copper content does not apply to green and blue SAE International colors as described in 2.3. | |



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE II. Total metals content for type V, VI, VII, VIII, and VIIIa coatings.

| Metal or its compounds in each individual dry paint | Maximum, wt% |
|---|---|
| Antimony | 0.015 |
| Arsenic | 0.005 |
| Barium (excluding barite) | 0.10 |
| Beryllium | 0.0002 |
| Cadmium | 0.0005 |
| Chromium (VI) compounds | 0.001 |
| Chromium or chromium (III) compounds | 0.56 |
| Cobalt | 0.005 |
| Copper | 0.01 |
| Fluoride salts | 0.18 |
| Lead | 0.005 |
| Mercury | 0.0002 |
| Molybdenum | 0.35 |
| Nickel | 0.02 |
| Selenium | 0.002 |
| Silver | 0.001 |
| Tantalum | 0.100 |
| Thallium | 0.007 |
| Tungsten | 0.100 |
| Vanadium | 0.01 |
| Zinc | 0.25 |

NOTE:

1. Copper content does not apply to green and blue SAE International colors as described in 2.3.

3.3 Color and gloss (all types except VIII and VIIIa, all classes except 15 and,17, all grades). When tested in accordance with the procedures of table V, each topcoat of the coating systems shall have a 60-degree specular gloss of not less than 30 percent. Succeeding coats of the coating system shall be of contrasting color, and the top coat shall be white or a very light pastel shade. Primer shall be a contrasting color to the bare steel substrate.

3.3.1 Color and gloss (types VIII and VIIIa). The as-cured type VIII powder coating colors shall be within 0.5 Delta E (ΔE) units of the specified SAE AMS-STD-595 color numbers as indicated below in table III. The as-cured type VIIIa powder coating colors shall be defined by the manufacturer.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE III. Color and gloss.

| Color | SAE AMS-STD-595 color number | DELETED |
|---|---|---|
| Green | 24272 | |
| Haze Gray | 26270 | |
| White | 27886 | |
| Brown | 20152 | |
| Light Gray | 26622 | |
| Yellow | 23695 | |
| Red Brown | 20109 | |
| Beach Sand | 22563 | |
| DELETED | | |
| DELETED | | |
| DELETED | | |
| Soft White | 27880 | |
| Pastel Green | 24585 | |
| Bulkhead Equipment Gray | 26307 | |
| DELETED | | |
| DELETED | | |
| DELETED | | |
| Dark Gray | 26081 | |
| Pastel Blue | 25526 | |
| Black | 27038 | |

3.3.2 Color (classes 15a, 15b, 15c, and 17a). Topcoat colors of class 15a, 15b, 15c, and 17a coating systems shall visually approximate the SAE AMS-STD-595 colors Green, Haze Gray, White, Red Brown, Light Gray, and Black.

3.3.3. Color (class 17b). Color (class 17b). Topcoat colors of class 17b coating systems shall visually approximate the commercial colors terracotta red, buff, off-white, haze gray, and dark gray that are defined by the manufacturer on their product data sheet and are not cited in table III.

3.4 Potable and freshwater (all types, class 9, all grades). See 4.5.11 for panel and test preparation.

3.4.1 NSF certification (required for each grade). Coatings for class 9 shall be certified by NSF International, NSF Standard 61, for use in 500-gallon (or smaller volume) water storage tanks. The use of Underwriters Laboratories or other NAVSEA approved testing laboratories is also acceptable.

3.4.2 Color in water. When tested as specified in 4.5.11.1, color units shall not be greater than 10.

3.4.3 Taste in water. When tested as specified in 4.5.11.2, threshold taste values shall not be greater than 2.

3.4.4 Odor in water. When tested as specified in 4.5.11.3, threshold odor values shall not be greater than 2.

3.4.5 Chlorine residual. When tested as specified in 4.5.11.4, chlorine residual shall not decrease in excess of 50 percent of concentration.

3.4.6 Phenol contamination. When tested as specified in 4.5.11.5, the cured film of each coating of the coating system shall not leach phenolic compounds in concentrations greater than 1 part per million.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

3.4.7 Immersion resistance (class 9). When tested in accordance with 4.5.2.3, the total coating system shall show no pinhole rusting, cracking, or loss of adhesion either between coats or to the substrate. There shall be no blisters rated in excess of ASTM D714, blister size number 4, Few. There shall be no surface imperfections (including peeling) larger than 1.5 millimeters (0.0625 inch) and any blisters shall be unbroken. Type VII coating systems shall have no edge rusting. Blisters and surface imperfections smaller than 1.5 millimeters (0.0625 inch) that do not increase in size after the tenth cycle and do not exceed 3 percent of the test panel surface area shall not be considered failures. At the completion of the test, adhesion of the recoat to the original coating shall be at least 50 percent of the original coating area of the test panel to itself. Type VII edge rusting shall not exceed 0.1 percent of total edge length. Physical damage caused by handling shall be identified and may be ignored in the post-test condition evaluation.

3.5 Cathodic protection (CP) compatibility (all types, all classes, all grades). When tested as specified in accordance with 4.5.16, the coating system shall not peel, flake, blister, dissolve, or otherwise fail. Undercutting or peeling shall not exceed 4 percent of the area of the test panel and all undercutting and peeling shall be located within ½ inch of the holiday.

3.6 Drying or curing time (all types, all classes, all grades). When tested in accordance with the procedures of table V, each individual coating of the coating system shall require not greater than 23 hours between coats for recoating and shall be ready for service within 7 days after the application of the last coat. Application and cure shall be at the temperature specified by the manufacturer. In the absence of manufacturer's guidance, the temperature selected shall be at the low end of the temperature range.

3.7 Flash point (all types except VIII and VIIIa, all classes, all grades). When tested in accordance with the procedures of table V, each individual coating of the coating system mixed for use shall not flash at temperatures lower than 38 ºC (100 ºF).

3.8 Application characteristics (all types except VIII and VIIIa, all classes, all grades). When tested as specified in 4.5.7 and 4.5.8, each individual coating of the coating system shall be readily applied by brushing (touch-up areas only), rolling, and spraying, using commercially available equipment specified by the manufacturer's data sheet. The coatings shall exhibit leveling without sagging when applied at the film thickness recommended by the manufacturer. The manufacturer's product data sheets shall state at which temperature it will be necessary to use plural component spray equipment in order to achieve an acceptable surface appearance. Apply types VIII and VIIIa in accordance with manufacturer's instructions.

3.8.1 Edge coverage retention (type VII, all classes, all grades). When tested as specified in 4.5.9, the retained percent dry film thickness (DFT) of coating on any single 90-degree outside edge test specimen shall not be less than 50 percent of the paint DFT on flat areas. The average coating (percent) retained on a 90-degree outside edge of no less than three specimens shall be an average minimum of 70 percent of the measured dry film thickness on the flat areas of the test specimen. There shall be no pin holes, cracks, or other defects along the edge that extend more than 10 percent into the thickness of the coating on the edge. No defect shall extend completely to the metal of the test specimen. The edge coverage retention applies to the topcoat only and not to the primer.

3.8.2 Sag resistance (all types, all classes, all grades). When tested in accordance with the ASTM Test Method cited in table V, sag resistance shall comply with the value submitted by the manufacturer (see 3.12).

3.9 Immersion resistance (all types, all grades). Any coating system failure prior to the completion of all class specific immersion cycles (see 4.5.2) shall constitute failure of the coating system to meet the requirements of this specification.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

3.9.1 Class 5 (fuel and seawater). When tested as specified in 4.5.2.1, the total coating system shall show no pinhole rusting, cracking, or loss of adhesion either between coats or to the substrate. There shall be no blisters rated in excess of ASTM D714, blister size number 4, Few. There shall be no surface imperfections (including peeling) larger than 1.5 millimeters (0.0625 inch) and any blisters shall be unbroken. Type VII coating system shall have no edge rusting. Blisters and surface imperfections smaller than 1.5 millimeters (0.0625 inch), which do not increase in size after the tenth cycle and that do not exceed 3 percent of the test panel surface area, shall not be considered failures. At the completion of the test, adhesion of the recoat to the original coating shall be at least 50 percent of the original coating area of the test panel to itself. Physical damage caused by handling shall be identified and may be ignored in the post-test condition evaluation.

3.9.2 Class 7 (seawater only). When tested as specified in 4.5.2.2, the total coating system shall show no pinhole rusting or loss of adhesion, either between coats or to the substrate. There shall be no blisters rated in excess of ASTM D714, blister size number 4, Few. There shall be no surface imperfections (including peeling) larger than 1.5 millimeters (0.0625 inch) and any blisters shall be unbroken. Type VII coating system shall have no edge rusting. Blisters and surface imperfections smaller than 1.5 millimeters (0.0625 inch), which do not increase in size after the tenth cycle and are not greater than 3 percent of the test panel surface area, shall not be considered failure. At completion of the test, adhesion of the recoat to the original coating shall be at least 50 percent of that of the original coating area of the test panel to itself. Physical damage caused by handling shall be identified and may be ignored in the post-test condition evaluation.

3.10 Condition in container (all types except VIII and VIIIa, all classes, all grades). When tested in accordance with table V, each individual coating component shall be usable; that is, shall be readily broken up with a paddle or mechanical stirring to a smooth uniform consistency, and shall not liver or show any other objectionable properties for at least 1 year. Coating shall apply satisfactorily when applied as specified in manufacturer's data sheet (see table V).

3.10.1 Accelerated storage stability. When mixed and tested as specified in 4.5.1.2, components shall meet the table IV characteristics submitted for consistency, fineness of grind, and condition in container. Mixed paints from these components shall be allowed a consistency increase of not more than 10 percent when tested in accordance with ASTM D562. When tested as specified in table V, mixed paints shall meet the requirements for dry time, pot life, sag resistance, gloss, and application characteristics (see 3.8).

3.10.2 Condition in container (types VIII and VIIIa). Types VIII and VIIIa powders shall meet all applicable specification requirements when stored in original unopened containers at or below 22 ºC (72 ºF) and less than 50 percent relative humidity for a period of 1 year from date of manufacture.

3.11 Toxicity (all types, all classes, all grades). When evaluated in accordance with 4.6, the coating system shall pose no serious or high risk to the health of personnel or the environment when used for its intended purpose (see 4.6 and 6.7).

3.12 Identification characteristics (all types, all classes, all grades). Values for identification (ID) characteristics shall be those established for the product at the time submitted for qualification testing (see table IV). The purpose of these values is to serve as a basis for determining that the material being offered is essentially the same as that which was approved under qualification testing. Identification characteristics for grade A and B materials shall be at the low end of their respective temperature range (see 1.2.3). The qualification testing for all types, classes, and grades shall be conducted at the low temperature in the range. Manufacturer shall provide ASTM method(s), FED-STD-141 methods, other consensus standards, or a copy of unique test methodology and any other necessary information on methodology used to determine reported ID characteristics.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE IV. Identification characteristic values.

| Property | Coating component [1/] | Coating [2/] | Coating system [3/] |
|---|---|---|---|
| Chemical nature | X | --- | --- |
| Principal constituents (10 percent or more of total) | X | --- | --- |
| Percent nonvolatile vehicle | X | --- | --- |
| Percent volatile | X | --- | --- |
| Mass per liter (L) (gallon [gal]) [4/] | X | --- | --- |
| Color [5/] | | X | --- |
| Viscosity [4/] | X | --- | --- |
| Flash point [4/] | X | X | --- |
| Fineness of grind [4/] | X | --- | --- |
| Odor | X | X | --- |
| Pot life [6/] | --- | X | --- |
| Drying or curing time - time to recoat | --- | X | --- |
| Gloss and appearance | --- | X | --- |
| Flexibility | --- | X | X |
| Mixing instructions [4/] | --- | X | X |
| Application instructions | --- | X | --- |
| Sag resistance | --- | X [6/] | --- |

NOTES:

1/ Coating components are individually packaged as base or resin component (part A) and converter or hardener component (part B). Indicate which component was tested for the given coating property.

2/ Coating base or resin component (part A) and converter or hardener component (part B) are mixed and the resulting coating is ready for application.

3/ Coating system is the total system (number and types of coats and approximate dry film thickness) as tested for qualification approval.

4/ Not applicable to types VIII or VIIIa.

5/ See 3.3 for the different color measurement requirements for liquid and powder coatings, and for depot-level and organizational-level maintenance coatings.

6/ Not applicable to types VIII or VIIIa or class 17b.

3.13 Aviation (JP-5) fuel and gasoline (aviation gasoline) compatibility (all types, class 5, all grades). When tested as specified in 4.5.4, the cured total coating system shall not contribute particulate or chemical contamination that is detrimental to subsequent logistics or aircraft operation. Particulate contamination occurs when solids, color bodies, and fuel reaction bodies are leached from the coating. Chemical contamination manifests itself when the fuel becomes corrosive, shows increased existent gum, or suffers a loss in diethylene bromide.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

3.13.1 Fuel color. When tested as specified in 4.5.4.2, the cured total coating system shall not affect the color of fuel as follows:

a. JP-5 fuel: Saybolt color difference shall be not greater than 2.

b. Aviation gas: There shall be no perceptible difference in color, turbidity, or precipitation.

3.13.2 Corrosion. When tested as specified in 4.5.4.3, JP-5 and aviation gas shall not become corrosive after contact with the coating system.

3.13.3 Existent gum. When tested as specified in 4.5.4.4, the cured total coating system effect on existent gum shall be as follows:

a. The difference in existent gum (unwashed) shall not be greater than 4 milligrams per 100 milliliters.

b. The difference in existent gum (washed) shall not be greater than 2 milligrams per 100 milliliters.

3.13.4 Solids (total sediment). When tested as specified in 4.5.4.5, the total cured coating system shall not cause a difference in total sediment greater than 2 milligrams per liter.

3.13.5 Bromine. When tested as specified in 4.5.4.6, the effect of the total cured coating system on the ethylene dibromide content of aviation gas shall be that the difference in bromine content shall not be greater than 10 percent.

3.14 Resistance to fuel and seawater at 32 ºC (90 ºF) (all types, class 5, all grades). When tested as specified in 4.5.2.4, coating:

a. Shall not chalk.

b. Shall not exhibit film failure such as peeling, blistering rated in excess of ASTM D714, blister size number 4, Few. There shall be no surface imperfections (including peeling) larger than 1.5 millimeters (0.0625 inch), and any blistering shall be unbroken. Type VII coating system shall have no surface or edge rusting.

c. Shall show no loss of apparent hardness and adhesion when examined visually and with a knife test.

3.15 Resistance to hot water - simulated boiler feedwater (all types, class 11, all grades). When tested as specified in 4.5.12, coating shall have no pinhole rusting. The ASTM D4541, type II tester, adhesion of the tested system to itself and the substrate shall be not less than 50 percent of that of the original coating before testing. There shall be no blistering rated in excess of ASTM D714, blister size number 4, Few. There shall be no surface imperfections (including peeling) larger than 1.5 millimeters (0.0625 inch), and any blistering shall be unbroken. Type VII coating system shall have no edge rusting.

3.16 Resistance to chemical solutions - simulated collection holding and transfer (CHT; sewage waste) tanks (all types, class 13 only, all grades). When tested as specified in 4.5.13, the coating shall have no pinhole rusting. After testing the ASTM D4541, type II tester, cohesion and adhesion values of the tested system to itself and the substrate shall be at least 50 percent of the values for cohesion and adhesion of the untested original coating to itself and the substrate before testing. There shall be no blistering rated in excess of ASTM D714, blister size number 4, Few. There shall be no surface imperfections (including peeling) larger than 1.5 millimeters (0.0625 inch), and any blistering shall be unbroken. Type VII coating system shall have no edge rusting.

3.17 Resistance to condensing water - simulated tank top test (all types, all classes, all grades). When tested as specified in 4.5.14, the coating system shall have no pinhole rusting. The ASTM D4541, type II tester, adhesion values of the tested system to itself and the substrate shall be at least 50 percent of the values for adhesion of the untested original coating before testing. There shall be no blistering rated in excess of ASTM D714, blister size number 4, Few. There shall be no surface imperfections (including peeling) larger than 1.5 millimeters (0.0625 inch), and any blistering shall be unbroken. Type VII coating system shall have no edge rusting.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

3.18 Ultraviolet fluorescence (applicable to primers of type VII, all classes, all grades). When tested in accordance with 4.5.15, the primer shall fluoresce with sufficient brightness to visually ascertain coverage of test panel.

3.19 Surface tolerant coating systems. When tested in accordance with 4.5.17, class 15 coating systems shall demonstrate adhesion values of at least 50 percent of the values obtained from testing when the same coating system is applied to a dry, clean SSPC-SP 15 surface condition.

3.20 Bilge coating systems. When tested in accordance with 4.5.18, class 17 coating systems shall demonstrate adhesion values of at least 50 percent of the value obtained when the same coating system is applied to dry, clean test panels prepared to surface cleanliness standard SSPC-SP 11.

3.21 Single coat coating system. When tested in accordance with 4.5.19, class 18 coating systems shall comply with the performance and verification requirements of all associated class coating systems (see 3.2.1).

3.22 Label. Manufacturer shall prepare label instructions in accordance with 29 CFR 1910. Each container shall be affixed with a hazardous chemical warning label in accordance with 29 CFR 1910.1200. To comply with the USEPA NESHAP requirements for shipbuilding and ship repair, the following two statements shall appear on each paint-can label:

a. Certification that the paint in the container meets the NESHAP requirements for shipbuilding and ship repair.

b. Statement of the ratio of volatile content to solids expressed as grams of volatile organic hazardous air pollutants (VOHAP) per liter of solids.

3.23 Well deck overhead coating systems. When tested in accordance with 4.5.20, class 19 coatings systems shall exhibit heat resistance up to 260 ºC (500 ºF). There shall be no degradation or delamination of the coating from the test panel. Adhesion of the coating system to the panel following the elevated heat test shall be at least 50 percent of the adhesion value obtained prior to the test.

3.24 Service test. When evaluated in accordance with 4.5.2.1, class 7 and class 19 coating systems shall exhibit less than 1 percent coating failure and surface imperfections such as blistering, corrosion, and delamination following 1 year of service. Application in other classes will be considered following successful service.

3.25 Pot life (all types, class 17b, all grades). When tested as specified in 4.5.1, the pot life shall be no less than 1 hour at a temperature of 21±3 ºC (70±5 ºF).

## 4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Conformance inspection (see 4.3).

4.2 Qualification inspection. Qualification inspection shall include the examination of table V and the tests of 4.5.1 through 4.5.2.1 and 4.6.

4.2.1 Extension of qualification. Testing and qualification approval for types VI and VII shall also constitute approval for type V coating systems of the same class and grade. Testing and qualification approval for type VII shall also constitute approval for types V and VI coatings of the same class and grade. Testing and qualification approval for types VIII and VIIIa is unique and not extended to other types.

4.2.2 Change approval. Changes in construction, formulation, materials, design, or manufacturing process of qualified products may require requalification. Unless otherwise specified by the qualifying activity, changes require written approval by NAVSEA.

DELETED

DELETED



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

DELETED

4.3 Conformance inspection. Conformance inspection shall consist of the conformance tests specified in table V.

4.4 Panel preparation. Test plates of the nature and size specified in the applicable test method shall be coated in accordance with the manufacturer's application instructions. Each individual coating of the coating system shall be mixed in accordance with the manufacturer's mixing instructions.

4.5 Test procedures. Tests shall be conducted as specified in table V. The temperature at which tests are conducted shall be in accordance with the applicable FED-STD-141 and ASTM test methods identified in table V. For reduced temperature materials (grades A and B), tests shall be conducted at the low end of the temperature range. Unless otherwise specified herein, test panel dimensions and test conditions, such as temperature, are nominal.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE V. Test procedures. [1/]

| Characteristics | Requirements | Test paragraph | Applicable FED-STD-141 method | Applicable ASTM test | Table IV ID test | Conformance test |
|---|---|---|---|---|---|---|
| Chemical nature | 3.2.2 | --- | --- | --- | X | --- |
| VOC | 3.2.2.2 | 4.5.5 | --- | --- | --- | --- |
| HAPs | 3.2.2.3 | 4.5.6 | --- | --- | --- | --- |
| Hazardous pigments | 3.2.3.1 | 4.5.10 | --- | --- | --- | --- |
| Color | 3.3 | --- | --- | D1729 [2/] | X | X |
| Gloss | 3.3 | --- | --- | D523 | X | X |
| Potable water | 3.4 | 4.5.11 | --- | --- | --- | --- |
| Color in water | 3.4.2 | 4.5.11.1 | --- | --- | --- | --- |
| Taste in water | 3.4.3 | 4.5.11.2 | --- | --- | --- | --- |
| Odor in water | 3.4.4 | 4.5.11.3 | --- | --- | --- | --- |
| Chlorine residual | 3.4.5 | 4.5.11.4 | --- | --- | --- | --- |
| Phenol | 3.4.6 | 4.5.11.5 | --- | --- | --- | --- |
| CP compatibility | 3.5 | 4.5.16 | --- | --- | --- | --- |
| Drying or cure time | 3.6 | --- | 4061 | --- | --- | X |
| Flash point | 3.7 | --- | --- | D93 or D3278 | X | X [3/, 4/] |
| Application characteristics (mixed) | 3.8 | 4.5.7, 4.5.8 | --- | D823 method B and D4417 | --- | --- |
| Edge coverage | 3.8.1 | 4.5.9 | --- | --- | --- | --- |
| Fuel & fuel/seawater ballast service- class 5 | 3.9.1 | 4.5.2.1 | --- | --- | --- | --- |
| Dedicated seawater service | 3.9.2 | 4.5.2.2 | --- | --- | --- | --- |
| Condition in container | 3.10 and 3.10.2 | 4.5.1.1 | 3011 | D562 | --- | |
| ID principal constituents | 3.12 | --- | --- | --- | X | --- |
| ID percent nonvolatile vehicle | 3.12 | --- | --- | --- | X | --- |
| ID percent volatile | 3.12 | --- | --- | --- | X | --- |



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE V. Test procedures – Continued. 1/

| Characteristics | Requirements | Test paragraph | Applicable FED-STD-141 method | Applicable ASTM test | Table IV ID test | Conformance test |
|---|---|---|---|---|---|---|
| ID mass (g/L) (lb/gal) | 3.12 | --- | --- | --- | X | X |
| ID color | 3.12 | --- | --- | --- | X | X |
| ID viscosity | 3.12 | --- | --- | --- | X | X 3/ |
| ID flash point | 3.12 | --- | --- | --- | X | X |
| ID fineness of grind | 3.12 | --- | --- | --- | X | X |
| ID odor | 3.12 | --- | --- | --- | X | --- |
| ID pot life | 3.12 | 4.5.1 | --- | --- | X | --- |
| ID drying or curing time | 3.12 | --- | --- | --- | X | X 3/ |
| ID gloss and appearance | 3.12 | --- | --- | --- | X | X |
| ID flexibility | 3.12 | --- | --- | --- | X | --- |
| ID sag resistance | 3.12 and 3.8.2 | --- | --- | D4400 | X | X 3/ |
| Aviation fuel compatibility | 3.13 | 4.5.4 | --- | --- | --- | --- |
| Fuel color | 3.13.1 | 4.5.4.2 | --- | --- | --- | --- |
| Corrosion | 3.13.2 | 4.5.4.3 | --- | --- | --- | --- |
| Existent gum | 3.13.3 | 4.5.4.4 | --- | --- | --- | --- |
| Solid (total sediment) | 3.13.4 | 4.5.4.5 | --- | --- | --- | --- |
| Bromine | 3.13.5 | 4.5.4.6 | --- | --- | --- | --- |
| Accelerated storage stability | 3.10.1 | 4.5.1.2 | 3011.3 | --- | --- | --- |
| Resistance to fuel and water at 32 ºC (90 ºF) | 3.14 | 4.5.2.4 | --- | --- | --- | --- |
| Boiler feedwater service -resistance to boiling water | 3.15 | 4.5.12 | --- | --- | --- | --- |
| CHT service - resistance to chemical solutions | 3.16 | 4.5.13 | --- | --- | --- | --- |
| Tank top - resistance to condensing water | 3.17 | 4.5.14 | --- | --- | --- | --- |
| Ultraviolet fluorescence | 3.183.18 | 4.5.15 | --- | --- | --- | --- |
| Surface tolerant coatings | 3.19 | 4.5.17 | --- | --- | --- | --- |



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE V. Test procedures – Continued. 1/

| Characteristics | Requirements | Test paragraph | Applicable FED-STD-141 method | Applicable ASTM test | Table IV ID test | Conformance test |
|---|---|---|---|---|---|---|
| Bilge coating systems | 3.20 | 4.5.18 | --- | --- | --- | --- |
| Single coat coating systems | 3.21 | 4.5.19 | --- | --- | --- | --- |
| Well deck overhead coating (class 19) resistance to heat | 3.23 | 4.5.20 | --- | --- | --- | --- |
| Pot life (class 17b) | 3.25 | 4.5.1 | --- | --- | --- | --- |
| Recoatability (except types VIII and VIIIa) | 3.4.7, 3.9.1, 3.9.2, 3.15, 3.16, and 3.17 | 4.5.3 | --- | --- | --- | --- |
| Recoatability (types VIII and VIIIa) | 3.9.1, 3.9.2, 3.15, 3.16, and 3.17 | 4.5.3.1 | --- | --- | --- | --- |
| Service test | 3.24 | 4.5.2.1 | --- | --- | --- | --- |
| Toxicity | 3.11 | 4.6 | --- | --- | --- | --- |

NOTES:

1/ All qualification tests shall be conducted on stored coatings after one year of storage. If all other requirements are met, qualification approval will be granted prior to receiving these results, but qualification approval will be withdrawn if results indicate non-compliance with this requirement (see 3.10).

2/ Shall visually approximate the coating manufacturer's color card or the specified SAE-AMS-STD-595 designated color (see 3.3).

3/ Mixed component A and component B for test.

4.5.1 Pot life (except types VIII and VIIIa). The coatings of the coating system shall be mixed from the components, in accordance with the manufacturer's instructions, in a container to result in approximately 3.78 liters (1 gallon) of finished material. For routine testing, ambient conditions above 21 ºC (70 ºF) and 50 percent relative humidity shall be satisfactory. For referee tests, 21±3 ºC (70±5 ºF) and 80±10 percent relative humidity shall prevail. The time between mixing and the loss of brushing and spraying properties shall be determined (see 3.8, 4.5.7, and 4.5.8). Record the actual temperature, humidity, and the time of loss of brushing and spraying properties. For reduced temperature coating systems (grades A and B), pot life of individual mixed coatings shall be determined at the lower end of the temperature range or as directed by the coating manufacturer. For class 17b coatings, the coating system shall be mixed in accordance with the NAVSEA-reviewed ASTM F718. For routine testing, ambient conditions above 21 ºC (70 ºF) and 50 percent relative humidity shall be satisfactory. For referee tests, 21±3 ºC (70±5 ºF) and 80±10 percent relative humidity shall prevail. The time between mixing and the loss of brushing properties shall be determined (see 3.8 and 4.5.7). Record the actual temperature, humidity, and the time of loss of brushing and rolling properties.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

4.5.1.1 Condition in container. When tested in accordance with FED-STD-141, method 3011.3, the individual components shall be readily broken up with a paddle to a smooth uniform consistency. When tested as specified in table V, paint, mixed from components aged at least 1 year in ambient laboratory conditions, shall be as specified in 3.10. When tested in accordance with ASTM D562, the consistency of the paint, mixed from the aged components, shall be as specified in 3.10.

4.5.1.2 Accelerated storage stability. After exposure of components A and B to a temperature of 60 ºC (140 ºF) for a period of 14 days, previously unopened containers of components A and B shall be prepared for testing in accordance with 4.5.1.1 and tested for compliance with the requirements of 3.10.1.

4.5.2 Immersion resistance – panel preparation of all coatings.

a. The coating systems shall be applied as specified in the manufacturer's instructions and shall completely coat three abrasive blasted, hot rolled, mild steel plates (minimum size: 150 by 300 by 3 millimeters (6 by 12 by 0.125 inch) [nominal]). The blast pattern shall be not greater than 0.08 millimeter (3 mils) (nominal) depth for coating systems having 0.13 millimeter (5 mils) or more DFT and 0.04 millimeter (1.5 mils) for systems having less than 0.13 millimeter (5 mils) DFT. The test panels shall have all mill scale, rust, and rough edges completely removed and prepared to applicable surface profile in accordance with SSPC-SP 10 before coating.

b. Unless otherwise specified in the manufacturer's data sheet, 24 hours dry time shall be allowed between coats, and 1 week at 21 ºC (70 ºF) (nominal) or equivalent between the last coat and immersion. Edges shall not receive extra paint thickness or be reinforced by additional coats unless such coating is specified in the manufacturer's ASTM F718 and product data sheets under application instructions. At test inspection points, the coatings shall be as specified for the appropriate type, class, and grade.

4.5.2.1 Immersion test for fuel and seawater ballast exposure (all types, class 5, all grades). Two coated panels shall be subjected to twenty-five cycles or to prior failure, whichever comes first, of the following test cycle. The cycle comprises three operations that are carried out in the order specified with panels prepared as specified in 4.5.2:

a. Salt water immersion for 1 week (7 days): Immerse panels totally for 1 week in natural seawater or in ASTM D1141, substitute ocean water, at a temperature of 27±6 ºC (80±10 ºF). There shall be no more than 8 hours between completion of step (a) and the beginning of step (b).

b. Aromatic fuel immersion for 1 week (7 days): Following salt water immersion, immerse the panels totally in MIL-DTL-5624, ASTM D1655, or commercial JP-4, JP-5 at a temperature of 27±6 ºC (80±10ºF). There shall be no more than 8 hours between completion of step (b) and the beginning of step (c).

c. Hot water immersion for 2 hours: This operation is intended to simulate conditions encountered in the use of tank cleaning equipment. Following fuel immersion, immerse the panels totally in hot, ASTM D1141 synthetic seawater or natural seawater having a salinity of 33 to 35 parts per million chloride, for 2 hours at 80 ºC (175 ºF) (nominal).

Operations (a) to (c) constitute one complete test cycle. This cycle is repeated and coating deterioration recorded after each complete cycle. If coating is still satisfactory after twenty cycles, wipe lightly with a soft cloth and freshwater, allow 48 hours to thoroughly dry, and recoat the upper one third of one side of each panel, masking off the edges, approximately 13 millimeters (0.5 inch), and the bottom portion of the panel with one coat of the system finish coat of the coating system (or primer coat and finish coat if appropriate). Allow a 1-week dry time at ambient laboratory conditions and complete immersion test with five additional test cycles. Test panels shall be inspected at the end of the tenth, twentieth, and twenty-fifth cycles for imperfections (see 3.9.1). On completion of testing, the coating system shall be evaluated for pinhole rusting, adhesion of both the original and recoated surfaces per ASTM D4541 (type II tester), and blistering and surface imperfections larger than 1.5 millimeters (0.0625 inch) in diameter. Type VII coating systems shall be evaluated for edge rusting. The test results shall be in accordance with the requirements of 3.9.1.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

4.5.2.2 Dedicated salt water ballast (all types, class 7, all grades). Two test panels, prepared as specified in 4.5.2, shall be tested in accordance with the following cycle:

a. Salt water immersion for 5 days: Immerse panels completely with panels prepared as specified in 4.5.2 for 1 week in either natural seawater or ASTM D1141, substitute ocean water solution at a temperature of 27±6 ºC (80±10 ºF).

b. Remove panels from test and allow to dry for 2 days.

c. Hot water immersion for 2 hours: This operation is intended to simulate conditions encountered in the use of tank cleaning equipment. Following the drying period, immerse the panels totally in hot freshwater for 2 hours at 80 ºC (175 ºF) (nominal).

Operations (a) to (c) constitute one complete test cycle. This cycle is repeated and coating deterioration recorded after each complete cycle. If coating is still satisfactory after twenty-five cycles, wipe lightly with a soft cloth and freshwater, allow 48 hours to thoroughly dry, and recoat the upper one third of one side of each panel, masking the portion from the edge to 13 millimeters (0.5 inch) inward, with one coat of the finish coat of the coating system (or primer coat and finish coat if appropriate). Allow a 1-week dry time and complete immersion test with twenty-five additional test cycles. Coating system shall be evaluated for pinhole rusting, adhesion of both original and recoated surfaces per ASTM D4541 (type II tester), and blistering and surface imperfections larger than 1.5 millimeters (0.0625 inch) in diameter. Type VII coating systems shall be evaluated for edge rusting. Test results shall be as specified in 3.9.

4.5.2.2.2 Cycle B. DELETED

4.5.2.3 Potable and freshwater immersion (all types, class 9, all grades). Class 9 coatings for use in dedicated potable and freshwater tanks shall be tested to the following cycle with panels prepared as specified in 4.5.2:

a. Immerse two panels totally for 5 days in ASTM D1193 (any type) distilled water, at a temperature of 27±6 ºC (80±10 ºF).

b. Remove panels from test and allow to dry for 2 days.

c. Hot water immersion for 2 hours: This operation is intended to simulate conditions encountered in the use of tank cleaning equipment. Following the drying period (see [b]), immerse the panels totally in ASTM D1193 (any type) distilled water for 2 hours at 80 ºC (175 ºF) (nominal).

Operations (a) to (c) constitute one complete test cycle. This cycle is repeated and coating deterioration recorded after each complete cycle. If the coating is still satisfactory after twenty cycles, wipe lightly with a soft cloth and freshwater, allow 48 hours to thoroughly dry, and recoat the upper one third of one side of each panel, masking the portion from the edge to 13 millimeters (0.5 inch) inward, with one coat of the finish coat of the coating system (or primer coat and finish coat if appropriate). Allow a 1-week dry time and complete immersion test with five additional test cycles. Coating system shall be evaluated for pinhole rusting, adhesion of both original and recoated surfaces, per ASTM D4541 (type II tester), and blistering and surface imperfections larger than 1.5 millimeters (0.0625 inch) in diameter. Type VII coating systems shall be evaluated for edge rusting. Evaluation results shall be as specified in 3.4.7.

4.5.2.4 Resistance to fuel and salt water at 32 ºC (90 ºF) (all types, class 5, all grades). Panels shall be prepared in accordance with 4.5.2 except for size. Two test panels approximately 60 by 120 millimeters (2.5 by 5 inches) shall be immersed in 500 millimeters (2 inches) of either natural seawater or ASTM D1141, substitute ocean water solution covered by 50 millimeters (2 inches) of the fuel specified in 4.5.2.1(b) in a glass jar, closed and sealed. The jar shall be kept at 32±3 ºC (90±5 ºF) by partial immersion in a water bath or other means for 240 hours. The panel shall be removed, immediately examined for any change in appearance, chalking or color change, film failure such as blistering and rusting, loss of apparent hardness and adhesion of the coating, and edge rusting by visual observation and FED-STD-141, method 6304.2 (knife used may be sharp commercial pocket knife). Panels shall be in accordance with the requirements of 3.14.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

4.5.3 Recoatability (except types VIII and VIIIa). Recoatability for qualification of the coating system shall be determined as specified in 4.5.2.1, 4.5.2.2, 4.5.2.3, 4.5.13, 4.5.14, and 4.5.17. Recoatability shall be in accordance as specified in 3.4.7, 3.9.1, 3.9.2, 3.15, 3.16, and 3.17.

4.5.3.1 Recoatability (types VIII and VIIIa). Recoatability of the type VIII and VIIIa powder coatings shall be demonstrated using the three-coat MIL-DTL-24441/29, type III and the two-coat MIL-DTL-24441/35, type IV systems. Recoatability shall be as specified in 3.9.1, 3.9.2, 3.15, 3.16, and 3.17.

4.5.4 Test for aviation (JP-5) fuel and gasoline (aviation gasoline) compatibility (class 5 only). The effect of coating systems on fuel degradation shall be measured by comparison of test results obtained on fuel in contact with the coating system and the same age unexposed fuel.

4.5.4.1 Preparation for fuel samples for test.

a. Apply coating system to four steel rods, 19 by 190 millimeters (0.75 by 7.5 inches), drilled, threaded, and fitted with a 3- by 19-millimeter (0.125- by 0.75-inch) all-thread bolt for suspension. Allow 7 days drying time at ambient laboratory temperature after application of last coat before immersion in fuel.

b. Prepare approximately 5 liters each of particle-free aviation gas and JP-5 fuel by repeated filtration through a type AA millipore filter as specified in ASTM and Other Specifications and Classifications for Petroleum Products and Lubricants: Fuels and Oils, Bituminous Materials, Solvents, using 100/130 aviation gas in accordance with ASTM D910 or commercial 100LL aviation gasoline, and JP-5 fuel in accordance with MIL-DTL-5624.

c. Wash coated test rods thoroughly with hot water at 82±6 ºC (180±10 ºF) for 15 to 30 minutes, drain, and dry. Mount test rod on a 6- by 180-millimeter (0.25- by 7-inch) square plastic beaker cover (for a 4-liter beaker), center drilled for mounting test rod.

d. Into four clean 2-liter beakers, pour 1,000 to 2,000 milliliters of particle-free aviation gasoline. Into four clean 2-liter beakers, pour 1,000 to 2,000 milliliters of particle-free JP-5 fuel. Cover two beakers of each fuel with rod-mounted cover (for exposed fuel samples). Cover two beakers of each fuel with 6 by 180 millimeters (0.25 by 7 inches) square plastic beaker covers, plain (for unexposed fuel samples). Store all beakers with fuel in the dark and maintain at 27±6 ºC (80±10 ºF) for 30 days. Swirl fuel by rotating beakers at least three times daily.

e. On the 31st exposure day, test the exposed and unexposed aviation and JP-5 fuel for color, corrosion, existent gum, and solids. Test the exposed and unexposed aviation gas for bromine as specified in the following test procedures.

4.5.4.2 Fuel color (class 5 only). Color for JP-5 fuel shall be determined in accordance with ASTM D156. Record the difference between exposed and unexposed fuels. Colors of exposed and unexposed aviation gas shall be compared visually. Record the difference as pass or fail. Fuel color shall be as specified in 3.13.1.

4.5.4.3 Corrosion (class 5 only). Corrosiveness of both exposed and unexposed fuels shall be determined in accordance with ASTM D130. Corrosiveness shall be as specified in 3.13.2.

4.5.4.4 Existent gum (class 5 only). Existent gum (both washed and unwashed) shall be determined in accordance with ASTM D381. Determine the difference between exposed and unexposed fuels. Existent gum shall be as specified in 3.13.3.

4.5.4.5 Solids (total sediment) (class 5 only). Solids shall be determined in accordance with ASTM D910. Solids shall be as specified in 3.13.4.

4.5.4.6 Bromine (class 5 only). Bromine shall be determined on both exposed and unexposed fuels in accordance with the following procedures:



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

4.5.4.6.1 Apparatus.

4.5.4.6.1.1 Decomposition. The apparatus used for decomposition of bromides by sodium in liquid ammonia shall be as shown on figure 1. The center neck of the 250-milliliter, 2-neck, round bottom flask carries a polytetrafluoroethylene sealed, corrosion resistant, steel stirring assembly. The side neck shall be fitted with a two-hole rubber stopper through which pass an ammonia delivery tube and a vent protected by a drying tube containing laboratory-grade, color indicating desiccant. After charging the flask with liquid ammonia, the pictured rubber stopper shall be replaced with a 1-hole stopper fitted with a vent tube, also protected by a drying tube.

4.5.4.6.1.2 Titration. The apparatus used for following the titration of bromide shall be a continuous indicating hydrogen ion concentration (pH) meter equipped with a glass electrode and a silver electrode (see 4.5.4.6.3[c]). A titration set-up shall be used, such as shown on figure 2, which shall accurately deliver slip-drop quantities of silver nitrate.

4.5.4.6.2 Materials and reagents. The following materials and reagents shall be required:

a. Dry ice and acetone for cooling
b. Laboratory-grade, color indicating desiccant
c. Ammonia
d. Sodium
e. Alcohol
f. Sodium hydroxide pellets
g. Ammonium persulfate
h. Sodium arsenite, 10 percent
i. Nitric acid ($HNO_3$) approximately 20 percent
j. Silver nitrate ($AgNO_3$), 0.05N

4.5.4.6.3 Procedure for the analysis of gasolines. The procedure for the analysis of decomposition of bromides shall be as follows:

a. Cool the flask with a dry-ice, acetone slurry, and introduce 15 grams of ammonia (see note 2). Replace the rubber stopper carrying the delivery tube by the one fitted only with a protected vent. Add a cube of freshly cut sodium, having an edge dimension of 5 millimeters (0.25 inch). Rotate the stirrer slowly by hand to partially dissolve the metal. Add exactly 50 milliliters of the gasoline under test (see notes 3 and 4), remove the cooling bath, and start the stirrer. As soon as the ammonia starts to evolve, disconnect the drying tube from the vent (see note 5). Continue the stirring until the ammonia has evaporated (about 20 minutes for a 15-gram charge). If the characteristic blue color of sodium in liquid ammonia should disappear during the earlier stages of the evaporation, add another piece of sodium.

b. Upon evaporation of the ammonia, add 5 milliliters of alcohol to the mixture to decompose the excess sodium. Next, add 30 milliliters of water and stir to aid in the extraction of inorganic salts. Remove the reaction flask from the stirrer, wash down the stirrer with water, and transfer the contents to a separatory funnel. Separate the aqueous layer and extract the organic layer with two additional 30-milliliter portions of water. Combine the three aqueous extracts, evaporate to 50 milliliters, and cool slightly. If, at this point, the mixture is not clear and contains a precipitate, filter and wash the paper several times with small portions of hot water. Evaporate the combined filtrate and washings to 50 milliliters and cool slightly. Add 2 grams of sodium hydroxide pellets, followed by 2 grams of ammonium persulfate. After the solids have dissolved, boil the solution for 15 minutes (see notes 6 and 7). Cool the solution slightly, add 10 milliliters of a 10 percent solution of sodium arsenite, boil for 10 minutes, and cool to room temperature. Make the solution acid to phenolphthalein by adding $HNO_3$ (20 percent) and determine the bromides as given below (see note 8).



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

c. Immerse the titration electrodes into the solution, start the stirrer, and set the pH meter to indicate readings on the acid scale. If the pH meter shows an apparent pH reading of greater than 1.5, add more $HNO_3$, until a reading of 0 to 1.5 is obtained. Next, titrate the bromides with 0.05N $AgNO_3$, making a record of apparent pH versus milliliter $AgNO_3$ added. From a plot of the record of the data, determine the appropriate inflection points, and calculate the quantities of bromine using the formulas below.

g Br = 0.003996B

Or

g Br/gal at 15.6 ºC (60 ºF) $= 0.3025B(1+0.00065(t_F-60))$

$= 0.3025B(1+0.00065(1.8\ t_C-281))$

Where:

B = mL 0.05N $AgNO_3$ required to titrate bromide, and

$t_F$ = temperature (ºF) of gasoline when sampled

$t_C$ = temperature (ºC) of gasoline when sampled

Bromine shall be as specified in 3.13.5.

NOTES:

1. A heavy-gauge silver wire attached directly to the calomel jack of the pH meter may be used. The portion that dips into the liquid shall be cleaned by rubbing lightly with fine emery paper and rinsing with ASTM D1193 (any type) distilled water.
2. Use a lecture bottle as the source of ammonia. From such a container, gaseous ammonia may be introduced into the flask with virtually complete condensation at rates up to 2 grams per minute. The quantity of ammonia being added can be followed by periodic weighing of the lecture bottle. Steps involving the charging and evaporation of ammonia should be carried out in a hood.
3. Pre-cool the sample by placing it in a flask surrounded by dry ice before introducing it into the sodium liquid ammonia mixture. In such cases, care should be taken to protect the sample from moisture and dissolving carbon dioxide. After adding a pre-cooled sample to the reaction mixture, rinse the cooling vessel with 10 milliliters of room temperature isooctane. This rinsing may be added directly to the reaction mixture.
4. By using a slightly larger amount of ammonia (about 20 grams), pre-cooling is not necessary. Under these conditions, a 50-milliliter sample of gasoline (at room temperature) may be added directly to the reaction mixture without causing excessive boiling of the ammonia, provided the addition is as slow as from a pipette.
5. If indicating Drierite or equal is used, evolution of ammonia is evidenced by a color change.
6. During this period, it is important that the solution remain alkaline. Since sulfuric acid is one of the decomposition products of ammonium persulfate, the solution should be checked occasionally to assure alkalinity. This is done by using either litmus paper as an external indicator or methyl orange as an internal indicator. In the majority of cases, the 2 grams of sodium hydroxide specified will be entirely sufficient. However, if the solution is becoming acidic, more sodium hydroxide should be used.
7. In some cases, a reddish solid or a dark solution may form during the oxidation step. Such behavior shall not affect the analyses.
8. At this point, the solution may contain a precipitate. This is of no consequence, and the precipitate will usually redissolve on further acidification in the next step.

4.5.5 VOC content. VOC content for all types, classes, and grades shall be determined in accordance with 40 CFR 60 ch.1, part 60, appendix A, method 24. Solvent content shall be as specified in 3.2.2.2.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

4.5.6 HAP content of coatings. Hazardous solvent content of each individual coating shall be determined in accordance with 40 CFR 63 appendix A (EPA) method 311 and ASTM E260. Solvent fractions shall be identified in accordance with ASTM E1252 with the results recorded as percent by weight of the total paint. Alternate methods of analysis must be reviewed and approved by NAVSEA. Formulation data may be used by manufacturers in lieu of testing to demonstrate compliance with HAP requirements of this specification. The manufacturer's formulation data must have a consistent and quantitatively known relationship to the testing required. Calculation of individual HAP content can be based on either the manufacturer's evaluation of batches or the supplier's data for raw materials used in the product. HAP content shall be specified in 3.2.2.3.

4.5.7 Brushing and rolling properties (not applicable to types VIII or VIIIa). Coatings shall be prepared in accordance with manufacturer's directions. Coatings shall be applied without further reduction in accordance with FED-STD-141, method 4321.2, for brushing and ASTM D5150 for rolling. For routine testing, ambient conditions above 21 ºC (70 ºF) and 50 percent relative humidity shall be satisfactory. For referee tests, Federal Test Method Standard No.141, section 9 shall prevail. For reduced temperature coating systems, brushability, and rolling properties shall be performed with mixed coating, components, and equipment equilibrated at the lower end of the temperature range. The actual brushing can be performed at ambient laboratory conditions so long as the paint and equipment are at the low range application temperature. Brushing and rolling properties shall be as specified in 3.8.

4.5.8 Spraying properties. The coating shall be prepared in accordance with the manufacturer's directions. Without further reduction, spray a coating on an abrasive blasted steel panel to the recommended wet film thickness. For routine testing, ambient conditions above 21 ºC (70 ºF) and 50 percent relative humidity shall be satisfactory. For referee tests, 21±3 ºC (70±5 ºF) and 50±5 percent relative humidity shall prevail. For reduced temperature coating systems, sprayability shall be performed with mixed coating, components, and equipment equilibrated at the lower end of the temperature range. The actual spraying can be performed at ambient laboratory conditions so long as the paint and all equipment are at the low range application temperature. The equilibration requirement for mixed paint does not apply to spraying using spray equipment that mixes the components at the gun, either internally or externally; however, coating components and all equipment shall be at the low range application temperature. Observe for spraying properties in accordance with FED-STD-141, method 4331.2. Spraying properties shall be as specified in 3.8. Type VIII and VIIIa powder coating shall be applied in accordance with manufacturer's instructions to meet 3.8.

4.5.9 Edge coverage retention (applicable to topcoat only of type VII, all classes, all grades). Panel preparation, paint application and percent of dry film thickness retained on an edge shall be as described in appendix A of this specification. Scaled photomicrographs of each edge shall be taken. This test procedure will be conducted at government expense at the Naval Research Laboratory, Key West, Florida. Coating shall meet 3.8.1.

4.5.10 Hazardous pigments and additives. Soluble and total metal content, except tantalum and tungsten, shall be determined on pulverized dry paint film of the coating system in accordance with 40 CFR 261, appendix II and the appropriate test listed below in table VI and VII. Test sample shall consist of particle sieved through a U.S. sieve no. 50. Asbestos shall be analyzed in accordance with OSHA Validated Analytical Method ID-191, with the coating sample treated as a bulk settled dust and test result reported as percent by weight of the cured coating. Crystalline silica (respirable) shall be analyzed in accordance with NIOSH Analytical Method 7500 with the coating sample treated as a bulk settled dust. Soluble metal content shall be reported as milligrams per liter. Total metal content shall be reported as percent by weight of the cured coating. The test results for each metal shall be in conformance with the appropriate requirements of 3.2.3.1. Tantalum and tungsten soluble metal content and total metal content shall be analyzed as specified in 4.5.10.1. Calculation of individual hazardous metal contents can be based on either the manufacturer's testing of batches, or the supplier's data for raw materials used in the product. The coating manufacturer must provide for each individual hazardous metal a formulation value that will not be exceeded if a sample from any quality control approved production batch of the coating is tested in accordance with this paragraph. Type VIIIa may have a high zinc content due to the presence of sacrificial zinc.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE VI. Test methods for evaluating solid waste - physical/chemical methods, EPA SW-846.

| Metal/material | Digestion test method |
|---|---|
| All metals, except chromium (VI) | 3050 |
| Chromium (VI) | 3060 |
| Antimony | 7040 or 7041 |
| Arsenic | 7060 or 7061 |
| Barium | 7080 or 7081 |
| Cadmium | 7131 |
| Total chromium | 7190 |
| Chromium (VI) | 7195, 7196, or 7197 |
| Lead | 7421 |
| Mercury | 7470 or 7471 |
| Nickel | 7520 or 7521 |
| Selenium | 7740 or 7741 |
| Silver | 7760 or 7761 |

TABLE VII. Methods for chemical analysis of water and waste, EPA 600/4-79/020.

| Metal/material | Test method |
|---|---|
| Beryllium | 210.1 or 210.2 |
| Cobalt | 219.1 or 219.2 |
| Copper | 220.1 or 220.2 |
| Fluoride | 340.1, 340.2, or 340.3 |
| Molybdenum | 246.1 or 246.2 |
| Thallium | 279.1 or 279.2 |
| Vanadium | 286.1 or 286.2 |
| Zinc | 289.1 or 289.2 |

4.5.10.1 Tantalum and tungsten content. The tantalum and tungsten content of the cured film shall be determined using any appropriate spectroscopy test method. Conduct the tests in accordance with the instrument manufacturer's directions for the use of the instrument. The manufacturer is responsible for establishing data supporting the test method choice and analytical accuracy. The test results for tantalum or tungsten shall be in conformance with the requirements of 3.2.3.1.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

4.5.11 Potable water tests (class 9).

a. Test sample preparation.

(1) Using an adjustable gap clearance film applicator ("doctor blade"), draw down a 305 millimeter (12-inch) wide by 408-millimeter (16-inch) long wet film of the first coat (primer) of the coating system on a flat thick polyethylene sheet (at least 0.5 inch). The coating shall be prepared (mixed) in accordance with manufacturer's instructions and the wet film thickness shall be the same as the manufacturer's recommended wet film thickness. Air dry this draw-down for 24 hours at 20 to 27 ºC (68 to 81 ºF).

(2) After the air dry of the first coat has been accomplished, using an adjustable gap clearance film applicator ("doctor blade"), draw down a 305-millimeter (12-inch) wide by 408-millimeter (16-inch) long wet film of the second coat (intermediate or topcoat, as applicable) of the coating system perpendicular to and across the dry first coat. The coating shall be prepared (mixed) in accordance with manufacturer's instructions, and the wet film thickness shall be the same as the manufacturer's recommended wet film thickness. Air dry this draw-down for 24 hours at 20 to 27 ºC (68 to 81 ºF).

(3) Repeat the procedure in (2) above for each additional coating in the coating system.

(4) Allow the completed test sample to cure for 7 days at 20 to 27 ºC (68 to 81 ºF) after the application of the final coating.

b. Bell jar preparation. Attach a bell jar of 500-milliliter capacity to the coated surface prepared in (a) above with molten paraffin wax. The bell jar shall be fitted with a tightly fitting stopper to prevent loss of volatile halogen reactants during testing.

4.5.11.1 Color in water (class 9). Prepare for test as specified in 4.5.11. Fill the bell jar with 200 parts per million chlorinated ASTM D1193 (any type) distilled water and age for 24 hours. Remove the chlorinated water by suction and rinse the bell jar twice with ASTM D1193 (any type) distilled water. Discard the 200 parts per million and rinse water. Prepare a solution of 0.2 parts per million chlorinated ASTM D1193 (any type) distilled water and determine the exact chlorine concentration using the DPD colorimetric method of APHA 4500Cl-F. Refill the bell jar with determined 0.2 parts per million chlorinated distilled water solution. Age the 0.2 parts per million chlorinated water solution for 24 hours in the bell jar at 20 to 27 ºC (68 to 81 ºF). Also retain and age the 200 milliliters of the 0.2 parts per million chlorinated water solution (control) in a clean, sealed glass container at 20 to 27 ºC (68 to 81 ºF). Withdraw 100 milliliters of water from both the bell jar and the control and determine the color of the water in the bell jar and the retained control water using APHA 2120B. Correct the bell jar color value for any change in the control color by subtracting the color change value of the control from the color change value of the bell jar water. Color value shall be in accordance with the requirements of 3.4.2.

4.5.11.2 Taste in water (class 9). To assure taster safety, the taste test shall be performed only after a coating system has been found to comply with all other requirements of this specification. The remaining chlorinated water in the bell jar in 4.5.11.1 shall be used for the taste in water test specified in APHA 2150B. The remaining water shall be withdrawn from the bell jar by suction and placed in a clean glass container and tightly sealed. The sealed container of chlorinated water shall be equilibrated to 40 ºC (104 ºF) in a water bath. Threshold taste values shall be in accordance with the requirements of 3.4.3.

4.5.11.3 Odor in water (class 9). After the chlorinated water has been removed from the bell jar (4.5.11.1) for the taste in water test (4.5.11.2), rinse the bell jar twice with ASTM D1193 (any type) distilled water. Prepare a solution of 0.2 parts per million chlorinated distilled water and determine the exact chlorine concentration using the DPD colorimetric method of APHA 4500Cl-F. Refill the bell jar with determined 0.2 parts per million chlorinated distilled water solution. Age the 0.2 parts per million water solution for 24 hours in the bell jar at 20 to 27 ºC (68 to 81 ºF). Conduct the odor in water test in accordance with APHA 2160B. The water bath temperature for this test shall be equilibrated to 40 ºC (104 ºF). Threshold odor values shall be in accordance with the requirements of 3.4.4.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

4.5.11.4 Chlorine residual (class 9). Prepare for test as specified in 4.5.11. Fill the bell jar with 200 parts per million chlorinated ASTM D1193 (any type) distilled water and age for 24 hours. Remove the chlorinated water by suction and rinse the bell jar twice with ASTM D1193 (any type) distilled water. Discard the 200 parts per million and rinse waters. Prepare a solution of 10 parts per million chlorinated ASTM D1193 (any type) distilled water and determine the exact chlorine concentration using the DPD colorimetric method of APHA 4500Cl-F. Refill the bell jar with determined 10 parts per million chlorinated distilled water solution. Age the 10 parts per million chlorinated water solution for 24 hours in the bell jar at 20 to 27 ºC (68 to 81 ºF). Also retain and age the 200 milliliters of the 10 parts per million chlorinated water solution (control) in a clean, sealed glass container at 20 to 27ºC (68 to 81 ºF). Determine the exact chlorine concentration of the water in the bell jar and the retained control water using the DPD colorimetric method of APHA 5530D. Correct the bell jar chlorine value for any loss in the control by subtracting the loss in chlorine parts per million of the control from the loss of chlorine content in the bell jar water. Chlorine residual value shall be in accordance with the requirements of 3.4.5.

4.5.11.5 Phenol leaching (class 9). After 4.5.11.4 testing is completed, remove coating from the polyethylene surface. (Note: Alternate method if coating cannot be removed from polyethylene surface, cast free films of each coating of the coating system. Cure at ambient laboratory conditions for 7 days.) Pulverize the coating film sample. (Note: If using alternate method, use equal weights of each coating of the coating system.) Sieve pulverized particles through a U.S. sieve number 50. A 1-gram (nominal) sample of the sieved material shall be placed on a paper thimble and lowered into a Soxhlet extractor. The 500-milliliter flask in this assembly shall be filled with 300 milliliters of ASTM D1193 (any type) distilled water and several boiling chips. The sample shall be refluxed until at least four complete siphonings of the sample chamber has occurred (several hours). Pour off the liquid into a tightly sealed, clean glass flask for phenolic concentration testing. Determine phenolic compound concentration as specified in APHA 5530C or APHA 5530D. Phenolic compound concentration for each coating of the coating system shall be as specified in the requirements of 3.4.6.

4.5.12 Resistance to hot water - simulated boiler feedwater (all types, class 11, all grades). Class 11 panels shall be prepared in accordance with 4.5.2. Test panels shall be immersed to 150 millimeters (6 inches) of the 300-millimeter (12-inch length in 82 ºC (180 ºF) distilled water in a beaker for 500 hours or to prior failure. The panel shall be removed, immediately examined. The extent, nature, and time of failure shall be reported in accordance with the requirements of 3.15.

4.5.13 Resistance to chemical solutions - simulated collection, holding, and transfer tanks (CHT; sewage waste) (all types, class 13, all grades). Paint system test panels shall be prepared as specified in 4.5.2. Test panels shall be tested to the following cycle:

a. Immerse test panels in a solution consisting of Acetic acid in ASTM D1141 substitute or natural ocean water (solution I) adjusted to a pH of 3.8 to 4.0 for 14 days at a temperature of 21±2.7 ºC (70±5 ºF).

b. Remove from solution I and immerse panels in a solution consisting of 10 parts concentrated ammonium hydroxide in 90 parts ASTM D1141 substitute or natural ocean water (solution II) for 14 days at a temperature of 21±2.7 ºC (70±5 ºF).

c. Remove from solution II and immerse panels in a solution consisting of 7 parts concentrated sulfuric acid in 93 parts ASTM D1141 substitute or natural ocean water (solution III) for 14 days at a temperature of 21±2.7 ºC (70±5 ºF).

d. Remove from solution III and immerse panels in a solution consisting of 10 parts Urea in 90 parts ASTM D1141 substitute or natural ocean water (solution IV) for 14 days at a temperature of 21±2.7 ºC (70±5 ºF).

e. Remove from solution IV and immerse panels in 2 parts detergent (commercial solid dishwasher detergent) and 98 parts ASTM D1141 substitute or natural ocean water (solution V) for 14 days at a temperature of 21±2.7 ºC (70±5 ºF).

Operations (a) to (e) constitute one complete test cycle (70 days). This cycle is repeated for a total test time of 140 days (20 weeks) and coating deterioration reported after each complete cycle. Care shall be taken not to contaminate solutions with carry-over of solution between immersions. Panels may be rinsed if desired. Solutions shall be tested, refreshed, or replaced as necessary to maintain solution composition. Coating system shall be evaluated for pinhole corrosion, ASTM D4541, type II tester, adhesion of the original surfaces, ASTM D4541, type II tester, adhesion of both original and recoated surfaces, blistering, and surface imperfections larger than 1.5 millimeters (0.0625 inch) in diameter. Coating systems shall be evaluated for edge rusting. Coating performance shall be as specified in 3.16 (see also 6.1.1.3).



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

4.5.14 Resistance to condensing water - simulated tank top test (all types, all classes, all grades). Panels shall be prepared as specified in 4.5.2. Expose test panels in a condensing cabinet as specified in ASTM D4585 for 2000 hours at 38 ºC (100 ºF). Coating system shall be evaluated for pinhole corrosion, ASTM D4541, type II tester, adhesion of both original and recoated surfaces, blistering and surface imperfections larger than 1.5 millimeters (0.0625 inch) in diameter. Coating systems shall be evaluated for edge rusting. Test results shall be as specified in 3.17.

4.5.15 Ultraviolet fluorescence (applicable to primers of all types, all classes, all grades). Mix primer in accordance with the manufacturer's data sheet. Apply primer to any convenient substrate. Cure hard. In a darkened room, use a 365-nanometer ultraviolet black light, to illuminate the primer. Determine if primer fluoresces uniformly and is sufficiently bright to easily ascertain presence of primer on all coated portions of substrate. Result shall be in accordance with the requirements of 3.18.

4.5.16 Cathodic protection compatibility. Two steel panels shall be prepared as specified in 4.5.2 and electrically connected to a commercial magnesium anode conforming to ASTM G8 and shall have a 0.25-inch (nominal) hole drilled through the coating to the metal at the center of the test panel. The electrical resistance between a point on the surface of the anode and the metal in the drilled hole of the test panel shall be less than 0.01 ohms, when checked with an ohm meter. Connecting points on the test panel shall be coated with an epoxy compound for insulation. The test panel shall be installed in a modified ASTM G8 test in such a manner as to separate the test panel from the magnesium anode by 2 feet (nominal) for a period of 3 months. At the completion of the 3-month test, inspect each test panel for peeling, flaking, blistering, dissolving, or other failure. Lifting, peeling, or undercutting around the drilled hole shall be measured. Test results shall be in accordance with the requirements of 3.5.

4.5.17 Surface tolerant coating systems (class 15) (not applicable to types VIII or VIIIa). Establish a uniform rusted condition over the entire surface of six steel panels (150 by 300 by 3 millimeters [6 by 12 by 0.125 inch]) by exposure for 300 hours in an ASTM B117 test apparatus. Surface preparation and paint application shall be as follows:

a. The first pair of panels shall be painted with the coating system applied to one panel in the clean, dry, SSPC-SP 15 condition and one panel in the SP 15 condition, but covered with a uniform film of oil similar to 10W40 motor oil. The film of oil shall be established by wiping an oil-soaked rag over the panel until a uniform film is established. There shall be no "pooling" of oil on the surface. Paint the oily panel in accordance with the manufacturer's instructions and cure in accordance with the manufacturer's instructions, but for a minimum of 7 days. Both panels shall be immersed per the requirements of 4.5.2.2 for ten cycles. At the end of the ten cycles, remove the panels from immersion, dry for 48 hours and determine compliance with 3.19. Test for adhesion by ASTM D4541, type II tester.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

b. The second pair of panels shall be painted with the coating system applied to one panel in the clean, dry, SSPC-SP-15 condition and one panel in the SP 15 condition, but covered with a uniform film of water. The film of water shall be established by wiping a seawater-soaked rag over the panel until a uniform film is established. There shall be no "pooling" of water on the surface. Paint the wet panel in accordance with the manufacturer's instructions and cure in accordance with the manufacturer's instructions, but for a minimum of 7 days. Both panels shall be immersed per the requirements of 4.5.2.2 for ten cycles. At the end of the ten cycles, remove the panels from immersion, dry for 48 hours and determine compliance with 3.19. Test for adhesion by Method ASTM D4541, type II tester.

c. The third pair of panels shall be painted with the coating system applied to one clean, dry panel prepared in accordance with SSPC-SP 2, and one panel prepared in accordance with SSPC-SP 2 but do the surface preparation of the second panel underwater (seawater). Paint the first panel in the dry condition and paint the second panel underwater in accordance with the manufacturer's instructions, and cure the second panel underwater in accordance with the manufacturer's instructions. Immerse both panels in seawater for 6 months, remove the panels, dry for 48 hours, and determine compliance with 3.19. Test for adhesion by Method ASTM D4541, type II tester.

4.5.18 Bilge coating systems (class 17). Bilge coating systems shall be tested in accordance with the following test sequence:

a. Paint and cure two steel test panels (150 by 300 by 3 millimeters [6 by 12 by 0.125 inch]) with one coat of Navy Formula 150 (type IV) and one coat of Navy Formula 156 (type IV). Observe the dry through times of MIL DTL-24441. Scribe one panel to the metal substrate with an "X" and expose both panels for 300 hours in an ASTM B117 test apparatus.

b. For one panel, remove all previously applied coatings (and corrosion products) at the "X" scribe mark by power tool cleaning to bare metal to achieve a SSPC-SP 11 surface and feather the interface edges between the bare metal and intact paint. Create an area of at least 12 square inches. This is intended to simulate repair of a damaged area in a bilge coating.

c. For the remaining panel, clean, degrease, remove any rust spots, lightly abrade with 100-grit sandpaper to break any remaining gloss, and finally solvent clean the panel. Again, create a test area of at least 12 square inches.

d. Apply to the prepared areas of the test panels the proposed bilge coating in the number of coats and with the procedure recommended by the coating manufacturer.

e. Reimmerse the two panels thus prepared into the desired test medium for twelve test cycles or until prior failure.

f. Following the twelve test cycles, remove the two panels from the immersion test, and examine for compliance with 3.20. Bilge coating systems exhibiting delamination, blisters larger than 1.5 millimeters, rust breakthrough, or any other coating failure compromising the substrate shall be considered a failure.

4.5.19 Single coat systems. Class X/18 single coat systems shall be tested to the respective service requirements of service class 5, 7, 9, 11, 13, 17, and 19 as requested in the manufacturer's application for qualification testing. The difference shall be in the number of coats in the coating system applied to the panels. A single coat of the coating system shall be applied to the panels and the panels shall then be tested in accordance with the class applicable tests specified in table V.

4.5.20 Well deck overhead coating systems (class 19). The evaluation procedure for well deck overhead coating systems shall consist of the following steps:

a. Two panels prepared as specified in 4.5.2 shall be coated with the well deck overhead coating system and cured for 30 days at an outdoor exposure site where the minimum ambient daytime temperature is 21 ºC (70 ºF) and minimum relative humidity is 50 percent.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

b. Each panel shall be exposed to a burn test where the panel is mounted at a 45-degree angle and a butane torch (or equal) heats the panel backside, which is uncoated. Temperature is measured on the bare uncoated backside (at the flame contact point) and on the front in the same general area as the flame contact on the back. The temperature at which the coating ignites is recorded. At that time the torch is removed, and the coating is allowed to burn out. The time and temperature when the coating self-extinguishes is recorded.

c. The heating sequence shall be for two hours at each of the temperatures in 10 ºC (50 ºF) increments from 66ºC (150 ºF) to 260 ºC (500 ºF) inclusive.

d. Adhesion values in pounds per square inch shall be determined and recorded before and after the heat resistance test.

e. Check for compliance with 3.23.

4.5.21 Service test. NAVSEA will coordinate application of class 7 and class 19 coatings based upon available Navy personnel to observe application and ship availabilities. Test coatings must be applied in accordance with current published Navy process instructions and any unique manufacturer's instructions. After one year of service, arrange for Navy inspection and check for compliance with 3.24.

4.6 Toxicity. A Health Hazard Assessment (HHA) will be conducted to ensure conformance to 3.11 as required by the qualifying activity. The Navy and Marine Corps Public Health Center (NMCPHC) will evaluate the coating system using data provided by the manufacturer/distributor to the NMCPHC (see 3.11 and 6.7).

## 5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When actual packaging of materiel is to be performed by DoD or in-house personnel, these personnel need to contact the responsible packaging activity to ascertain requisite packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

## 6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. Although the different types of coating systems of this specification afford superior protection for various shipboard tanks, structures, and similar ship applications, the coating systems are not necessarily interchangeable or of equal merit for all kinds of tanks, structures, and conditions of application. Classes 17a and 17b are for use as appropriate in either depot-level or organizational-level maintenance painting. Types VIII and VIIIa are powder coatings intended for use in severe marine service such as immersion and wet space application.

6.1.1 Coating selection.

6.1.1.1 Types V, VI, VII, VIII, and VIIIa. Type V coatings are acceptable for use where environmental regulations limit VOC of organic coatings to a maximum of 340 grams of solvent per liter of coating. Type VI coatings have VOCs less than 250 grams per liter and type VII coatings have VOCs of less than 150 grams per liter. Types V, VI, VII, and VIII dried coating residues are non-hazardous waste under USEPA regulations in effect on the date of this specification. All types contain less lead, chromium, cadmium, asbestos, and other hazardous ingredients than OSHA regulations allow or restrict in effect on the date of this specification.

6.1.1.2 Proprietary products. Depending on local application conditions, the acquisition guidance in 6.2 may also apply to selection of specific proprietary products within each type, class, and grade.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

6.1.1.3 Alternate test for resistance to chemical solutions. In addition to the test procedure of 4.5.13, coating systems proposed for qualification to class 13 of this specification may be tested to the following protocol:

a. through e. as currently specified.

f. Fourteen-day immersion in 10 percent fatty acid, 90 percent seawater.

g. Fourteen-day immersion in 50 percent fatty acid, 50 percent seawater.

h. Fourteen-day immersion in 100 percent fatty acid.

This alternate immersion resistance will not be required for qualification to this revision of this specification, but may be required by subsequent amendments or revisions. Data generated by Navy testing to this alternate requirement will be made available to manufacturers, for information purposes, who submit coating systems for qualification to 3.16. This alternate testing will not affect current qualifications.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Type, class, and grade required (see 1.2).

c. Toxicity requirements (see 3.11 and 6.4).

d. Packaging and labeling requirements (see 5.1 and 6.8). (Attention is directed to regulatory and safety requirements for labels.)

6.2.1 Acquisition guidance. Coatings in accordance with this specification vary to some extent in surface preparation required, and the effect of high humidity, slight surface moisture, and temperature during applications. Requirements for specific products can be found in contractor's instructions. Many factors affect the total overall cost per square foot per year for tank applications, possibly the least of which is the cost of the coating systems which average about 10 percent of the total cost. The number of coats per coating system and square foot coverage per liter, per gallon, or per pound further complicate the equity of purchase solely on the basis of lowest cost per liter or cost per gallon. Contracting officers should therefore fully consider such factors.

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Products List QPL no. 23236 whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or purchase orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Commander, Naval Sea Systems Command, ATTN: SEA 05S, 1333 Isaac Hull Avenue, SE, Stop 5160, Washington Navy Yard DC 20376-5160 or emailed to CommandStandards@navy.mil. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://assist.dla.mil.

6.4 Safety data sheets. The contracting activity should be given SDS at the time of contract award. The SDS should be provided in accordance with FED-STD-313 and ANSI Z400.1. Contracting officers should identify those activities requiring copies of completed SDS prepared as specified in FED-STD-313. Additional required government information is contained in FED-STD-313. In order to obtain the SDS, federal acquisition regulation clause 52.223-3 must be in the contract (see 6.2).

6.5 Comparability. This specification and amendment supersede MIL-P-23236(SHIPS), DOD-P-23236A(SH), MIL-P-23236B(SH) and MIL-PRF-23236C and the comparability of types and classes is shown in table VIII.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE VIII. Comparability data.

| Coating | MIL-P-23236(SH) | DOD-P-23236A(SH) | MIL-P-23236B(SH) | MIL-PRF-23236C(SH) |
|---|---|---|---|---|
| Type I | X | X | X | DELETED |
| Type II | X | DELETED | DELETED | DELETED |
| Type III | --- | X | X | DELETED |
| Type IIIa | --- | X | DELETED | DELETED |
| Type IIIb | --- | X | DELETED | DELETED |
| Type IV | --- | --- | X | DELETED |
| Type V | --- | --- | --- | X |
| Type VI | --- | --- | --- | X |
| Type VII | --- | --- | --- | X |
| Type VIII | --- | --- | --- | X |
| Type VIIIa | --- | --- | --- | X |
| Class 1 | X | X | X | DELETED |
| Class 2 | X | DELETED | X | DELETED |
| Class 3 | X | DELETED | DELETED | DELETED |
| Class 4 | X | DELETED | DELETED | DELETED |
| Class 5 | --- | --- | --- | X |
| Class 6 | --- | --- | --- | X |
| Class 7 | --- | --- | --- | X |
| Class 8 | --- | --- | --- | X |
| Class 9 | --- | --- | --- | X |
| Class 10 | --- | --- | --- | X |
| Class 11 | --- | --- | --- | X |
| Class 12 | --- | --- | --- | X |
| Class 13 | --- | --- | --- | X |
| Class 14 | --- | --- | --- | X |
| Class 15 | --- | --- | --- | DELETED |
| Class 16 | --- | --- | --- | DELETED |
| Grade A | --- | --- | X | X |
| Grade B | --- | --- | --- | X |
| Grade C | --- | --- | --- | X |

6.6 Definitions. Interpretation of the meaning of coating related terms in this specification are to be consistent with the Coatings Encyclopedic Dictionary, Federation of Societies for Coating Technology, 492 Norristown Road, Blue Bell, PA 19422-2350. A limited number of definitions are given below.

6.6.1 Coating components (except types VIII and VIIIa). Coating components are individually packaged components such as base component (part A) and converter component or hardener (part B).

6.6.2 Coating. A coating is the resin component (base) and converter mixed and ready for application.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

6.6.3 Coat. A coat is a single application of the coating which may be composed of multiple passes by application equipment.

6.6.4 Coating system. A coating system is the total number of coats as specified by the manufacturer at the time of qualification testing and at the dry film thickness per coat as specified by the manufacturer at the time of qualification testing.

6.6.5 DELETED

6.6.6 Qualifying activity. The activity that has been given responsibility to develop, implement, and maintain the qualification program as specified in the applicable specification, and authorized by its DepSO to input information into the QPD. NAVSEA 05S may be contacted to determine the appropriate qualifying authority for any given requirement related to equipment and systems of U.S. Navy ships and submarines.

6.7 Toxicity evaluation. The NMCPHC requires sufficient information to permit an HHA of the product. Upon completion of the HHA, a copy will be provided by the NMCPHC to the Government for evaluation. The HHA process is described on the NMCPHC's website, https://www.med.navy.mil/Navy-Marine-Corps-Public-Health-Center/.

6.8 Packaging recommendations. Suggested packaging requirements are contained on table IX (see 6.2).



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE IX. Packaging.

| Packaging | Recommended requirements for direct Government acquisitions |
|---|---|
| Containers (except types VIII and VIIIa) | 1. The components should be specified to be furnished in cans appropriate to kit requirements capable of holding 0.47 liter (1 pint), 0.945 liter (1 quart), 3.78 liters (1 gallon), and 18.9 liters (5 gallons). Kits should consist of two containers, one of which should be large enough to contain all components for mixing purposes. For class 17b, or other classes as specified in 6.2, the components may be specified to be furnished in cartridges, burst packs, or burst pouches. A static mixer should be affixed to each cartridge to form a packaged set; shrink wrapping has proven effective.<br>2. Multiple friction plug containers should be in accordance with PPP-C-96, type V, class 2. Interior coatings should be as specified therein. Exterior coatings, including side seam stripping, should be as specified therein for plan B. Wire handles as specified therein, should be provided for the 1-gallon container. Closure of the properly filled and sealed cans should be as specified in the appendix thereto.<br>3. All containers should comply with the requirements of the Uniform Freight Classifications (UFC), the National Motor Freight Classification (NMFC), and the applicable requirements of 49 CFR, Department of Transportation (DOT).<br>4. Unit of procurement: the paints covered by this specification should be purchased by volume. The unit of procurement should be in multiples of 1L or 1 U.S. liquid gallon at 15.5 ºC (60 ºF). |
| Commercial packaging (Including types VIII and VIIIa) | 1. Commercial packaging should be to ASTM D3951.<br>2. All containers should comply with the requirements of the UFC, the NMFC, and the applicable requirements of 49 CFR, DOT. |
| Packing | Packing should be specified as follows:<br>1. Overseas delivery packing. Intermediate containers of like size kits of paint should be packed in close-fitting wood boxes conforming to ASTM D6251, overseas type, or ASTM D6880-05, class 2. Box closure and strapping should be as specified in the applicable box specification or the appendix thereto except that strapping should be flat and the finish B.<br>2. Domestic delivery (level B) packing. Level B packing should be as for level A, except that boxes should be domestic type or class and the strapping should be finish A or B.<br>3. Commercial packing. The paint, in the unit kit and intermediate containers should, as applicable, be packed in multiples of like sizes in accordance with UFC, NMFC and 49 CFR requirements. |
| Palletization | Intermediate containers should be palletized in accordance with MIL-STD-147. Only one size unit or intermediate container should be placed on a pallet. |
| Intermediate containers | Paints should be packaged in intermediate containers as kits. Intermediate containers should be close-fitting corrugated fiberboard boxes in accordance with UFC, NMFC, and 49 CFR requirements. Fiberboard used in the construction of interior (unit and intermediate) and exterior containers, including interior packaging forms, should conform to the ASTM D4727. ASTM D4727 classes should be domestic fire-retardant or weather resistant fire-retardant (see 6.2). |



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

TABLE IX. Packaging – Continued.

| Packaging | Recommended requirements for direct Government acquisitions |
|---|---|
| Packing for acquisitions involving direct delivery to Navy ships or installations | Treated lumber and plywood. All lumber and plywood, including laminated veneer materials, used in shipping container and pallet construction, member, blocking, bracing, and reinforcing must be fire-retardant treated material in accordance with MIL-L-19140 as follows:<br>a. General use, weather resistant: MIL-L-19140, type II, category I.<br>b. General use, non-weather resistant: MIL-L-19140, type I, category I. |
| Unit kits | The paints covered by this specification should be packaged as kits. |
| SDS and product/procedure data sheets | A copy of the SDS and company product data/procedure sheets should be attached to the shipping document for each destination (see 6.4). |
| VOC Certification sheets | VOC Certification sheets will be provided by the manufacturer for each batch of combined parts A and B for each coat of the coating system when requested by the procuring activity. |
| Bar codes | Marking should include bar codes. |
| Hazardous warnings | a. Labels should be in accordance with 29 CFR Parts 1910, 1915, 1917, 1918, 1926, and 1928.<br>b. All individual containers should have the following marking:<br>"CAUTION: this paint contains volatile solvents, with probable hazardous vapors. Use with ventilation. Avoid prolonged breathing of vapors or spray mists. The solvents are highly flammable, avoid open flame and smoking."<br>c. Each component container, shipping container, and palletized load should be marked with the appropriate hazardous symbol.<br>d. Unit containers should be marked: "This product is asbestos, lead, chromium, cadmium free, except for possible trace levels." Types V, VI, and VII should also be marked: "This product is free of volatile organic hazardous air pollutants (VOHAP/HAP), except for possible trace levels." |
| VOC content | Contains (insert VOC content) grams per liter (insert VOC content in lb/gal) of VOC content per 40 CFR 60, appendix A (EPA), method 24. |
| HAPs | Contains (insert HAP content here in g/L and lb/gal) solids (nonvolatiles) per 40 CFR 63, appendix A, method 311. |
| Shelf life | Each unit container, intermediate container where applicable, and shipping container should be marked as follows: "Date of first re-inspection (insert here date 2 years after date of manufacture)." |
| Application Instructions | Manufacturers should include their NAVSEA-reviewed ASTM F718 with each shipment of the material covered by this specification. |



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

6.9 Subject term (key word) listing.

Asbestos
Ballast
Boiler water
Fuel
HAP
Lead free
Paint
Potable
Powder coating
Seawater
Sewage
Tank
VOC content
VOHAP

6.10 Amendment notations. The margins of this specification are marked with vertical lines to indicate modifications generated by this amendment. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

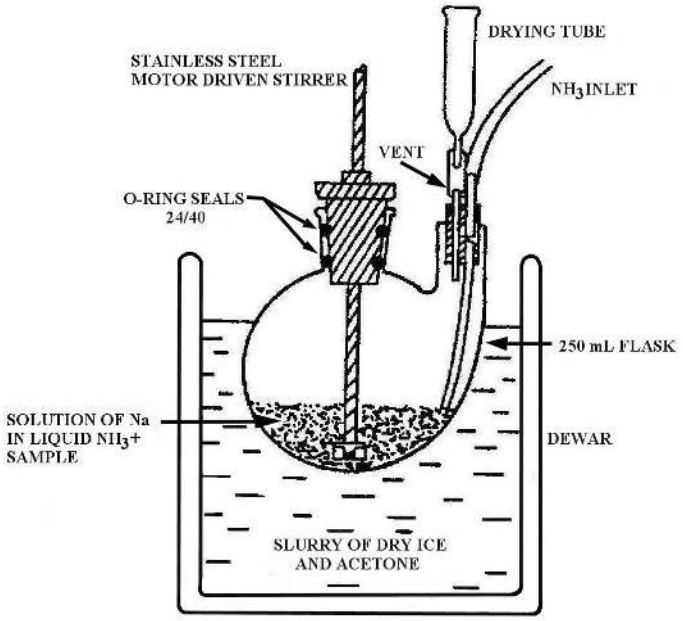



FIGURE 1. Apparatus for the decomposition of organic halides.

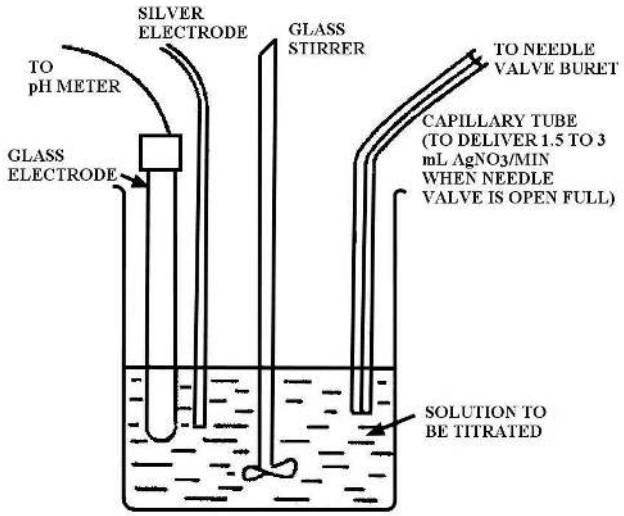



FIGURE 2. Potentiometric titration assembly.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

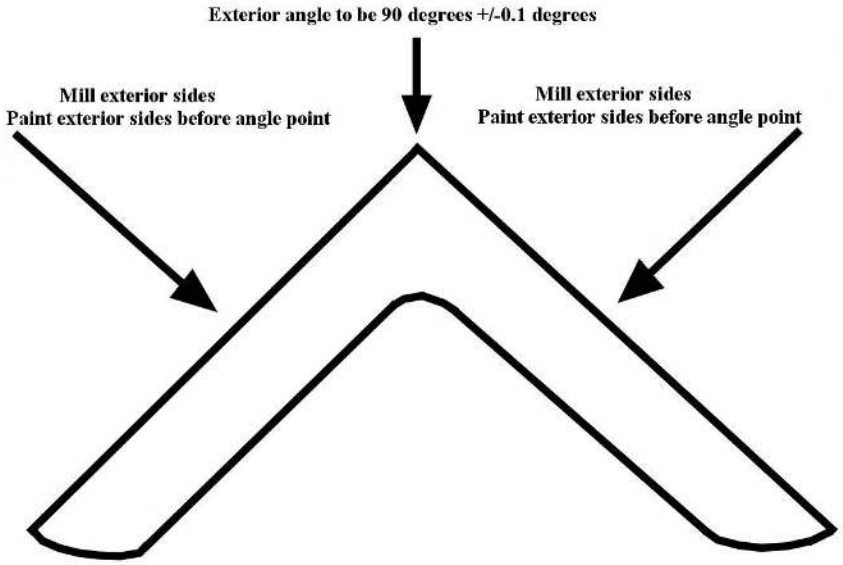



FIGURE 3. Structural angle milling and painting.

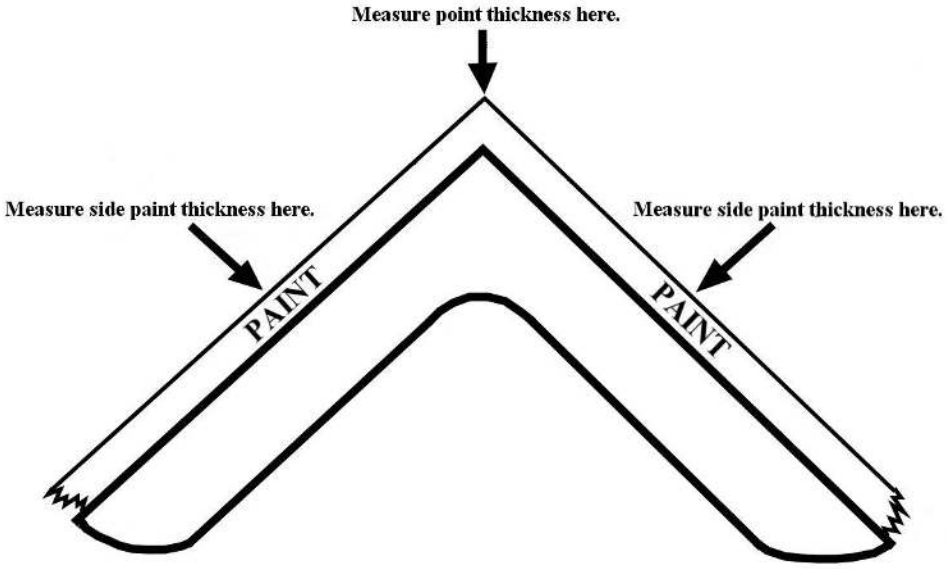



FIGURE 4. Paint film thickness measurement.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

APPENDIX A

EDGE RETENTION TEST

A.1 SCOPE

A.1.1 Scope. This appendix provides the test method procedure referenced in 4.5.9 of this specification for compliance with 3.8.1 of this specification. This appendix is a mandatory part of the specification. The information contained herein is intended for compliance.

A.2 Edge retention sample preparation.

A.2.1 Specimen preparation. The edge retention specimen should use an Aluminum Alloy 6061 structural angle (90-degree) section approximately 6 inches long. Preparation of the specimen for test will require three basic steps: sample machining to meet initial dimension requirements, grit blasting to provide acceptable anchor tooth, and surface cleaning prior to coatings application. Procedures for preparation are as follows:

A.2.1.1 Sample machining. Both exterior surfaces should be milled so that faces are square (90±0.1 degrees) and have a surface finish of 63 micro-inches. The exterior edge should be left as a “sharp” edge with no radius tolerance or chamfer.

A.2.1.2 Grit blasting. Specimen should be grit blasted using $Al_2O_3$ media to achieve an anchor tooth profile of 1-3 mils. Care should be taken to minimize rounding of the edge with excess blasting. Final edge radius should not exceed 0.04 inch (±10 percent).

A.2.1.3 Cleaning. Specimen should be cleaned thoroughly with acetone or appropriate solvent to remove all traces of grease prior to abrasive blasting and coating application.

A.2.3 Paint application. Topcoat is then spray applied to unprimed metal, maintaining correct pump pressure and distance from substrate (approximately 18 inches) according to manufacturer’s recommendations. Paint is applied to both sides (first) and the edge (last) within 1 minute. Measure the wet film thickness on the flat sides to ensure compliance with minimum recommended film thickness. After paint application, cure the specimens at ambient laboratory conditions for a minimum of 72 hours before sectioning (see figure 5).



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

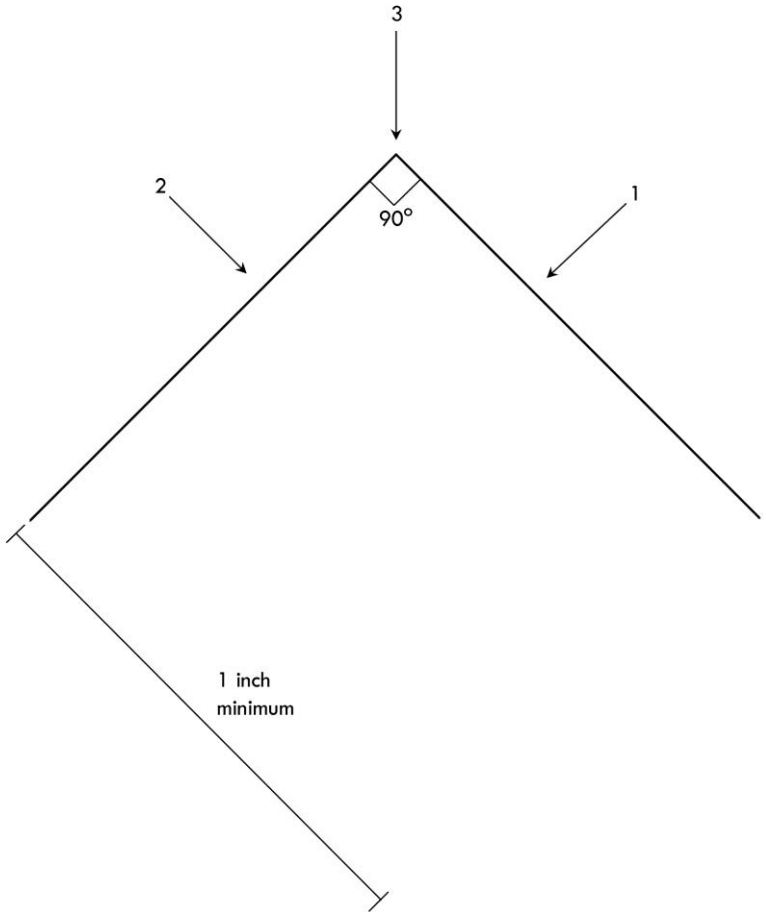



FIGURE 5. Spray.


A.2.4 Dry film thickness. The test sample is cut at a minimum of 0.5-inch thicknesses, mounted in metallurgical sample holder, and the cut is smoothed by sanding. The dry film thickness (DFT) is measured using an optical microscope. Measurements are made at sufficient distance from the 90-degree angle to ensure there is no edge effect; this is DFT (flat). The lowest thickness visible at the edge is also measured to determine DFT (edge).

A.2.5 Edge retention calculation. The edge retention is calculated from:

% retention = DFT (edge)/DFT (flat) x 100 (see figure 6).



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

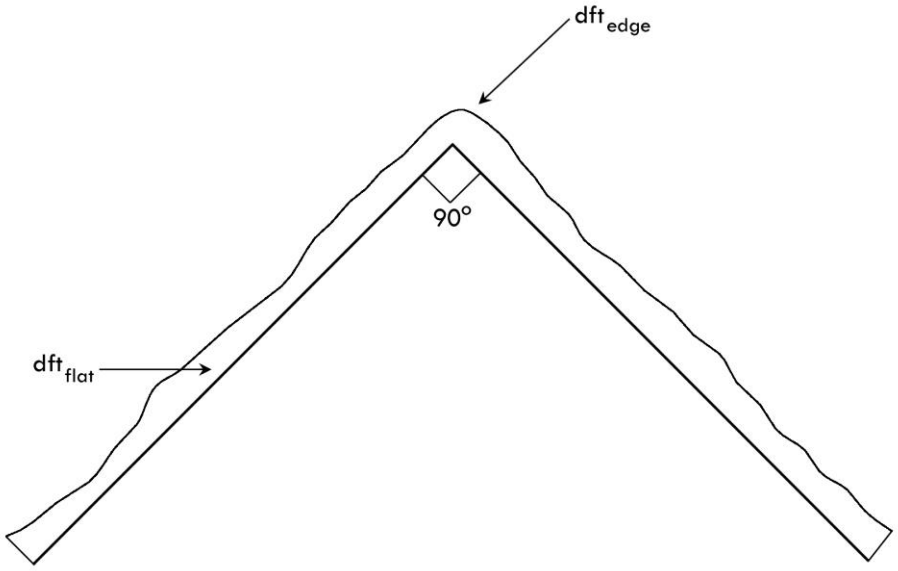


NOTES:

1. Aluminum is used due to ease of availability, handling, and cutting.
2. Mounting the sample in a metallurgical mount prevents damage to the edge during measurement and allows "polishing" of the specimen to highlight the interfaces for measurement.

FIGURE 6. Edge retention calculation.

A.2.6 Pass/fail criteria. Three sectioned specimens shall be cut from each sample, the coating thickness measured, and edge retention calculated. Any specimen with less than 50 percent edge retention shall constitute a failure. The average of the three shall not be less than 70 percent.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.

## CONCLUDING MATERIAL

Custodians:
Army – MR
Navy – SH

Preparing activity:
Navy – SH
(Project 8010-2020-012)

Review activities:
Navy – AS, CG
Air Force – 03

Civil agency:
GSA – FAS

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.



Source: https://assist.dla.mil -- Downloaded: 2026-10-19T16:00Z
Check the source to verify that this is the current version before use.