CCC-C-428d
August 5, 1965

SUPERSEDING
Fed. Spec. CCC-C-428c
October 22, 1962

FEDERAL SPECIFICATION

CLOTH, DUCK, COTTON; FIRE, WATER, WEATHER, AND MILDEW RESISTANT

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers the requirements for fire, water, weather, and mildew resistant cotton duck.

1.2 Classification.

1.2.1 *Types and classes.* The finished cloth shall be of the following types and classes as specified (see 6.2):

Type I—Cloth finished in olive drab No. 7 color.
Type II—Cloth finished in deck grey color.
Class 1—Regular finish.
Class 2—Dry finish.

2. APPLICABLE SPECIFICATIONS, STANDARDS, AND OTHER PUBLICATIONS

2.1 Specifications and standards. The following specifications and standards, of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

Federal Specifications:

CCC-C-419—Cloth, Duck, Cotton, Unbleached, Plied-Yarns, (Army and Numbered).
CCC-C-443—Cloth, Cotton, Duck; (Single and Plied Filling Yarns Flat).
CCC-T-191—Textile Test Methods.
PPP-P-51—Packaging, Packing, and Marking of Textile Fabrics (Woolens, Worsteds, Cottons, Silks and Synthetics).

Federal Standards:

Fed. Std. No. 4—Glossary of Fabric Imperfections (Section 1).
Fed. Std. No. 102—Preservation, Packaging, and Packing Levels.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington, D. C. 20402.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D. C., Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, Los Angeles, and Seattle, Wash.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

Military Specification:

MIL-C-2384—Cloth, Duck, Cotton, Plied and Single Yarns (High Sley).

Military Standard:

MIL-STD-105—Sampling Procedures and Tables for Inspection by Attributes.

(Copies of Military Specifications and Standards required by contractors in connection with specific

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publication. The following document forms a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal, shall apply.

Rules and Regulations Under the Textile Fiber Products Identification Act.

(Application for copies should be addressed to the Federal Trade Commission, Washington, D. C., 20580.)

3. REQUIREMENTS

3.1 Standard sample. When a standard sample is available, the cloth shall match the standard sample for shade and shall be equal to, or better than the standard sample with respect to all characteristics for which the standard sample is referenced (see 6.4).

3.2 Laboratory report approval and bid sample approval. Unless otherwise specified at the time of submission of a bid, the prospective supplier shall submit to the contracting officer for approval, a sample 5 by 9 inches (minimum) and a certified copy of a recent laboratory report covering the type (i.e. flat duck, numbered duck, etc.) which he proposes to deliver (see 6.2). Unless otherwise specified by the contracting officer, the bidder shall certify that the sample and laboratory report submitted cover cloth which was finished in the mill where the finishing will be performed if the contract is awarded. The laboratory report shall contain test data which demonstrate that the finished cloth, which the supplier proposes to deliver, has been tested and has been found to comply with all requirements of this specification. Any of the following types of reports will be satisfactory from the standpoint of this requirement:

(*a*) An independent or commercial laboratory report.

(*b*) The prospective bidder's own laboratory report.

(*c*) A Government laboratory report from a contract within not more than 6 months of date of submission of bid.

The purpose of the above requirement is to assist the Government to determine the capability of bidders to manufacture a cloth meeting all the requirements of the specification. The submission of an acceptable sample under this requirement shall not be construed as relieving a supplier from subsequently meeting all requirements of the specification on all deliveries.

3.3 Formula approval. The prospective supplier or his finishing plant shall submit with their bid to the contracting officer for approval, a list of materials which the prospective supplier or his finishing plant intends to use, stipulating grades and the standards of all materials including solvents and manufacturer's name. This list is for the information of the Government only, and is not to be made available to the public (see 6.5). The use of compounds containing mercury in any form are prohibited. Approval of the qualitative formula submitted shall in no way absolve the supplier from complying with the performance requirements of this specification.

3.4 Materials.

3.4.1 *Basic cloth.* The cloth shall be as specified by the contracting agency and shall conform to CCC-C-419, CCC-C-443, or MIL-C-2384 (see 6.2), except that the nonfibrous material for CCC-C-443 and MIL-C-2384 shall be as specified in 3.4.1.1.

3.4.1.1 *Nonfibrous material content.* The cloth prior to finishing, shall contain not more than 2.5 percent starch and protein content excluding chloroform-soluble and water-soluble material and not more than 5.0 percent starch and protein content including chloroform-soluble and water-soluble material when tested as specified in 4.4.

3.4.2 *Grey-cloth weight.* Unless otherwise

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

specified in subsequent tables and paragraphs, where reference is made to grey-cloth weight, the minimum acceptable grey-cloth weight as given in the applicable grey-cloth specification shall be used to determine the requirements under these paragraphs.

3.4.3 *Compound.* The compound to provide fire, water, weather, and mildew resistance shall be well ground and evenly blended. Compounds containing sulfur may be permitted when specifically indicated by name in formulas approved by the contracting officer. The compound shall be of the same ingredients as contained in the list of materials submitted and approved under 3.3.

3.5 Finished cloth.

3.5.1 *Construction.* The number of yarns per inch of the finished cloth shall conform to the requirements of the specification covering the grey cloth specified except that a minus tolerance in the filling yarn will be allowed as follows:

Designation	Minus tolerance
Flat ducks (requiring desizing)	Up to 10 percent
Army duck	Up to 5 percent
No. 8 and lighter duck	Up to 5 percent
Heavier than No. 8 duck	Up to 3 percent

3.5.2 *Finished width.* The minimum overall width of the finished cloth shall be as specified (see 6.2).

3.5.3 *Breaking strength.* The breaking strength of the finished cloth in both warp and filling directions shall be not less than that of the corresponding specification requirements for the grey cloth.

3.5.4 *Weight.* The weight of the finished cloth shall be the actual weight of the grey cloth plus an allowance for the treatment in accordance with table I.

TABLE I.

Grey weight (ounces per sq. yd.)	Allowable maximum increase in weight due to treatment based on actual gray-cloth weight (percent)
12 and over	50
Under 12	65

3.5.5 *Color.* The color shall be as specified for the applicable type and shall match the standard sample when furnished by the contracting activity (see 6.4). The color shall be obtained with carbon black or lamp black, inorganic or phthalocyanine pigments, or such other coloring materials as shall not be appreciably affected by exposure to weathering when tested as specified in 4.4.

3.5.5.1 *Colorfastness.* When a standard sample is available, the colored and finished cloth shall show fastness to accelerated weathering equal to or better than the standard sample when tested as specified in 4.4. When a standard sample is not available or is not referenced as a standard for colorfastness, the colored and finished cloth shall show "good" colorfastness to accelerated weathering when tested as specified in 4.4.

3.5.5.2 *Matching.* The color of the finished cloth shall match the standard shade under a natural (north sky) daylight or artificial daylight having a color temperature of 7500° Kelvin and shall be a good approximation to the standard sample under incandescent lamplight at 2800° Kelvin.

3.5.6 *Crocking.*

3.5.6.1 *Class* 1. Cloths with the regular finish shall show no more crocking on dry white cotton cloth than the Munsell neutral value of 5.0 when tested as specified in 4.4.

3.5.6.2 *Class* 2. Cloths finished with a dry finish for upholstery purposes shall show no more crocking on dry white cotton cloth than Munsell neutral value of 7.0 when tested as specified in 4.4.

3.5.7 *Flexibility.* The finished cloth shall

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

show a bending moment of not more than that specified in table II when tested as specified in 4.4.

TABLE II. *Flexibility*

CCC-C-419 cloth designations	Initial bending moment inch-lbs. maximum	After heating at 200°-205° F. (bending moment inch-lbs.) maximum	At 0° ± 5° F. (bending moment inch-lbs.) maximum
Numbered			
2	0.16	0.400	0.400
4	0.12	0.300	0.300
6	0.06	0.180	0.180
8	0.05	0.125	0.125
10	0.03	0.075	0.075
12	0.02	0.050	0.050
Army ducks			
8.25	0.013	0.032	0.032
9.85	0.013	0.032	0.032
12.29	0.013	0.032	0.032

3.5.7.1 For all other cloths, the flexibility requirements shall be as specified (see 6.2).

3.5.8 *Water resistance.* The finished cloth shall have a maximum leakage of 50 ml. at the height indicated in table III when tested by the water-permeability test specified in 4.4. The cloth shall conform to the same maximum leakage requirements after the accelerated weathering test specified in 4.4.

3.5.8.1 The requirements for resistance to water permeability shall be applicable only to the flat ducks of CCC-C-443 having weights of 14.90 and 17.55 ounces per square yard and to all ducks of CCC-C-419 and MIL-C-2384.

TABLE III. *Height for test of water resistance*

Untreated weight (oz./sq. yd.)	Hydrostatic height		Time of exposure, minutes
	Inches	Centimeters	
Over 20 ...	20	50.80	10
14 thru 20 .	14	35.56	10
Under 14 ..	8	20.32	10

3.5.9 *Flame resistance.* When tested as specified in 4.4, the time of flaming of the specimens shall not exceed 2 seconds. The average length of char shall not exceed the requirements of table IV. The cloth shall conform to the same fire-resistance requirements after the accelerated weathering period as specified in 4.4 and also after being exposed to water leaching when tested as specified in 4.4.

TABLE IV. *Average length of char*

Untreated weight (oz./sq. yd.)	Maximum average length of char (inches)
Under 10	4.5
10 thru 20	3.5
Over 20	2.0

3.5.10 *Mildew resistance.*

3.5.10.1 *For type I cloths.* The cloth shall be made mildew resistant by proper deposition within the cloth of a fungicide which is currently approved for this use by the procuring activity. Unless otherwise specified (see 6.2), the fungicide shall be one of the following in the specified concentration:

(*a*) Copper 8-quinolinolate to deposit a minimum of 0.18 percent copper as metal from copper 8-quinolinolate to a maximum of 0.27 percent copper as metal from copper 8-quinolinolate.

(*b*) Copper naphthenate combined with copper 8-quinolinolate to deposit a minimum of 0.35 percent total copper with a minimum of 0.05 percent copper as metal from copper 8-quinolinolate to a maximum of 1.48 percent total copper with a maximum of 0.18 percent copper as metal from copper 8-quinolinolate.

The fungicide shall be uniformly applied and the cloth shall be well penetrated.

3.5.10.2 *For type II cloths.* The cloth shall be made mildew resistant by proper deposition within the cloth of a fungicide which is currently approved for this use by the procuring activity.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

3.5.11 *Breaking strength after accelerated weathering.* The requirements for breaking strength after accelerated weathering shall be applicable for civil agencies procurements only.

3.5.11.1 *Army and numbered duck.* The breaking strength of the finished cloth after exposure to 100 hours accelerated weathering as specified in 4.4 shall conform to the following requirements:

Untreated (grey weight) (ounces per square yard)	Minimum percent retention of finished cloth breaking strength
Under 15 ozs.	60.0 percent
15 oz. and over	75.0 percent

3.5.11.2 *Alternate ducks.* The breaking strength requirements for the material listed herein shall be the same as specified in 3.5.11.1 for Army and numbered duck:

MIL-C-2384—Type I, class 1, 10.75 ounce (high sley).
Type I, class 2, 14.75 ounce (high sley).
CCC-C-443—Type I, 14.90 ounce (Flat duck).
Type I, 17.55 ounce (flat duck).

3.5.11.3 *Flat ducks.* The breaking strength for flat ducks after accelerated weathering, except those listed in 3.5.11.2, shall be not less than 80 percent of the finished cloth, or not less than that specified in the base cloth specification after exposure to 200 hours accelerated weathering, when tested as specified in 4.4.

3.6 Fiber identification. Each roll shall be labeled, ticketed, or invoiced for fiber content in accordance with the Rules and Regulations Under the Textile Fiber Products Identification Act (see 2.2).

3.7 Length and put-up. The cloth shall be put-up on rolls in accordance with PPP-P-51. The minimum length of pieces shall be in accordance with the applicable grey cloth specification.

3.8 Workmanship. The cloth shall conform to the quality and grade of product established by this specification. The occurrence of defects shall not exceed the applicable acceptable quality levels (AQLs).

4. SAMPLING, INSPECTION, AND TEST PROCEDURES

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.2 Inspection. Except when otherwise specified by civil agencies, inspection shall be in accordance with the provisions of MIL-STD-105 except where otherwise indicated herein.

4.2.1 *Testing of components.* Quality assurance provisions for components described shall be in accordance with subsidiary specifications and standards referenced to the extent applicable. In addition to the quality assurance provisions of the subsidiary specifications, the supplier shall submit a certificate of compliance that the fire, water, weather, and mildew resistant compound contains no mercury, and that only the formulas approved were utilized.

4.2.2 *Examination of the end item.* Examination of the end item shall be in accordance with the provisions of MIL-STD-105 and 4.2.2.1 through 4.2.2.3.

4.2.2.1 *Yard-by-yard examination.* The required yardage of each roll shall be examined on the face side and all defects defined in section 1 of Fed. Std. No. 4 which are clearly noticeable at normal inspection distance (3 feet) shall be scored and as-

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

signed demerit points as listed in 4.2.2.1.1, except only those slubs and knots which exceed the maximum acceptable limits shown for each in figure 1 shall be scored. None of the 30 contiguous yards (increments of one yard on the measuring device of the inspection machine) selected for examination from any one roll within the sample shall be penalized more than four points. The sample unit for this examination shall be one linear yard. The sample size shall be 750 linear yards, regardless of lot size. The sample yardage shall be examined from 25 rolls. An approximately equal number of yards shall be examined in each roll of the sample. The lot shall be unacceptable if the points per hundred square yards exceeds 40.0. Point computation shall be as follows:

$$\frac{\text{Total points scored in sample size} \times 3600}{\text{Sample size (yards)} \times \text{contracted width of material}} = \text{points per 100 square yards}$$

4.2.2.1.1 *Demerit points.* Demerit points shall be assigned as follows:

For defects 3 inches or less in any dimension	—one point.
For defects exceeding 3 inches but not exceeding 6 inches in any dimension	—two points.
For defects exceeding 6 inches but not exceeding 9 inches in any dimension	—three points.
For defects exceeding 9 inches in any dimension	—four points.

The following defects when present shall be scored four points for each yard in which they occur:

Baggy, ridgy, or wavy cloth.
Color not uniform, off shade, (not within established tolerance), shaded end to end, side to side, or side to center.
Poor dye penetration, mottled, streaky or cloudy.
Overall application of compound not uniform.
Objectionable odor.
Overall uncleanness.
Clearly visible crystallization of mildew inhibitors.
Poorly constructed—not firmly or tightly woven.
Bias or bowed filling.
Tackiness (sticky to the touch).
Width less than specified.

4.2.2.2 *Examination for length.* During the yard-by-yard examination, each roll in the sample shall be examined for put-up and length in accordance with the provisions of the untreated cloth specification.

4.2.2.3 *Examination for compliance with Textile Fiber Products Identification Act.* During the yard-by-yard examination, each roll in the sample shall be examined for compliance with the Rules and Regulations under the Textile Fiber Products Identification Act. Each roll not labeled in accordance with this act shall be a defect. The lot shall be unacceptable if two or more of these defects occur.

4.3 Examination of preparation for delivery requirements. An examination shall be made in accordance with the provisions of PPP-P-51 to determine that packaging, packing, and marking requirements of section 5 of this specification are complied with.

4.4 Testing of the end item. The method of testing specified in CCC-T-191, wherever applicable and as listed in table VI shall be followed. The physical and chemical values specified in section 3 (except where otherwise indicated) apply to the average of the determinations made on a sample unit for test purposes as specified in the applicable test methods. The sample unit for testing shall be 1/4 yard of the desized untreated cloth and 5 continuous yards of the finished cloth, all full width of the material. The sample size (number of sample units) shall be in accordance with table V except for the inhibitor content. The sample unit for testing the inhibitor content shall be 1/4 yard and the sample size shall be 5 for all lots less than 22,001 units in size, and 8 for all lots over 22,000 units in size. The lot size shall be expressed in units of 1 yard each. The lot shall be unacceptable if one or more sample units fail to meet any test requirement specified, or if the lot average determination for allowable increase in weight due to treatment exceeds requirements. Unless otherwise specified, all phy-

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

sical tests shall be performed under standard conditions as defined in CCC-T-191. When the data in the "number of determinations per individual sample unit" and "results reported as" columns are not specified in table VI, they shall be as required by the referenced test method. All test reports shall contain the individual values utilized in expressing the final results.

TABLE V. *Sample size*

Lot size in yards	Sample size
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

TABLE VI. *Test method*

Characteristic	Requirement paragraph	Test method	Number of determinations per individual sample unit	Results reported as
Nonfibrous material content	3.4.1.1	2611	—	—
Materials:				
Compound	3.4.3	[6]	—	—
Finished cloth:				
Weight	3.5.4	5041	5	Average of 5 determinations to nearest 0.01 ounce.[7]
Yarns per inch	3.5.1	5050	—	Pass or fail.
Breaking strength:				
Initial	3.5.3	5100	—	—
After accelerated weathering	3.5.11.1 3.5.11.2 3.5.11.3	5100, 4.4.2[1]	—	[8]
Flexibility:				
Initial				
Warp	3.5.7	5202, 4.4.1	4	Average of 4 determinations to nearest 0.001 inch pound.
Filling	3.5.7	5202, 4.4.1	4	Average of 4 determinations to nearest 0.001 inch pound.
After heat aging				
Warp	3.5.7	5202, 4.4.1	4	Average of 4 determinations to nearest 0.001 inch pound.
Filling	3.5.7	5202, 4.4.1	4	Average of 4 determinations to nearest 0.001 inch pound.
At low temperature				
Warp	3.5.7	5202, 4.4.1	4	Average of 4 determinations to nearest 0.001 inch pound.
Filling	3.5.7	5202, 4.4.1	4	Average of 4 determinations to nearest 0.001 inch pound.
Colorfastness to weathering	3.5.5.1	5671[1 2]	—	—
Fastness to crocking	3.5.6	5651	—	—
Flame resistance: Initial				
Char length				
Warp	3.5.9	5903T	4	Average of 4 determinations to nearest 0.1 inch.
Filling	3.5.9	5903T	4	Average of 4 determinations to nearest 0.1 inch.
Flaming time				
Warp	3.5.9	5903T	4	Each determination and average of 4 determinations to nearest 1/5 second.
Filling	3.5.9	5903T	4	Each determination and average of 4 determinations to nearest 1/5 second.

Source: https://assist.dla.mil --Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

TABLE VI. *Test method (cont'd)*

Characteristic	Requirement paragraph	Test method	Number of determinations per individual sample unit	Results reported as
After accelerated weathering:				
Char length				
Warp	3.5.9	5903T, 4.4.2[1]	4	Average of 4 determinations to nearest 0.1 inch.
Filling	3.5.9	5903T, 4.4.2[1]	4	Average of 4 determinations to nearest 0.1 inch.
Flaming time				
Warp	3.5.9	5903T, 4.4.2[1]	4	Each determination and average of 4 determinations to nearest 1/5 second.
Filling	3.5.9	5903T, 4.4.2[1]	4	Each determination and average of 4 determinations to nearest 1/5 second.
After water leaching:				
Char length				
Warp	3.5.9	5903T, 5832[3]	4	Average of 4 determinations to nearest 0.1 inch.
Filling	3.5.9	5903T, 5832[3]	4	Average of 4 determinations to nearest 0.1 inch.
Flaming time				
Warp	3.5.9	5903T, 5832[3]	4	Each determination and average of 4 determinations to nearest 1/5 second.
Filling	3.5.9	5903T, 5832[3]	4	Each determination and average of 4 determinations to nearest 1/5 second.
Dye identification	3.5.5	[6]		—
Water resistance:				
Initially	3.5.8	5516		—
After accelerated weathering	3.5.8	5516, 4.4.2[1]	3	Average of 3 determinations to nearest 1.0 cc.
Mildew resistance				
Type I:				
Total copper analysis	3.5.10.1	2050 or 2051[4]		—
Fungicide identification and concentration	3.5.10.1	[5]		—
Type II:				
Fungicide	3.5.10.2	[6]		—

[1] The time of exposure shall be 100 standard hours.

[2] The test apparatus shall be as specified in 4.4.2, except that the filters shall not be removed.

[3] Leaching period shall be 24 hours.

[4] Suppliers shall indicate on their test reports which fungicides were used.

[5] The supplier shall certify that the required amount of copper as metal from copper 8-quinolinolate has been used in the treatment of the duck. The certificate shall be accompanied by actual test, inspection, or other verifiable quality data.

[6] When supplier shall submit a certificate of compliance for this characteristic. When required, the certificate shall be accompanied by actual test, inspection, or other verifiable quality data.

[7] All test results on the weight of the basic untreated cloth and finished cloth shall be averaged separately to determine the respective lot average weights. These values shall then be utilized in calculating the

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

percent increase in the finished cloth weight. Results shall be calculated to the nearest 0.1 percent.
[8] All test results shall be averaged and this average value shall be utilized in calculating the percent change from the initial treated cloth value. Results shall be calculated to the nearest 0.1 percent.

4.4.1 *Flexibility tests.* The test shall be conducted in accordance with method 5202 with the following modifications:
Load scale reading. The load scale reading shall be taken at a 20 degree angular deflection of the specimen.
Specimens. Eight specimens, 1 inch by 2 inches, shall be cut: four with the long dimension in the warp direction, and four in the filling direction, and pressed between two 6- by 6-inch glass plates weighted with a 20-pound weight for four hours at standard condition prior to testing.

4.4.1.1 *After heat aging.* Flexibility test specimens shall be cut from the conditioned specimens as specified in 4.4.1. However, prior to putting them under glass plates and a 20-pound weight, the specimens shall be subjected to a temperature between 200° to 205°F. for 120 hours in a well ventilated oven and then allowed to cool at standard conditions for 16 hours. The heat aged and conditioned samples shall then be placed on glass plates under weight for four hours prior to testing.

4.4.1.2 *At low temperature.* Flexibility test specimens shall be prepared as specified in 4.4.1. After the required pressing for four hours, weight and upper glass plate shall be removed. The lower plate holding the conditioned and pressed specimens shall then be subjected to a temperature of 0° ± 5°F. for not less than one hour and then tested at that temperature.

4.4.2 *Accelerated weathering test.*

4.4.2.1 *Apparatus and procedure.* The apparatus shall be in accordance with method 5804 except as modified below (see 6.3).

4.4.2.2 *Filters.* The filters shall be removed when testing the following materials:

CCC-C-419—All types Army and numbered duck.

MIL-C-2384—Type I, class 1, 10.75 ounce (high sley).

Type I, class 2, 14.75 ounce (high sley).

CCC-C-443—Type I, 14.90 ounce (flat duck).

Type I, 17.55 ounce (flat duck).

4.4.2.3 *Procedure.* Two samples 9-1/2 by 28 inches, constituting the material required to complete all weathering tests, shall be cut from the sample unit. One sample shall be cut with the long dimension in the direction of the warp; the other with the long dimension in the direction of the filling. When the width of the sample unit does not permit a full 28-inch specimen to be taken in the filling direction, two 9-1/2- by 14-inch samples shall be cut. The specimens shall be exposed one above the other in the quadrant of the accelerated weathering apparatus. The specimens shall be changed from the top to bottom racks approximately every 25 hours during the designated exposure period (see 3.5.11). At the conclusion of the exposure period, the samples shall be removed from the apparatus and allowed to dry; then the breaking strength and fire resistance specimens shall be cut from the exposed material. All specimens shall be conditioned at standard conditions prior to testing. The four fire resistance specimens shall be cut from the exposed samples such that the direction being tested shall have been exposed to accelerated weathering in the vertical position. In conducting fire resistance tests on these specimens, two specimens shall be subjected to the test flame at the end which was at the top of the exposed material, and two shall be subjected to the test flame at the end which was at the bottom of the specimen. The lower edges of the fire resistance test specimens shall be trimmed, if necessary, so that a freshly cut end is exposed to the test flame.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

5. PREPARATION FOR DELIVERY

(For civil agency procurement, the definitions and application of levels of packaging and packing shall be in accordance with Fed. Std. No. 102.)

5.1 Packaging. Packaging shall be level A or C as specified (see 6.2 and 6.2.1).

5.1.1 *Levels A and C.* The cloth, put-up as specified, shall be packaged in accordance with the applicable requirements for class 4 cloth of PPP-P-51.

5.2 Packing. Packing shall be level A, B, or C as specified (see 6.2 and 6.2.1).

5.2.1 *Levels A, B, and C.* The cloth shall be packed in accordance with the applicable requirements of PPP-P-51.

5.3 Marking. In addition to any special marking required by the contract or order, shipments shall be marked in accordance with the applicable requirements of PPP-P-51.

6. NOTES

6.1 Intended use.

6.1.1 *Types I and II.*

6.1.1.1 *Class* 1. Cloth treated for fire, water, weather and mildew resistance as covered by this specification for class 1 is intended for use in the manufacture of canvas covers, tents, tarpaulins, and other duck items providing protection under conditions of prolonged outdoor use.

6.1.1.2 *Class* 2. Cloth treated for fire, water, weather, and mildew resistance as covered by this specification for class 2 is intended for use as upholstery material in motorized vehicles and uses where a higher degree of resistance to crocking is required by the condition of the end use.

6.2 Ordering data. Purchasers should exercise any desired options offered herein and procurement documents should specify the following:

(*a*) Title, number, and date of this specification.
(*b*) Base cloth required (see 3.4.1).
(*c*) Type and class required (see 1.2.1).
(*d*) Width of cloth required (see 3.5.2).
(*e*) When bid sample or laboratory report is not required (see 3.2).
(*f*) Submission of certification as to the place of finishing, when required (see 3.2).
(*g*) Flexibility requirements for duck other than numbered or Army duck specified in 3.5.7.
(*h*) Mildew inhibitor (if other than specified in 3.5.10.1).
(*i*) Civil agencies exceptions (see 4.2).
(*j*) Selection of applicable levels of packaging and packing (see 5.1 and 5.2).

6.2.1 In the preparation of contract or orders, it must be noted that various options, choices and alternatives, as indicated in PPP-P-51 may be exercised in the preparation for the delivery of cloth.

6.3 Accelerated aging. Where the accelerated aging apparatus specified in 4.4.2 is not available, other tests and requirements may be substituted provided data is submitted showing correlation with the accelerated weathering test of table VII.

6.4 Standard sample. For access to standard sample, address the procuring office issuing the invitation for bids.

6.5 Formula disapproval. For the information of the supplier, the use of proteins and their derivatives, starch, hydrophylic materials, oxidizing oils, and oxidizing resins and resin or compounds to increase hygroscopicity may lead to formula disapproval (see 3.3).

6.6 It is believed that Dark Green FWWMR Duck may be finished under the requirements for type I of this specification and the Duck (dark) Blue FWWMR Duck may be finished under the requirements for type II of this specification.

6.7 Transportation description. The trans-

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

portation description and minimum weights applicable to this commodity are:

Rail:

Cloth, cotton, fireproofed, oiled or waterproofed, not coated, not otherwise indexed by name.
Carload minimum weight—Any quantity.

Motor:

Cloth, cotton, fireproofed, oiled or waterproofed, not coated, not otherwise indexed.
Truckload minimum weight 30,000 pounds, subject to Rule 115, National Motor Freight Classification.

MILITARY CUSTODIANS:

Army—GL
Navy—SA
Air Force—11

Preparing activity:

Army—GL

Review activities:

Army—MD, MI
Navy—SA, MC
Air Force—11, 67

User activities:


Army—MU, MO
Navy—YD, SH
DSA—DM

Review and User information is current as of the date of this document. For future coordination of changes to this document, draft circulation should be based on the information in the current Federal Supply Classification Listing Of DOD Standardization Documents.


Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

FIGURE 1 (Limits of Acceptability)


Slub

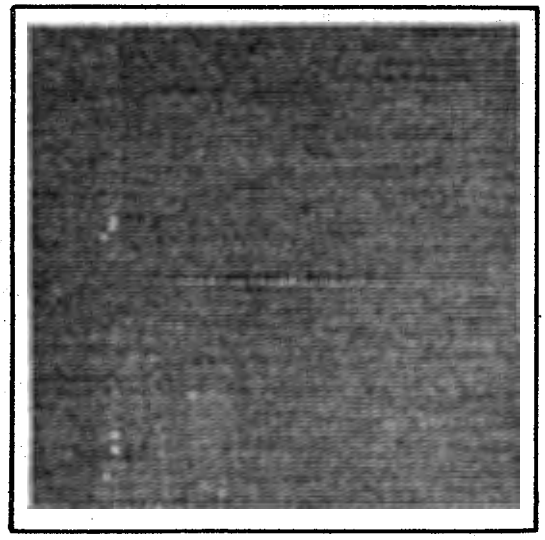

Slub (Loose, Thick)

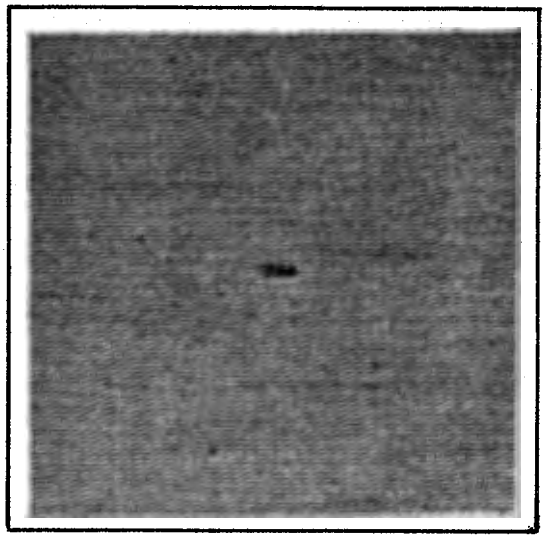

Lump or Knot (Fuzz)

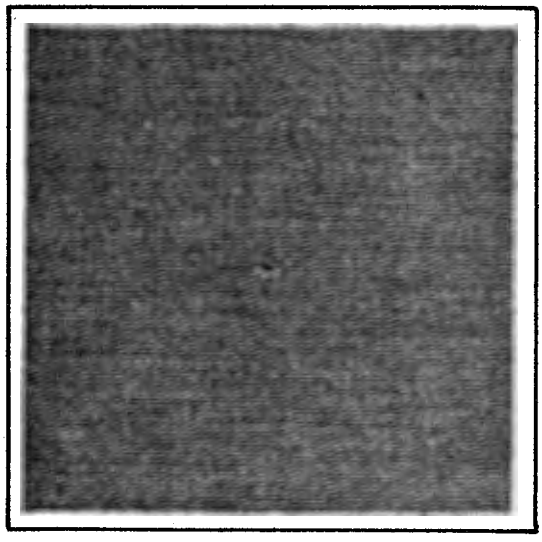

Copies of this specification may be purchased for 10 cents each.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.