CCC-C-448c
November 17, 1967
SUPERSEDING
Fed. Spec. CCC-C-448b
January 10, 1962

FEDERAL SPECIFICATION

CLOTH, SEERSUCKER, COTTON

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers cloth, cotton seersucker.

1.2 Classification.

1.2.1 Types and classes. The cloth, cotton, seersucker covered by this specification shall be of the following types and classes (see 6.2):

Type I - Narrow stripe.
  Class 1 - 82 by 86 texture.
Type II - Medium stripe.
  Class 1 - 112 by 78 texture.
  Class 2 - 80 by 80 texture.
Type IIa - Narrow stripe.
  Class 1 - 112 by 78 texture.
Type III - Stripe pattern effect.
  Class 1 - 280 1/ by 72 texture.

1/ 280 ends per repeat (approximately 2-5/8 inches).

2. APPLICABLE DOCUMENTS

2.1 Specifications and standards. The following specifications and standards, of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extend specified herein:

Federal Specifications:

CCC-T-191 - Textile Test Methods.
PPP-P-1134 - Packaging and Packing of Cotton and Cotton-Synthetic Fiber Blend Fabrics (Excluding Duck Fabrics).

Federal Standard:

Fed. Std. No. 4 - Glossary of Fabric Imperfections.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington, D. C. 20402.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D. C., Atlanta, Chicago, Kansas City, Mo., Ft. Worth, Denver, San Francisco, Los Angeles, and Seattle, Wash.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

Military Standard:

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

(Copies of Military Specifications and Standards required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following document forms a part of this specification to the extend specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

Rules and Regulations Under the Textile Fiber Products Identification Act.

(Copies may be obtained without charge from the Federal Trade Commission, Washington, D. C. 20580.)

3. REQUIREMENTS

3.1 Standard sample. When a standard sample is available, the finished cloth shall match the standard sample for shade and shall be equal to or better than the standard sample with respect to all characteristics for which the standard sample is referenced (see 6.3).

3.2 Material.

3.2.1 Yarn. The yarn shall be made from cotton which has been cleaned, carded, combed, drawn and spun into single yarns except that the slack beam warp yarn for the type I, class 1 cloth and tight beam warp yarn for the type II, class 2 cloth shall be two-ply.

3.3 Color. The color shall be as specified and where applicable (see 3.1) shall match the standard sample (see 6.3). The use of sulfur dyes or dyes containing sulfur compounds capable of oxidation to form sulfuric acid is prohibited. The dyestuffs shall be chosen and applied so that the dyed cloth shall show no more labile sulfur than shown by the standard sample when tested as specified in 4.4. When no standard sample is established, there shall be a minimum of staining of the test paper when tested as specified in 4.4.

3.3.1 Matching. When a standard sample is available, the dyed cloth shall match the standard sample under natural (north sky) daylight or artificial daylight having a color temperature of 7500° Kelvin and shall be a good approximation to the standard sample under incadescent lamplight at 2800° Kelvin.

3.3.2 Colorfastness. The finished cloth shall show colorfastness to combined laundering and bleaching, perspiration, crocking, and light equal to or better than the standard sample when tested as specified in 4.4. When no standard sample is established for colorfastness, the finished cloth shall show "good" colorfastness to combined laundering and bleaching, perspiration, crocking, and light when tested as specified in 4.4.

3.4 Physical requirements. The finished cloth shall conform to the requirements shown in table I when tested as specified in 4.4.

TABLE I. Physical requirements

Type	Class	Weight (ounces per square yard) minimum	Yarns per inch minimum		Breaking strength minimum (pounds)	
			Warp	Filling	Warp	Filling
I	1	4.0	82	86	24	45
II	1	4.0	112	78	30	35
IIa	1	4.0	112	78	30	35
II	2	4.0	80	80	30	40
III	1	4.0	280 1/	72	25	30

1/ Per repeat (see 3.4.3.4).

3.4.1 Weave.

3.4.1.1 Types I and III. The weave shall be plain.

3.4.1.2 Types II and IIa. The weave shall be plain with the slack warp weaving two ends as one.

3.4.2 Slack beam take-up. The minimum slack beam take-up for all types and classes shall be 30 to 35 percent when tested as specified in 4.4.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

3.4.3 Stripes or pattern effect.

3.4.3.1 Type I, class 1. The stripe effect of the type I cloth shall be produced by using two warp beams, one tight and one slack. The color of the tight beam warp yarn shall be as specified (see 6.2). The slack beam warp yarns shall be natural or bleached. The two warps shall alternate in sections of tight and slack ends and each color pattern repeat shall be as follows:

Tight - 6
Slack - 4

3.4.3.2 Type II, classes 1 and 2. The stripe effect of the type II cloth shall be produced by using two warp beams, one tight and one slack. The color of the tight beam warp yarn shall be as specified (see 6.2). The slack beam warp yarn shall be natural or bleached. The two warps shall alternate in sections of tight and slack ends and each color pattern repeat shall be as follows:

Tight - 10
Slack - 12

The reeding plan shall produce a concentration of slack beam warp ends double that of the tight beam ends.

3.4.3.3 Type IIa, class 1. The stripe effect of the type IIa cloth shall be produced by using two warp beams, one tight and one slack. The color of the tight warp beam yarn shall be as specified (see 6.2). The slack beam warp yarn shall be natural or bleached. The two warps shall alternate in sections of tight and slack ends and each color pattern repeat shall be as follows:

Tight - 6
Slack - 8

The reeding plan shall produce a concentration of slack beam warp ends double that of the tight beam ends.

3.4.3.4 Type III, class 1. The pattern effect of the type III, class 1 cloth shall be produced by using two warp beams, one tight and one slack. The color of the slack beam warp yarn shall be as specified (see 6.2). The tight beam warp yarn shall be natural or bleached. The two warps shall alternate in sections of tight and slack ends and each color pattern repeat shall be as follows:

Tight beam -	16	16	16	16	16	8	8	8	8	
Slack beam -	12	12	12	12	24	24	24	24	24	

The warp reeding plans shall produce finished strips of the following widths:

Colored yarn 24 ends - 3/16 ± 1/32 inch
Colored yarn 12 ends - 3/32 ± 1/32 inch
Bleached yarn 8 ends - 3/32 ± 1/32 inch
Bleached yarn 16 ends - 3/16 ± 1/32 inch

The total width of each 280 end repeat shall be 2-5/8 ± 1/8 inch. The repeats of the patterns shall be balanced between the selvages.

3.5 Width. The width shall be as specified and shall be the minimum width inclusive of selvage (see 6.2).

3.6 Nonfibrous materials. The starch and protein content including chloroform-soluble and water-soluble material of the finished cloth shall not exceed 3 percent when tested as specified in 4.4.

3.7 Finish. The cloth shall be singed, desized and bleached. When bleached warp and filling yarns are used for the undyed yarns, yarn or piece bleaching is optional.

3.8 Acidity pH. The pH value of the water extract of dyed and finished cloth shall be not less than 5.5 nor more than 8.5 when tested as specified in 4.4

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

3.9 Shrinkage. The cloth shall be preshrunk so that the residual shrinkage shall be not more than 4 percent in the direction of the warp nor more than 3 percent in the direction of the filling when tested as specified in 4.4. The preshrinking process shall not be identified on the cloth, the ticket or on the package.

3.10 Length and put-up. Unless otherwise specified, the cloth shall be in one continuous piece of not less than 50 yards (see 6.2), and shall be put up in folded pieces as specified in PPP-P-1134.

3.11 Fiber identification. The material shall be labeled, ticketed or invoiced for fiber content in accordance with the Textile Fiber Products Identification Act.

3.12 Workmanship. The cloth shall conform to the quality established by this specification. The demerit points per 100 square yards when calculated as specified in section 4 shall not exceed the established maximum point value.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribe requirements.

4.1.1 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Inspection. Sampling for inspection shall be performed in accordance with MIL-STD-105, except when otherwise indicated hereinafter.

4.2.1 Component and material inspection. In accordance with 4.1 above, components and materials shall be tested in accordance with all the requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified or qualified in this specification or applicable purchase document. In addition, the supplier shall submit a certificate of compliance stating that cotton yarns were the only yarns used in the weaving of the cloth.

4.2.2 Examination of the end item. Examination of the end item shall be in accordance with 4.2.2.1 through 4.2.2.4.

4.2.2.1 Yard-by-yard examination. The entire yardage of each piece in the sample but not more than 100 yards per piece shall be examined on the face side. Defects as defined in section I of Fed. Std. No. 4 which are clearly noticable at normal inspection distance (3 feet) shall be scored and assigned demerit points as listed in 4.2.2.1.1, except that only those slubs and knots which exceed the maximum acceptable limits shown for each on figure 1 shall be scored. No folded linear yard shall be penalized more than 4 points. The sample size shall be 20 pieces selected from 20 containers. For determination of acceptability of the average quality of the lot, the lot shall be unacceptable if the points per 100 square yards exceed the following values:

Type I - 25.0 points
Type II - 25.0 points
Type IIa - 25.0 points
Type III - 25.0 points

For determination of acceptability on the individual piece quality basis, the lot shall be unacceptable if two or more individual pieces exceed the following values:

Type I - 38.0 points
Type II - 38.0 points
Type IIa - 38.0 points
Type III - 38.0 points

If no individual piece exceeds the point level, the lot shall be accepted. If one piece exceeds the point level, a second sample of 20 pieces shall be selected for individual piece quality examination only. If no piece in the second sample exceeds the point value, the lot shall be accepted. If one or more pieces exceed the value, the lot shall be rejected. For individual

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

piece quality examination local type defects only shall be scored. Overall type defects shall be scored only in determining compliance with the lot average quality requirement. Point computation for lot quality and individual piece quality shall be as follows:

$$\frac{\text{Total points scored in sample} \times 3600}{\text{Contracted width of cloth (inches)} \times \text{total yards inspected}} = \text{Points per 100 square yards}$$

4.2.2.1.1 Demerit points. Demerit points shall be assigned as follows:

For defects up to 3 inches in any dimension	- one point.
For defects exceeding 3 inches, but not exceeding 6 inches in any dimension	- two points.
For defects exceeding 6 inches, but not exceeding 9 inches in any dimension	- three points.
For defects exceeding 9 inches in any dimension	- four points.

The following defects, when present, shall be scored four points for each yard in which they occur:

Overall uncleanness.
Incorrect pattern i.e., color arrangement or width of stripes not as specified.
Pattern not centered against both selvages as specified.
Cloudy, streaky or mottled throughout the piece.
Uneven weaving throughout.
Selvage beaded, rolled, folded, or slack, continuously or intermittently for more than half the length of the piece.
Width beyond specified tolerances.

4.2.2.2 Examination for length.

4.2.2.2.1 Individual pieces. During the yard-by-yard examination, each piece in the sample shall be examined for length. Any length found to be less than the minimum specified or more than two yards less than the length marked on the ticket, shall be considered a defect with respect to length. The lot shall be unacceptable if two or more pieces in the sample are defective in respect to length.

4.2.2.2.2 Total yardage in sample. The lot shall be unacceptable if the total of the actual length of pieces in the sample is less than the total of the lengths marked on the tickets.

4.2.2.3 Examination for color and shade. During the yard-by-yard examination, each piece in the sample shall be examined for color and shade. Any piece in the sample off shade, shaded side to side, side to center, or end to end shall be caused for rejection of the entire lot represented by the sample.

4.2.2.4 Examination for identification of preshrinkage process and compliance with Textile Fiber Products Identification Act. During the yard-by-yard examination, each piece in the sample shall be examined for these defects. The lot shall be unacceptable if two or more pieces in the sample contain identification of preshrinkage process by name or trademark on the cloth or ticket or are not labeled, ticketed or the cloth invoiced (if appropriate) in accordance with the Textile Fiber Products Identification Act.

4.3 Examination of preparation for delivery requirements. An examination shall be made in accordance with the provisions of PPP-P-1134 to determine that packaging, packing and marking requirements of section 5 of this specification are complied with.

4.4 Testing of the end item. The methods of testing specified in CCC-T-191, wherever applicable and as listed in table II shall be followed. When the data in the "number of determinations" and "results reported as" columns are not specified in the table, they shall be as required by the referenced test method. The physical and chemical values specified in section 3 apply to the results of the determinations made on a sample unit for test purposes as specified in the applicable test method. All test reports shall contain the individual values utilized in expressing the final result. The sample unit shall be 3 yards full width of the finished cloth. The lot size shall be expressed in units of one yard. The lot size shall be unacceptable if one or more sample units fail to meet any test requirement specified. The sample size (number of sample units) shall be in accordance with the following:

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

Lot size (yards)	Sample size (units)
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

TABLE II. Test methods

Characteristic	Requirement Paragraph	Test method	Number of determinations	Results reported as
Material (cotton yarn)	3.2.1	1200 1/	—	—
Yarn ply	3.2.1	Visual 1/	1	Pass or fail
Weight in ounces per square yard	3.4	5041	—	—
Yarns per inch:				
Warp	3.4	5050	—	—
Filling	3.4	5050	—	—
Breaking strength pounds:				
Warp	3.4	5100	—	—
Filling	3.4	5100	—	—
Weave	3.4.1	Visual	1	Pass or fail
Take-up warp, percent	3.4.2	4110 2/	10	Average reported to nearest 0.1 percent
Warp pattern	3.4.3	Visual	1	Pass or fail
Test for sulfur dyes	3.3	2020	—	—
Colorfastness to:				
Light	3.3.2	5660	—	—
Combined laundering and bleaching	3.3.2	5605	—	—
Perspiration	3.3.2	5680	—	—
Crocking	3.3.2	5651	—	—
Nonfibrous material content	3.6	2611 1/	—	—
Acidity pH	3.8	2811	—	—
Shrinkage in laundering	3.9	5550	—	—

1/ A supplier shall submit a certificate of compliance for these characteristics. When required the certificate shall be accompanied by actual test inspection or other verifiable quality data.

2/ The following changes shall be incorporated in the test method:
a. Substitute the word "take-up" wherever the word "crimp" appears.
b. The test specimen shall be a slack warp yarn removed from a 14-inch length of cloth.
c. Delete the formula for percent crimp and substitute as follows:

$$\text{Take-up, percent} = \frac{L - 10}{L} \times 100$$

L = Total distance between marks under tension.

5. PREPARATION FOR DELIVERY

5.1 Packaging. Packaging shall be level A or C as specified (see 6.2).

5.1.1 Levels A and C. The cloth, put up as specified, shall be packaged in accordance with the applicable requirements of PPP-P-1134.

5.2 Packing. Packing shall be level A, B or C (see 6.2).

5.2.1 Levels A, B and C. The cloth shall be packed in accordance with the applicable requirements of PPP-P-1134.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

5.3 Marking. In addition to any special marking required by the contract or order, shipments shall be marked in accordance with PPP-P-1134.

6. NOTES

6.1 Intended use. The cloth covered by this specification is intended for use in bathrobes and clothing items.

6.2 Ordering data. Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

(a) Title, number, and date of this specification.
(b) Type and class of cloth required (see 1.2.1).
(c) Color of cloth required (see 3.3).
(d) Color of tight beam warp yarn (see 3.4.3.1 thru 3.4.3.3).
(e) Color of slack beam warp yarn (see 3.4.3.4).
(f) Width of cloth required (see 3.5).
(g) Length of piece if other than specified (see 3.10).
(h) Selection of applicable levels of packaging and packing (see 5.1 and 5.2).

6.3 Standard sample. For access to standard sample, address the procuring office issuing the invitation for bids.

6.4 For civil agency procurement. When level B packaging is required for civil agency procurement, the level A requirements shall apply.

MILITARY CUSTODIANS:

Army - GL
Navy - SA
Air Force - 82

Review activities:

Army - MD
Navy - SA
Air Force - 82, 85

User activity:

Navy - MS

Preparing activity:


Army - GL

CIVIL AGENCIES INTEREST:
COM - NBS
HEW -
JUS - FPI
VA - DMS
GSA - FSS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

Limits of Acceptability

Knot or Lump

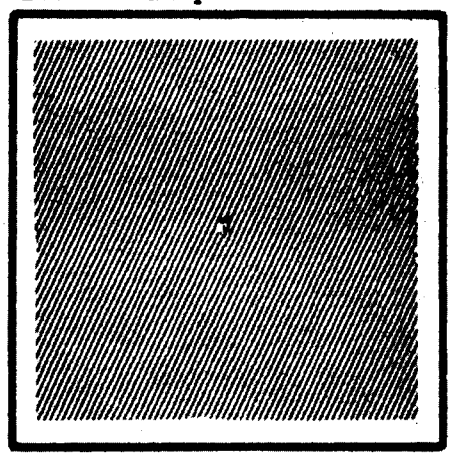

Yarn Thickening (Slub)

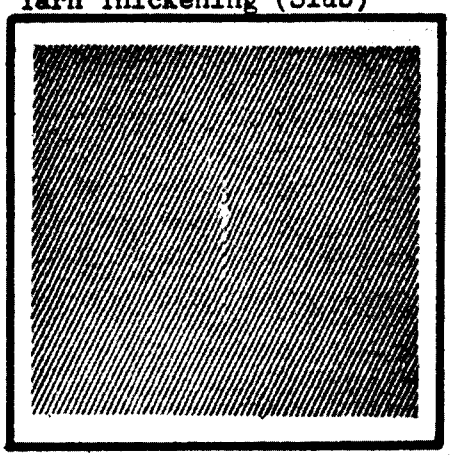


Figure 1.

Orders for this publication are to be placed with General Services Administration, acting as an agent for the Superintendent of Documents. See section 2 of this specification to obtain extra copies and other documents referenced herein. Price of this specification 5 cents each.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

SPECIFICATION ANALYSIS SHEET

Form Approved
Budget Bureau No. 22-R255

INSTRUCTIONS: This sheet is to be filled out by personnel, either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments and suggestions submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or serve to amend contractual requirements.

SPECIFICATION

Cloth, Seersucker, Cotton CCC-C-448c

ORGANIZATION

CITY AND STATE

CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?

☐ YES ☐ NO *(If "yes", in what way?)*

4. REMARKS *(Attach any pertinent data which may be of use in improving this specification. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity)*

SUBMITTED BY *(Printed or typed name and activity - Optional)*

DATE

DD FORM 1 JAN 66 1426

REPLACES EDITION OF 1 OCT 64 WHICH MAY BE USED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.