CCC-C-482B
August 20, 1968
SUPERSEDING
Fed. Spec. CCC-C-482A
October 23, 1964

FEDERAL SPECIFICATION

CLOTH, PRESSING, NYLON

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers the requirements for four types of nylon pressing cloth (see 6.1).

1.2 Classification.

1.2.1 Types. Nylon pressing cloth shall be of the following types as specified (see 6.2):

Type I - Spun yarn warp and filling.
Type II - Filament yarn warp and spun yarn filling.
Type III - Spun yarn warp and filament yarn filling.
Type IV - Filament yarn warp and filling.

2. APPLICABLE DOCUMENTS

2.1 Specifications and standards. The following specifications and standards of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

Federal Specifications:

P-S-579 - Soap, Laundry, Chip and Powdered.
UU-P-268 - Paper, Kraft, Untreated, Wrapping.
CCC-T-191 - Textile Test Methods.
PPP-B-636 - Box, Fiberboard.
PPP-P-1133 - Packaging and Packing of Synthetic Fiber Fabrics.
PPP-T-45 - Tape, Gummed, Paper, Reinforced and Plain, for Sealing and Securing.

Federal Standards:

Fed. Std. No. 4 - Glossary of Fabric Imperfections.

Fed. Std. No. 123 - Marking for Domestic Shipment (Civilian Agencies).

(Activities outside the Federal Government may obtain copies of Federal Specification, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington, D. C. 20402.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D. C., Atlanta, Chicago, Kansas City, Mo., Fort Worth, Denver, San Francisco, Los Angeles, and Seattle, Wash.

FSC 8305

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

Military Standard:

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following document forms a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

Rules and Regulations Under the Textile Fiber Products Identification Act.

(Copies may be obtained without charge from the Federal Trade Commission, Washington, D. C. 20580.)

3. REQUIREMENTS

3.1 Standard sample. When a standard sample is available, the finished cloth shall be equal to or better than the sample with respect to all characteristics for which the standard sample is referenced (see 6.4).

3.2 Material.

3.2.1 Nylon. The yarn used in the manufacture of the cloth shall be of cut staple or multifilament nylon as specified in 3.2.2, and shall be a polyamide prepared from hexamethylene diamine and adipic acid or its derivatives. The nylon shall have a melting point of 250° C + 6° C. When cut staple is used, the use of any form of nylon waste is prohibited, e.g., undrawn fiber, mixtures of deniers, lusters or cross sections, and waste from any stage of fiber production; whether drawn, undrawn or mixed or garnetted fiber. The supplier shall submit a fiber producer's certification that each lot of nylon staple used conforms to the requirements specified herein. Tests shall be as specified in 4.2.1.

3.2.2 Yarn.

3.2.2.1 Spun yarn. The nylon staple shall be drawn, spun and twisted into a 2-ply yarn for the warp of types I and III, and the filling of types I and II.

3.2.2.2 Filament yarn. The yarn for the warp of type II, the filling of type III, and the warp and filling of type IV shall be bright multifilament nylon.

3.3 Color. The color of the finished cloth shall be that shade imparted by the finish, provided the individual pieces are uniform in shade and the finished cloth meets the requirements as specified in 3.5 and 3.7.

3.3.1 Colorfastness. The finished cloth shall show colorfastness equal to or better than the standard sample when tested as specified in 4.4. When no standard sample is established the cloth shall show no staining of the test cloth when tested as specified in 4.4.

3.4 Physical requirements. The finished cloth shall conform to the minimum plysical requirements specified in table I, when tested as specified in 4.4.

TABLE I. Physical requirements

Type	Weight per square yard	Yarns per inch		Breaking strength	
		Warp	Filling	Warp	Filling
	Ounces			Pounds	Pounds
I	7.0	38	36	210	220
II	5.6	66	54	280	240
III	5.6	54	60	240	280
IV	3.6	60	42	250	180

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

3.4.1 Weave. The weave shall be plain for types I and IV and a 2 up and 1 down right twill for types II and III.

3.4.2 Width. The width of the finished cloth shall be a minimum of 54 inches, inclusive of selvage.

3.5 Finish. The cloth shall be heat treated at not less than 380° F. The heat treated cloth shall be given an additional resin or other type of finish to increase the heat resistant properties.

3.6 Slippage. The warp and filling yarns in the finished cloth shall show no slippage when tested as specified in 4.4.

3.7 Accelerated ageing. The finished cloth shall not lose more than 50 percent of the original breaking strength for both warp and filling when tested in accordance with breaking strength and ageing test as specified in 4.4.

3.8 Acidity (pH). The pH value of the finished cloth shall be no lower than 4.5 nor higher than 8.0 when tested as specified in 4.4.

3.9 Adherence. When exposed to a heated hand iron, the finished cloth shall not adhere to the iron when tested as specified in 4.4.

3.10 Dimensional stability. The finished cloth shall not shrink nor elongate more than 3.0 percent in the warp nor more than 2.0 percent in the filling when tested as specified in 4.4.

3.11 Length and put-up.

3.11.1 Rolls (military requirements). Unless otherwise specified (see 6.2), the cloth shall be furnished in continuous lengths, each not less than 50 yards. Each length shall be put-up on a full width roll as specified in PPP-P-1133.

3.11.2 Bolts (civil agencies). Approximately 50 continuous yards (plus or minus 5 percent) of cloth of the type specified shall be put up as flat folded pieces (bolts) in accordance with level A put-up of PPP-P-1133, or at the option of the supplier, the cloth may be put-up by winding on a flat chipboard or cardboard insert of not less than 1/8 inch thick by 12 ± 1/4 inches wide, by specified length.

3.12 Fiber identification. Each roll of cloth shall be labeled, ticketed, or invoiced for fiber content in accordance with the Rules and Regulations Under the Textile Fiber Products Identification Act.

3.13 Workmanship. The finished cloth shall conform to the quality established by this specification. The demerit points per 100 square yards when calculated as specified in section 4 shall not exceed the established maximum point value.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.1.1 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Inspection. Sampling for inspection shall be in accordance with MIL-STD-105, except where otherwise indicated hereinafter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

4.2.1 Component and material inspection. In accordance with 4.1 above, components and materials shall be tested in accordance with all the requirements of referenced specifications, drawings and standards unless otherwise excluded, amended, modified or qualified in this specification or applicable procurement documents. In addition, components and materials listed in table II shall be tested for the characteristics specified and in accordance with the referenced test methods of CCC-T-191. The lot size shall be expressed in pounds, and the sample unit shall be 500 yards of the yarn. The lot shall be unacceptable if one or more units fail to meet any requirement specified. All test reports shall contain the individual values utilized in expressing the final result. The sample size shall be as follows:

Lot size (pounds)	Sample size
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

TABLE II. Testing of components

Characteristic	Requirement paragraph	Test method
Material identification	3.2.1	1/
Melting point	3.2.1	1534 1/
Absence of any form of nylon waste	3.2.1	3/
Ply and staple yarns	3.2.2	Visual 2/
Filament	3.2.2	Visual 2/
Luster	3.2.2	1/

1/ Unless otherwise specified, a supplier's certificate of compliance shall be required for this characteristic. The certificate shall be accompanied by actual test inspection or other verifiable data.

2/ One determination shall be made from each sample unit and the results reported as "pass" or "fail".

3/ The supplier shall furnish a certificate of compliance furnished by the fiber producer that each lot of nylon staple used conforms to the requirements.

4.2.2 Examination of the end item. Examination of the end item shall be in accordance with 4.2.2.1 through 4.2.2.3.

4.2.2.1 Yard-by-yard examination. Each roll in the sample shall be examined on the face side only. When the total yardage in the roll does not exceed 100 yards, the entire yardage in the roll shall be examined. When the total yardage in the roll exceeds 100 yards, only 100 yards shall be examined. All defects as defined in Section III of Fed. Std. No. 4, which are clearly noticeable at normal inspection distance (3 feet) shall be scored and assigned demerit points as listed in 4.2.2.1.1 (except that only those slubs and knots which exceed the limits shown in figure 1 shall be scored). No linear yard (increments of one yard on the measuring device of the inspection machine) from any one roll or bolt within the sample shall be penalized more than 4 points. The sample size shall be 20 rolls or bolts selected from 20 containers. The lot shall be unacceptable if the points per 100 square yards of the total yardage examined exceeds the following point values:

Types I, II and III - 35.0 points.
Type IV - 30.0 points.

The lot shall be unacceptable if the points per 100 square yards of two or more individual rolls or bolts exceed the following point values:

Types I, II and III - 53.0 points.
Type IV - 45.0 points.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

If no individual roll or bolt exceeds the point level, the lot shall be acceptable with respect to this characteristic. If one roll or bolt exceeds the point level, a second sample of 20 rolls or bolts shall be examined only for individual roll or bolt quality examination. The lot shall be unacceptable if one or more rolls or bolts in the second sample exceeds the point level. For individual roll or bolt quality, examination of local defects only shall be scored. Overall type defects shall be scored only in determining compliance with the lot average quality requirements. Point computation for lot quality and individual roll quality shall be as follows:

$$\frac{\text{Total points scored in sample} \times 3600}{\text{Contracted width of cloth (inches)} \times \text{total yards inspected}} = \text{Points per 100 square yards}$$

4.2.2.1.1 Demerit points. Demerit points shall be scored as follows:

For defects up to 3 inches in any dimension	- one point.
For defects exceeding 3 inches, but not exceeding 6 inches in any dimension	- two points.
For defects exceeding 6 inches, but not exceeding 9 inches in any dimension	- three points.
For defects exceeding 9 inches in any dimension	- four points.

The following defects, when present, shall be scored four points for each yard in which they occur:

Shade other than natural or not within specified shade range, or not uniform.
Baggy, ridgy or wavy cloth.
Objectionable odor.
Width less than specified.
Overall uncleanness.

4.2.2.2 Examination for length.

4.2.2.2.1 Individual rolls or bolts. During the yard-by-yard examination, each roll or bolt in the sample shall be examined for length. Any length found to be less than the minimum specified or more than two yards less than the length marked on the ticket shall be considered a defect with respect to length. The lot shall be unacceptable if two or more rolls or bolts in the sample are defective in respect to length.

4.2.2.2.2 Total yardage in sample. The lot shall be unacceptable if the total of the actual lenghts of rolls or bolts in the sample is less than the total of the lengths marked on the ticket.

4.2.2.3 Examination for compliance with Textile Fiber Products Identification Act. During the yard-by-yard examination, each roll or bolt in the sample shall be examined for conformance with the Textile Fiber Products Identification Act. Each roll or bolt not labeled in accordance with this act shall be a defect. The lot shall be unacceptable if two or more of these defects occur.

4.3 Examination of preparation for delivery requirements. An examination shall be made in accordance with the provisions of PPP-P-1133 to determine that packaging, packing and marking requirements of section 5 of this specification are complied with.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

4.4 Testing of the end item. The methods of testing specified in CCC-T-191, wherever applicable and as listed in table IV shall be followed. The physical and chemical values specified in section 3 apply to the results of the determinations made on a sample unit for test purposes as specified in the applicable test method. The sample unit shall be 3 continuous yards full width of the finished cloth. The sample size shall be as listed in table III. The lot size shall be expressed in units of 1 yard. The lot shall be unacceptable if one or more sample units fail to meet any requirement specified. All test reports shall contain the individual values utilized in expressing the final results.

TABLE III. Sample size

Lot size (units)	Sample size
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

TABLE IV. Test methods

Characteristic	Requirement paragraph	Test method
Colorfastness to pressing	3.3.1	4.4.1 1/
Weight	3.4	5041
Yarns per inch:		
Warp	3.4	5050
Filling	3.4	5050
Breaking strength:		
Initial:		
Warp	3.4	5100
Filling	3.4	5100
After accelerated ageing:		
Warp	3.7	5100 and 4.4.2
Filling	3.7	5100 and 4.4.2
Weave	3.4.1	Visual 1/
Finish	3.5	2/
Yarn slippage	3.6	5410 3/
Acidity (pH)	3.8	2811
Adherence	3.9	4.4.3 1/
Dimensional stability	3.10	4.4.4

1/ One determination shall be made from each sample unit and the results reported as "pass" or "fail".

2/ The supplier shall submit a certificate of compliance indicating that the cloth was heat treated at not less than 380°F and that a resin or other type finish was added to increase the heat resistance properties. The certificate shall be accompanied by actual tests, inspection or other verifiable data.

3/ The general procedure of method 5410 shall be followed except that the evaluation shall be by visual examination for evidence of yarn slippage. Any yarn slippage observed shall be considered as a test failure.

4.4.1 Colorfastness to pressing. The colorfastness to pressing of the finished cloth shall be determined as follows:

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

4.4.1.1 Specimen. The specimen shall be a strip 1 inch by 10 inches long cut from the nylon cloth.

4.4.1.2 Apparatus. A wooden block 6 inches wide by 12 inches long and 2 inches thick shall be drilled across the width approximately 1 inch from each end to accommodate two bolts, threaded on both ends, for wing nuts. Two metal bands, 1 inch wide by 12 inches long, with holes drilled to fit the bolt positions, shall be placed on either lengthwise side. The wooden block shall be covered over the top with a cotton roving pad to simulate the buck of a press. The top of the roving pad shall be covered with the standard six-fiber repeat test cloth consisting of a warp of polyester fiber or orlon 81 and a six-fiber filling with equal bars of wool, spun nylon, spun rayon, spun silk, spun acetate and bleached cotton. The strip of nylon cloth shall be placed over the test cloth. Secure the strip by means of the metal bands and tighten the wing nuts.

4.4.1.3 Procedure. The whole apparatus shall be exposed in a circulating hot air oven at 176°C ± 2°C for 15 minutes and then removed. The specimen shall be covered immediately with a cotton strip cloth saturated with distilled water and pressed with a hand iron, having a temperature of 325°F to 350°F for 45 seconds. The water saturated cloth shall be removed and replaced with another cotton cloth strip that has been saturated in soap solution conforming to P-S-579, type I. The stock solution of the soap may be prepared by dissolving 1 pound of chip soap in 1 gallon of hot water containing 0.3 percent available chlorine. The soap saturated test cloth shall be placed over the specimen and covered with dry cloth and pressed as specified above. The soap saturated cloth shall be removed and the specimen covered with a cotton cloth saturated in a 5 percent boiling starch solution having 0.3 percent available chlorine, over which a dry cotton cloth shall be placed and pressed as specified above. The apparatus shall be unclamped and the multifiber test cloth examined for stains. One determination shall be made from each sample unit. Report staining or no staining of test cloth.

4.4.2 Resistance to ageing. The test specimens of cloth for determining resistance to ageing shall be so selected that the identical warp and filling yarns are tested originally and after subjection to ageing. This shall be done by marking all the specimens required before cutting. The specimens shall be so cut and marked that specimens in each group, warp and filling, for original breaking strength and for resistance to ageing shall contain the identical yarns.

4.4.2.1 Procedure. Five warp and five filling tests shall be made. The test specimens shall be exposed in the accelerated ageing unit as specified in method 5850 of CCC-T-191. The specimens shall be exposed in the oven for 5 hours at a temperature of 176°C ± 2°C. After removal from the oven, the specimens shall be brought to equilibrium under Standard Condition as defined in CCC-T-191. They shall then be tested for breaking strength as specified in table IV and the percent of breaking strength (B.S.) lost shall be calculated as follows:

$$\text{Percent of B.S. lost} = \frac{\text{original B.S - B.S. after ageing x 100}}{\text{original B.S.}}$$

4.4.3 Adherence. A sample of the finished cloth 5 ± 0.5 inches square shall be placed on a flat surface. A heated hand iron, which has not been treated with any antistick agent such as wax, weighing 4 to 5 pounds and having a temperature of 325°F to 350°F shall be placed stationary under its own weight on the sample for 60 seconds. At the end of this period the iron is lifted and observed for adherence of material to the pressing surface of the iron. Material shall be considered as failing the adherence test if the sample adheres to the iron when the iron is lifted off the flat surface.

4.4.4 Dimensional stability. Three specimens shall be selected from the cloth sample unit as follows: One specimen from each side of the cloth to within three inches of the selvage and one specimen from the center of the cloth. No two specimens shall contain the same filling yarns. Each specimen, 20 inches square, shall be cut from the cloth and conditioned for 4 hours in an atmosphere having a relative humidity of 65 ± 2 percent and a temperature of 70°F ± 5°F. Each specimen shall have an 18 inch square mark off and then formed into a loop by stapling two opposite sides together. A glass rod 1/2 inch in diameter and 21 inches long shall be placed inside the loop at the top, and a glass rod 1/4 inch in diameter and 21 inches long weighing approximately 100 grams shall be placed inside the loop at the bottom. Each specimen shall be immersed in a tub of boiling water by attaching twine or wire to the ends of the top glass rod and allowing the specimen to hang freely in the boiling water for 15 minutes. Each specimen shall be removed and allowed to drain. After the staples are removed, each specimen shall be dried in a flat position on a horizontal screen and reconditioned as stated above.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

The marked square shall be measured in three places in the warp direction and three places in the filling direction and the percent of dimensional stability determined. The dimensional stability of the sample unit shall be calculated as follows and reported to nearest 0.1 percent:

$$\text{Dimensional stability, percent} = \frac{A - B}{A} \times 100$$

A = Average of initial measurements (3 specimens)
B = Average of measurements after immersion and reconditioning (3 specimens)

The shrinkage of the sample unit in the warp direction and the filling direction shall be average of the specimens tested from each direction respectively, and shall be reported separately to the nearest 0.1 percent. When a test result registers elongation rather than shrinkage, each elongation result shall be prefixed with a minus sign and inclosed in parenthesis.

5. PREPARATION FOR DELIVERY

5.1 Packaging. Packaging shall be level A or C as specified (see 6.2 and 6.2.1).

5.1.1 Military agencies.

5.1.1.1 Levels A and C. The cloth put up as specified, shall be packaged in accordance with the applicable requirements of PPP-P-1133.

5.1.2 Civil agencies.

5.1.2.1 Level B (standard pack). Cloth, put up in bolts as specified, shall be completely wrapped in a 30-pound minimum basis weight kraft paper conforming to grade B of UU-P-268. The bolt shall be so wrapped that the paper encircles the bolt twice with the width of paper sufficient to fold over and protect the ends of the bolt. The wrapping shall be secured with 2-1/2 inch minimum width gummed paper tape conforming to type III, grade C of PPP-T-45, applied over the folded ends of wrapping, centered approximately to the width of the bolt. Wrapping shall be applied in a manner which shall permit the bolt identification tag attached to selvage of material to be on the outside of the wrapped bolt.

5.2 Packing. Packing shall be level A, B or C as specified (see 6.2 and 6.2.1).

5.2.1 Military agencies.

5.2.1.1 Levels A, B and C. The cloth shall be packed in accordance with the applicable requirements of PPP-P-1133.

5.2.2 Civil agencies.

5.2.2.1 Level B (standard pack). Bolts of cloth packaged as specified in 5.1.2, shall be packed in fiberboard containers conforming to type CF (variety DW) or SF, class domestic, style FTC, FOL, SFF or RSC-L of PPP-B-636, except that in no event shall the gross weight of box and contents exceed 90 pounds, nor the burst test of the fiberboard be less than grade 275. Sleeve liner for RSC-L boxes shall be not less than grade 175, and the top and bottom full width by full length fiberboard pads shall test not less than grade 125. Box closure shall be in accordance with appendix of the box specification. According to weight of wrapped bolts; 12 bolts of up to 6 pounds each, 8 bolts of up to 10 pounds each, 6 bolts of from 11 to 14 pounds each, 4 bolts of from 15 to 21 pounds each, 3 bolts of from 22 to 28 pounds each, 2 bolts of from 29 to 42 pounds each, or one bolt of over 43 pounds shall be packed per shipping container. Containers of 6 to 12 bolts shall be packed with bolts in 2 stacks side by side, 4 bolts or less shall be in a single stack within the container.

5.3 Marking.

5.3.1 Military agencies. In addition to any special marking required by the contract or order, shipments shall be marked in accordance with the applicable requirements of PPP-P-1133.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

5.3.2 Civil agencies. Each bolt shall be provided with an identification tag on the outside of the wrapping. No other marking is required for the individual bolts. Each shipping container shall be marked in accordance with Fed. Std. No. 123 with the additional precautionary markings as follows:

On each side panel: "DO NOT STAND ON END" in 1-inch letters.

For quantity contained: "....BOLTS - Total Yardage....yds." indicating total number of bolts and total yardage contained.

6. NOTES

6.1 Intended use. Nylon pressing cloth is intended for use as covers for flat bed laundry presses.

6.2 Ordering data. Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

(a) Title, number and date of this specification.
(b) Type required (see 1.2).
(c) When verification of melting point is required (see 3.2.1 and 4.2.1).
(d) Length, if other than specified (see 3.11).
(e) Selection of applicable levels of packaging and packing (see 5.1 and 5.2).

6.2.1 In the preparation of contracts or orders, it must be noted that various options, choices and alternatives as indicated in PPP-P-1133 may be exercised in the preparation for delivery of cloth.

6.3 Civil agencies. The standard pack requirements in 5.1.2 and 5.2.2 cover packaging and packing for bolts of cloth approximating 50 continuous yards in length and are intended for use in stores stock replenishments. Procuring officers should use the standard pack requirements when it is known that the cloth approximating 50 continuous yards in length will be shipped from supplier to a domestic warehouse, supply depot or intermediate storage point for temporary storage, subsequent issue or shipment to eventual user.

6.4 Standard sample. For access to standard sample, address the procuring office issuing the invitation for bids.

MILITARY CUSTODIANS:

Army - GL
Navy - SA
Air Force - 11

Review activities:

Army - MD
Navy - SA
Air Force - 82, 84, 85

User activity:

Navy - YD


Preparing activity:


Army - GL

CIVIL AGENCIES INTEREST:

AGR
COM-NBS
DC
GSA-FSS
PO
TR
VA-DMS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

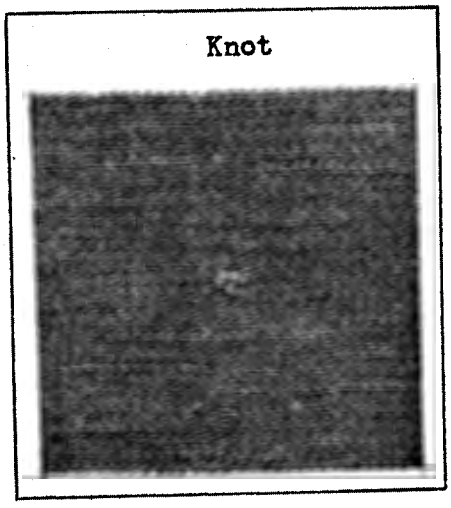

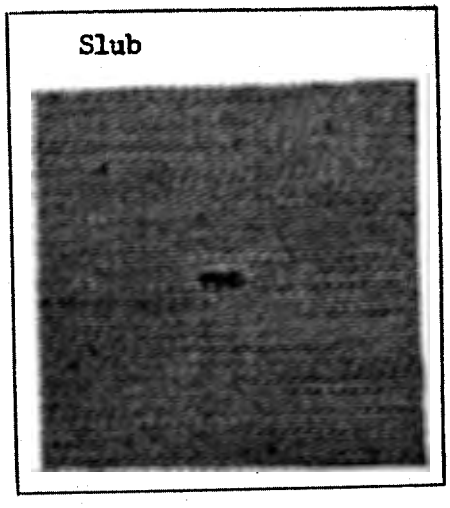

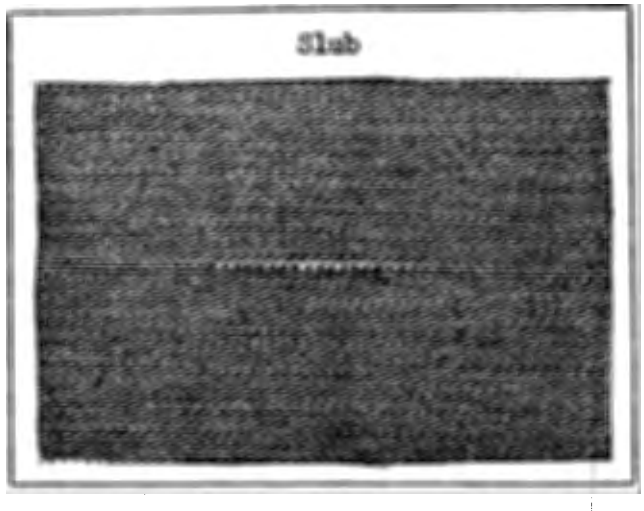


FIGURE 1

Orders for this publication are to be placed with General Services Administration, acting as an agent for the Superintendent of Documents. See section 2 of this specification to obtain extra copies and other documents reference herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

SPECIFICATION ANALYSIS SHEET

Form Approved
Budget Bureau No. 22-R255

INSTRUCTIONS: This sheet is to be filled out by personnel, either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments and suggestions submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or serve to amend contractual requirements.

SPECIFICATION

Cloth, Pressing, Nylon - CCC-C-482b

ORGANIZATION

CITY AND STATE	CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?

☐ YES ☐ NO *(If "yes", in what way?)*

4. REMARKS *(Attach any pertinent data which may be of use in improving this specification. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity)*

SUBMITTED BY *(Printed or typed name and activity - Optional)*	DATE

DD FORM 1 JAN 66 1426 REPLACES EDITION OF 1 OCT 64 WHICH MAY BE USED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.

FOLD

DEPARTMENT OF THE ARMY
U. S. Army Natick Laboratories
Natick, Massachusetts 01760

POSTAGE AND FEES PAID
DEPARTMENT OF THE ARMY

OFFICIAL BUSINESS

Commanding General
U. S. Army Natick Laboratories
ATTN: AMXRES-EQS
Natick, Massachusetts 01760

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:30Z
Check the source to verify that this is the current version before use.