INTERIM FEDERAL SPECIFICATION

SHEARS AND SCISSORS

This Interim Federal Specification was developed by the Standardization Division, Federal Supply Service, General Services Administration, Washington, D. C. 20407, based upon currently available technical information. It is recommended that Federal agencies use it in procurement and forward recommendations for changes to the preparing activity at the address shown above.

1. SCOPE AND CLASSIFICATION

1.1 Scope.- This specification covers shears and scissors generally used for various cutting, trimming, and clipping tasks.

1.1.1 Federal specification coverage.- Federal specifications do not include all varieties of the commodity as indicated by the title of the specification, or which are commercially available, but are intended to cover only those generally used by the Federal Government.

1.2 Classification.

1.2.1 Types, classes, designs, and styles.- The shears and scissors covered by this specification shall be of the following types, classes, designs, and styles, as specified (see 6.2):

Type I. - Shears.
- Class 1. - Straight trimmers.
  - Design 1. - Paper or Stationers'.
    - Style A - Heavy duty.
    - Style C - Light duty.
  - Design 2. - Household or Industrial.
    - Style A - Heavy duty.
    - Style C - Light duty.
- Class 2. - Bent trimmers.
  - Style A - Heavy duty.
  - Style C - Light duty.
- Class 3. - Pinking.
  - Style A - Heavy duty.
  - Style B - Light duty.
- Class 4. - Tailors' (Sailmakers').
- Class 5. - Barbers'.

Type II. - Scissors
- Class 1. - Embroidery.
  - Style A - Heavy duty.
  - Style B - Light duty.
- Class 2. - Ladies' (sewing).
  - Style A - Heavy duty.
  - Style B - Light duty.
- Class 3. - Pocket.
  - Style A - Heavy duty.
  - Style B - Light duty.

Source: https://assist.dla.mil -- Downloaded: 20261O-26T12:38Z
Check the source to verify that this is the current version before use.

Class 4. - Manicure, curved blades.
Class 5. - Manicure, straight blades.
Class 6. - Electricians'.

1.2.2 Sizes.- Shears and scissors shall be of the sizes shown in Tables I - XII.

2. APPLICABLE SPECIFICATIONS, STANDARDS, AND OTHER PUBLICATIONS

2.1 Specifications and standards.- The following specifications and standards, of the issues in effect on date of invitation for bids, form a part of this specification:

Federal Standards:

Fed. Std. No. 102 - Preservation, Packaging, and Packing Levels.
Fed. Std. No. 123 - Marking for Domestic Shipment (Civilian Agencies).
Fed. Test Method Std. No. 151 - Metals; Test Methods.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U.S. Government Printing Office, Washington, D.C. 20402.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D.C., Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, Los Angeles, and Seattle, Wash.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

Military Specification:

MIL-H-15424 - Hand Tools; Packaging of.

Military Standards:

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 - Marking for Shipment and Storage.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications.- The following publication, of the issue in effect on date of invitation for bids, unless otherwise stated, forms a part of this specification:

Governmental:

National Bureau of Standards Handbook:
H28 - Screw-Thread Standards for Federal Services.

(Copies of the National Bureau of Standards Handbook may be obtained upon application, accompanied by money order, coupon, or cash to the Superintendent of Documents, Government Printing Office, Washington, D. C. 20402. Price may be obtained from the Superintendent of Documents.)

3. REQUIREMENTS

3.1 Illustrations.- The illustrations shown herein are for the convenience of identification, and are not intended to preclude the purchase of shears or scissors which are otherwise in accordance with this specification.

3.2 Materials.- Materials used in the construction of shears and scissors shall be of the highest commercial quality, fully suited for each particular application and as specified herein. Materials shall be free from any defects and imperfections which might affect the serviceability of the finished product.

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:38Z
Check the source to verify that this is the current version before use.

3.3 Threaded parts.- Threaded parts shall be in conformance with the applicable requirements of National Bureau of Standards Handbook H28, and latest supplement thereto.

3.4 Identification marking.- Each pair of shears or scissors shall be marked in a plain and permanent manner with the manufacturer's name or with a trademark of such known character that the source of manufacture may be readily determined.

3.5 Coatings.- Unless otherwise specified (see 6.2), shears and scissors shall be coated with one of the following coatings, at the option of the manufacturer:

(a) Japanned handles with chrome-plated blades.
(b) Fully nickel-plated blades and handles.
(c) Fully chrome-plated over nickel-plated blades and handles.
(d) Japanned handles with nickel-plated blades.
(e) Japanned handles with chrome-plated over nickel-plated blades.

3.5.1 Chromium plate.- The coating shall be electrodeposited coating of chromium not less than 0.00001 inch thick.

3.5.2 Nickel plate.- The coating shall be electrodeposited coating of nickel not less than 0.0002 inch thick.

3.5.3 Chromium over nickel plate.- The coating shall be electrodeposited metals consisting of nickel, followed by chromium, the minimum thickness being 0.0002 inch for nickel and 0.00001 inch for chromium.

3.6 Blades.

3.6.1 Blade hardness.- Unless otherwise specified herein (see 3.9.3 and 3.10.3.2), the blade hardness of all shears and scissors shall show a hardness on the Rockwell "C" scale of not less than 52 nor more than 61 when tested as specified in 4.4.2 and 4.4.2.1.

3.6.2 Joining blades of type I shears.- Blades of type I shears shall be joined by a steel bolt or screw except for type I, class 2 bent trimmers (10 and 12 inch sizes), class 3 pinking shears, and class 4 tailor's shears, where a steel bolt with nut shall be used.

3.6.3 Joining blades of type II scissors.- Blades of type II scissors shall be joined by a steel bolt or screw except type II, class 3, style B pocket scissors which shall be joined by a square-shouldered rivet locked in one blade or other suitable means.

3.6.4 Blade adjustments.- Shears and scissors shall be adjusted for proper contact along the entire length of the blade cutting edges. The pressure between the blades shall not be such as to cause binding, the shears and scissors shall work smoothly with a minimum of effort, and there shall be no rough spots, blemishes, or other defects observed when cutting tests are conducted as specified in 4.5.1. Type I, class 4 tailors' shears shall be provided with a means for adjusting the pressure between the blades.

3.7 Length of cut.- The minimum length of cut shall be as specified in tables I - XII and shall be defined as the cutting edge of blades measured from the outer end of the blade (tip) to the point at which the blades cross one another in the fully opened position.

3.8 Handles.- Unless otherwise specified, handles shall be designed for a right-hand operator.

3.8.1 Type I shears.- All type I shears shall be furnished with the large or handgrip all-metal handles (fingers and thumb bows) except type I, class 5 which shall have double rings and a finger rest on one handle.

3.8.2 Type II scissors.- All type II scissors shall be furnished with either double-ring or symmetrical all-metal bow handles.

3.9 Type I shears.

3.9.1 Type I, class 1, straight trimmers, design 1 and design 2.- Design 1 shears shall have both blades pointed or when specified (see 6.2) one blade pointed and one beveled. Design 2 shears shall have the blade with the thumb ring pointed and the other blade beveled.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:38Z
Check the source to verify that this is the current version before use.

3.9.1.1 Design 1, paper or stationers', style A, heavy duty.- Design 1, style A heavy duty shears shall be of steel, forged, and of either inlaid or solid steel construction. When inlaid construction is used, the inlaid piece for each blade shall be high carbon steel having .85 percent carbon (minimum) and securely joined by welding to the blade and handle forming a single integral unit. When solid steel construction is used, blades and handles shall be of one of the following: (1) High carbon steel having .65 percent carbon (minimum); (2) Alloy steel with a minimum carbon content of .50 percent (i.e. AISI 4150). Matching points on the blades of a pair of shears shall be within four points (hardness). Design 1, style A shears shall conform to table I and be similar to figure 1.

Table I, type I, class 1, design 1, styles A & C
straight trimmers, paper or stationers'

	Style A Forged		Style C Forged	
Overall Length Nominal (inches)	Min. Length of cut (inches)	Minimum Wt. per dozen (pounds)	Min. Length of cut (inches)	Minimum Wt. per dozen (pounds)
9	4-5/8	3	4-1/2	4
10	5-1/2	4-1/4	5	4-1/2
12	6-3/4	7	6-3/4	6-1/2
14	8-1/2	9	---	---



Figure 1. - Type I, class 1, design 1,
styles A and C, straight trimmer,
paper or stationers'

3.9.1.2 Design 1, paper or stationers', style C, light duty.- Design 1, style C , light duty shears shall be of either cold-forged steel or cast metal construction, if available in both materials (see tables). When of cold-forged steel construction, shears shall be of carbon steel having a minimum of .10 percent carbon. Shears shall have all flash removed and blades shall be properly case hardened and tempered to a depth of .015 minimum. When of cast construction, shears shall be of ferrous alloy having a minimum of 3.0 percent carbon and 2.2 percent silicon. Shears shall be free from pinholes, cracks, blow holes and blades shall be chilled on the flat survace. Hardness readings shall be taken on the superficial hardness tester and when converted, shall conform to the Rockwell "C" range specified in 3.6.1. Design 1, style C shears shall conform to table I and be similar to figure 1.

3.9.1.3 Design 2, household or industrial, style A, heavy duty.- Design 2, style A, heavy duty shears shall be as specified in 3.9.1.1 except design 2 shears shall conform to table II and be similar to figure 2.

Table II, type I, class 1, design 2, styles A & C, straight
trimmers, household or industrial

	Style A Forged		Style C Forged or Cast	
Overall Length Nominal (inches)	Min. Length of cut (inches)	Minimum Wt. per dozen (pounds)	Min. Length of cut (inches)	Minimum Wt. per dozen (pounds)
6	2-1/2	1-1/2	2-5/8	1-3/4
7	3	1-3/4	3	2-1/2
8	3-5/8	2-7/8	3-5/8	3
9	4	5	4	5

Source: https://assist.dla.mil -- Downloaded: 202640-26T12:38Z
Check the source to verify that this is the current version before use.



Figure 2. - Type I, class 1, design 2, styles A and C, straight trimmer, household or industrial

3.9.1.4 Design 2, household or industrial, style C, light duty.- Design 2, style C, light duty shears shall be as specified in 3.9.1.2 except design 2 shears shall conform to table II and be similar to figure 2.

3.9.2 Type I, class 2, bent trimmers.- Bent trimmers shall be designed with bent handles and shall have either, both blades pointed, or when specified (see 6.2) the blade with the thumb ring shall be pointed and the other blade beveled.

3.9.2.1 Style A, heavy duty.- Style A, heavy duty shears shall be specified in 3.9.1.1 except style A shears shall conform to table III and be similar to figure 3.

Table III, type I, class 2, styles A & C bent trimmers.

Overall length Nominal (inches)	Style A Forged		Style C Forged or Cast	
	Min. length of cut (inches)	Minimum Wt. per dozen (pounds)	Min. length of cut (inches)	Approx. Wt. per dozen (pounds)
7	3-1/8	2-1/4	3-1/8	2-1/2
8	3-1/2	3	3-1/2	3
9	4	5-1/4	---	---
1/ 10	4-3/4	6-1/4	---	---
12	5-7/8	10-3/4	---	---

1/ For left hand operation when specified (see 6.2)

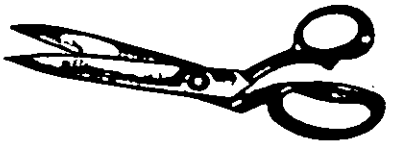


Figure 3. - Type I, class 2, styles A & C bent trimmer shears.

Source: https://assist.dla.mil -- Downloaded: 202640-26T12:38Z
Check the source to verify that this is the current version before use.

3.9.2.2 Style C.- Style C, light duty shears shall be as specified in 3.9.1.2 except style C shears shall conform to table III and be similar to figure 3.

3.9.3 Type I, class 3, pinking shears.- Pinking shears shall be designed to leave scalloped edges (to prevent unraveling of cloth). Blades shall show a hardness on the Rockwell "C" scale of not less than 20. Both blades shall be blunt.

3.9.3.1 Style A, heavy duty.- Style A, heavy duty shears shall be of forged solid steel having a minimum carbon content of 0.20 percent. Style A shears shall conform to table IV and be similar to figure 4.

Table IV, type I, styles A & B, pinking shears.

	Style A Forged		Style B Forged or Cast	
Overall length Nominal (inches)	Min. length of cut (inches)	Minimum Wt. per dozen (pounds)	Min. length of cut (inches)	Minimum Wt. per dozen (pounds)
7-1/2	2-5/8	4-7/8	2-5/8	4-7/8
9	3-1/2	5-3/4	---	---
11	3-7/8	8-3/4	---	---



Figure 4. - Type I, class 3 styles A & B, pinking shears.

3.9.3.2 Style B, light duty.- Style B, light duty shears shall be as specified in 3.9.1.2 except the Rockwell hardness shall be as specified in 3.9.3. Style B shears shall conform to table IV and be similar to figure 4.

3.9.4 Type I, class 4, tailors' (sailmakers). Sailmakers shears shall have the blade with the thumb ring pointed and the other blade either beveled or blunted. Class 4 shears shall be as specified in 3.9.1.1 except class 4 shears shall conform to table V and be similar to figure 5.

Table V. - Type I, class 4, tailors' (sailmakers').

Overall Nominal Length (inches)	Minimum Length of cut (inches)	Minimum weight per dozen (pounds)
12	6	14

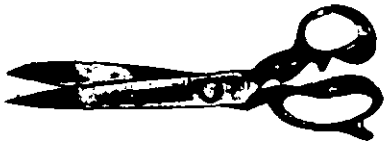


Figure 5. - Type I, class 4, tailors' (sailmakers') shears.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:38Z
Check the source to verify that this is the current version before use.

3.9.5 Type I, class 5, barbers'.- Barbers' shears shall be designed with both blades pointed. Class 5 shears shall be forged from solid steel with a minimum carbon content of .60 percent. Class 5 shears shall conform to table VI and be similar to figure 6.-

Table VI. - Type 1, class 5, barbers' shears.

Overall Nominal Length (inches)	Minimum length of cut (inches)	Minimum weight per dozen (pounds)
7-1/2	3-1/4	1-1/2



Figure 6. - Type 1, class 5, barbers' shears.

3.10 Type II, scissors.- All type II scissors shall be forged of steel.

3.10.1 Type II, class 1, embroidery.- Class 1, embroidery scissors shall be designed with both blades pointed.

3.10.1.1 Style A, heavy duty.- Style A, heavy duty scissors shall be forged from solid steel with a minimum carbon content of .55 percent. Style A scissors shall conform to table VII and be similar to figure 7.

Table VII, Type II, class 1, styles A and B embroidery scissors

	Style A		Style B	
Overall length Nominal (inches)	Min. length of cut (inches)	Minimum wt. per dozen (pounds)	Min. length of cut (inches)	Minimum wt. per dozen (pounds)
4	1-3/8	3/8	1-3/8	5/8
4-1/2	1-3/4	5/8	1-3/4	1
5	2	3/4	2	1-3/8
6	2-3/8	1-1/4	2-3/8	1-7/8

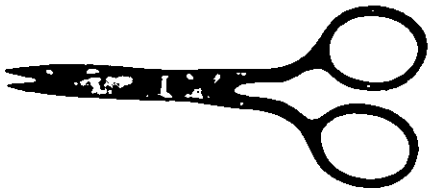


Figure 7.-Type II, class 1, embroidery Scissors

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:38Z
Check the source to verify that this is the current version before use.

3.10.1.2 Style B, light duty.- Style B, light duty scissors shall be forged from steel having a minimum of .10 percent carbon content. Scissors shall have all flash removed and blades shall be properly case hardened and tempered to a depth of .015 inch thick minimum. Style B scissors shall conform to table VII and be similar to figure 7.

3.10.2 Type II, class 2, ladies (sewing).- Class 2 "sewing" or "trimming" scissors shall be designed with one blade pointed and the other blade blunted.

3.10.2.1 Style A, heavy duty.- Style A, heavy duty scissors shall be as specified in 3.10.1.1 except style A scissors shall conform to table VIII and be similar to figure 8.

Table VIII. Type II, class 2, styles A and B, ladies (sewing) scissors.

	Style A		Style B	
Overall length Nominal (inches)	Min. length of cut (inches)	Minimum wt. per dozen (pounds)	Min. Length of cut (inches)	Minimum wt. per dozen (pounds)
4	1-5/8	1/2	---	---
5	2-1/4	7/8	2-1/16	1-3/8
6	2-5/8	1-3/8	---	---

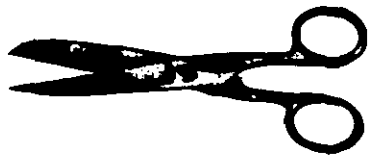


Figure 8. - Type II, class 2, styles A & B ladies' (sewing) scissors.

3.10.2.2 Style B, light duty.- Style B, light duty scissors shall be as specified in 3.10.1.2 except style B scissors shall conform to table VIII and be similar to figure 8.

3.10.3 Type II, class 3, pocket.- Class 3 pocket scissors shall be designed with the points of both blades rounded.

3.10.3.1 Style A, heavy duty.- Style A, heavy duty scissors shall be as specified in 3.10.1.1 except style A scissors shall conform to table IX and be similar to figure 9.

Table IX, Type II, class 3, styles A and B, pocket scissors.

	Style A		Style B	
Overall length Nominal (inches)	Min. length of cut (inches)	Minimum wt. per dozen (pounds)	Min. length of cut (inches)	Minimum wt. per dozen (pounds)
4	1-1/2	3/4	1-1/2	3/4
4-1/2	1-3/4	1	1-3/4	1
5	1-7/8	1-3/8	---	---
6	2-5/8	1-7/8	---	---



Figure 9. - Type II, class 3, styles A & B, pocket scissors.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:38Z
Check the source to verify that this is the current version before use.

3.10.3.2 Style B, light duty.- Style B, light duty scissors shall be forged from steel having a minimum of .10 percent carbon content. Scissors shall have all flash removed and blades shall be case hardened to a depth of .015 minimum and to the equivalent of a hardness on the Rockwell "C" scale of not less than 20. Style B scissors shall conform to table IX and be similar to figure 9.

3.10.4 Type II, class 4, manicure, curved blades.- Class 4 scissors shall be designed with both blades pointed. Class 4 scissors shall be as specified in 3.10.1.1 except these scissors shall conform to table X and be similar to figure 10.

Table X, Type II, class 4, curved-blade manicure scissors.

Overall Nominal Length (inches)	Minimum length of cut (inches)	Minimum weight per dozen (pounds)
3 4	3/4 1	3/8 1/2



Figure 10. - Type II, class 4, manicure scissors (curved blades).

3.10.5 Type II, class 5, manicure, straight blades.- Class 5 scissors shall be designed with both blades pointed. Class 5 scissors shall be as specified in 3.10.1.1 except these scissors shall conform to table XI and be similar to figure 11.

Table XI, Type II, class 5, straight-blade manicure scissors.

Overall Nominal Length (inches)	Minimum length of cut (inches)	Minimum weight per dozen (pounds)
3 4	3/4 1	3/8 1/2

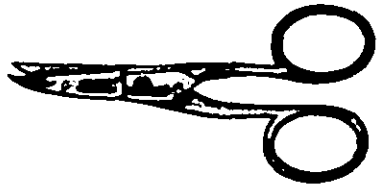


Figure 11. - Type II, class 5, manicure scissors (straight blades).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:38Z
Check the source to verify that this is the current version before use.

3.10.6 Type II, class 6, electricians'.- Class 6, electricians scissors shall be designed with both blades pointed and shall have file and scraping edges on the backs of the blades. Electricians' scissors shall be as specified in 3.10.1.1 except class 6 scissors shall conform to table XII and be similar to figure 12.

Table XII, Type II, class 6, electricians' scissors

Overall Nominal Length (inches)	Minimum length of cut (inches)	Minimum weight per dozen (pounds)
5	1-5/8	1-1/2

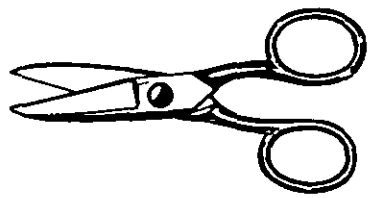


Figure 12. - Type II, class 6, electricians' scissors.

3.11 Workmanship.- Workmanship shall be first class throughout. Shears and scissors shall be smoothly and fully finished with no rough or irregular edges. There shall be no uncoated or unplated areas on the shears or scissors except for the cutting edge and inside of blade. Excess flash or welds, or any other defects which detract from the appearance or which might impair the serviceability are not acceptable.

4. SAMPLING, INSPECTION, AND TEST PROCEDURES

4.1 *Inspection responsibility.- The supplier is responsible for the performance of all inspection* requirements as specified herein. Except as otherwise specified, the supplier may utilize his own or any other inspection facilities and services acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Sampling for inspection and acceptance.- Sampling for inspection and acceptance shall be performed in accordance with the provisions set forth in Standard MIL-STD-105, except where otherwise indicated.

4.2.1 Inspection of components and materials.- In accordance with 4.1 above, the supplier is responsible for insuring that components and materials used are manufactured, tested and inspected in accordance with the requirements of referenced subsidiary specifications and standards to the extent specified, or, if none, in accordance with this specification.

4.2.2 End product inspection.- Inspection of the shears and scissors shall be performed as specified in the following paragraphs. The sample unit shall be one completely fabricated shears or scissors. The lot size shall be expressed in units of shears or scissors of one type, class, style, and size offered for inspection at one time for the purpose of determining the sample size in accordance with Standard MIL-STD-105.

Source: https://assist.dla.mil -- Downloaded: 2026l0-26T12:38Z
Check the source to verify that this is the current version before use.

4.2.2.1 Visual examination.- Each sample unit shall be examined for defects set forth below. The inspection level shall be Level II with AQL of 2.5 for Major defects and 6.5 for Total defects expressed in defects per hundred units.

Examine	Defect	Major	Minor
Coating	Missing or not as specified.	X	
	Evidence of rust.	X	
Design	Any characteristic not in accordance with specified requirements.	X	
Construction	Part missing.	X	
Workmanship	Sharp burr or edges that may be injurious to personnel.	X	
	Not joined as specified.	X	
	Loose or not in proper alignment.	X	
	Any adjustable part that cannot be adjusted or is not properly adjusted to perform the function intended.	X	
	Functional part that requires abnormal force to operate.	X	
	Cracked, broken, malformed, bent, bowed or otherwise damaged.	X	
	Ragged or damaged cutting edges.	X	
Threads	Stripped, broken or damaged.	X	
Marking Identification	Missing, incomplete, not legible, not permanent or not as specified.		X

4.2.2.2 Dimensional examination.- Each sample unit shall be examined to determine compliance with the dimensional requirements specified herein. Any dimension that is not within the specified requirements shall be classified a defect. The inspection level shall be S3 with AQL of 1.5 defects expressed in defects per hundred units.

4.2.2.3 Testing of the end item.- Each sample unit shall be tested for cutting performance to the applicable tests specified under 4.4 to determine compliance with the applicable requirements specified in 4.5. The inspection level shall be S3 with an AQL of 1.0 defects expressed in defects per hundred units.

4.2.3 Inspection of preparation for delivery.- Inspection to determine compliance with preparation for delivery requirements shall be accomplished in accordance with Military Specification MIL-S-15424 for shear, tailor.

4.3 Carbon content.- The supplier shall furnish certification that the chemical composition of each lot or batch of steel used in the end item meets the applicable carbon requirements as specified in 3.9.1.1, 3.9.1.2, 3.9.3.1, 3.9.5, 3.10.1.1, 3.10.1.2, and 3.10.3.2.

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:38Z
Check the source to verify that this is the current version before use.

4.4 Lot acceptance tests.

4.4.1 Cutting tests.- Each of the sample shears or scissors taken in accordance with 4.2.2.3 shall be tested as specified in 4.5.1 to verify compliance with the requirements of this specification. Any sample shears or scissors which do not meet the requirements for the cutting tests shall be rejected, and if the number of non-conforming shears or scissors in any sample exceeds the acceptance number for that sample, the lot represented by the sample shall be rejected.

4.4.2 Hardness tests.- The Rockwell hardness tests shall be conducted in accordance with method 243 of Federal Standard No. 151.

4.4.2.1 Blade hardness.- The blades of each sample shear shall be tested to determine compliance with the hardness requirements specified in 3.6.1, 3.9.3, and 3.10.3.2. Readings shall be taken within 1/8 inch from the cutting edge.

4.5 Test procedures.

4.5.1 Cutting tests.

4.5.1.1 Shears and scissors shall be tested as follows:

4.5.1.1.1 Each sample shall be submitted to hand-cutting tests, using the following materials:

(a) Silk cloth, plain weave, 68x132 threads per inch and .5 ounces per square yard.
(b) Tissue paper, weight 11.6 pounds per 500 sheets, size 25 by 40 inches.
(c) Cotton sheeting, plain weave, 56x60 threads per inch and 3.8 ounces per square yard.

4.5.1.1.2 The material in the following tests shall be cut cleanly, without any drag or pull, and shall fall freely away from the cutting edges, including the points.

4.5.1.1.3 Tests as specified in 4.5.1.1.4 shall consist of three cuts in the following order:

(1) Using only the extreme end of the cutting blades, beginning one inch from the point of blades.
(2) The full cutting edges. (See 3.7)

4.5.1.1.4 The cutting tests shall be made as follows and in the order given.

(1) Cut one thickness of silk cloth.
(2) Cut one thickness of tissue paper.
(3) Cut one thickness of cotton sheeting.
(4) Cut multiple thicknesses of cotton sheeting, for three-fourths of length of the cutting blade measured from the point, using the number of thicknesses prescribed below (see 3.7.):

	Length (in inches)				
	Up to 6	6 to 8	9	10	Over 10
Shears, trimmers'	---	6	8	12	14
Scissors, except class 6	4	---	---	---	---

(5) Cut one thickness of cotton sheeting.
(6) Cut one thickness of tissue paper.
(7) Cut one thickness of silk cloth.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:38Z
Check the source to verify that this is the current version before use.

4.5.1.2 Pinking shears.- The cutting test shall consist of cutting one thickness of silk and three thicknesses of cotton sheeting for the full length of the toothed edge after engagement of the first tooth.

4.5.1.3 Tailors' (sailmakers') shears.- The cutting test shall consist of cutting 25 thicknesses of cotton sheeting for three-fourths of the length of the cutting blade measured from the point.

4.5.1.4 Barbers' shears.- The cutting test shall consist of cutting one thickness of cotton sheeting for one-fourth of the length of the cutting blade measured from the point.

4.5.1.5 Electricians' scissors.- The cutting test shall consist of cutting wire consisting of 10 copper-wire strands of No. 36 (0.0050) A.W.G. or heavier. The scissors under test shall cleanly cut the wire without any assistance such as bending, pulling, or twisting of the wire by the operator. There shall be no visible deformation or damage to the cutting edges of the scissors.

5. PREPARATION FOR DELIVERY

(For civil agency procurement, the definitions and applications of the levels of packaging and packing shall be in accordance with Federal Standard No. 102.)

5.1 Cleaning, preservation and packaging.

5.1.1 Level A.- Level A cleaning, preservation, and packaging shall be in accordance with level A in Military Specification MIL-H-15424 for shears, tailor.

5.1.2 Level C.- Level C cleaning, preservation, and packaging shall be in accordance with the contractor's commercial practice.

5.2 Packing.

5.2.1 Level A.- Level A packing shall be in accordance with level A in Military Specification MIL-H-15424, for shears tailor.

5.2.2 Level B.- Level B packing shall be in accordance with level B in Military Specification MIL-H-15424, for shears, tailor.

5.2.3 Level C.- Shears and scissors preserved and packaged in accordance with 5.1.1 and 5.1.2 shall be packed in a manner to insure carrier acceptance and safe delivery at destination. Containers shall be in accordance with the rules or regulations of carriers as applicable to the mode of transportation.

5.3 Marking.

5.3.1 Civil agencies.- In addition to any special marking required by the contract or order (see 6.2), shipping containers shall be marked in accordance with Federal Standard No. 123.

5.3.2 Military.- In addition to any special marking required by the contract or order (see 6.2), shipping containers shall be marked in accordance with Military Standard MIL-STD-129.

6. NOTES

6.1 Intended use.

6.1.1 Style A, heavy duty.- Style A shears or scissors are recommended when cutting requirements are of such a specialized nature that only the best quality all steel (forged, solid or inlaid) shears or scissors will perform satisfactorily.

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:38Z
Check the source to verify that this is the current version before use.

6.1.2 Styles B & C, light duty.- Styles B and C light duty shears or scissors are recommended when cutting requirements are of a less critical or general purpose nature.

6.2 *Ordering data.*- Purchasers should exercise any desired options offered herein (see 3.5) and should specify the following:

(a) Title, number, and date of this specification.
(b) Type, class, design, and style of shears and scissors required (see 1.2.1).
(c) Size of item required (see 1.2.2).
(d) One blade pointed and one beveled (see 3.9.1).
(e) The blade with the thumb ring pointed and the other blade beveled (see 3.9.2).
(f) For left hand operation (see note on table III).
(g) Levels of packaging and packing required (see 5.1 and 5.2).
(h) Any special marking for shipment required (see 5.3).

6.3 Superseding data.- The types, classes, designs, and styles in this specification, compared with those covered in Federal Specification GGG-S-278, are as follows:

This Specification	GGG-S-278
Type I, shears	Type I, shears
Class 1	Class 1
Design 1	
Style A	Style A
Style C	Not covered
Design 2	
Style A	Style B
Style C	Not covered
Class 2	Class 2
Style A	Style A
	Style B
Style C	Not covered
Class 3	
Style A	Class 3
Style B	Not covered
Class 4	Class 4
	Style A
	Style B
Class 5	Class 5
Type II, scissors	Type II, scissors
Class 1	Class 1
Style A	Not covered
Style B	
Class 2	Class 2
Style A	
Style B	Not covered
Class 3	Class 3
Style A	Style A
Style B	Style B
Class 4	Class 4
Class 5	Class 5

6.4 Transportation data.- Transportation description and minimum weights applicable to these items are:

Scissors or shears, not otherwise indexed by name.

In boxes:

Carload weight 20,000 pounds subject to Rule 34, Consolidated.
Freight Classification.
Truckload weight 20,000 pounds.

GSA DC 64-18905

Source: https://assist.dla.mil -- Downloaded: 202640-26T12:38Z
Check the source to verify that this is the current version before use.