AA-D-00195d(GSA-FSS)
April 7, 1967
SUPERSEDING
Int. Fed. Spec. AA-D-00195c(GSA-FSS)
April 16, 1965

INTERIM FEDERAL SPECIFICATION

FOR

DESK, FLAT TOP, STEEL, CONFERENCE-TYPE

This Interim Federal Specification was developed by General Services Administration, Federal Supply Service, Standardization Division, Washington, D. C., 20406, based upon currently available technical information. It is recommended that Federal agencies use it in procurement and forward recommendations for changes to the preparing activity at the address shown above.

The General Services Administration has authorized the use of this Interim Federal Specification as a valid exception to Federal Specification AA-D-195b, dated March 2, 1961.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers a steel conference-type desk designed for use in a private or semi-private office (see 6.1).

1.2 Classification.

1.2.1 Type and size. The conference-type desk covered by this specification shall be of but one type and one size: The desk shall be 78 inches wide by 40 inches deep by 30-1/2 inches high with an 8-inch overhang on the back and two sides.

2. APPLICABLE DOCUMENTS

2.1 Specifications and standards, The following documents, of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

Federal Specifications:

L-P-508 - Plastic Sheet, Laminated, Decorative, and Nondecorative.
QQ-C-320 - Chromium Plating (Electrodeposited).
QQ-N-290 - Nickel Plating (Electrodeposited).
QQ-P-416 - Plating Cadmium (Electrodeposited).
QQ-S-781 - Steel Strapping Flat.
QQ-Z-325 - Zinc Coating, Electrodeposited, Requirements for.
TT-C-490 - Cleaning Methods and Pretreatment of Ferrous Surfaces.
UU-P-271 - Paper, Wrapping, Waterproofed Kraft.
LLL-L-354 - Linoleum; Desk-Top.
PPP-B-591 - Boxes, Fiberboard, Wood-Cleated.
PPP-B-601 - Boxes, Wood, Cleated-Plywood.
PPP-B-621 - Boxes, Wood, Nailed and Lock-Corner.
PPP-B-636 - Box Fiberboard.
PPP-C-843 - Cushioning Material, Cellulosic.
PPP-T-97 - Tape; Pressure-sensitive, Adhesive, Filament Reinforced.

Federal Standards:

Fed. Std. No. 102 - Preservation, Packaging, and Packing Levels.
Fed. Std. No. 123 - Marking for Domestic Shipment (Civilian Agnecies).
Fed. Std. No. 187 - Identification of Pressed Bends, Forms, Seams and Joints (Sheet Metal).
Fed. Std. No. 595 - Color.

Source: https://assist.dla.mil -- Downloaded: 20261O-26T11:39Z
Check the source to verify that this is the current version before use.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendedt of Documents, U. S. Government Printing Office, Washington, D. C., 20402.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D. C., Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, Los Angeles, and Seattle, Wash.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

Military Specifications:

MIL-A-140 - Adhesive, Water-Resistant, Waterproof Barrier-Material.
MIL-C-11456 - Crates; Wood, Nailed, Unsheathed; Domestic Shipment, 1,500 Pounds Maximum Load.
MIL-W-12332 - Welding, Resistance, Spot and Projection; for Fabricating Assemblies of Low-Carbon Steel.

Military Standards:

MIL-STD-20 - Welding Terms and Definitions.
MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 - Marking for Shipment and Storage.
MIL-STD-130 - Identification Marking for U. S. Military Property.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or requests for proposal shall apply:

Uniform Freight Classification Rules.

(Application for copies should be addressed to the Uniform Freight Classification Committee, 202 Chicago Union Station, Chicago 6, Illinois.)

Steel Products Manual, Carbon Steel Sheets.

(Application for copies should be addressed to the American Iron and Steel Institute, 150 East Forty-Second Street New York, New York 10017.)

3. REQUIREMENTS

3.1 Preproduction sample. Unless otherwise specified (see 6.2), before production is commenced a sample of the finished commodity and each component part on contract shall be submitted or made ready for the contracting officer or his authorized representatives to examine and test to determine compliance with this specification. Approval of the preproduction sample authorizes the commencement of production, but does not relieve the contractor of responsibility for compliance with all other applicable provisions of this specification. Production units shall not vary from the approved preproduction sample in design or construction without written approval of the contracting officer,

3.2 Material. All material used shall be as hereinafter specified. All materials shall be unused and free from defects which affect serviceability or appearance of the finished product.

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:39Z
Check the source to verify that this is the current version before use.

3.2.1 Steel. The steel sheets used for all exposed parts and tops shall be of commercial quality, cold-rolled steel with a stretcher leveled standard of flatness as defined in Steel Products Manual. Other sheets may be cold rolled oiled, hot rolled pickled and oiled or hot rolled annealed. The sheet steel shall withstand the bend test specified in 4.5.8. The steel shall be smooth, free from rust, scale, pits, scratches, laps and buckles affecting strength or appearance. The gage numbers specified are the manufacturer's standard gages for Steel Sheet. The decimal equivalents shown for the steel sheet thickness are subject to the standard tolerances given in the Steel Products Manual.

3.2.2 Linoleum. The linoleum shall conform to Type I or Type II of LLL-L-354 and shall be furnished without transparent factory finish. The thickness of linoleum shall be not less than 0.075 inch. The linoleum color shall be as specified in 3.3.4.2.

3.2.3 Plastic laminate sheet. When plastic covered tops are specified, the plastic laminate sheet shall conform to the requirements of L-P-508, Style D, Type I, Grade HP, Class 1, Finish A. The plastic sheet shall be 0.062 inch thick with a plus or minus tolerance of 0.005 inch. The plastic sheet color shall be as specified in 3.3.4.3.

3.2.4 Finishing materials.

3.2.4.1 Primer. The primer, when used, shall be compatible with the finishing enamel used.

3.2.4.2 Enamel. Enamel shall be of the baking type in accordance with manufacturer's commercial product. The color shall be as specified in 3.3.4.1, except for the bottom of the top plate, which may be a commercial gray color.

3.2.4.3 Zinc coating. Zinc coating shall be in accordance with Type I, Class 2 of QQ-Z-325.

3.2.4.4 Cadmium plating. Cadmium plating shall be in accordance with Class 1, Type I of QQ-P-416.

3.2.4.5 Chromium plating. Chromium plating shall be in accordance with QQ-C-320, Class 1 Decorative plating, Type II, satin, over a steel basis metal in accordance with QQ-N-290, Class 1, decorative plating, Type IV(QS).

3.2.5 Face hardware. The face hardware shall be constructed of satin finished anodized aluminum; type 430 corrosion-resistant steel; satin finished chromium on steel, die cast zinc, brass or bronze in accordance with 3.2.4.5. Tensile strength of die cast zinc shall be not less than 40,000 p.s.i. The exposed surfaces of drawer pulls and sliding shelf pulls used on a single desk shall be of the same material and finish.

3.3 Construction.

3.3.1 Spot welding. Spot welds shall not be closer to the edge of either adjoining member than one-half the greatest dimension of the spot weld, nor shall they be centered closer together than twice the greatest dimension. Squeeze time, weld time and hold time shall be controlled to produce uniform welds that will meet the test specified in 4.5.7. All depressed or protruding spot welds on exterior surfaces shall be filled and sanded or ground smooth as applicable. Spot welding shall be on not more than 6 inch centers unless otherwise specified herein.

3.3.2 Definition of terms used herein.

3.3.2.1 Welding terms. All spot welding and electrical resistance welding shall be as defined in MIL-STD-20. Definitions of these terms in MIL-STD-20 are as follows:

Resistance welding: A group of welding processes wherein coalescence is produced by the heat obtained from resistance of the work to the flow of electric current in a circuit of which the work is a part, and by the application of pressure.

Spot welding: A resistance welding process wherein coalescence is produced by the heat obtained from resistance to the flow of electric current through the work parts held together under pressure by electrodes. The size and shape of the individually formed welds are limited primarily by the size and contour of the electrodes.

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:39Z
Check the source to verify that this is the currentversion before use.

Fusion welding and brazing shall be defined as follows:

Fusion welding: Fusion welding consists of any welding process in which the weld is carried out solely by the melting of the metals to be joined, without any mechanical pressure. The joining is usually accomplished through the fusion of metal deposits from an external source.

Brazing: Brazing is a process wherein coalescence is produced by heating to suitable temperatures above 800 degrees F. and by using a filler matel having a melting point below that of the base metals. The filler metal is distributed between the surfaces of the joint by capillary attraction. The filler metal shall be nickel bronze rod (nickel content 9.5% tensile strength 70,000 - 75,000 p.s.i.) unless otherwise specified herein.

3.3.2.2 Fabricating terms. All bends, forms, seams and joints of the metal specified herein shall be as defined in Federal Standard No. 187.

3.3.3 Design. The conference-type desk covered by this specification shall be center of pedestal leg support style. The design and dimensions shall be as shown in Figures 1 thru 4 which illustrates the general appearance and typical features of construction required. The desk shall be 78 inches wide by 40 inches deep with a minimum overhang of 8 inches on the back and two sides. The height shall be 30-1/2 inches. The desks shall withstand the test specified in 4.5.

3.3.4 Color.

3.3.4.1 Metal finish. The color of the enamel finish shall be gray, Color No. 26134, of Federal Standard No. 595. Sample panels of the standard color of metal finish are obtainable from the Business Service Center, Federal Supply Service, General Services Administration, Washington, D. C. 20407, or from the Business Service Center of the nearest General Services Administration Regional Office.

3.3.4.2 Linoleum. The linoleum color shall be gray and shall match the standard linoleum color adopted by the Federal Supply Service, General Services Administration. Samples of the standard color of linoleum are obtainable from the Business Service Center, Federal Supply Service, General Services Administration, Washington, D. C. 20407, or from the Business Service Center of the nearest General Services Administration Regional Office.

3.3.4.3 Plastic laminate sheet. The plastic sheet color shall be green and shall match the standard color adopted by the Federal Supply Service, General Services Administration. Sample panels of the color are obtainable from the Business Service Center, Federal Supply Service, General Services Administration, Washington, D. C. 20407 or from the Business Service Center of the nearest General Services Administration Regional Office.

3.3.5 Tolerances; top size and height. Unless otherwise specified herein, permissible tolerances shall be as follows: Desk top width; plus or minus 1/8 inch. Desk top depth; plus 1/8 inch. Desk height; plus or minus 1/16 inch.

3.3.6 Assembly. The joining of all members shall result in a compact and rigid unit of sufficient strength to prevent distortion, breaking or loosening of any part of the desk during heavy duty daily usage and to withstand rough handling in moving while fully loaded. All flanges which are to be welded to another piece shall be positioned to provide maximum welding area and strength and rigidity to the welded assembly. Each desk produced shall be fully assembled, ready for use. Disassembly for the purpose of packing and shipping (knocked-down construction) will be permitted only as specified in 3.7.

3.3.7 Drawer pulls. The drawer pulls shall be similar in design and located as indicated in figure 1. All pulls shall be of the material specified in 3.2.5. Stamped drawer pulls will not be permitted. All surfaces and edges of the pulls shall be ground smooth to eliminate roughness and sharp edges. A design which incorporated open or squared-off ends will not be permitted. The pulls shall be securely attached by a method which is not visible on the outside of the drawer. The pulls shall have threaded studs or shall have a flat base with tapped holes for attachment and shall be securely attached with screws or with nuts and lock washers. The screws or nuts and lock washers shall be recessed and no part of the attachment shall project beyond the inside drawer front. The hand hold shall be a minimum of 7-1/2 inches in length.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.8 Sliding shelf pulls. The sliding shelf pulls shall be similar to either of the designs shown in Figure 2. The dimensions shall be as shown in Figure 2. The pulls shall be of the material specified in 3.2.5. Stamped pulls will not be permitted. All surfaces and edges shall be smooth and free from roughness and sharp edges. The pulls shall be securely attached.

3.3.9 Locks. When specified in the Invitation for Bids the desk shall be equipped with a lock (see 6.2). The lock shall be a disc tumbler type operated by a grooved key. The face of the lock shall be of the material specified in 3.2.5 or alternatively, shall be dull nickel finish on die-case zinc. The contractor shall certify that he has ordered each lot of 200 locks with 200 key changes. Two keys shall be furnished with each lock. It is not required that desks ordered without locks have provisions for installing locks at a later date.

3.3.10 Top construction.

3.3.10.1 Top plate and edge molding. The top dimensions shall be as shown in Figure 1. The top plate shall be not less than 16 gage (0.0598 inch) steel specified in 3.2.1 and shall be reinforced with not less than 3 members formed from not less than 18 gage (0.0478 inch) steel, each of which shall have not less than 4 bends. All reinforcing members shall abut or extend into the edge molding. The reinforcing members shall be spot welded to the top plate. In addition, each end of the center reinforcing member shall be secured to the edge molding by brazing in not less than 2 places at each end. Each brazed area shall be not less than 3/8 inch in length. The edge molding shall be not less than 18 gage (0.0478 inch) steel if formed from a single thickness of steel. Alternatively, the edge molding may be formed from two thicknesses of steel placed back-to-back and together equaling the thickness of 18 gage. Alternatively, the edge molding may be constructed of 20 gage (0.0359 inch) steel and the ends of all top reinforcing members shall be brazed to the edge molding as described above. The bottom edge of the edge molding shall be formed inward in not less than a flange formation. The edge molding shall be formed to provide for the binding strip specified in 3.3.10.2. The edge molding shall be installed in one piece or not more than 2 pieces and shall be butt joined at the ends by means of an 18 gage (0.0478 inch) steel reinforcing angle spot welded to the inside of the edge molding. The overall height of the edge molding and the binding strip shall be not less than 1-7/16 inches or more than 1-1/2 inches. All corners of the top shall be rounded on not less than 3/4 inch or more than 15/16 inch radius. **The top shall be securely attached to the pedestals. The top may be dismounted for shipment as specified in 3.7.**

3.3.10.2 Binding strip. The binding strip shall be formed of satin finished anodized aluminum or type 430 corrosion resistant steel. The binding strip shall have an upper outside radius of not less than 1/32 inch or more than 3/64 inch and shall be not less than 11/64 inch or more than 1/4 inch wide when installed. The binding strip shall be either vertically flush with the outside of the edge molding or may extend outside the edge molding by not more than 1/16 inch. The insetting web of the binding strip shall be flanged, embossed or serrated to grip the edge molding and top plate when in place. A friction fit of the binding strip will not be considered secure. The top of the binding strip shall not project above the top surface of the linoleum or plastic sheet. Linoleum covering shall not project more than 1/3 of its thickness above the binding strip and plastic covering shall not project more than 1/2 of its thickness above the binding strip. The top shall have not more than two pieces of binding strip butt joined with a hair line seam; touching or with not more than .030 inch gap. Allowable misalignment of binding strip shall be .012 inch. The binding strip shall be designed to be removable without damage to the top or edge molding.

3.3.10.3 Linoleum top covering. The top plate shall be covered with linoleum specified in 3.2.2 which shall be cemented uniformly to the top plate by a cement recommended by the linoleum manufacturer. The cement shall be free of lumps or foreign matter.

3.3.10.4 Plastic laminate top covering. When specified, the top plate shall be covered with plastic laminate sheet specified in 3.2.3. The plastic sheet shall be bonded uniformly to the top plate by an adhesive suitable for the application of plastic to steel. The plastic sheet shall be applied at a controlled temperature and sufficient pinch roller pressure (see 6.3) to insure an immediate, even and permanent bond between the plastic sheet and the entire steel top plate surface. A back-up board under the top is required as a part of the rolling process. The steel top plate shall be properly cleaned prior to the application of the adhesive.

Source: https://assist.dla.mil -- Downloaded: 20261O-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.10.4.1 Control samples for plastic laminate covered tops. Two samples, each 12 inches by 24 inches shall be prepared for each 500 tops processed. The samples shall be prepared under plant conditions, using the steel sheet, plastic laminate and adhesive materials and the same time-temperature-pressure cycle as used for the desk tops. Test specimens from the control samples shall show no evidence of delamination, blistering cracking or crazing when examined after the test specified in 4.5.5.

3.3.11 Leg. The leg shall be similar in design and positioned as shown in Figure 1, which indicates a shaped leg with tapering sides in a curved or straight design. All sides and bottom shall be fully closed and shall have no rough or sharp edges. Legs shall be constructed of not less than 18 gage (0.0478 inch) steel and shall be made corrosion resistant by satin finished chromium plating in accordance with 3.2.4.5 or by enameling in accordance with 3.2.4, 3.4 and 3.3.4.1. Legs finished by enameling shall be equipped with foot sockets specified in 3.3.11.1. The legs shall be securely attached to the pedestal by bolts, nuts and lockwasher, or by extruded holes and self-tapping screws. Legs may be dismounted for shipment as specified in 3.7.

3.3.11.1 Foot socket. Foot sockets shall be constructed of the material specified in 3.2.5. Steel foot sockets shall be not less than 0.0299 inch thick and aluminum foot sockets shall be not less than 0.039 inch thick. Foot sockets shall be not less than 1-1/2 inches high and shall be formed to conform to the shape of the leg. The foot socket shall be flush with, or slightly inset, the outside surface of the leg and shall be firmly secured with concealed fastenings which are designed to protect floors and to be removable with simple tools.

3.3.11.2 Alternate leg construction. A leg which incorporates a height adjustment mechanism may be furnished. The legs must be set at the 30-1/2 inch height. The configuration of the leg shall be similar to that shown in Figure 1. The leg shall consist of a cover which conceals the height adjustment mechanism. The cover shall be constructed of not less than 18 gage (0.0478 inch) steel and shall be made corrosion resistant by satin finish chromium plating in accordance with 3.2.4.5 or by enameling in accordance with 3.2.4.1, 3.2.4.2 and 3.4. Alternatively, the cover may be molded of non-woven fiber-glass-mat filled polyester in a color which matches the enamel color specified in 3.3.4.1. The cover shall be securely attached to the height adjustment mechanism. The height adjustment mechanism shall permit continuous height adjustment over a range of 1-1/2 inches minimum and shall be entirely operable by hand. The height adjustment mechanism shall consist of a metal tube with a diameter of at least 1-1/2 inches with a 3/8 inch 16 threaded stem. The bearing surface of the tube shall be fully closed and smooth. The tube and stem shall operate with a solid threaded nut incorporated in a support constructed of not less than 18 gage (0.0478 inch) steel. The stem and tube shall operate in a manner to prevent the leg cover from contacting the floor when the mechanism is adjusted to the lowest setting. The tube and threaded stem shall be made corrosion resistant by cadmium plating in accordance with 3.2.4.4. The support may be zinc or cadmium plated in accordance with 3.2.4.3 and 3.2.4.4. or enameled in accordance with 3.2.4.1, 3.2.4.2 and 3.4. The height adjustment mechanism shall be constructed and attached to the pedestal in a manner to prevent loosening or instability.

3.3.12 Desk pedestal construction. The pedestal sides and back shall be formed from one piece of not less than 20 gage (0.0359 inch) steel. The front of the side panels shall be formed inward in a return flange. The top and bottom edges of the sides and back shall be formed in a 90 degree flange. The pedestal shall have a 3/4 inch radius along the four back and front vertical edges. The pedestal bottom plate shall be not less than 20 gage (0.0359 inch) steel and shall be attached by spot welding on maximum of 4 inch centers to the bottom flanges of the sides and back. The front edge of the bottom plate shall be formed upward in a return flange to form the bottom part of the pedestal front section. Alternatively, the front edge of the bottom plate may be spot welded to a channel formation to form the pedestal front section. The front face of this formation shall be flush with and securely welded to the front return flange of the side panel. The exposed joint in the front section shall be brazed and ground smooth. The front section and front part of bottom panel shall be reinforced by an 18 gage (0.0478 inch) steel member combining a "Z" and hat section formation as shown in Figure 3. Alternatively, the front section may be formed in a channel and 90° flange formation. The front section and front part of bottom panel shall then be reinforced by an 18 gage (0.0478 inch) steel hat section formation. Provision shall be made in this member for attachment of leg. This reinforcement shall be placed in across-the-pedestal position, extending the full inside width of the pedestal and shall be spot welded on maximum 4 inch centers to the pedestal bottom through the areas indicated in Figure 3. The ends of the return flange or channel formation shall be brazed to the return flanges of the front edges of

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:39Z
Check the source to verify that this is the current version before use.

the pedestal. Alternatively, the top return flange of the front section may be spot welded on maximum 4 inch centers to the reinforcing member. To provide for attachment of rear leg, the bottom plate shall be reinforced by means of an 18 gage (0.0478 inch) steel hat section placed in across-the-pedestal position extending the full inside width of the pedestal. The flanges of the hat section shall be spot welded to the bottom plate. The pedestal shall be securely attached to the top through the front and rear reinforcing members with bolts, nuts and lockwashers or by clips designed for this purpose. No holes or punch marks will be permitted in the surface of the outside pedestal side or back. An area not less than 10 inches by 14 inches on the inside of each side panel shall be permanently covered with a felt composition sound-deadening material .080 inch thick.

3.3.12.1 Pedestal interior reinforcing members. Each pedestal side shall be reinforced by not less than two vertical reinforcing members constructed of not less than 18 gage (0.0478 inch) steel. The front reinforcing member shall have a minimum of 4 bends (an offset formation may be counted as 2 bends) and the rear reinforcing member shall be formed in a "Z" shape. The bottom end of the front and rear reinforcing members shall rest on top of the front and rear leg reinforcement members and shall extend as close as practical to the full height of the pedestal. The front and rear vertical reinforcing members shall be connected at top and bottom by horizontal braces constructed of not less than 20 gage (0.0359 inch) steel formed with not less than 2 bends. The back vertical reinforcing members shall be joined at the top by a horizontal brace of not less than 20 gage (0.0478 inch) steel, formed for strength. The front vertical reinforcing members shall be joined by a horizontal reinforcing member of not less than 18 gage (0.0478 inch) steel, formed with no fewer than 5 bends. This member shall form the top rail of the pedestal front. The vertical reinforcing members shall be spot welded on a maximum of 4 inch centers to the pedestal sides. The vertical reinforcing members shall be punched and slotted for attachment of drawer suspension members.

3.3.13 Desk pedestal assembly. The desk pedestals and back panel, without the top, shall form a free standing unit. The pedestals and back panel assembly shall be reinforced and securely held in line by means of two reinforcing members. The reinforcing members shall be of 16 gage (0.0598 inch) steel and each shall be formed with not less than two bends (an offset formation shall be considered as one bend). One reinforcing member shall be placed across the assembled pedestal tops near the front and the other across the pedestal tops near the rear. The reinforcing members shall be attached directly to both side top flanges of both pedestals. The reinforcing members shall be attached to the flanges by not less than four bolts, nuts and lockwashers or by not less than four welds to each pedestal.

3.3.14 Back panel. The back panel shall be constructed of not less than 20 gage (0.0359 inch) steel. The side edges and the top edge shall be formed in a 90 degree flange. The bottom edge shall be formed in a return flange or closed bead formation. The side flanges of the back panel shall be attached to the pedestal side by not less than 3 attachments. Alternatively, the back panel may be attached to the pedestal by brackets at the top and bottom of each side of the back panel. The back panel shall extend the full height of the pedestal. The back panel shall be located in from the back of the pedestal over a range of from 1-1/4 inches to 1-3/4 inches.

3.3.15 Locking mechanism. The locking mechanism shall be activated by the lock specified in 3.3.9. When the locking drawer is locked, it shall control a positive locking device capable of locking all drawers in one operation, and also permit closing and locking any drawer after the control drawer is locked, without distorting the locking mechanism. Unlocking the control drawer shall automatically unlock all other drawers, permitting the opening of any drawer without opening the unlocked control drawer beyond the overhang of the desk top.

3.3.16 Sliding shelf. The drawer pedestal sliding shelf shall be not less than 18 gage (0.0478 inch) steel with the side edges formed in a return flange and with the front edge formed in a flange and flat fold or other formation consisiting of not less than two bends. Alternatively, the sliding shelf may be formed of not less than 20 gage (0.0359 inch) steel with the sides reinforced with not less than 16 gage (0.0598 inch) steel channels inset and spot welded to the side flanges of the top plate of the shelf. The two front corners of the sliding shelf shall be brazed and ground smooth along the seam where the front and side flanges meet. The sliding shelf shall operate on 16 gage (0.0598 inch) steel runners formed in a return flange and Z shape which will permit the shelf to extend horizontally not less than 14-3/4 inches from the front of the top of the desk. Alternatively, the shelf may operate on 18 gage (0.0478 inch) steel runners when the steel runners, formed in a return flange and Z shape, shall be incorporated as part of a one-piece formed assembly consisting of the desk front and rear horizontal reinforcing members, the two steel runners, and

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:39Z
Check the source to verify that this is the current version before use.

the necessary reinforcing gussets and stops. Rubber or felt bumpers or coil or leaf springs shall be provided as noise reducing stop when shelf is fully extended or pushed into the pedestal. The shelf may also incorporate a convenience tray with a sliding plastic or metal cover. The sliding shelf shall be equipped with a drawer pull specified in 3.3.8 or shall have a spring arrangement activated when the shelf is pushed inward. An area not less than 10 inches by 14 inches on the underside of the sliding shelf shall be covered with a felt composition sound-deading material 1/8 inch thick, permanently adhered to the area with a suitable adhesive. Alternatively, an equivalent sound-deadening material on pressure sensitive tape is permissible. In the closed position the face of the shelf shall be flush with, or inset not more than 1/16 inch, the face of the pedestal.

3.3.17 Drawer construction. The number, kind and minimum inside clear dimensions of the drawers shall be as shown in Figure 1. The drawer fronts shall fit square in the drawer opening, horizontally and vertically, and shall show equal opening between the drawer front and pedestal frame, on the sides and top when the drawer is closed. In the closed position, the drawer fronts shall be flush with the face of the pedestals, or alternatively, shall inset the face of the pedestal not more than 1/16 inch. The drawer fronts shall not touch when drawers are equally extended or during the full course of travel when adjoining drawers are opened or closed at the same time. Storage drawers, when fully opened, shall extend not less than 20 inches from the inside front of the drawer to the front of the pedestal. The letter drawer shall extend, when fully opened, not less than 20-3/4 inches from the inside front of the drawer to the front of the pedestal.

3.3.17.1 Drawer fronts. The drawer front shall be of double wall construction. The outside drawer front shall be not less than 20 gage (0.0259 inch) steel. The top edge of the outside front shall be formed in a return flange to receive the inside drawer front. The side and bottom edges shall be formed in a return flange and an additional 90 degree flange to provide for welding to the drawer body by not less than four spot welds to each side and four spot welds to the bottom (See Figure 4). The return flange above the drawer side shall be flush with the inside drawer front. The inside drawer front shall be not less than 26 gage (0.0179 inch) steel. The four edges of the inside drawer front shall be formed in a flange or offset formation to fit into the outside drawer front and shall be held in place by spot welding or by the drawer pull fastenings. The bolt fastenings shall be recessed. The recessing may be in the form of a continuous channel across the inside drawer front. Alternatively, the side flanges may be omitted from the inside drawer front provided the latter has a channel formation, not less than 1-1/4 inch wide, extending the full length of the inside drawer front and centered on the attaching point. All corners of the outside drawer front shall be neatly closed and free of sharpness and burrs with the top corners brazed and ground smooth along the entire seam where the top and side flanges meet. The brazing shall be continued along the rear joints on the inside of the drawer for 1/2 inch.

3.3.17.2 Storage drawer body and back. The storage drawer body shall be not less than 24 gage (0.0239 inch) steel. The height of the drawer sides shall be not less than 4 inches. The sides and bottom shall be formed in one piece. The upper edges of the sides shall be formed in a bead or return flange. The back shall be not less than 22 gage (0.0299 inch) steel and the upper edge shall be folded over. Alternatively, the drawer back may be not less than 18 gage (0.0478 inch) steel and the upper edge shall be smooth. The back shall be securely welded to the sides and bottom of the drawer body. The back shall be the same height as the drawer sides or not more than 1/8 inch less height. To provide for insertion of adjustable partitions specified in 3.3.18.2, the sides of the storage drawer are to be slotted or formed and slotted on not less than 1 inch or more than 1-1/32 inch centers from front to back. Partitions shall be secured at the top by two slots or at the top and bottom by slots and formation in the drawer bottom. The slots may begin not more than 5-1/4 inches from inside drawer front.

3.3.17.3 Letter drawer body and back. The letter drawer body shall be not less than 24 gage (0.0239 inch) steel. The sides and bottom shall be formed in one piece. The upper edges of the sides of the drawer body shall be formed in a bead or return flange. Alternatively, the upper edges of the sides may be formed in a flat fold if the upper part of the drawer side is formed in a channel shape. The letter drawer back shall be of not less than 22 gage (0.0299 inch) steel and the top shall have a flat fold. Alternatively, the drawer back may be not less than 18 gage (0.0478 inch) steel and the upper edge shall be smooth. The back shall be securely welded to the sides and bottom of the drawer body. The back shall be the same height as the drawer sides. The inside height of the drawer sides shall be not less htan 9-3/8 inches. The letter drawer body construction shall provide for the proper operation of the compressor specified in 3.3.18.1 and for use of hanging files specified in 3.3.18.3.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.17.4 Center drawer. The center drawer body shall be not less than 24 gage (0.0239 inch) steel. The top edge of the drawer side shall be not more than 1/2 inch below the top edge of the drawer front. The sides and bottom shall be formed in one piece. The upper edges of the sides shall be formed in a bead or return flange or 90 degree flange with end formation. The back shall be not less than 24 gage (0.0239 inch) steel and shall be the same height as the drawer sides. The back shall have a hood formed from the drawer back in a 90 degree flange, or alternatively from a separate piece of 24 gage steel attached as a 90 degree flange. The hood shall be not less than 1-1/2 inches wide. The sides of the hood shall be spot welded to the drawer sides. The front edge of the hood shall be formed in a flat fold. The center drawer shall be equipped with a convenience tray which shall be not less than 1 inch high and 3 inches wide and shall be divided into not less than 3 compartments. Two of the compartments shall be 3 inches wide, plus or minus 3/8 inch, and one compartment shall be not less than 8-1/2 inches wide. Provision shall be made to hold the convenience tray firmly in place in the front of the drawer. The tray shall extend the full inside width of the drawer. The inside drawer front may be a part of the convenience tray. The center drawer shall be equipped with a lock specified in 3.3.9 when specified in the Invitation for Bids.

3.3.17.5 Drawer suspensions. The storage and center drawers shall operate on slide suspensions of the type specified in 3.3.17.5.1. The letter drawer shall operate on a progressive side-arm suspension or on a progressive cradle suspension of the types specified in 3.3.17.5.2 or 3.3.17.5.3.

3.3.17.5.1 Slide suspension. The case track shall be of not less than 16 gage (0.0598 inch) steel formed channel shape. Case tracks shall be secured to the pedestal inside vertical reinforcements as specified in 3.3.17.5.4. The drawer track shall be of not less than 16 gage (0.0598 inch) steel formed channel or "Z" shape with the bends so located as to provide maximum strength to the bearing surface. It shall be secured to the sides of the drawers by two rows of spot welds on not more than 4 inch centers or alternatively, by one row of staggered spot welds on not more than 3 inch centers diagonally measured. Alternatively, the drawer track may be formed as an integral part of the drawer body provided the total metal thickness of the bearing surface is equal to or exceeds 16 gage (0.0598 inch) steel in thickness and a return flange or "Z" formation in structural rigidity. There shall be nylon glides on each suspension, positioned to eliminate metal-to-metal contact between drawer and case tracks and to meet the pull test specified in 4.4.3. The glide shall be designed to insure against the head shearing of during operation of the drawer or while removing and inserting the drawers. The glide design shall also insure against loosening or falling out.

3.3.17.5.2 Progressive suspension, side arm type. The steel used in the construction of the neutral members shall be not less than 16 gage (0.0598 inch) and shall be cadmium or zinc plated in accordance with 3.2.5 and 3.2.6 except for areas burned during the welding process. Alternatively, black oxide coating may be used provided the entire member is then coated with a clear organic finish which dries to a hard film. The slides shall travel easily, quietly and smoothly with the drawer. Each neutral member shall have at least there main bearing rollers which are fixed journal ball bearing rollers and at least one solid stud bearing roller. Alternatively, each neutral member may operate on free solid rollers or solid balls. There shall be not less than five balls or rollers to each neutral member. If the design of the suspension is such that a separate housing is required for rollers or balls, the housing shall be not less than 16 gage (0.0598 inch) cold rolled steel, welded to the neutral member at each end by not less than two spot welds. Balls or rollers shall be incapable of dislocation or removal unless the suspension is dismantled.

3.3.17.5.3 Progressive suspension, cradle-type. There shall be two neutral members and not less than two tie members, all of which shall be not less than 16 gage (0.0598 inch) steel. The neutral members and tie members shall be joined by not less than two spot welds at each connection. All members shall be cadmium or zinc plated in accordance with 3.2.5 and 3.2.6, except for areas burned during the welding process. Alternatively, black oxide coating may be used provided the entire member is then coated with a clear organic finish which dries to a hard film. The slides shall travel easily, quietly and smoothly with the drawer. Each neutral member shall have at least three main bearing rollers which are fixed journal ball bearing rollers and at least one solid stud bearing roller.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.17.5.4 Drawer and case tracks, progressive suspension. The drawer and case tracks shall be hot or cold rolled 14 gage (0.0747 inch) steel. After forming to shape, the drawer and case tracks shall have a Rockwell hardness of not less than 70 nor more than 85 on the "B" scale, or equivalent hardness on a comparable scale. All outer surfaces of the drawer and case tracks shall be finished in accordance with 3.2.4 and 3.4. The case tracks shall be secured to at least the front and rear pedestal interior reinforcing members by interlocking of lugs on the case tracks into appropriate openings in the interior reinforcing members or by welding or bolting. Any of these attachments shall provide secure connections without vertical or horizontal movement. The drawer tracks shall be attached to the drawer sides by spot welding as specified in 3.3.17.5.1.

3.3.17.5.5 Rollers and ball bearings. Fixed journal ball bearing rollers shall be accurately turned from cold rolled steel and case hardened and shall be not less than 7/8 inch in diameter and not less than 1/4 inch thick and both edges shall be chamfered. Free rolling solid balls shall be not less than 3/8 inch diameter, hardened and polished. Alternatively, fixed journal ball bearing rollers may be cold formed from cold rolled steel and case hardened. Cold formed rollers shall be not less than 7/8 inch diameter and not less than 1/4 inch wide axially. Cold formed rollers shall be of the unitary type, consisting of a one piece outer and a one piece inner race, with an unbroken smooth surface in the raceway, and a smooth unbroken rolling surface on the outer race, with the edges of the outer race chamfered, or formed with a radius, or a combination of both. The outer and inner races shall be concentric to within plus or minus .0025 inch, and the entire outer rolling surface shall be parallel to the axis of the bearing to within plus or minus .0025 inch.

3.3.17.5.6 Drawer stops. Each drawer shall be equipped with a positive stop which will prevent the drawer from falling out when fully extended but will premit easy removal of the drawer when desired without prior removal of any other drawer. The drawers shall contact bumpers of rubber or other durable energy absorbing material on the inward movement.

3.3.18 Drawer accessories.

3.3.18.1 Compressor. Required for all letter drawers. The compressor shall operate within the letter drawer to support front-to-back filing. The compressor shall be of the friction locking type controlled by spring tension and shall operate easily within the drawer when released and be held firmly when engaged. The clearance between the compressor and its track or guide shall be kept to a minimum, so as to prevent the compressor from facing off at an angle and out-of-square with the drawer sides when in operation, and from seating out-of-square when engaged. The compressor plate shall be not less than 18 gage (0.0478 inch) steel and shall have a roll or bead formation across the top edge, or shall have the top edge free of burrs and finished so as to eliminate any sharp edges of metal. The tension release lever shall be not less than 20 gage (0.0359 inch) steel, shall be smoothly formed and reinforced for strength and for convenience of releasing.

3.3.18.2 Drawer partition. A minimum of two partitions shall be furnished for each storage drawer. Partition may be double wall or single wall construction. Double wall partitions shall be made of not less than 24 gage (0.0239 inch) steel with a rounded top edge and shall have not less than 2 reinforcing dimples for spot welding the two walls together. Single wall partitions shall be made of not less than 20 gage (0.0359 inch) steel and the top edge shall be folded or beaded. In order to secure to the drawer sides, the partition shall have two integral lugs on each side which engage slots in the drawer sides, or by one integral lug on the partition side and not less than 1 integral lug on the partition bottom which engages a formation in the drawer bottom. The partitions shall remain firmly engaged and in a vertical position at all times.

3.3.18.3 Hanging file supports. Hanging file supports shall be provided for all letter drawers. The hanging file supports shall accommodate across-the-drawer filing of both letter size and legal size hanging folders. Letter size hanging folders are 11-3/4 inches wide by 9-7/8 inches high and legal size hanging folders are 14-/34 inches wide by 9-7/8 inches high. (The 9-7/8 inch height of both sizes includes 5/8 inch high tabs). The folders are hung by means of arms which end in hooks and which extend 5/8 inch beyond each side edge of the folder. The hanging file supports shall consist of two removable supports and one removable partition. The supports shall be located across the drawer. One support shall be attached not more than 1-1/8 inch from the inside drawer front. The other support shall be capable of being attached at either of two positions; 12 inches, plus or minus 1/8 inch, or 15 inches, plus or minus 1/8 inch, back of first support. The back support shall be capable of repositioning in the field without the use of special tools.

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:39Z
Check the source to verify that this is the current version before use.

The removable partition shall be located a sufficient distance from the back support to provide clearance for the folder arm and hook to rest and slide easily on the second support. The partition shall be constructed of not less than 20 gage (0.0359 inch) steel. The upper edges of the file supports shall be the same height as the inside height of the drawer side. The upper edge of the partition shall be not more than 1 inch below the drawer side (9-3/8 inches). The edges of the supports and the partition shall be formed in a bead or fold to prevent rough or sharp edges. Any bends in the design for the purpose of attachment to the drawer sides shall not interfere with insertion or withdrawal of hanging files. The partition shall be held in a vertical position at all times. The supports shall have sufficient strength and rigidity to hold the full capacity of hanging folders and filing material without sagging.

3.4 Pretreatment and finishing.

3.4.1 Pretreatment. All exterior and interior unplated ferrous metal surfaces shall be treated for painting in accordance with any method of TT-C-490.

3.4.2 Priming. Unless Type I or Type II of TT-C-490 is used, all exterior and interior surfaces (except the top of the top plate) treated as specified in 3.4.1 shall be coated with primer specified in 3.2.4.1.

3.4.3 Enameling. All primed surfaces of the desks shall be coated with enamel specified in 3.2.4.2 and shall be baked at a time temperature cycle recommended by the enamel manufacturer. Total dry film thickness of enamel and primer shall be not less than 1.4 mils on all "wear areas" (outside edges of top, all drawer fronts, and front edge of sliding shelf) and not less than 1.0 mils on other surfaces, inside and outside, of the desk. Primer may be omitted from any surface prepared for painting in accordance with Type I or Type II of TT-C-490 provided the dry enamel film thickness is not less than 1.1 mils on all "wear areas", and not less than 1.0 mils on all other surfaces, inside and outside. The finish shall level out to produce smooth, uniform surfaces without runs, wrinkles, grits, areas of thin film or no film, and separation of color. Finish panels shall withstand the test specified in 4.5.6.

3.4.4 Bolts, nuts, screws, and fastening devices. The bolts, nuts, screws, clips and other fastening devices for which finish is not otherwise specified herein shall be made to resist rust by electrogalvanizing or by zinc, chromium or cadmium plating in accordance with the Standard Commercial Process of the manufacturer of these items.

3.5 Identification marking. Unless otherwise specified, each desk shall be permanently marked on the kneespace side of the back panel, starting 8 inches from the top in a plain and legible manner with the specification number, the Federal stock number, the month and year of manufacture, the contractor's name or trade-mark, and the contract order number, so that the source of supply may be readily determined. When specified, identification marking shall be in accordance with Military Standard MIL-STD-130.

3.6 Workmanship. A high degree of craftmanship shall be exercised while performing the various operations of manufacture to eliminate the possibility of personal injury due to burrs and sharp edges; to assure that the occurrence of defects will not exceed the acceptable quality levels specified; and to produce a finished commodity that is satisfactory in function, serviceability and appearance.

3.7 Knocked-down construction. Unless otherwise specified, desks may be furnished either completely set-up, or knocked-down to the extent only that either the top or the legs are to be attached after delivery. The supply of both unattached tops and legs is not permitted. When legs are furnished detached they shall be furnished in the same container as the desk body. The supplier shall furnish with each desk printed instructions which indicate clearly the method to follow in assembling the desk.

4. QUALITY ASSURANCE PROVISIONS

4.1 Inspection and testing responsibility. The supplier is responsible for the performance of all inspection and testing requirements as specified herein. Except as otherwise specified, the supplier may utilize his own or any other inspection facilities and services acceptable to the Government. Inspection records of the examination and tests shall be kept complete and available to the Government as specified in the contract or order. The Government reservs the right to perform any of the inspections and tests set forth in the specification where they are deemed necessary to assure supplies and services conform to prescribed requirement.

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:39Z
Check the source to verify that this is the currentversion before use.

4.2 Sampling for inspection and acceptance. Sampling for inspection and acceptance shall be performed in accordance with the provisions set forth in MIL-STD-105, except where otherwise indicated.

4.2.1 Component and material inspection. In accordance with 4.1, the supplier is responsible for insuring that components and materials used are manufactured, tested and inspected in accordance with the requirements of referenced subsidiary specifications and standards to the extend specified, or, if none, in accordance with this specification.

4.2.1.1 Process examination. Examination shall be made of the following operations to establish that no deviation is made from the indicated requirements. Wherever a deviation is noted, correction shall be made. Failure to make immediate correction may cause rejection of affected end item lots.

(a) Pretreatment and priming before finish material is applied as specified in 3.4.1 and 3.4.2.
(b) Baking of enamel as specified in 3.4.3.
(c) Preparation of control samples for tops (3.3.10.4.1).

4.2.2 End item inspection.

4.2.2.1 Visual examination. Examination of the desks shall be in accordance with the classification of defects in Table I. The lot size shall be expressed in units of desks for the purpose of determining the sample size in accordance with MIL-STD-105. The sample unit for this examination shall be one complete desk.

TABLE I - Classification of Defects.

Examine	Defect	Classification Major	Classification Minor
Linoleum or plastic laminate	Any separation from top plate Color not as specified Any cracks Any delamination	X	
Welding	Spot welds spaced on more than 6 inch centers, unless otherwise specified.		X
	Burnt through, cracked, fractured or not fused		X
	Flash or spatter on drawer interiors and exposed surfaces not removed. Depressed or protruding spot welds on exterior surface not filled, sanded or ground smooth.		X
Drawer and sliding shelf pulls	Not according to design. Not secured as specified.		X
	Rough or sharp edges that may cause injury.	X	
Lock	Wrong type.		X
Top plate and edge molding	Reinforcements less than number specified. Reinforcements have less than number of bends specified.	X	
	Edge molding not channel shape. Edge molding in more than 2 pieces. Corners not rounded as specified.		X

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:39Z
Check the source to verify that this is the currenversion before use.

TABLE I - Classification of Defects (Cont'd).

Examine	Defect	Classification Major	Classification Minor
Binding strip	Binding strip loose or does not closely fit top material. Not of material specified	X	
	Not radius specified. More than 2 pieces of binding strip per top.		X
Pedestal	Components less than minimum gages specified.	X	
	Top and bottom edges not flanged.		X
	Interior frame not as specified. Botton not reinforced as specified.	X	
	Holes for self-topping screws not extruted. Reinforcements of pedestal assembly not as specified. No sound deadening material.		X
Back panel	Edges not properly formed. Not full height of pedestal.		X
Locking mechanism	Will not operate as specified.	X	
Sliding shelf	No sound deadening material on underside Not properly secured.		X
	Has sharp or unprotected edges affecting safety.	X	
	Not provided with noise reducing stop. Not horizontal when extended.		X
Drawers	Drawer front does not fit square in opening.		X
	Components less than minimum gages specified.	X	
	Not flanged, channeled, folded or beaded as specified.		X
	Storage drawer does not provide for adjustable partition on 1 inch centers. Letter drawer does not provide for hanging files. Center drawer tray not as specified.		X
Drawer suspensions	Less than minimum gages specified Has rough or sharp edges affecting serviceability.	X	
	Not finished as specified.		X
	Suspensions not rigidly secured to drawer sides or pedestal.	X	
	Roller and ball bearings not as specified.		X

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:39Z
Check the source to verify that this is the current version before use.

TABLE I - Classification of Defects (Cont'd).

Examine	Defect	Classification Major	Classification Minor
Drawer stops	Do not prevent drawer from falling out.		X
	Not equipped with bumpers.		
Compressor	Does not operate smoothly.		X
	Will not hold firmly in place.		
	Rough or sharp edges that may cause injury.	X	
Partitions	Do not hold securely in place.		X
	Top edge not formed or rounded.		
Hanging file supports	Will not accommodate hanging folders.		X
	Not located as specified.		
	Partition not maintained in vertical position.		
Leg	Less than minimum gage specified.	X	
	Not finished as specified.		X
	Socket not material specified.		
Height adjustment mechanism	Not continuous adjustment over full range.	X	
	Not finished as specified.		X
	Not operable by hand.		
	Not closed tube.		
Enamel finish	Indication of rust under coating	X	
	Poor adhesion, tacky, color separation, stain, runs or foreign matter in coating.		X
	Wrong color.	X	
	Scratches or unpainted areas.		
	Abrasion or areas of thin coating		X
	Film thickness less than specified or wear surfaces.	X	
	Film thickness less than specified on other than wear surfaces.		X
Bolts, nuts, screws and fastening devices	Not metal plated.		X
	Threads stripped.		
Workmanship	Any part missing, affecting appearance or serviceability.	X	
	Malformed, damaged, buckled or warped parts affecting serviceability.	X	
	Sharp edges or projections that may cause injury.	X	
	Malformed damaged, buckled or warped parts affecting appearance.		X
	Legs not securely attached.		X
	Pedestal not securely attached to top.		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

4.2.2.2 Dimensional examination. Inspection will be made of desks for compliance with dimensions specified herein including thickness of metal and film thickness of enamel. Any dimension not within tolerance specified shall be classified as a defect.

4.2.2.3 Inspection levels and AQL's. The inspection levels and the acceptable quality levels (AQL's) expressed in defects per hundred units, shall be in accordance with MIL-STD-105, and shall be as follows:

	Inspection levels	AQL's
For examination in Table I Major	I	4.0
For examination in Table I Total	I	10.0
For examination in 4.2.2.2 (One class)	I	4.0

4.3 Inspection of preparation for delivery requirements. An inspection shall be made to determine that the packaging, packing and marking comply with the requirements in Section 5 of this specification. Defects shall be scored in accordance with Table II. For examination of interior packaging, the sample unit shall be one shipping container fully prepared for delivery, selected at random just prior to the closing operations. Sampling shall be in accordance with MIL-STD-105. Defects of closure listed in Table II shall be examined on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be I of MIL-STD-105 and the acceptable quality level (AQL) shall be 4.0 defects per hundred units.

TABLE II - Classification of Defects

Examine:	Defect:
Markings	Omitted; incorrect; illegible; of improper size, location, sequence or method of application.
Materials	Any nonconforming component; component missing, damaged or otherwise defective affecting serviceability.
Workmanship	Inadequate application of components such as incomplete closure of shroud, inadequate securing of keys, drawers or contents and padding of perimeter edges.

4.4 Testing of end items. Tests shall be regularly performed as described herein on each complete style, class, size, etc., of items being produced under the contract to assure continuous quality production. Tests shall be repeated whenever a change is made in material, design, or method of production. Additional tests shall be performed at the discretion of the Government. (See 4.1).

4.5 Tests. Tests shall be conducted as specified herein. Paragraphs 4.5.1 through 4.5.5 specify test requirements but do not preclude the use of other test fixtures if the machanics of the systems are duplicated for similar tests. Any failure of welds or mechanical joints or any permanent distortions in excess of that specified or any other damage to any part of the item that would affect serviceability will be considered as failing to comply with the requirements of this specification. Certified evidence of compliance with all applicable tests must be submitted upon request. Items used in the tests must be available for examination by the inspector.

4.5.1 Top test, method. The desk to be tested shall be placed in a position to provide a level top surface. A weight of not less than 600 pounds shall be applied all at one time to an area not to exceed 12 inches in diameter for at least 5 minutes. The test area shall be at the front center of the knee-space. The desk top shall not deflect more than 1/8 inch during the test and shall not take on any permanent set.

Source: https://assist.dla.mil -- Downloaded: 202610-26T11:39Z
Check the source to verify that this is the current version before use.

4.5.2 Letter drawer service test, method. The desk to be tested shall be placed in a position to provide a level top and shall be bolted or otherwise secured in a proper position. The letter drawer shall be connected by the drawer pull to a machine which will operate the drawer. The machine shall have a positive means (no springs) for adjusting the length of its stroke so that the drawer will travel the full distance (not more than 1/4 inch clearance at each end of stroke) from back stop to front stop. The machine shall drive the drawer at a rate of 20 cycles per minute (plus or minus 2 cycles per minute). The mechanism shall in no way contribute to the support of the drawer. The drawer shall be loaded with papers, guide cards and folders, or their equivalent weight, which shall be equally distributed from front to back of drawer and shall total 52 pounds. The suspensions of the drawer being tested shall be cleaned and lubricated with SAE 30 machine oil at the end of 10,000 cycles and shall have no further attention until the test is completed. At the beginning of the test and at each increment of 10,000 cycles, a drawer pull test as specified in 4.5.3 shall be conducted to determine the force required to start the loaded drawer forward and to move it to its full outward limit. The drawer suspension shall be considered as having failed the service test if the drawer operating force exceeds 3 pounds or 5 pounds as applicable (as specified in 4.5.3) to complete the forward stroke before or at 50,000 cycles. Should failure be perceptible during the increments of 10.000 cycles, the machine shall be stopped and the drawer pull test specified in 4.5.3 shall be conducted at that point.

4.5.3 Drawer pull test, method. The drawer to be tested shall be loaded with typical filing material such as papers, guide cards and folders or their equivalent weight equally distributed front to back of drawer in the following amounts:

File drawer - 52 pounds
Storage drawer - 20 pounds

The test shall be conducted by passing a limp cord, attached to the center of the drawer pull, over a sheave with a weight applied to the free end. The force required to start the loaded drawer forward and to move it to its full outward limit shall be recorded.

The drawer operating force for the file drawer shall not exceed 3 pounds, except when the drawer suspension assembly incorporates a feature which drops the drawer into place to facilitate closing of the drawer, the drawer operating force shall not exceed 5 pounds maximum to bring the suspension out of the depression. At that point the drawer will be stopped and the operating force required to continue the drawer to full extension shall not exceed 3 pounds.

The drawer operating force for the storage drawer shall not exceed 4-1/2 pounds.

4.5.4 Drawer interference test. With the drawers loaded with the weights specified in 4.5.3, the drawer fronts shall not touch each other at any point of extension, up to and including full extension when adjoining drawers are opened or closed at the same time.

4.5.5 Plastic laminate delamination test. Three test specimens 4 inches by 8 inches shall be cut from the sample panels prepared in 3.3.10.4.1. The test specimens shall be completely immersed in boiling distilled water for one hour, then removed and immersed in distilled water at 23 degrees, plus or minus 1.1 degrees C (73.5 degrees, plus or minus 2 degrees F) for 30 minutes. The test specimens shall then be dried at 60 degrees, plus or minus 3 degrees C (140 degrees, plus or minus 5 degrees F) in a circulating air oven for 20 hours. The specimens shall be removed from the oven, allowed to cool for 2 hours and then shall be bent over a 16 inch diameter mandrel in 3 to 6 seconds until the entire specimen is in contact with the surface of the mandrel. The specimen shall be examined for evidence of delamination, cracking, crazing and blistering.

4.5.6 Finish test for steel panels. A 20 gage steel panel prepared in accordance with 3.4 shall bent at room temperature around a 1/8 inch diameter rod to 180 degrees without cracking, flaking or loss of adhesion of the enamel.

4.5.6.1 Hardness. A test panel shall be prepared in accordance with 4.5.6. The dried film shall withstand the firm stroke of a 2H pencil held at a 45 degree angle and pushed across the film surface without evidence of marring when viewed at an oblique angle in a strong light.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

4.5.6.2 Adhesion. A test panel shall be prepared in accordance with 4.5.6. The dried film shall not be removed from the panel when the latter has been scored with a razor blade through the film to the base metal in such a manner as to produce a grid of 1/8 inch squares and a one inch wide piece of cellophane tape (Scotch Brand No. 600) is applied firmly to the grid surface, (full length of panel), and then is quickly pulled from the surface.

4.5.7 Spot welds. Spot welds shall meet the peel test specified in 4.1.4 of MIL-W-12332 and button diameter shall conform to Table II as specified therein.

4.5.8 Bend test for steel sheets. The steel sheets used for parts to be formed shall withstand a 180 degree bend at room temperature with and across the grain without showing any crystallization, cracks or fractures on the outside of the bend.

4.5.9 Compressor test. The letter drawer to be tested shall be loaded with filing material consisting of paper, guide cards and folders with a total weight of 30 pounds. The filing material shall be held against the front of the drawer by the compressor. The location of the compressor shall then be marked by a mark or scratch on the bottom of the drawer. The apparatus specified in 4.5.2 for operating the drawer shall be connected to the drawer being tested and set in motion and made to operate 500 cycles. Upon completion of the 500 cycles the position of the follower block shall be indicated by a second mark or scratch on the bottom of the drawer. The rearward movement of the follower block, as indicated by the distance between the two marks as a result of this test shall not exceed 1/2 inch.

4.5.10 Hanging file support test. The hanging file support shall be installed in the drawer in the manner in which it will be supplied. A reference line shall be established from drawer side to side and measurement point established at dead center of reference line. Hanging files filled with standard filing material in the weights specified below shall be hung on the supports.

	Weight
Legal size	40 pounds
Letter size	35 pounds

The weight of hanging files shall remain in place, undisturbed, for 8 hours. The two file supports shall be examined and deviation from the reference line noted. The hanging files shall be removed and the two file supports shall be examined and deviation from the reference line noted. The hanging file supports shall have failed the test if the loaded support deviation exceeds 1/16 inch. Any deviation noted when supports are empty shall constitute a failure. Any loosening or displacement of file support attachments to drawer sides will constitute a failure.

4.5.11 Top level test. Place a steel straight-edge on edge diagonally (corner-to-corner) across the top. The length of the straight-edge shall be greater than the diagonal length of the top. There shall be no gaps between the straight-edge and the top greater than 3/64 inch at any point along the diagonal length of the top. This test shall be performed along both diagonals of the top and both before and after performing the top test specified in 4.5.1.

5. PREPARATION FOR DELIVERY

(Federal Standard No. 102 shall be referred to for definitions and application of the various levels of packaging and packing for civilian procurement. Level A - Should be used for shipments to overseas destinations; Level B - Should be used for shipments from supplier to domestic warehouses, supply depots, or intermediate storage points for storage and subsequest issue and/or shipment to eventual user; and Level C - Should be used for shipments from supplier direct to first receiver/consumer).

5.1 Packaging. Packaging shall be Level A, B or C as specified (see 6.2).

5.1.1 Level A.

5.1.1.1 Drawers and sliding shelves. All drawers shall be prevented from vibrating while in transit by wedging cushioning material conforming to type III of PP-C-843 between the drawer and the drawer frame. The sliding shelf shall be secured closed by means of pressure-sensitive adhesive tape conforming to PPP-T-97 applied over edges of shelf and adjacent desk body, or by wedging cushioning material as specified for drawers between the sliding shelf and the shelf frame, or by the use of commercial type clips designed for this purpose. All drawers shall be secured closed by locking the center drawer. The keys shall be placed in a cotton cloth drawstring

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:39Z
Check the source to verify that this is the currentversion before use.

bag, securely knotted closed, and then securely tied to a drawer handle. Loose drawer partitions shall be wrapped in cushioning material specified or similar cushioning material and secured within the drawer with tape specified.

5.1.1.2 Cushioning. Each desk shall be completely covered with 30-pound basis weight (24 by 36 - 500) machine-glazed kraft paper, highly calendared paper, or waxed paper. The desk top, edges of top, desk front, and drawer handles shall be protected with cushioning material fabricated in the form of pads or blankets made of the following materials or a combination of these materials to provide a built-up cushioning of not less than three-fourths of an inch in thickness:

Macerated paper, plain	Excelsior (sealed ends)
Macerated paper, tissue faced	Cotton wadding
Shredded paper	Molded pulpboard
Wood wool	Laminated cellulose wadding backed with corrugated fiberboard
Wood fiber felt	
Cellulose wadding	

When cellulose wadding, cotton wadding, or laminated cellulose wadding backed with corrugated fiberboard is used, the initial sheet of kraft or waxed paper may be omitted under the cushioning material.

5.1.2 Level B. (Civilian Agencies)

(Listing of drawings for methods of Packaging, Packing, Blocking and Bracing of desks).

A. For desks shipped knocked-down.

Desk top in one container, desk body with legs attached in a separate container.

Method R-1
Drawing No. PP-1103-C(Figure 5-A)
Drawing No. PP-1104-C(Figure 5-B)
Drawing No. PP-1105-C(Figure 6)
Drawing No. None (Figure 7)

Method R-2
Drawing No. None(Figure 8) (Page 1 and Page 2)

B. For desks shipped knocked-down.

Desk with top secured in position with legs removed and enclosed with desk pack.

Method A-1
Drawings Nos. 9, 10 and 11 (3 sheets)

Method A-2
Drawings Nos. 12 and 13 (2 sheets)

5.1.2.1 Knocked-down construction. Desks shall be shipped "knocked-down" as specified in 3.7, desk top in one container, desk body with legs attached in a separate container, METHODS R-1 OR R-2, or with top attached and legs detached complete in one container in accordance with ALTERNATE METHODS "A-1" or "A-2".

THE FOLLOWING SECTIONS APPLICABLE TO R-1 and R-2, AND TOPS SHIPPED SEPARATELY FROM BODIES.

5.1.2.2 Sliding Shelves, Drawers. Exposed finished edge surfaces of sliding reference shelves and the top-edges of drawers shall be covered by .120-inch thick embossed cellulose wadding strips (or strips of equivalent material), or 30-pound oil-impregnated kraft paper, or 30-pound machine-glazed or highly calendared kraft paper, having sufficient width to overlap inside and outside top edges, and length sufficient to fold down over vertical end edges. Strips shall be positioned in

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

such manner that will insure their remaining in place when the shelves or drawers are secured in closed position. Drawers shall be secured in closed position by either: (a) closing all pedestal drawers then closing and locking center drawer; or (b) closing all pedestal drawers, then inserting a steel packing clip in center drawer, closing the drawer and securing by bending the clip downward. When closure is by locking of center drawer, the keys shall be placed in an envelope or bag of heavy kraft paper or cloth, and secured to a drawer handle. When the steel-clip method of locking drawers is used, the keys shall be securely fastened within the top center drawer prior to closing.

5.1.2.3 Partitions, Trays, Compressors. Partitions, compressor and hanging file supports shall be secured in place within appropriate drawers in such manner as to prevent vibration or movement during handling or shipment.

5.1.2.4 Corner and legs. Corners of desk body that will come in contact with interior forms within the shipping container shall be protected by use of cushioning pads or blankets of:

Macerated paper, plain	Excelsior (sealed ends)
Macerated paper, tissue faced	Cotton Wadding
Shredded paper	Molded pulpboard
Wood wool	Laminated cellulose
Wood fiber felt	Wadding backed with corrugated fiberboard
Cellulose wadding	

When cellulose wadding, cotton wadding, or laminated cellulose wadding backed with corrugated fiberboard is used, the initial sheet of kraft or waxed paper may be omitted under the cushioning material.

Each leg shall be protected by a tube of C-flute corrugated fiberboard, contact surface lined with nonmarring material, slipped over the leg and secured in place, or each leg may be wrapped with a nonmarring cellulose wadding or equivalent, taped securely in place.

5.1.2.5 Body. Finished surfaces of body which will come in contact with any part of the shipping container or interior fittings shall be protected by blankets or pads of material as specified in 5.1.2.4. Drawer handles shall be protected by built-up pads of corrugated fiberboard not less than 1-inch in width and at least 1-inch longer than the handle length, nor less than 1/4-inch greater thickness than depth of handle, slotted to fit over the handle, and secured in place. Surface of pad in contact with finished surface of desk shall be lined with a nonmarring material.

5.1.2.6 Desk Tops. Top surface and edges of top shall be protected by a sheet of corrugated or solid fiberboard having the contact surface of the sheet lined with a nonmarring material. The protective sheet shall be not less than .125 inches in thickness if of corrugated, or not less than .040 inches in thickness if of solid fiberboard. The sheet shall completely cover the top surface and extend down over all edges for a distance equal to the thickness of the edges. If the fiberboard sheet above is not lined as specified, the top surfaces and edges of desk top shall be protected by a sheet of polyethylene film, or other nonmarring material, as specified in 5.1.2.4, placed beneath the fiberboard sheet.

5.1.3 Level C. Unless otherwise specified, desk top and desk body shall be packaged in accordance with the manufacturer's standard practice to insure protection during shipment to initial destination for immediate use.

5.2 Packing. Packaging shall be Level A, B or C as specified (see 6.2).

5.2.1 Level A. Each desk, packaged as specified in 5.1.1 shall be packed in a shipping container conforming to class 2, style 2, 2-1/2, 3 or 4 of PPP-B-621 or overseas type of PPP-B-601. The desk shall be braced, blocked, bolted, or strapped within the shipping container to prevent movement and subsequent damage to the desk. Surfaces of the desk in contact with blocks, braces, or straps shall be cushioned to prevent damage to the desk. End grain nailing shall not be used to hold blocking in place. Strapping used for anchoring shall conform to type I, class A or B of QQ-S-781. When specified, the desk shall be blocked and braced in a manner to insure that the weight of the desk will not rest upon the desk legs. Each desk shall be covered with a full length shroud made of waterproof barrier-material conforming to class E-2, H-1, H-5 or M of UU-P-271. All seams of the shroud shall be sealed with a minimum three-fourths of an inch wide continuous seam of water-resistant adhesive conforming to MIL-A-140. Closure and strapping shall be in accordance with the appendix of the applicable container specification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

5.2.2 Level B. (Civil Agencies). Desk bodies and desk tops, packaged as specified, shall be packed as specified in the following sub-sections. Palletization of packed bodies and packed tops, when specified, shall be in accordance with applicable paragraphs below. Alternatively, desk may be packed as specified in accordance with METHOD "A-1" or "A-2" (drawings attached) at the option of the supplier.

THE FOLLOWING SECTIONS APPLICABLE TO R-1 and R-2, AND TOPS SHIPPED SEPARATELY FROM BODIES.

5.2.2.1 Shipping Containers. Shipping containers, either for the fully enclosed or wood-frame pedestal base packing, shall conform to type I, class 1, of PPP-B-636 for material used in the construction of the container. Burst test of fiberboard shall be as specified in the applicable paragraph. Style of box or cover shall be as specified in applicable paragraph or referenced drawing (figure). Separately packed desk tops shall be in shipping containers conforming to the above specification and the burst test of the fiberboard (exterior container) shall be not less than 275 p.s.i.

5.2.2.2 Desk Body with Leg Assembly Attached.

5.2.2.2.1 Wood-Frame Pedestal Base. (METHOD R-1) When specified, desk body shall be packed for shipment, legs down, mounted on a wood-frame base. Base shall be constructed in accordance with figure 5A, except that a tolerance in the given dimensions will be allowed to accommodate the particular desk being packed. Desk bodies so packed shall be suitable for handling (unloading, storage five high in warehouses, reshipment LCL or LTL freight) using conventional forklifts with standard 36-inch length blades for the entire handling operation. Desk bodies shall be packaged as specified in 5.1.2 except that in 5.1.2.4 ADD: The four outside corners of the desk pedestals shall be protected by use of built-up corrugated fiberboard pads of not less than 3/4 inch thickness, die-cut to fold and fit around the corners for a distance of not less than two inches on each side, and of a length to extend from top edge of desk corners (under top pad) to the top deck surface of wood-frame base. Pad surfaces in contact with finished surfaces of desk shall be lined or coated with a nonmarring substance or material. A scored and folded top pad, as shown in figure 5B, shall be used under the cover box specified in 5.2.2.2.2.

5.2.2.2.2 Cover Box. (METHOD R-1) The cover box shall be constructed of fiberboard, testing not less than 275 p.s.i., and in accordance with 5.2.2.1. The box may be of either the Side-Slotted Blank type or the RSC Half Slotted Box type, with depth sufficient to extend down on all sides for stapling to the deckboards of the wood-frame base (item A- Figure 6) when placed over the top of the mounted and packaged desk body. Bottom edges of cover box shall be stapled to the deckboards of the wood-frame base (item A-Figure 6), when placed over the top of the mounted and packaged desk body.

5.2.2.2.3 Strapping. (METHOD R-1) Mounted and covered desk body shall be secured to wood-frame pedestal base by two steel straps (minimum 1/2 x 0.020) placed one each at either end approximately 5 to 6 inches from the end, encircling the desk, and top deck boards(e) girthwise, but not in contact with leg assembly of desk. Preformed plastic or metal corner-edge protectors (4 inch minimum width) shall be used beneath strapping over corrugated fiberboard. Metal strapping shall conform to QQ-S-781. Plastic laminated strapping of equivalent tensile strength is an acceptable alternate.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

5.2.2.2.4 Fully-Enclosed Pack.- (METHOD R-2) (Desk Body) In accordance with Figure 8, when specified, each desk body, complete with leg assemblies attached, shall be packed in a fully-enclosed shipping container mounted on a wood-base frame. The shipping container shall conform to requirements of 5.2.2.1 with burst test of fiberboard being not less than 275 p.s.i, type RSC or CSSC at the option of the supplier. Shipping container shall be fitted with scored-and-folded pads of double-faced or double-walled fiberboard which when inserted within the container will "float" the desk body assembly in such manner as to prevent weight of desk from resting on legs. Scored-and-folded pads shall be of a minimum thickness when folded and inserted to provide not less than 1-inch of clearance between surfaces of sides and top of desk body, and inside surface of container. The bottom scored-and-folded pad shall be of fiberboard testing not less than 350 p.s.i. and of sufficient depth when folded and inserted to provide a minimum clearance of 1-inch between bottom of legs and inside surface of the bottom of the container. The bottom pad shall be slotted (die-cut) to take the leg assemblies, allowing the weight of the desk to be borne upon the bottoms of the desk pedestals. The bottom pads shall be full width and length of the inside dimensions of the container and shall provide the necessary support for the desk. (See drawing figure 8. for types of pads). Pads for top, front back, and sides shall be 200 p.s.i. burst test (minimum) and shall be of a type and style as shown on drawing figure 8. The pad across the desk front may be of such thickness and design to permit die-cut slotting for drawer handles, and in such cases, built-up pads required for drawer handles, and in such cases, built-up pads required for drawer handles in 5.1.2.5 may be omitted. Pad shall in no event provide less than 1/4 inch clearance between handles and inside surface of shipping container. Finished surfaces of desks shall be protected as specified in 5.1.2.5.

5.2.2.2.4.1 Alternate. (METHOD R-2) Where the manufacturer's standard commercial shipping container provides adequate interior protection in the form of pads, built-up and die-cut corner post protection, and desk is securely mounted on a suitable interior wood frame, with box constructed of not less than 275 p.s.i. test fiberboard, such container shall be acceptable in lieu of that specified in 5.2.2.2.4, provided that container is mounted on skid or expendable wood pallet for forklift handling. (see drawing figure 8.- Notes 1 and 2).

5.2.2.2.5 Palletization.- (METHOD R-2) Each fully enclosed desk body shipping container(5.2.2.2.4 or 5.2.2.2.4.1) shall be securely mounted on a base frame or expendable pallet which provides 4-way entry for conventional type forklift blades 36 inches in length. (see drawing figure 8). Securing of the shipping container to the base frame or expendable pallet shall be accomplished by either steel strapping or by use of a suitable adhesive (Morningstar-Paisley #65-554 or equal), or a combination of the two. Steel strapping shall conform to Specification QQ-S-781, type I, class A or B (3/4 inch by 0.020 min.), two bands encircling the container and top deck of base frame or pallet, applied one at either end, each being approximately 8 to 9 inches in from end. Preformed plastic or metal corner-edge protectors (4-inch minimum width) shall be used beneath steel straps over corrugated fiberboard. Plastic laminated strapping of equivalent tensile strength is an acceptable alternate for steel strapping. The bottom deck of either base frame or pallet shall provide sufficient load-bearing surface to prevent damage to tops of other containers when desk bodies are stacked five (5) high in storage.

5.2.2.2.6 Desk tops.- Desk tops packaged as specified in 5.1.2.6 shall be individually packed in shipping containers as specified in 5.2.2.1. Top and bottom surfaces shall be adequately cushioned and protected. Shipping container shall be fitted with scored-and-folded or built-up corrugated fiberboard pads around all edges of tops to maintain a minimum clearance of 1/2 inch between edges of top and inside surface of shipping container. Shipping container shall be of 275 p.s.i. test fiberboard, style FPF (five-panel-folder) or FTC (full telescope cover).

5.2.2.2.6.1 Palletization.- Eight desk tops, packed as specified in 5.2.2.2.6, shall be stacked flat on an expendable type wood pallet providing 2-way entry (sides only) for forklift handling, and banded with not less than three (3) straps, either steel or plastic laminated strapping, one strap at either end approximately 18 inches from end, with the third strap centered around girth of stack. Pallets shall be constructed to match the dimensions of the desk top containers (length and width) (See drawing figure 7). Top deck of pallet shall provide complete support for the packed tops, bottom deck shall provide sufficient load-bearing surface to prevent damage to top container of other palletized desk tops when stacked four (4) pallets high in storage. Preformed plastic or metal corner-edge protectors shall be used beneath strapping over corrugated fiberboard (4-inch minimum width). Lesser quantities shall be palletized in a like manner.

5.2.2.2.7 Bases and Pallets or Base Frames. Unless otherwise specified the detailed information incorporated in applicable drawings (figures) shall govern the requirements for dimensions, and construction of pedestals, frames, and pallets. Where an adhesive is to be applied to unitize container and base, wood surfaces shall be smooth and uniform to assure good adherence between the wood and fiberboard.

5.2.2.3 Alternate Methods.Methods A-1 and A-2 drawings (Figures 9, 10, 11, 12, 13 and 14) are self-explanatory and the preceeding paragraphs are applicable only in general to material used. Where dimensions shown for length and width of containers and palletization thereof are inconsistent with the actual length and width dimensions of the top of desk (78 inches by 40 inches), adjustments shall be made to suit the items being packed.

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:39Z
Check the source to verify that this is the current version before use.

5.2.3 Level B (Military). Each desk packaged as specified if 5.1.1 shall be packed in a shipping container conforming to domestic type, style A or B of PPP-B-591. The bottom panel of the shipping container shall have additional cleats provided so that all legs of the desk will rest on cleat members. Cleats on which legs of desk are brought to bear shall span the entire interior width of the container and shall be of sufficient width to equal the thickness of legs plus adequate projection at each side of legs to prevent legs from being shifted off cleats while in transit. The desk shall be braced, blocked, bolted, or strapped within the shipping container to prevent movement and subsequent damage to the desk. Surfaces of the desk in contact with blocks, braces, or straps shall be cushioned to prevent damage to the desk. End grain nailing shall not be used to hold blocking in place. Strapping used for anchoring shall conform to type I, class A or B of QQ-S-781. When specified, the desk shall be blocked and braced in a manner to insure that the weight of the desk will not rest upon the desk legs.

5.2.3.1 Alternatively, shipping containers may be used that conform to domestic type style A or B of PPP-B-601; or class I, style 2, 2-1/2 or 4 of PPP-B-621.

5.2.3.2 Alternatively, shipping containers may be used that conform to style B-4 of MIL-C-11456. Crates shall have skid frames so designed that all legs of the desk will rest on cleat members placed across crate bottom to provide an equal degree of load bearing surface for all legs. Cleats on which legs of desk are brought to bear shall be of sufficient width to equal the thickness of legs plus adequate projection at each side of legs to prevent legs from being shifted off cleats while in transit. When specified, the desk shall be blocked and braced in a manner to insure that the weight of the desk will not rest upon the desk legs.

5.2.4 Level C. Unless otherwise specified, desks, tops or desk bodies, packaged and packed to insure safe transportation to point of destination and immediate use, may be packed in accordance with manufacturer's standard commercial practice when such is acceptable to common or other carrier.

5.3 Marking.

5.3.1 Civil Agencies. In accordance with Federal Standard No. 123, shipping containers shall be marked with (1) applicable Federal Stock Number; (2) Federal Item Description, including specification name, type, class, style, and color; (3) Quantity and Unit (e.g. 1 Each Body Only; 1 - Each Top Only; (5) Name and Address of Contractor/Manufacturer; (6) Contract and Order Number; (7) Gross Weight and Cube; (8) Special Marking D. to indicate that the item is packed in two (2) containers and the additional marking as specified in 5.4.3.

5.3.2 Military Requirements. In addition to any special marking required by the contract or order, shipping containers shall be marked in accordance with MIL-STD-129.

5.3.3 Additional Marking. Arrows and the word "UP" shall be printed or stenciled on the upper third of the sides of the containers and "FRAGILE, THIS SIDE UP" shall be printed or stenciled on the top of the containers in letters two inches high. Other markings, as required by carriers, shall be applied in accordance with carrier regulations.

6. NOTES

6.1 Intended use. The desk covered by this specification is designed for use in a private or or semi-private office. It has an overhanging back and sides which serve for conference-work and eliminate the need for a separate conference table. Metal general office accessory furniture items and the bookcase and credenza covered by Federal Specification AA-O-240, Office Furniture, Steel, Unitized, are recommended for use with this style of desk.

6.2 Ordering data. Purchasers should exercise any desired options offered herein and procurement documents should specify the following:

(a) Title, symbol, and date of this specification.
(b) Whether preproduction sample is required (see 3.1).
(c) Whether linoleum or plastic tops are required (see 3.2.3 and 3.3.10.4).
(d) Whether locks are required (see 3.3.9).
(e) Whether hanging file supports are required (see 3.3.18.3).
(f) Whether special identification marking is required (see 3.5).
(g) Whether completely set-up desk is required (see 3.6).
(h) Selection of applicable levels of packaging (see 5.1).
(i) Selection of applicable levels of packing (see 5.2).
(j) Marking requirements (see 5.3).

6.3 Plastic laminate top. A pinch roller pressure of 50 pounds per square inch has been found to give a satisfactory bond for the adhesive.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

Desk Contains:

	Minimum Inside Clear Dimensions (Usable Space)
2 Storage Drawers	12" W x 5-13/16" H x 24-7/16" D
1 Center Drawer	20-1/8" W x 1-5/16" H x 18-1/16" D
2 Letter Drawers	12" W x 11-1/8" H x 23-15/16" D

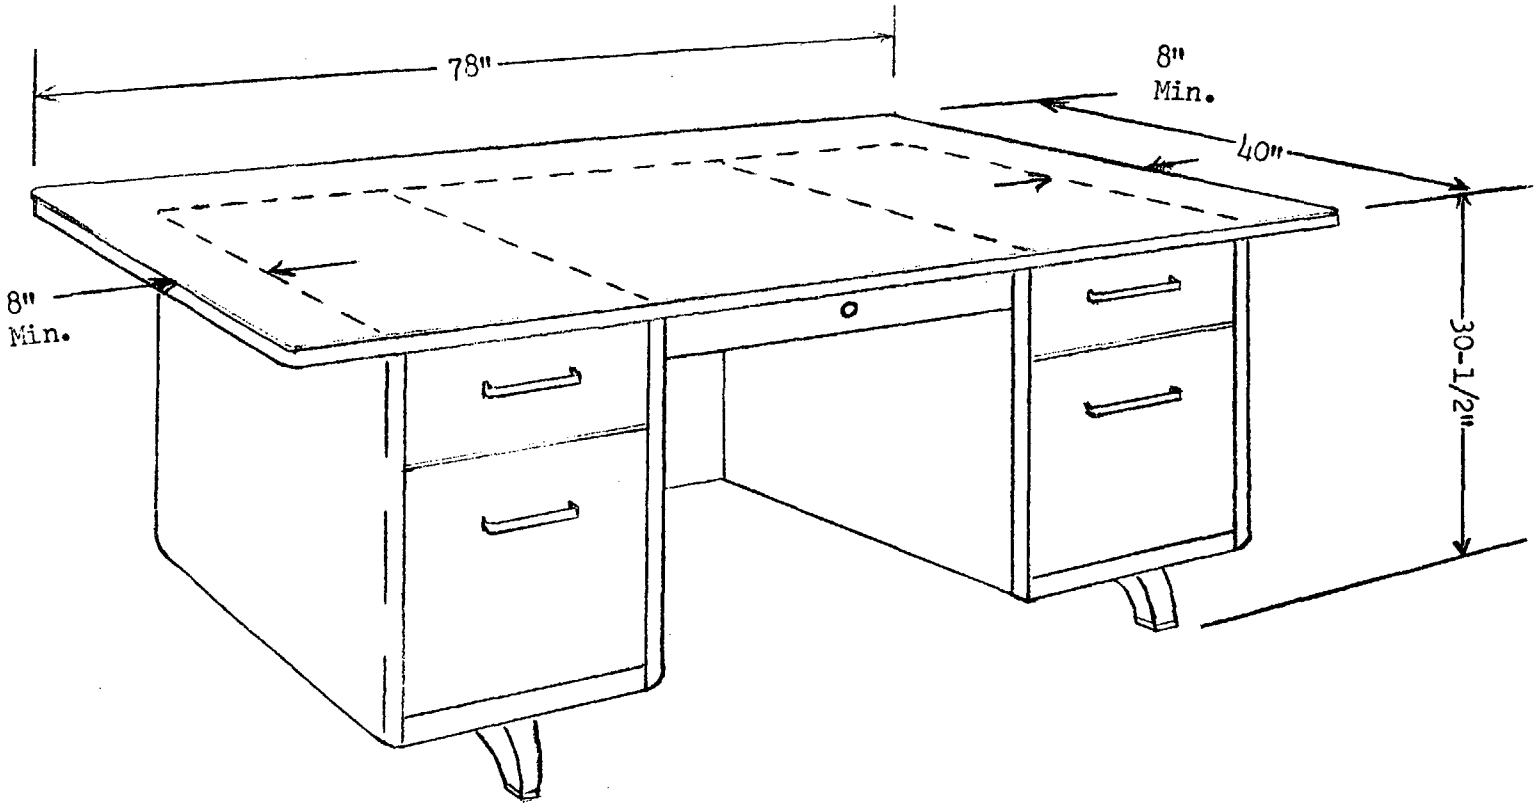


Figure 1 - Desk, Conference Type

Source: https://assist.dla.mil - Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

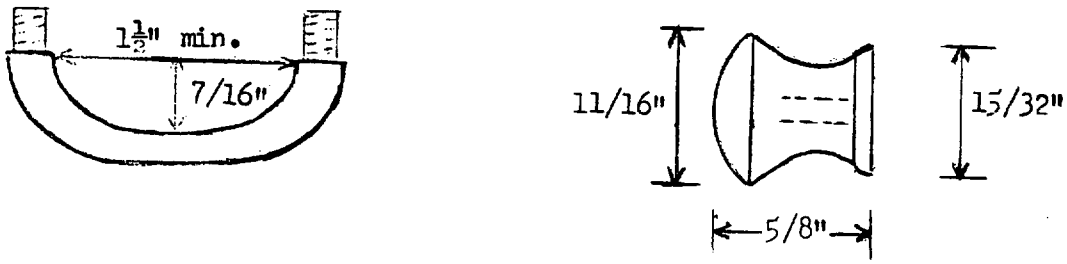


Figure 2 - Sliding Shelf Pull, Alternate Designs

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

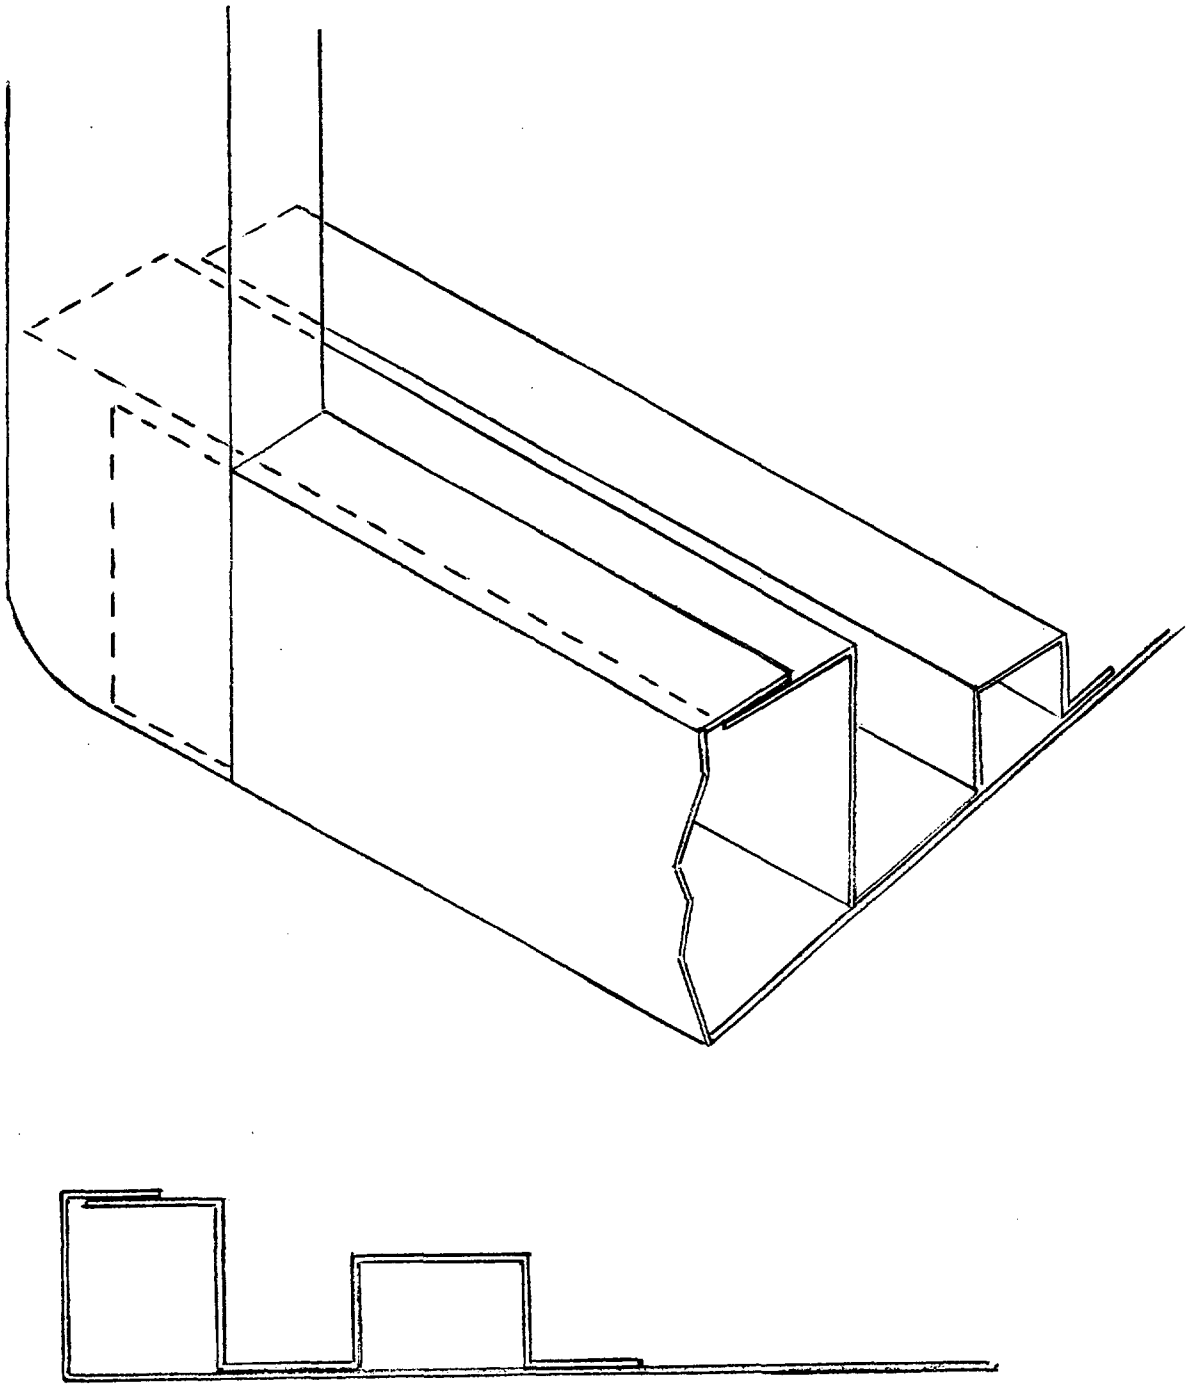


Figure 3 - Bottom Panel Reinforcement

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

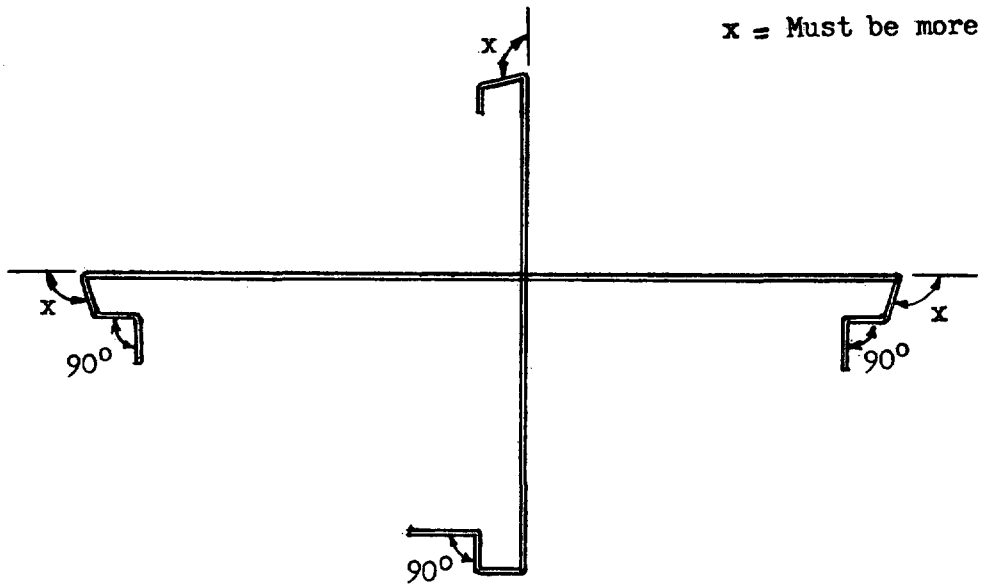


Figure 4 - Outside Drawer Front
(Horizontal and Vertical Sections)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

AA-D-00195d

ITEM	MATERIAL LIST	REQ
A	1X4 NOM.	2
B	2X4 NOM.	2
C	2X4 NOM.	4

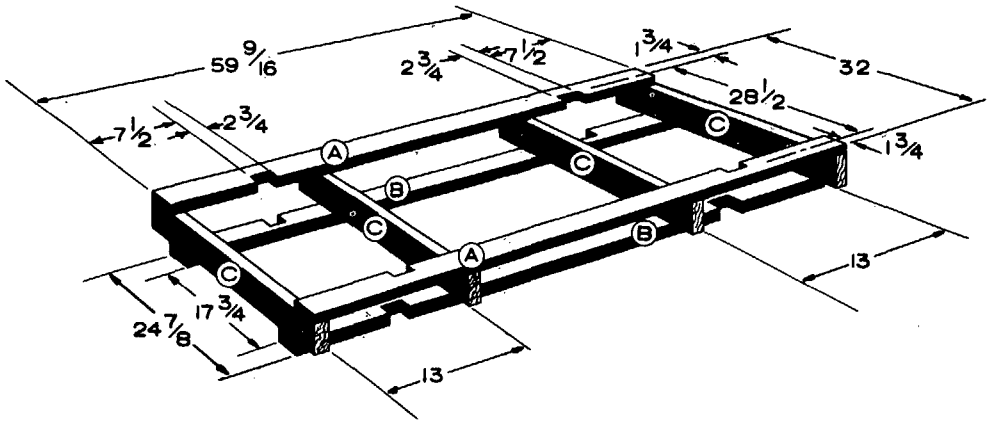


Figure 5-A

Method R-1

GENERAL SERVICES ADMINISTRATION FEDERAL SUPPLY SERVICE
SUPPLY DISTRIBUTION DIVISION
WASHINGTON, D. C.

SKID FOR CONFERENCE DESK PACK, R-1


DRAWN BY	DATE	SCALE (Unless otherwise specified)
CHARLES W. OGDEN	4/8/63	NONE
CHECKED	DATE	DRAWING NO.
APPROVED BY	DATE	PP-1103-C
A. Allegri	2.14.63	

REV.	REV. BY	DATE	CHECKED BY	DATE

REVISIONS

27

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

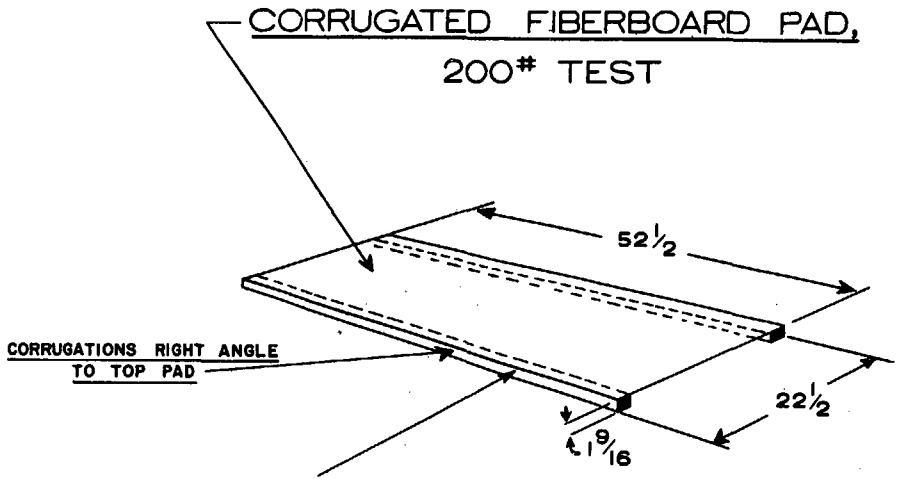

BUILT-UP PAD OF 200# TEST CORRUGATED FIBERBOARD (2)
9 LAYERS

Figure 5-B

Method R-1

GENERAL SERVICES ADMINISTRATION FEDERAL SUPPLY SERVICE
SUPPLY DISTRIBUTION DIVISION
WASHINGTON, D. C.

TOP PAD FOR CONFERENCE DESK, R-1

DRAWN BY	DATE	SCALE (Unless otherwise specified)
CHARLES W. OGDEN	9/9/63	NONE
APPROVED BY	DATE	DRAWING NO.
	2-14-65	PP-1104-C

REV.	REV. BY	DATE	CHECKED BY	DATE	APPROVED BY	DATE
REVISIONS						

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

AA-D-00195d

ITEM	DESCRIPTION	REQ
1	SKID	1
2	LEG PROTECTORS	4
3	POLY BAG	1
4	FRONT CORNER PROTECT.	2
5	HANDLE PROTECTORS	4
6	REAR CORNER PROTECT.	2
7	REAR STRAPPING PROTECT.	2
8	FRONT " "	2
9	TOP PAD	1
10	CARTON	1
11	CORK DISKS	8

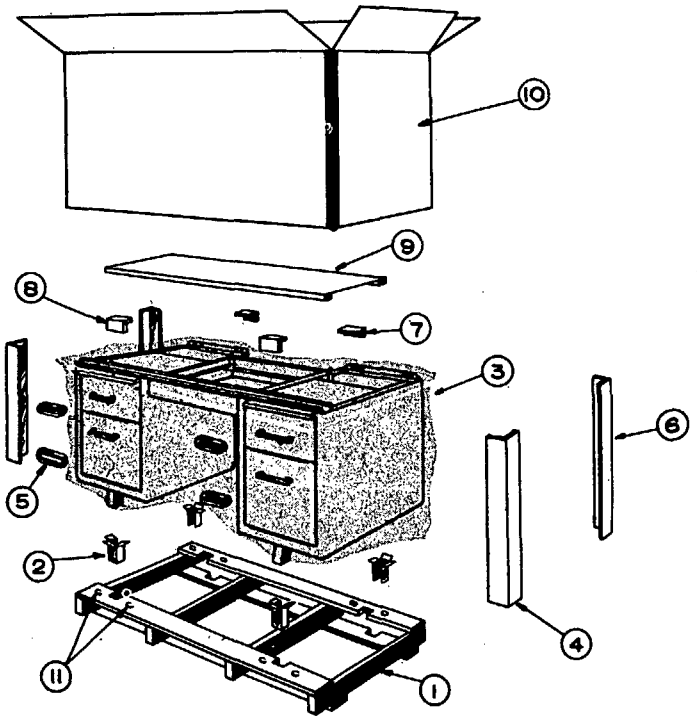


Figure 6

Method R-1

GENERAL SERVICES ADMINISTRATION FEDERAL SUPPLY SERVICE
SUPPLY DISTRIBUTION DIVISION
WASHINGTON, D. C.

R-1 PACKAGING, CONFERENCE DESK

DRAWN BY CHARLES W. OGDEN 2/14/63
CHECKED BY
APPROVED BY Jos. Allegri 2/14/63
SCALE (Unless otherwise specified) NONE
DRAWING NO. PP-1105-C


REV.	REV. BY	DATE	CHECKED BY	DATE

REVISIONS

29

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

Not To Scale

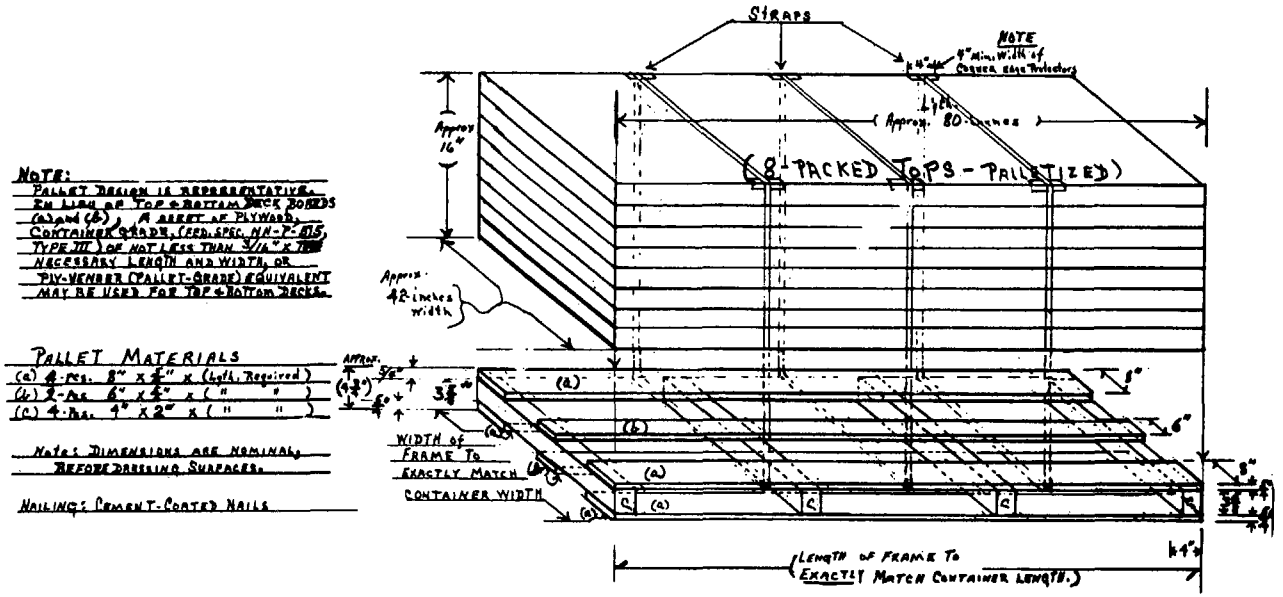


Palletization of Tops
Paragraph 5.2.2.2.6.1

Figure 7

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

Figure 8, Page 1, Method R-2

Fully enclosed pack (body only)

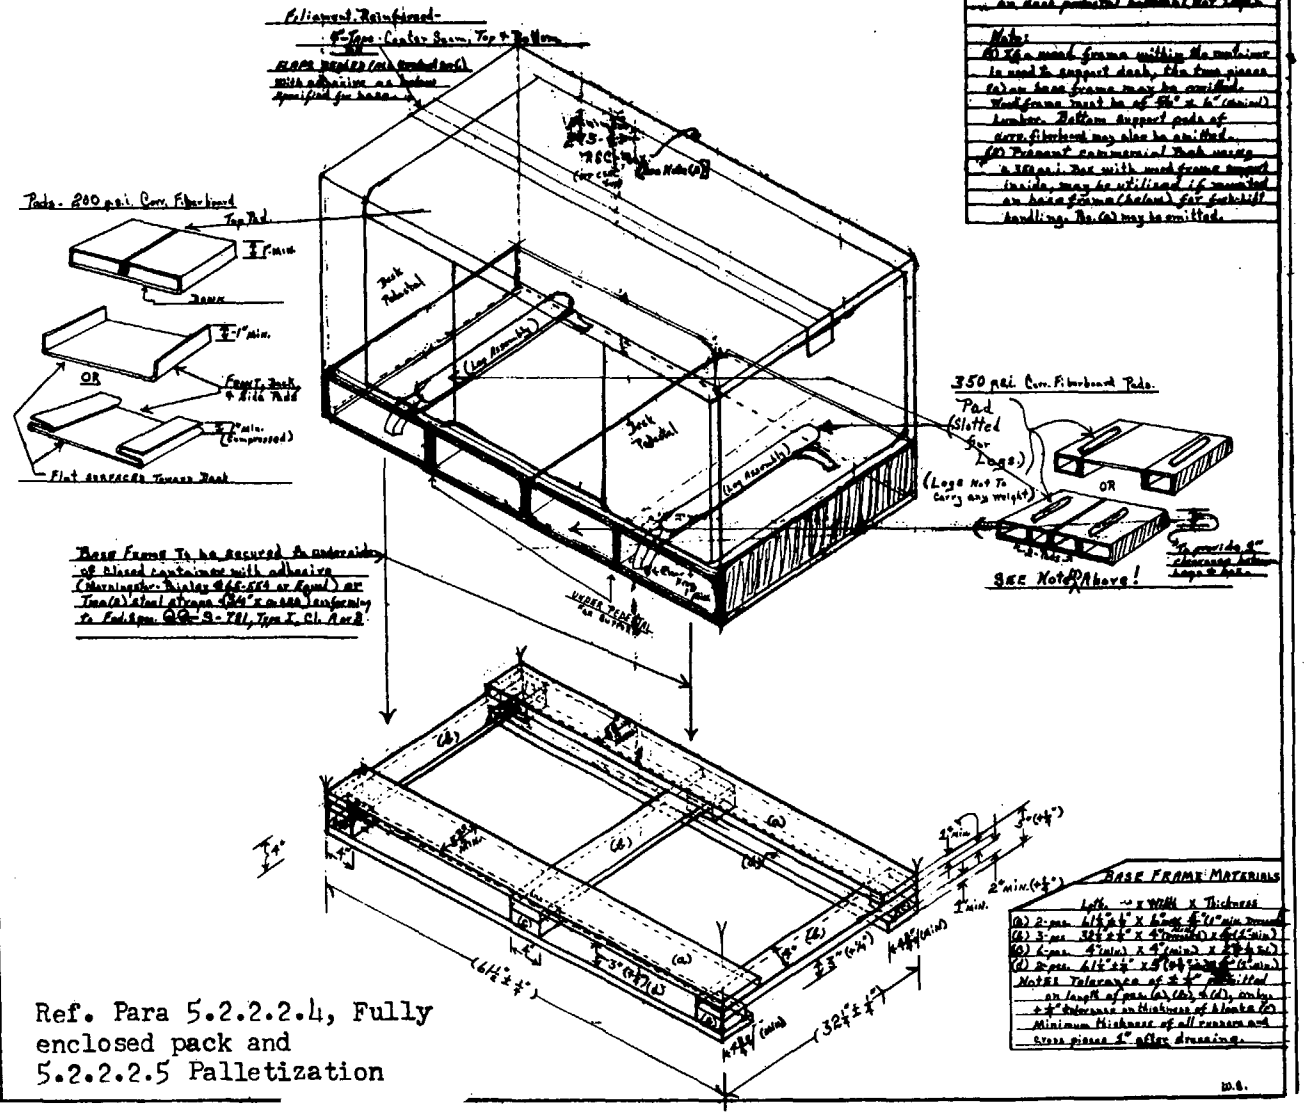

Ref. Para 5.2.2.2.4, Fully enclosed pack and 5.2.2.2.5 Palletization

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

Ref. Notes (1) and (2)
Figure 8, Page 1

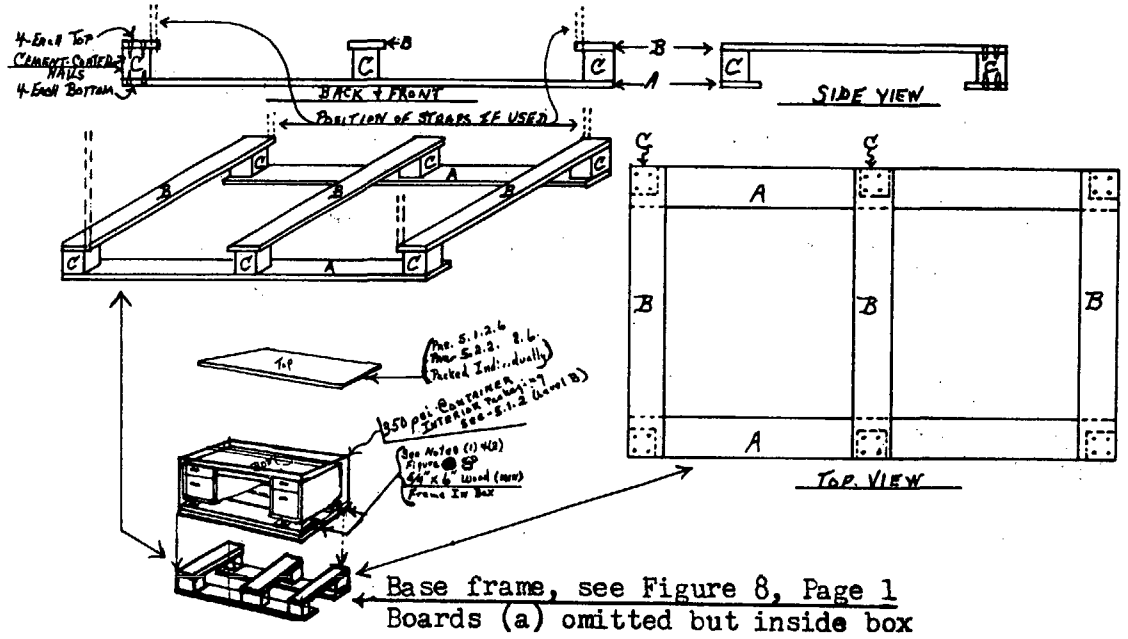


Figure 8, Page 2, Method R-2

Source: https://assist.dla.mil -- Downloaded: 20260-26T11:39Z
Check the source to verify that this is the current version before use.

Note: See "Notice" and Packaging & Packing Exceptions on Figure 11, Method A-1

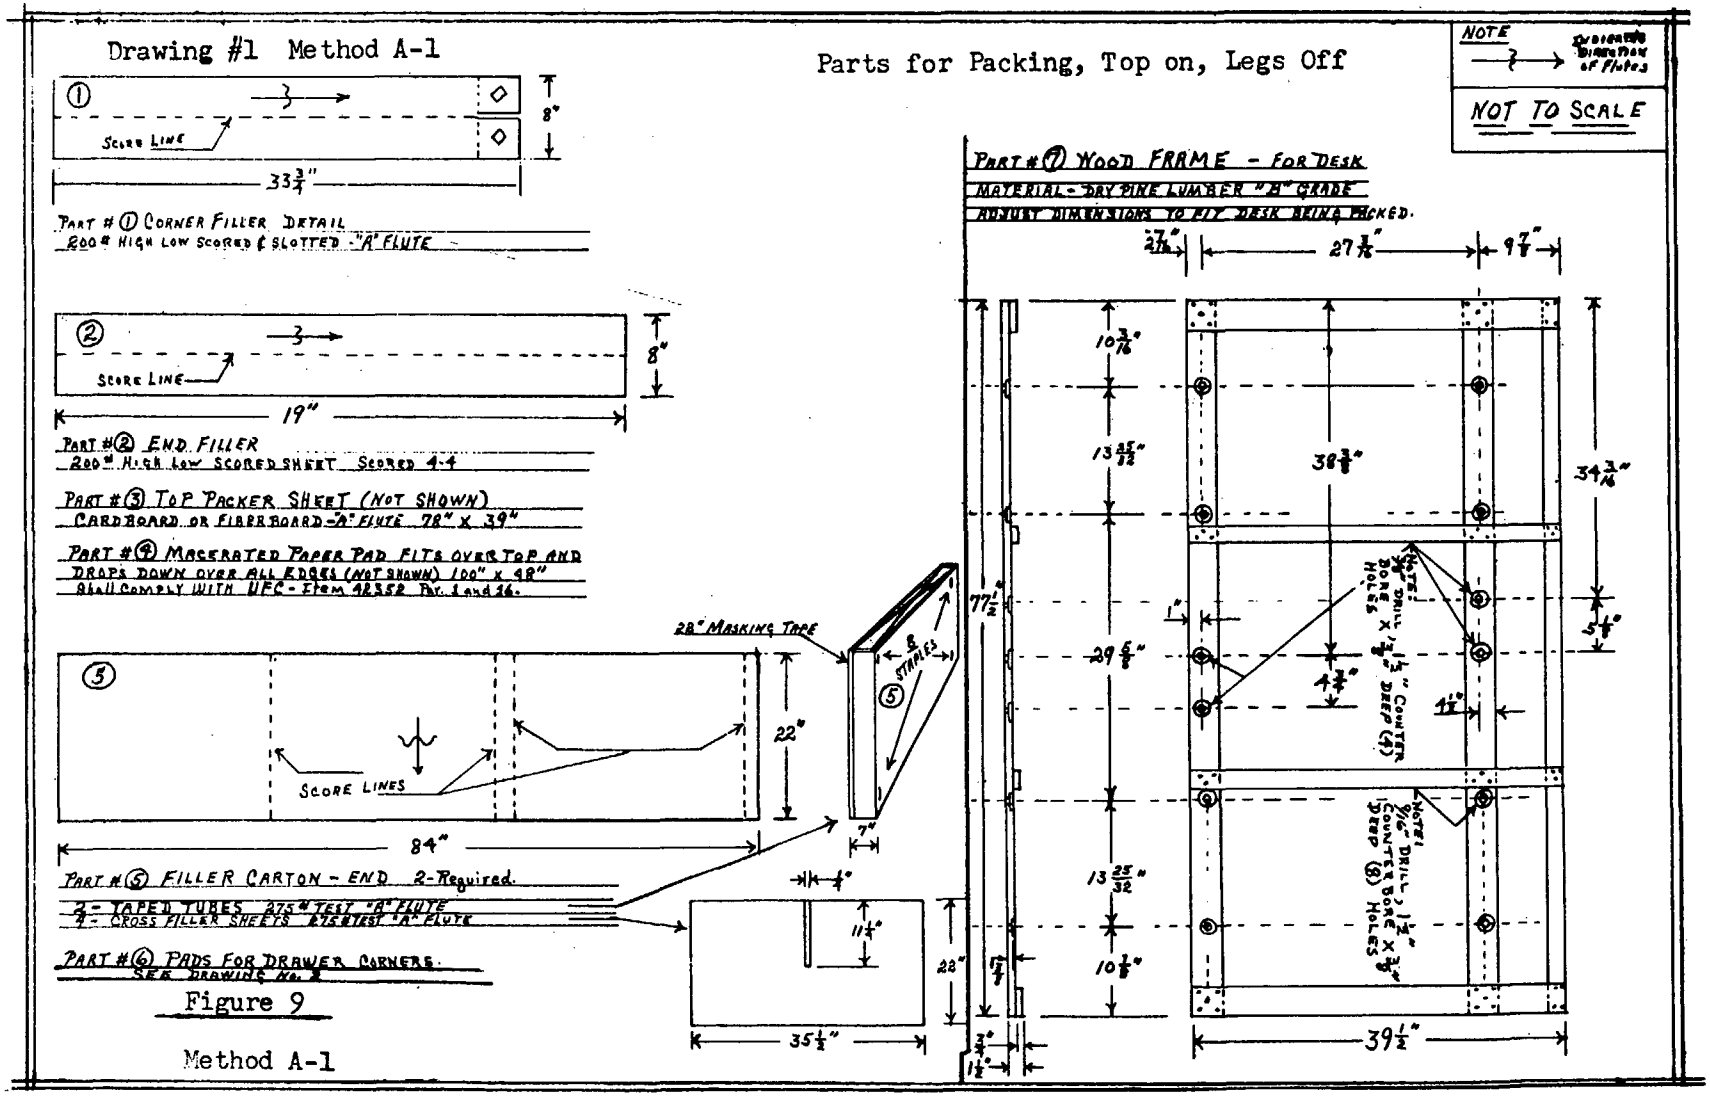


Figure 9

Method A-1

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.


Figure 10

Method A-1

Drawing #2

Assembly of Parts for Packing
(See detail of parts, Drawing #1
For Carton and Expendable Pallet, Drawing #3


NOT TO SCALE

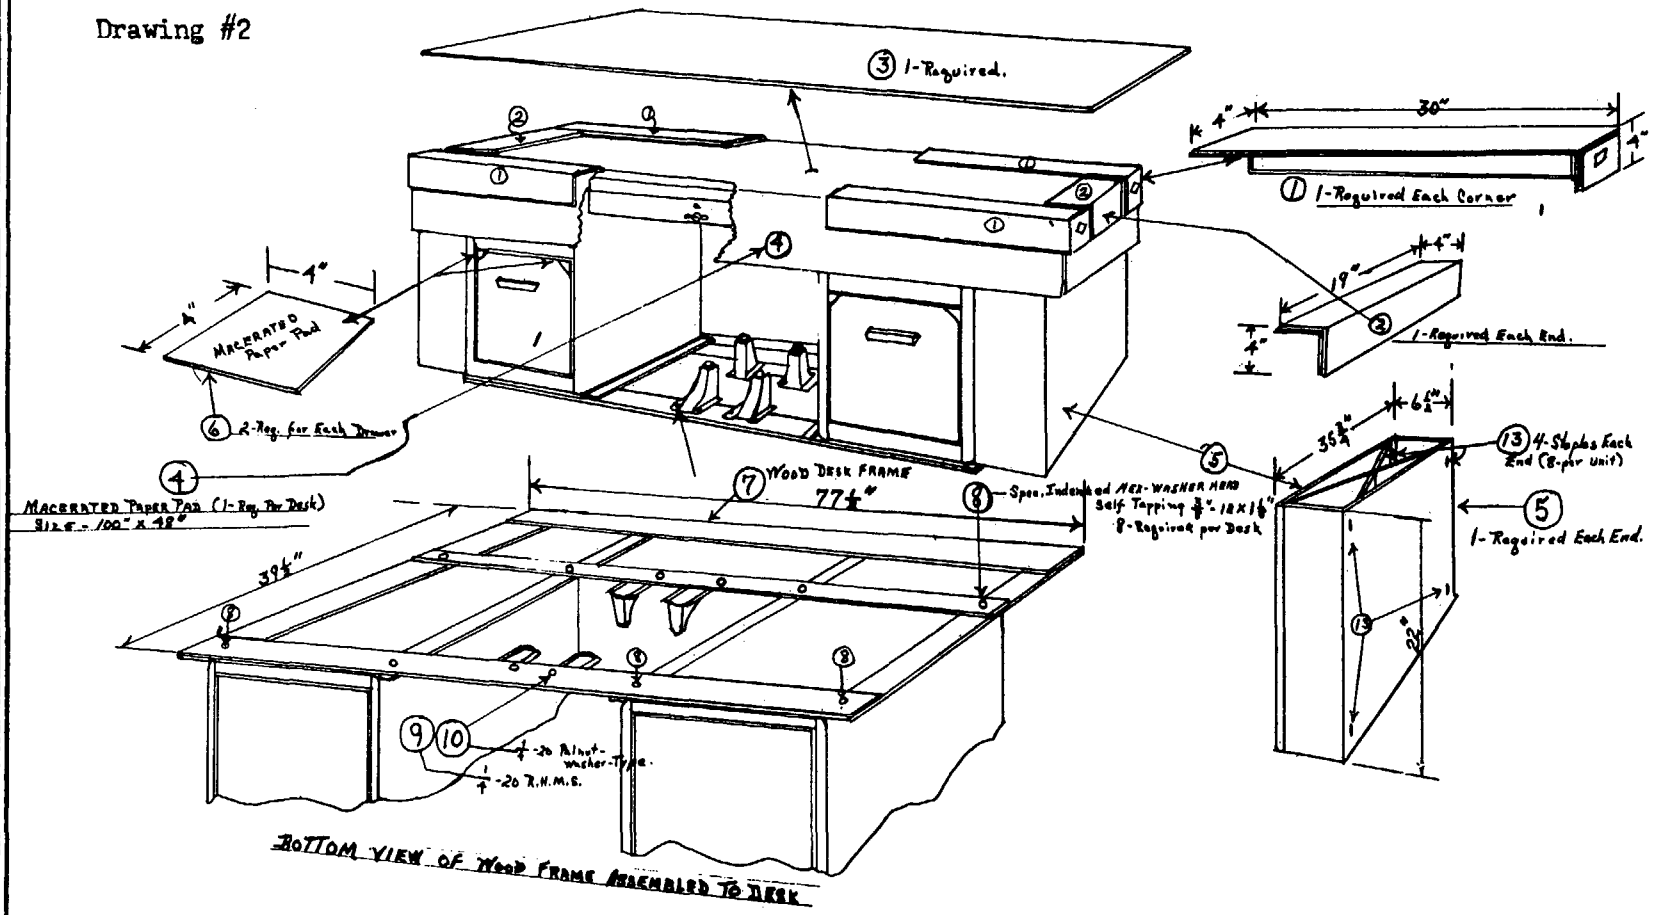

Source: https://assist.dla.mil -- Downloaded: 2026/10-26T11:39Z
Check the source to verify that this is the current version before use.

Final Assembly, Tops on, Legs off

NOT TO SCALE

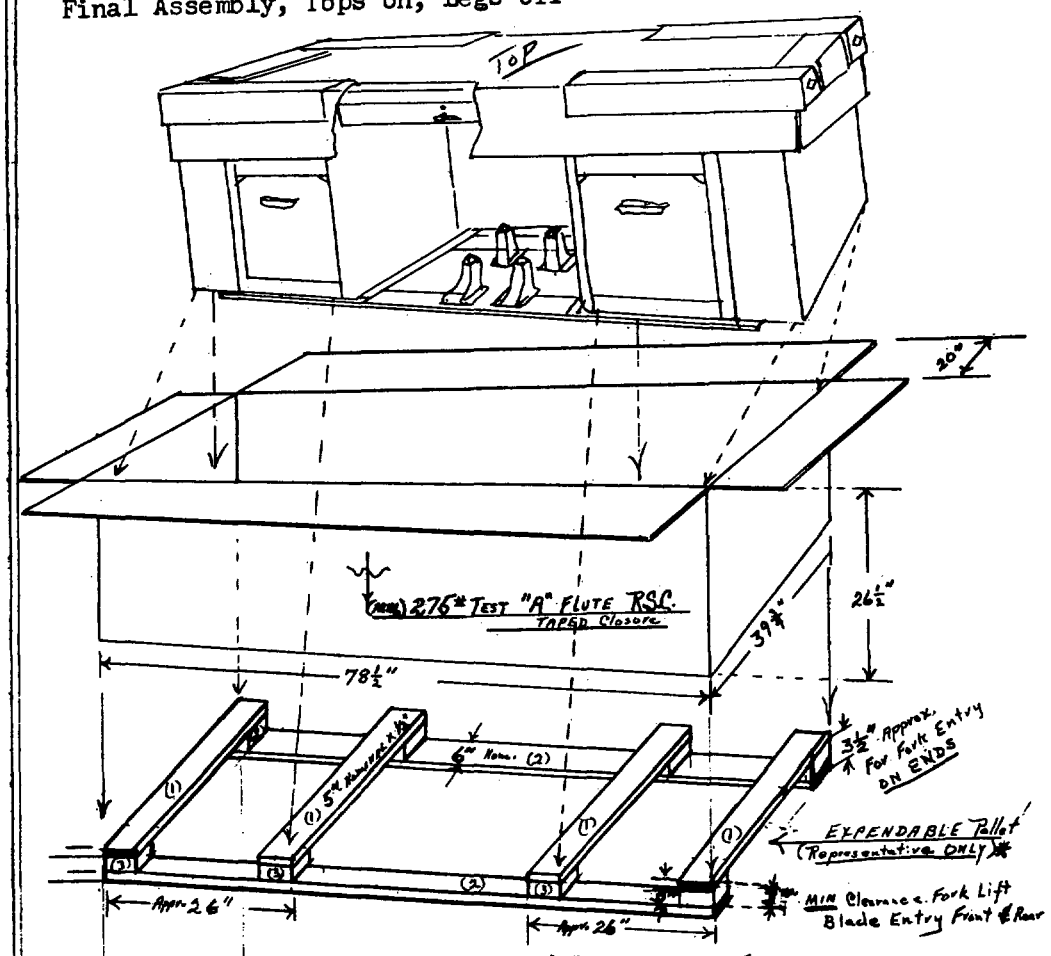

PALLET Materials - HARDWOOD OR DRY PINE "B" Grade, OR SPRUCE
(1) 1" X 5" (NOMINAL) PINE / ½" X 5" (Nom.) Hardwood / X Lgth. to EXACTLY MATCH CONTAINER WIDTH.
(2) 1" X 6" (") " / ½" X 6" (") " / X " " " " " LENGTH.
(3) Support Blocks - 6" X 5" (Nominal) X Thickness Necessary to Provide Entry [illegible] For Blades of Forks
NOTE: SECURE CONTAINER TO PALLET WITH ADHESIVE (MORNING STAR-PAISLEY #645-554 or Equal) OR Steel Strapping OR Plastic-LAMINATED Strapping.
* PALLET MAY BE OF MATERIAL & DESIGN OF CONTRACTOR BUT MUST PROVIDE 3½" FORK ENTRY

N O T I C E :
THE SPECIFICATION FOR DESK CONSTRUCTION PERMITS WIDE LATITUDE IN THE MANUFACTURING METHODS, ALSO SHIPMENT IS PERMITTED IN METHODS OPTIONAL WITH THE MANUFACTURER, DEPENDING ON DESK CONSTRUCTION. THIS METHOD OF SHIPMENT ALTERNATE "A - 1" ALLOWS FOR SHIPMENT WITH THE TOP OF THE DESK SECURED IN POSITION BUT WITH THE LEGS OF THE DESK REMOVED AND ENCLOSED IN THE DESK PACK. LEGS ARE INSTALLED AT TIME OF SET UP FOR USE. INSTRUCTIONS FOR INSTALLATION OF LEGS MUST BE ENCLOSED IN THE SHIPPING CONTAINER WITH THE DESK.


PACKAGING AND PACKING EXCEPTIONS:
METHOD "A-1" ALTERNATE METHOD OF PACKING IS COMPLETELY DETAILED IN THE THREE (3) DRAWINGS, THEREFORE THE REQUIREMENTS OF THE TEXT MATTER OF SECTION 5, PREPARATION FOR DELIVERY, pertaining to packaging with LEGS-ON and TOP-REMOVED) LEVEL B ARE APPLICABLE INSOFAR AS GENERAL REQUIREMENTS ONLY, AND THE REQUIREMENTS CONTAINED IN THESE DRAWINGS SHALL BE USED IF METHOD "A-1" ALTERNATE METHOD IS SELECTED BY A BIDDER.

Figure 11

Method A-1

Source: https://assist.dla.mil -- Downloaded: 202640-26T11:39Z
Check the source to verify that this is the current version before use.

Figure 12
Method A-2

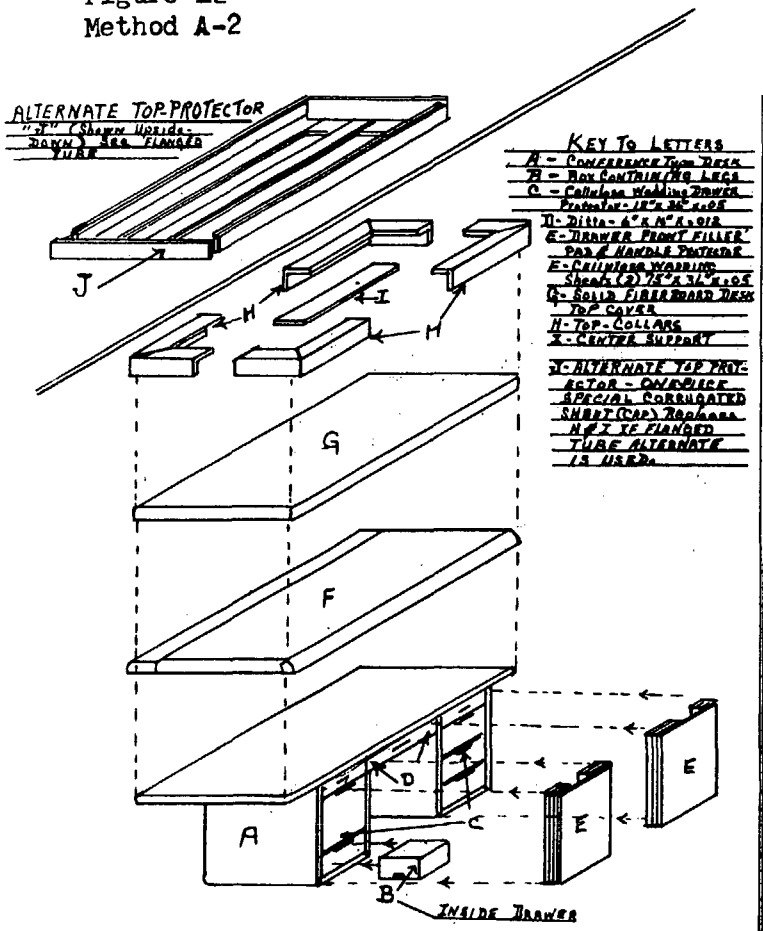


Note: See Notice and Packaging and Packing exceptions on Figure 14, Method A-2

Figure 13, Method A-2

Alternate packaging and packing.
Top on and legs off

NOT TO SCALE

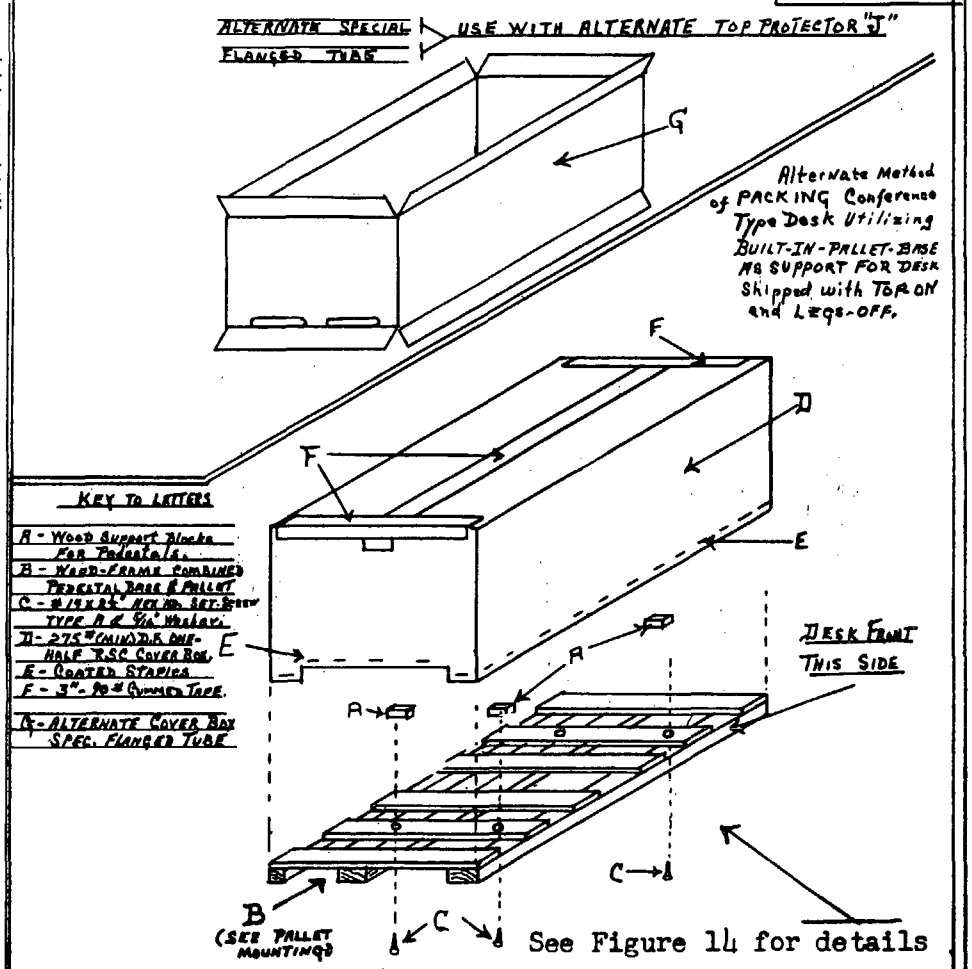

See Figure 14 for details

Source: https://assist.dla.mil -- Downloaded: 20260-26T11:39Z
Check the source to verify that this is the current version before use.

Figure 14 - Method A-2

Top on, Legs off


NOT TO SCALE


NOTICE: THE SPECIFICATION FOR DESK CONSTRUCTION PERMITS WIDE LATITUDE IN THE MANUFACTURING METHODS. ALSO SHIPMENT IS PERMITTED IN METHODS OPTIONAL WITH THE MANUFACTURER, DEPENDING ON DESK CONSTRUCTION. THIS METHOD OF SHIPMENT ALTERNATE "A-2" ALLOWS FOR SHIPMENT WITH THE TOP OF THE DESK SECURED IN POSITION BUT WITH THE LEGS OF THE DESK REMOVED AND ENCLOSED IN THE DESK PACK. LEGS ARE INSTALLED AT THE TIME OF SET UP FOR USE. INSTRUCTIONS FOR INSTALLATION OF LEGS MUST BE ENCLOSED IN THE SHIPPING CONTAINER WITH THE DESK.

PACKING AND PACKAGING EXCEPTIONS: METHOD "A-2" ALTERNATE METHOD OF PACKING IS COMPLETELY DETAILED IN THE TWO (2) DRAWINGS, THEREFORE THE REQUIREMENTS OF THE TEXT MATTER OF SECTION 5. PREPARATION FOR DELIVERY, _____ (pertaining to packaging and packing with LEGS-ON and TOP-REMOVED) LEVEL B are APPLICABLE INSOFAR AS GENERAL REQUIREMENTS ONLY, AND THE REQUIREMENTS CONTAINED IN THESE DRAWINGS SHALL BE USED IF METHOD "A-2" ALTERNATE METHOD IS SELECTED BY A BIDDER.

WOOD FRAME PEDESTAL BASE - MOUNTED ON 4-WAY ENTRY PALLET

(See "B", Figure 8, Page 1

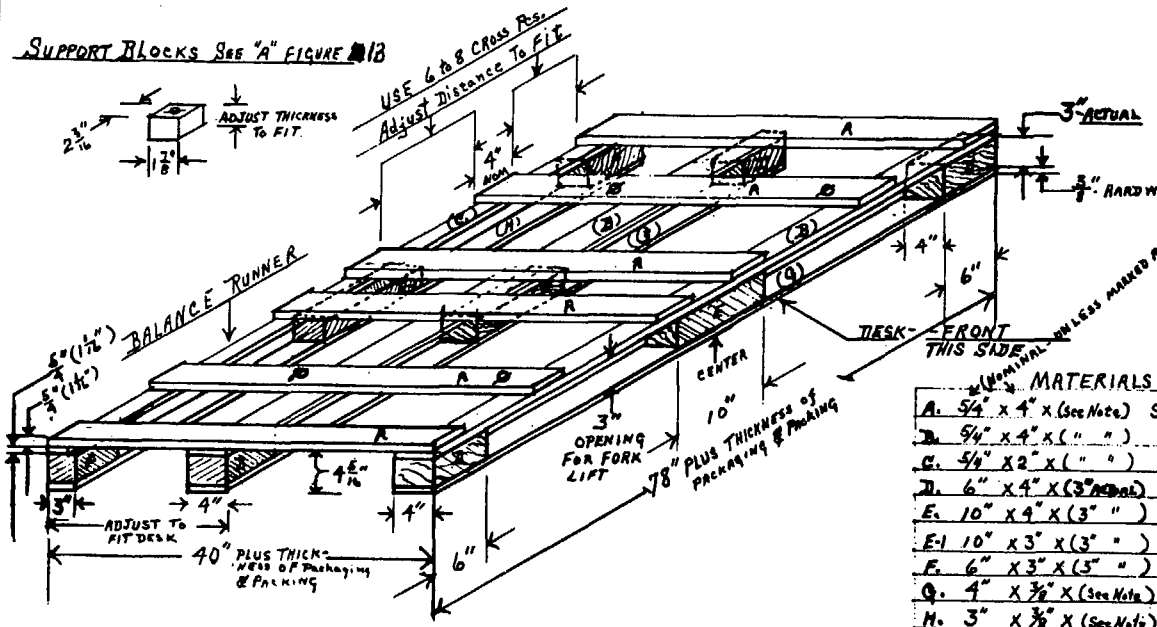

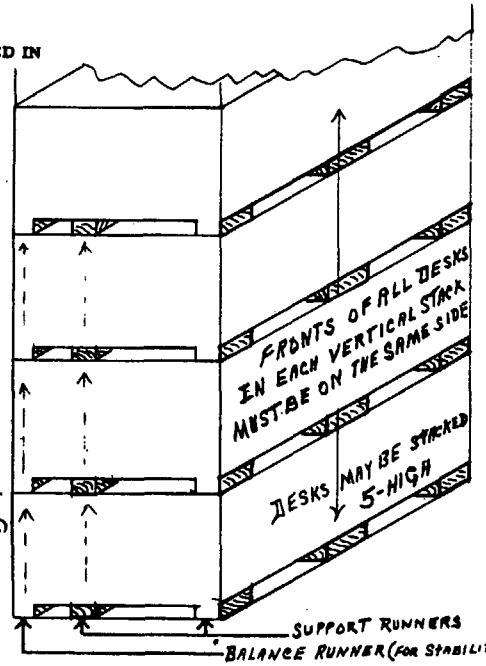

	MATERIALS (Nominal)		REQ.	USE
A.	5/4" x 4" x (See Note)	SPRUCE*	- 4-6-8	CROSS-RUNNERS DESK PEDESTAL RESTS
B.	5/4" x 4" x (" ")	"	- 2	LONGITUDINAL TOP RUNNERS - "SUPPORT"
C.	5/4" x 2" x (" ")	"	- 1	" " "BALANCE" TOP RUNNER
D.	6" x 4" x (3" Actual)	"	- 4	SUPPORT BLOCKS TO PROVIDE MIN. 3" FORK LIFT BLADE OPENINGS - FRONT & REAR PICK-UP
E.	10" x 4" x (3" ")	"	- 2	
E-1	10" x 3" x (3" ")	"	- 1	
F.	6" x 3" x (3" ")	"	- 2	
G.	4" x 3/8" x (See Note)	HARDWOOD	- 2	LONGITUDINAL BOTTOM "SUPPORT" RUNNERS
H.	3" x 3/8" x (See Note)	" "	- 1	" " BOTTOM "BALANCE" RUNNER.

NOTE: LENGTH ADJUSTABLE TO EXACTLY MATCH DIMENSIONS OF DESK CONTAINER

* SPRUCE OR GRADE "A" DRY PINE OR EQUIVALENT.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.