MILITARY SPECIFICATION

WEBBING, TEXTILE, TUBULAR, PARA-ARAMID, INTERMEDIATE MODULUS

This amendment forms a part of Military Specification MIL-W-87127(USAF), 17 May 1978.

PAGE 9

TABLE IV, Column 3, line 7: Add "3/".

After footnote 2/: Add "3/ Testing may be done using double pin jaw design as specified in 4.4.1 through 4.4.1.4. In case of dispute of test values, the higher values obtained with either the double pin jaws or the split drum jaws, separately, are acceptable."

Add the following new paragraphs:

"4.4.1 Double pin and jaw design.

4.4.1.1 Alternate jaw design. The alternate jaw design is identified as the double pin jaws of the design specified in Figures 1 through 7.

4.4.1.2 Machine adjustment. Mount the jaws with careful attention to rotational and axial alignment. Set the speed of the moving jaw at 1 ± 1/4 inch per minute and the initial jaw separation such that the distance between the tangent points where the specimen first touches the primary (large diameter) pins is 12 ± 0.1 inch.

4.4.1.3 Specimen size and number. Each specimen shall be the full width of the tape or webbing and 60 inches long. Test five specimens or enough to get five acceptable breaks. An acceptable break is defined as one which occurs in the unsupported length of the specimen between the primary pin tangent contact points or at the contact points, but not within the material which is wrapped around each double pin jaw.

4.4.1.4 Specimen mounting. Wrap the specimen around the primary and secondary pins of each jaw as shown in Figure 8. Be careful to keep all legs of the specimen in alignment with the direction of stress application, and successive wraps exactly in line. For materials having a strength less than 500 lbs./inch of width, or for stronger materials which are not breaking acceptably, insert a double layer of cotton fabric (Cloth, Silesta, Cotton, MIL-C-326)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:50Z
Check the source to verify that this is the current version before use.

between the two layers of Kevlar which pass around the primary pin in both top and bottom jaws."


Add Figures 1 through 8.

Custodian:
Air Force - 11

Preparing Activity:
Air Force - 11

(Project 8305-F764)


Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:50Z
Check the source to verify that this is the current version before use.

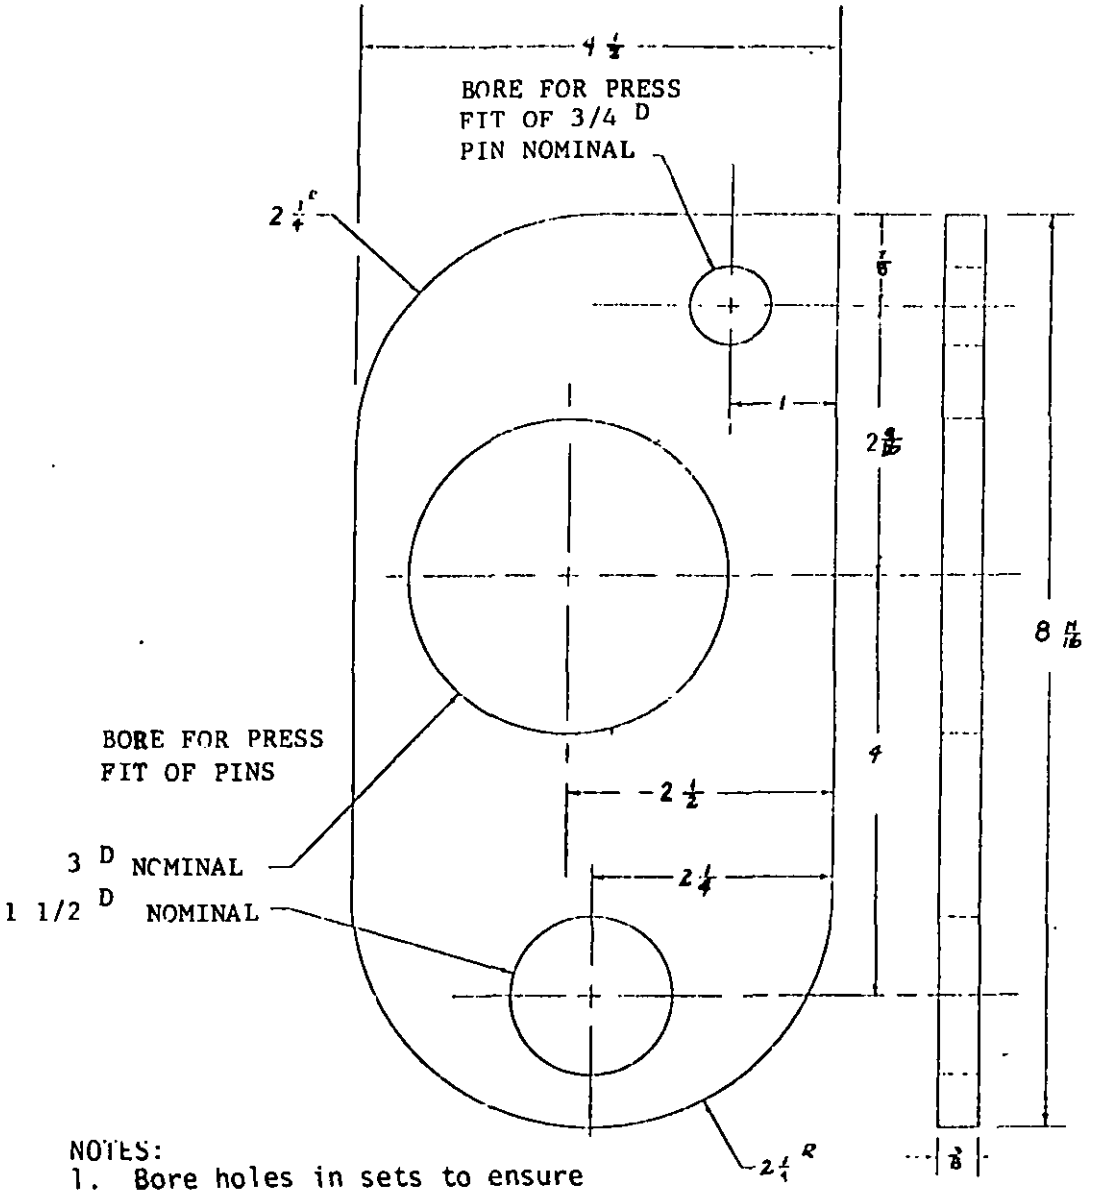

NOTES:
1. Bore holes in sets to ensure hole alignment.
2. Heat treat 3/4 D pin before boring.
3. Minimum interference fit between pin and hole - .001 per inch dia.
4. Type 303 stainless steel - material.
5. Quantity required - 4.
6. Dimensions are in inches. Tolerances: fractions ± 1/64, decimals ± .005, and angles ± 1/4°. Deburr and break all edges to .005 maximum. Concentricity on common diameter: within .003 tir. All surfaces to be machined to rms of 125. Threads are class 2. Normality, squareness, and parallelism of all surfaces to be within .005 per inch to a maximum of .010 per surface.

FIGURE 1. Side plate.


Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:50Z
Check the source to verify that this is the current version before use.

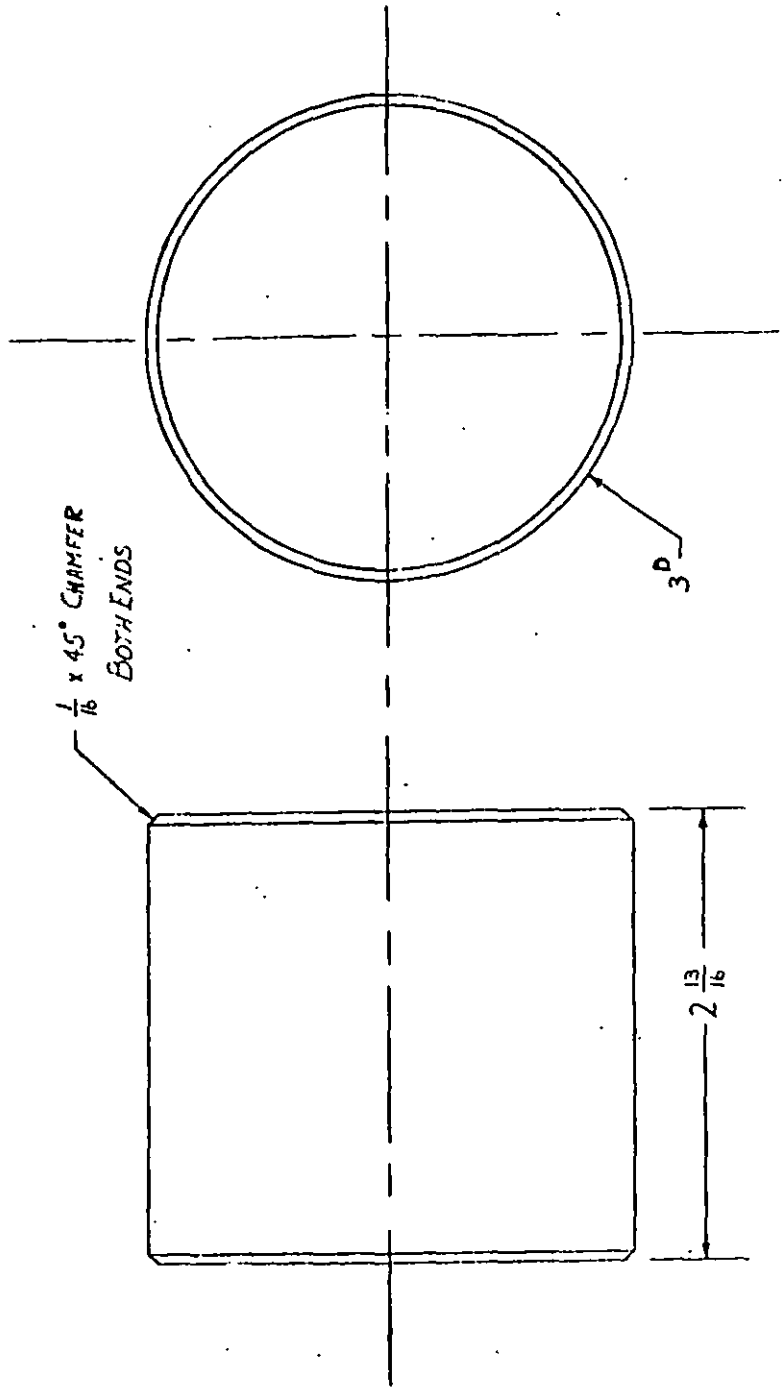

NOTES:
1. Type 303 stainless steel - material.
2. Quantity required - 2.
3. See Figure 1, Note 6.

FIGURE 2. Primary pin.


Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:50Z
Check the source to verify that this is the current version before use.

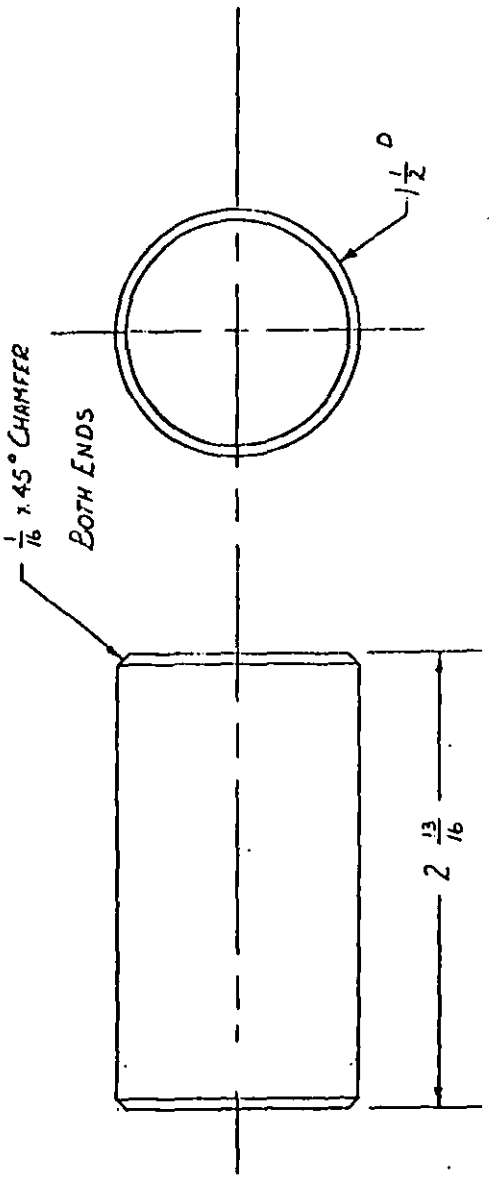

NOTES:
1. Type 303 stainless steel - material.
2. Quantity required - 2.
3. See Figure 1, Note 6.

FIGURE 3. Secondary pin

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:50Z
Check the source to verify that this is the current version before use.

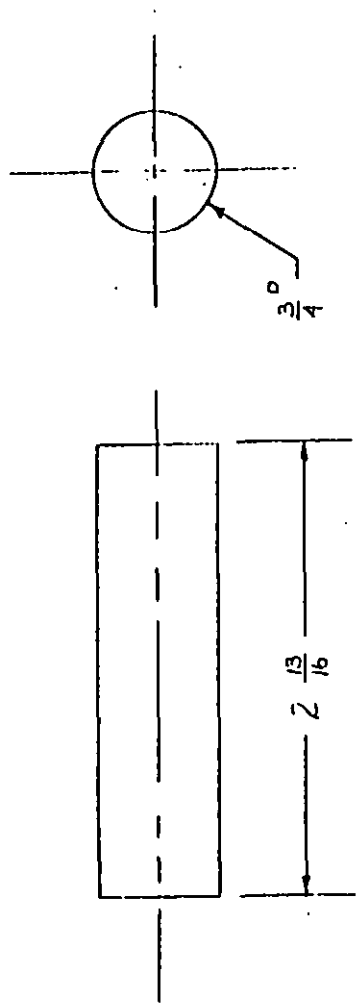

NOTES:
1. Type 416 stainless steel - material.
2. Quantity required - 4.
3. Heat treat to full hardness.
4. Draw for stress relief.
5. See Figure 1, Note 6.

FIGURE 4. Attachment pin.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:50Z
Check the source to verify that this is the current version before use.


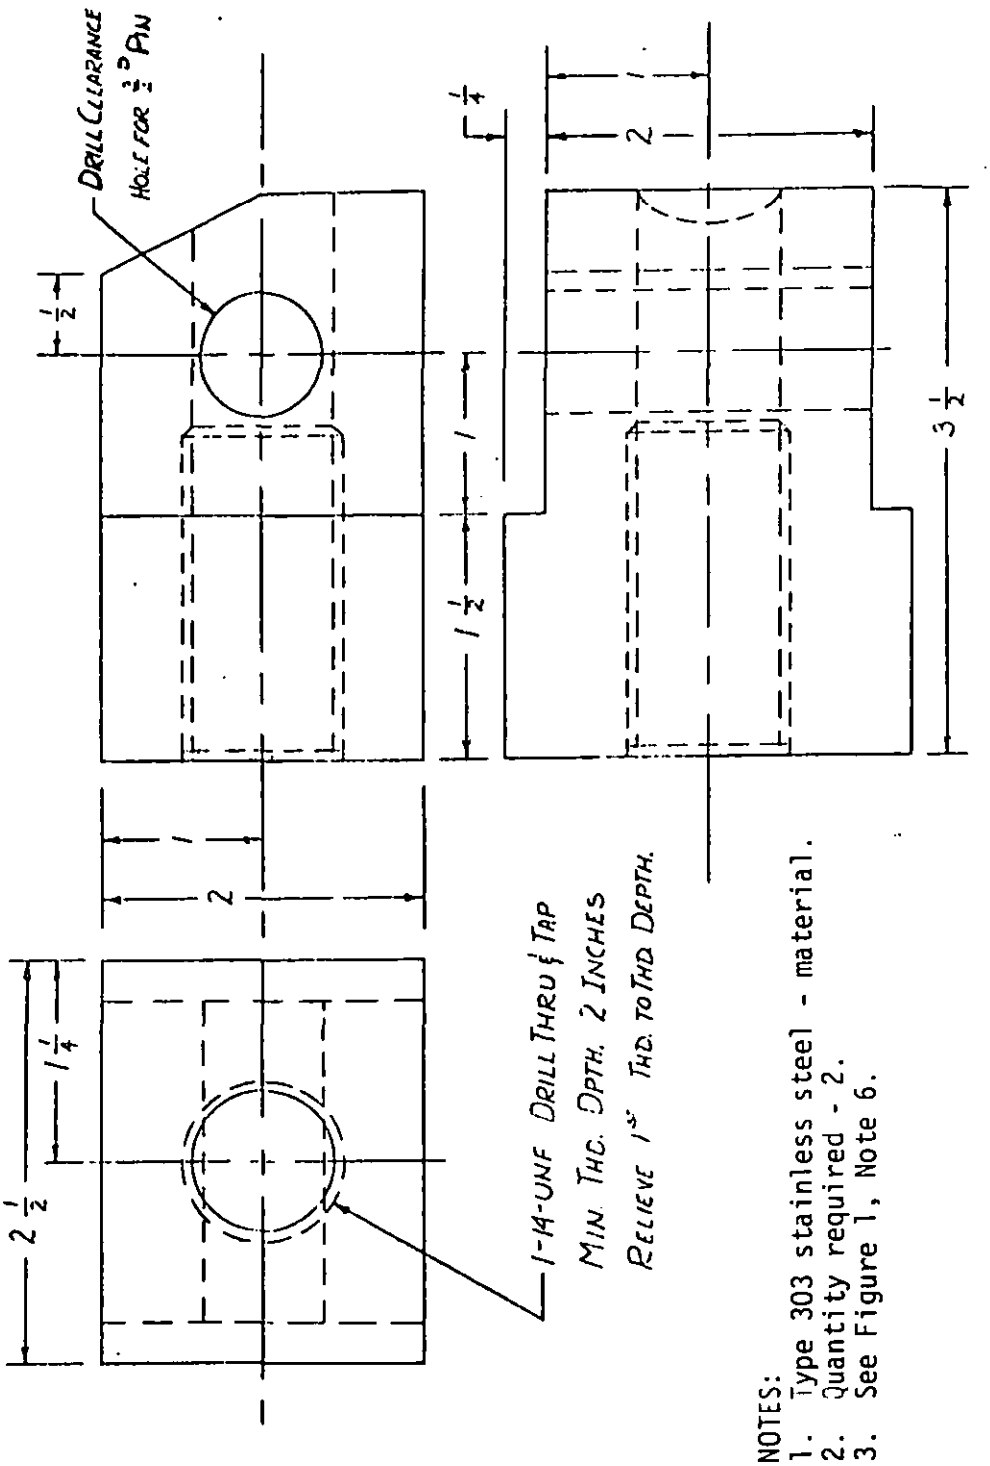


FIGURE 5. Attachment block.


Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:50Z
Check the source to verify that this is the current version before use.

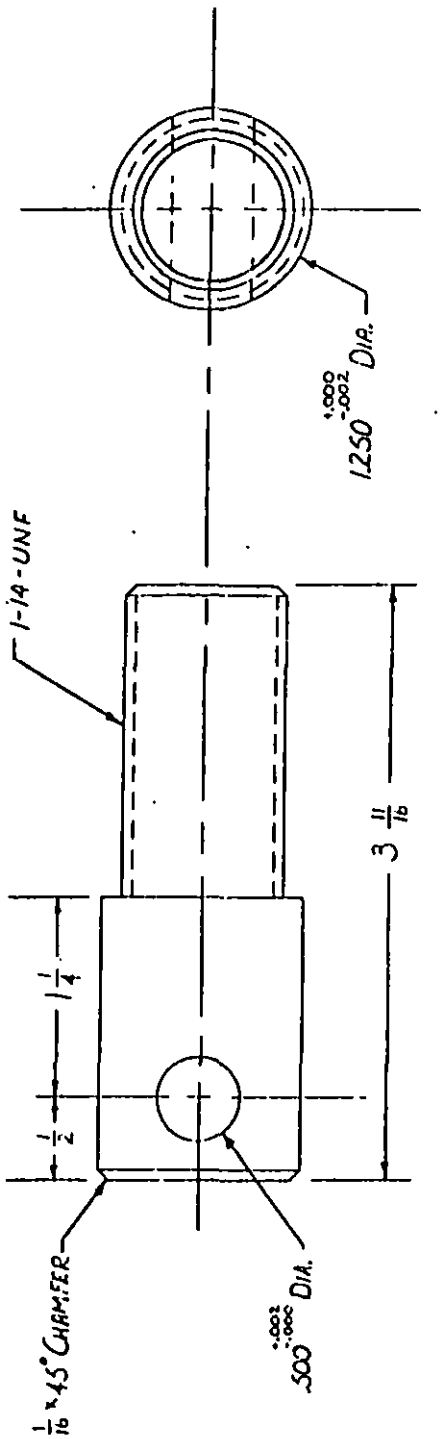

NOTES:
1. Type 303 stainless steel - material.
2. Quantity required - 2.
3. See Figure 1, Note 6.

FIGURE 6. Instron connector pin.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:50Z
Check the source to verify that this is the current version before use.

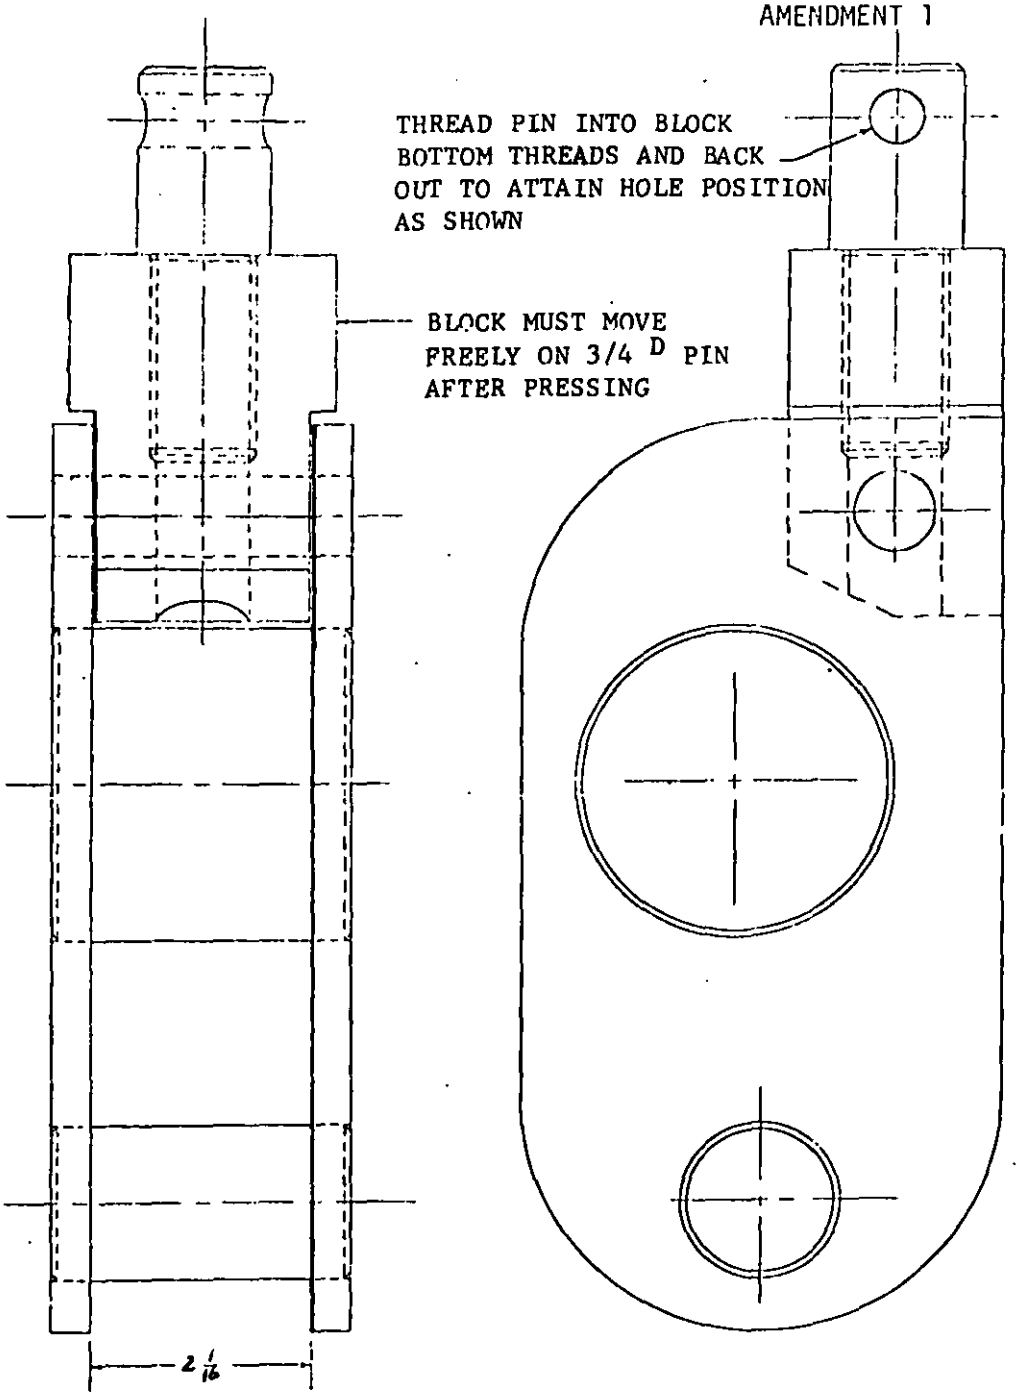

NOTES:
1. Press side plates on to pins to attain specified separation.
2. Ends of pins should be flush with outside surface of side plates after pressing.
3. Pins must be parallel, side plates must be parallel and pins must be perpendicular to side plates after pressing.
4. See Figure 1, Note 6.

FIGURE 7. Double pin jaw - assembly.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:50Z
Check the source to verify that this is the current version before use.

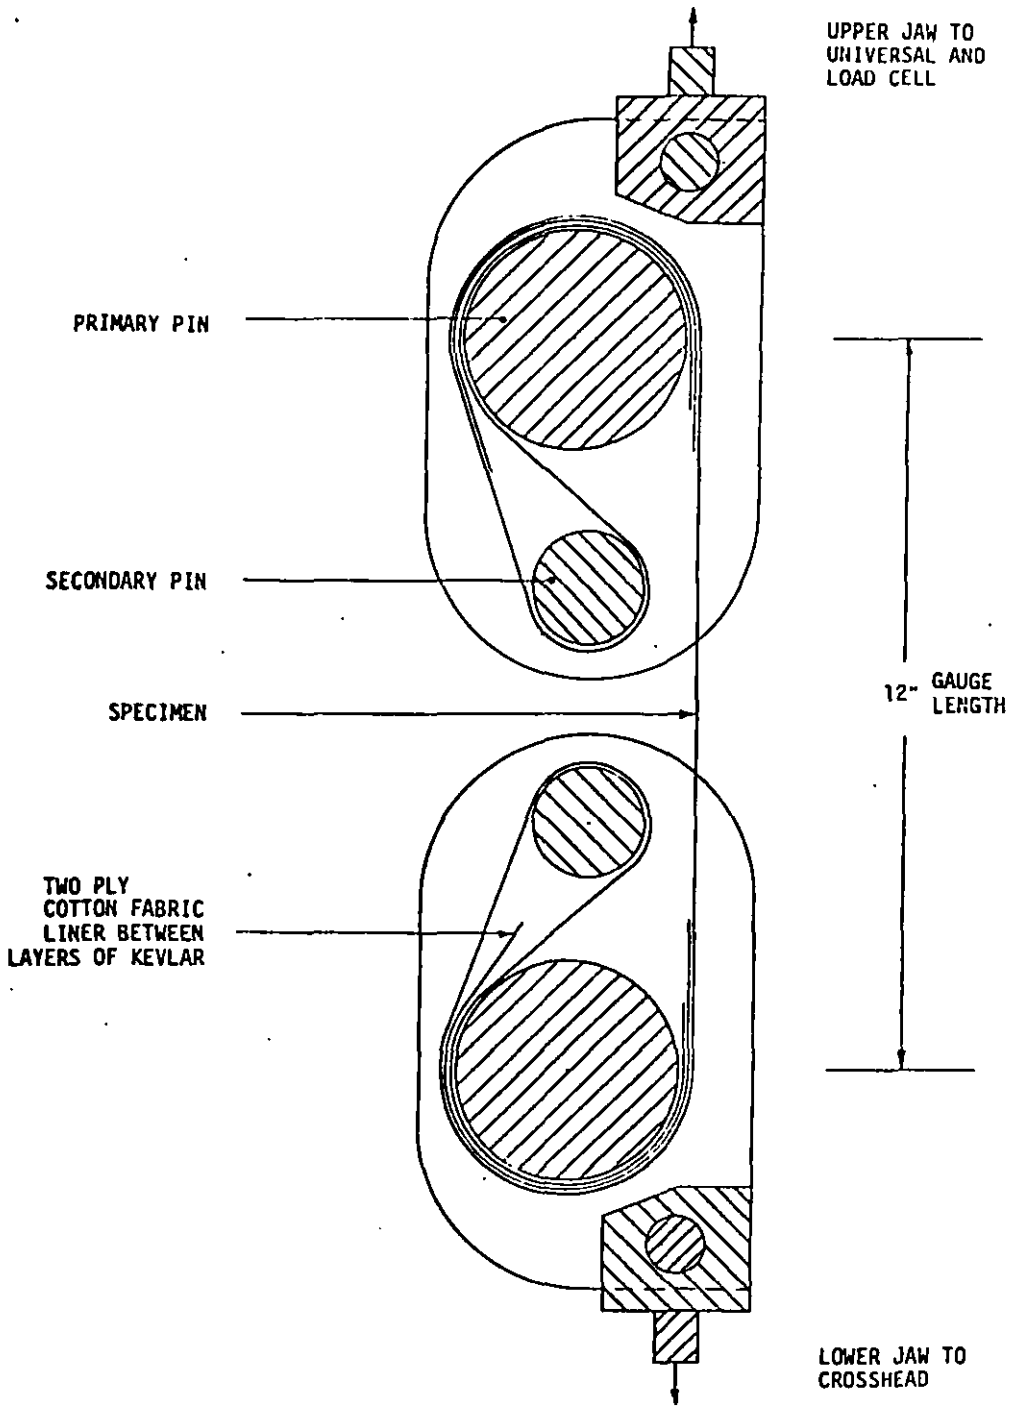


FIGURE 8. Test configuration for double pin jaw.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:50Z
Check the source to verify that this is the current version before use.