INCH-POUND
MIL-DTL-45913E
w/ AMENDMENT 1
21 February 2024
SUPERSEDING
MIL-DTL-45913E
19 May 2021

DETAIL SPECIFICATION
NUTS, SELF-LOCKING, HEXAGON, PREVAILING TORQUE

This specification is approved for use by all Departments and Agencies of the Departments of Defense.

1 SCOPE

1.1 Scope. This specification establishes mechanical and performance requirements for prevailing-torque hexagon locknuts.

1.2 Classification. Locknuts will be of the following types, grades and series (see 6.2).

1.2.1 Types.

Type I Nut, self-locking, hexagon, UNC/UNF-2B (see MIL-DTL-45913/1 and /2).
Type II Nut, self-locking, hexagon, UNC/UNF-3B (see MIL-DTL-45913/3 and /4).
Type III Nut, self-locking, flanged, prevailing-torque.

1.2.2 Grades. Three grades of carbon and alloy steel locknuts are designated as Grade 2, Grade 5, and Grade 8 in accordance with SAE J995, and two groups of corrosion resistant steels, designated as Group 1 or Group 2 as noted in ASTM F594. Nonferrous materials as specified herein may be used for locknuts, but tensile strengths specified below do not apply (see 6.2).

1.2.3 Series. Locknuts covered by this specification are intended to be of the following series.

Hex locknut (regular)
Hex thin locknut (jam)
Hex thick locknut
Hex heavy locknut
Hex flanged locknut

Comments, suggestions, or questions on this document should be addressed to U.S. Army DEVCOM, Ground Vehicle Systems Center, ATTN: Standardization, FCDD-GVS-SAT, MS #268, 6501 E. 11 Mile Road, Warren, MI 48397-5000 or emailed to usarmy.detroit.devcom-gvsc.mbx.standardization@army.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A FSC 5310

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.
Source: https://assist.dla.mil -- Downloaded: 2026-10-22T04:10Z
Check the source to verify that this is the current version before use.

2 APPLICABLE DOCUMENTS.

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification and in the associated specification sheets. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-DTL-13924	-	Coating, Inorganic, Black, for Ferrous Metals
MIL-DTL-45913/1	-	Nut, Self-Locking, Hexagon, Non-Metallic Locking Feature, 250°F, UNC/UNF-2B.
MIL-DTL-45913/2	-	Nut, Self-Locking, Hexagon, All-Metal Locking Feature, 250°F, UNC/UNF-2B.
MIL-DTL-45913/3	-	Nut, Self-Locking, Hexagon, Non-Metallic Locking Feature, 250°F, UNC/UNF-3B.
MIL-DTL-45913/4	-	Nut, Self-Locking, Hexagon, All-Metal Locking Feature, 250°F, UNC/UNF-3B.
MIL-DTL-495	-	Finish, Chemical, Black, for Copper Alloys
MIL-PRF-8625	-	Anodic Coatings for Aluminum and Aluminum Alloy
MIL-PRF-32647	-	Zinc-Nickel Electroplating for Fasteners

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-1916	-	DOD Preferred Methods for Acceptance of Product

(Copies of these documents are available online at https://quicksearch.dla.mil.)

2.3 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

AEROSPACE INDUSTRIES ASSOCIATION (AIA)

NASM1312	-	Fastener Test Methods
NASM1312-1	-	Fastener Test Methods; Method 1 Salt Spray
NASM1312-6	-	Fastener Test Methods; Method 6 Hardness
NASM25027	-	Nut, Self-Locking, 250° F, 450° F and 800° F

(Copies of these documents are available online at http://www.aia-aerospace.org.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T04:10Z
Check the source to verify that this is the current version before use.

AMERICAN SOCIETY OF MECHANICAL ENGINEERS (ASME):

ASME B1.1	-	Unified Inch Screw Threads (UN and UNR Thread Form)
ASME B1.3	-	Screw Thread Gaging Systems for Acceptability: Inch and Metric Screw Threads (UN, UNR, UNJ, M, and MJ)
ASME B1.15	-	Unified Inch Screw Threads (UNJ Thread Form)
ASME B46.1	-	Surface Texture (Surface Roughness, Waviness, and Lay)
ASME Y14.5	-	Dimensioning and Tolerancing

(Copies of these documents are available online at https://www.asme.org.)

ASTM INTERNATIONAL

ASTM A342/A342M	-	Standard Test Methods for Permeability of Weakly Magnetic Materials
ASTM B633	-	Standard Specification for Electrodeposited Coatings of Zinc on Iron and Steel
ASTM F594	-	Standard Specification for Stainless Steel Nuts
ASTM F606/F606M	-	Standard Test Methods for Determining the Mechanical Properties of Externally and Internally Threaded Fasteners, Washers, Direct Tension Indicators and Rivets
ASTM F812/F812M	-	Standard Specification for Surface Discontinuities of Nuts, Inch and Metric Series
ASTM F1470	-	Standard Practice for Fastener Sampling for Specified Mechanical Properties and Performance Inspection
ASTM F1941/F1941M	-	Standard Specification for Electrodeposited Coatings on Mechanical Fasteners, Inch and Metric

(Copies of these documents are available online at https://www.astm.org.)

AMERICAN SOCIETY FOR QUALITY (ASQ)

ASQ H1607	-	Zero Acceptance Number Sampling Plans
ASQ Z1.4	-	Sampling Procedures and Tables for Inspection by Attributes

(Copies of this document are available online at https://www.asq.org.)

INTERNATIONAL AEROSPACE ENVIRONMENTAL GROUP

AD-DSL	-	Aerospace and Defense Declarable Substances List

(Copies of this document are available online at https://www.iaeg.com/chemicalrpt/addsl/.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T04:10Z
Check the source to verify that this is the current version before use.

SAE INTERNATIONAL

SAE J995	-	Mechanical and Material Requirements for Steel Nuts
SAE AMS2700	-	Passivation of Corrosion Resistant Steels
SAE AMS4507	-	Copper Alloy (Brass), Sheet, Strip, and Plate 70Cu - 30Zn Half Hard (H02) - UNS C26000
SAE AMS4117	-	Aluminum Alloy, Rolled or Cold Finished, Bars, Rods, and Wire and Flash Welded Rings 1.0Mg - 0.60Si - 0.28Cu 0.20Cr (6061; -T6, -T651) - UNS A96061
SAE AMS-QQ-N-290	-	Nickel Plating (Electrodeposited)
SAE AMS-QQ-P-416	-	Plating, Cadmium (Electrodeposited)

(Copies of these documents are available online at https://www.sae.org.)

2.4 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein (except for related specification sheets), the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3 REQUIREMENTS

3.1 Specification sheets. The individual item requirements shall be as specified herein and in accordance with the applicable specification sheet. In the event of any conflict between the requirements of this specification and the specification sheet, the latter shall govern.

3.2 Materials. Materials shall be as specified in the associated specification sheet(s) and reference herein.

3.3 Dimensions. Locknuts shall conform to the dimensions specified on the applicable specification sheet. The portion of the locknut containing the locking feature may have a special contour within the maximum permitted width across flats and thickness. Bearing surfaces shall be flat and perpendicular to the axis of the thread hole within a tolerance of 2°. Bearing surface roughness shall not exceed 125 Ra microinches in accordance with ASME B46.1.

3.4 Threads.

3.4.1 Thread series and class. Thread series, class, and tolerances shall be called out on the applicable specification sheet and be in accordance with ASME B1.1 except minor diameters where ASME B1.15 may apply. Thread inspection and acceptability shall be in accordance with ASME B1.3, System 21. Threads shall be inspected prior to installation of locking feature.

3.4.2 Locking feature. Locknuts shall be checked after installation of the locking feature, and shall allow the “GO” gage to enter not less than a half turn with a basic GO thread plug gage to ensure that the locknut is functional.

3.5 Mechanical requirements.

3.5.1 Hardness. Carbon and alloy steel locknut hardness shall be in accordance with SAE J995.

3.5.2 Magnetic permeability. The magnetic permeability of the corrosion resistant steel locknuts shall be less than 2.0 (air = 1.0) in a field strength of H= 200 oersteds.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T04:10Z
Check the source to verify that this is the current version before use.

3.6 Construction. The locknut shall be a self-contained unit or assembly, including the locking feature. The locking feature shall not operate by means of separate movement from the installation and shall not depend upon pressure on the bearing surface for locking action.

3.7 Marking. All nuts of .250 nominal thread size and larger shall be marked with equally spaced identical symbols (notch, dot, letter or number) as indicated in Figure 1 or SAE J995, for Grade 5 and 8 locknuts. All locknuts shall be marked to identify the manufacturer. Such markings may be additional to the grade markings or an alteration of one or more of the three or six grade marking symbols. Marks shall be raised or depressed, at the manufacturer's option. Raised marks shall not project beyond the specified maximum height or width of the locknut. The color of the non-metallic locking element may be used to identify the manufacturer if the color has been established as the manufacturer's legitimate trademark or symbol. The shape of the all metal locking feature may also be used if it has been established as the manufacturer's legitimate trademark.

3.8 Discontinuities. Limits on presence of discontinuities shall be in accordance with ASTM F812/F812M.

4 VERIFICATION

4.1 Classification of inspections. Inspections shall be classified as quality conformance inspection (see 4.2).

4.1.1 Inspection lot. All locknuts of the same type, material, protective finish, thread series, and size produced under essentially the same conditions and offered for acceptance at one time shall be considered a lot for the inspection purposes.

4.2 Quality conformance inspection.

4.2.1 Sampling. The sampling method shall be in accordance with MIL-STD-1916 or ASQ H1607 or a comparable zero based sampling plan unless otherwise specified by the contract. If the applicable drawing, specification, standard, or quality assurance provision (QAP) specifies Critical, Major and/or Minor attributes, they shall be assigned Verification Levels of VII, IV and II or AQLs of 0.1, 1.0 and 4.0 respectively. Unspecified attributes shall be considered as Major unless sampling plans are specified in applicable documents. For MIL-STD-1916 the manufacturer may use the attribute or variable inspection method at their option. ASQ Z1.4 may be used to set sample lot size but acceptance is at zero non-conformances in the sample lot unless otherwise specified in the contract.

4.2.2 Proof load and prevailing torque testing (steel nuts).

4.2.2.1 Carbon and alloy steel locknuts. Carbon and alloy steel locknuts shall be subjected to the proof loads and prevailing torque specified in SAE J995 or Table I of this specification.

4.2.2.2 CRES locknuts. CRES locknuts shall be subjected to the proof loads and prevailing torque specified in ASTM F594.

4.2.3 Protective finish test. Nuts shall be tested in accordance with the applicable protective finish or plating specification. Each lot shall be tested for protective finish thickness and, when specified, salt spray tested.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T04:10Z
Check the source to verify that this is the current version before use.

4.2.4 Hardness test. When a hardness test is to be conducted in lieu of a proof load test, it shall be conducted in accordance with NASM1312-6. Hardness tests may not be substituted for proof tests on nuts that require a proof load over 120,000 pounds.

4.2.5 Magnetic permeability. Magnetic permeability shall be determined by the use of an indicator in accordance with ASTM A342/A342M. Magnetic permeability sampling shall be in accordance with ASTM F1470.

4.2.6 Discontinuities. The acceptance of locknuts shall in accordance with the requirements contained in sampling for discontinuities, ASTM F812/F812M.

4.3 Test methods.

4.3.1 Proof load test. Steel locknuts shall be tested in accordance with ASTM F606/F606M. Proof load values shall be per Table 1 or SAE J995 or ASTM F594.

4.3.2 Prevailing torque test. Steel locknuts shall be subjected to the prevailing torque test as specified in National Aerospace Standard specification NASM25027.

4.3.3 Test equipment. A hardened threaded mandrel or bolt shall be used in conjunction with a tension testing machine for conducting the proof load test. The mandrel or bolt shall be threaded to the unified thread series and class of the locknut being tested. The mandrel or bolt shall have sufficient strength to ensure failure of the locknut.

4.3.4 Test procedures. Locknuts shall be assembled and mounted in a tension testing machine and subjected to a load equal to the proof load specified in SAE J995 or Table I. To meet the requirements of this test, the locknut shall resist the load without stripping or rupture.

4.3.5 Test bolt. The test bolt used in the prevailing-torque test of steel locknuts shall have a zinc phosphate, cadmium, or zinc-nickel plating and oil finish (dry to the touch) meeting a 72 hour salt spray test when tested in accordance with Test 1 of NASM1312-1. Corrosion-resisting steel locknuts shall be torque tested on corrosion-resisting steel test bolts. Aluminum alloy locknuts shall be torque tested on anodized aluminum alloy test bolts. Brass locknuts shall be torque tested on plain brass test bolts.

4.3.6 Load measuring device. The load measuring device used in the prevailing-torque test shall be an instrument capable of measuring the actual tension induced in the test bolt as the locknut is tightened. The device shall be accurate within plus or minus 5 percent of the test load.

5 PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T04:10Z
Check the source to verify that this is the current version before use.

6 NOTES

(This section contains information of a general or explanatory nature which may be helpful, but is not mandatory.)

6.1 Intended use. A prevailing-torque type locknut is a nut which is frictionally resistant to rotation due to a self-contained prevailing-torque (locking) feature, and not because of a compressive load developed against the bearing surface of the locknut. Each grade of carbon and alloy steel locknuts identified in this document is intended for use with bolts having specified minimum tensile strengths within the following values:

TABLE I. Specified minimum ultimate tensile.

Grade of Locknut	Strength of Bolt, P.S.I.
Grade 2 (formerly Grade A)	not greater than 90,000
Grade 5 (formerly Grade B and F)	not greater than 120,000
Grade 8 (formerly Grade C and G)	not less than 105,000 or greater than 150,000

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number and date of this specification.
b. Type, grade and series (see individual slash sheet).
c. Specification sheet number (see individual slash sheet)
d. Material (see individual slash sheet).
e. Protective finish, when required (see individual slash sheet).
f. Thread form, series and class (see individual slash sheet).
g. Grade marking, if required (see 3.7).
h. Packaging requirements (see 5.1).

6.3 Non-metallic insert. Locknuts with non-metallic inserts should not be used in installations where temperatures exceed 250°F.

6.4 Subject term (key words) listing.

Acceptability
Brass
Grade
Stainless steel
Temper

6.5 Information deleted from previous issue. Deleted 3.2.1-3.4.3, information is contained in slash sheets.

6.6 Amendment notations. The margins of this specification are marked with vertical lines to indicate modifications generated by this amendment. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T04:10Z
Check the source to verify that this is the current version before use.

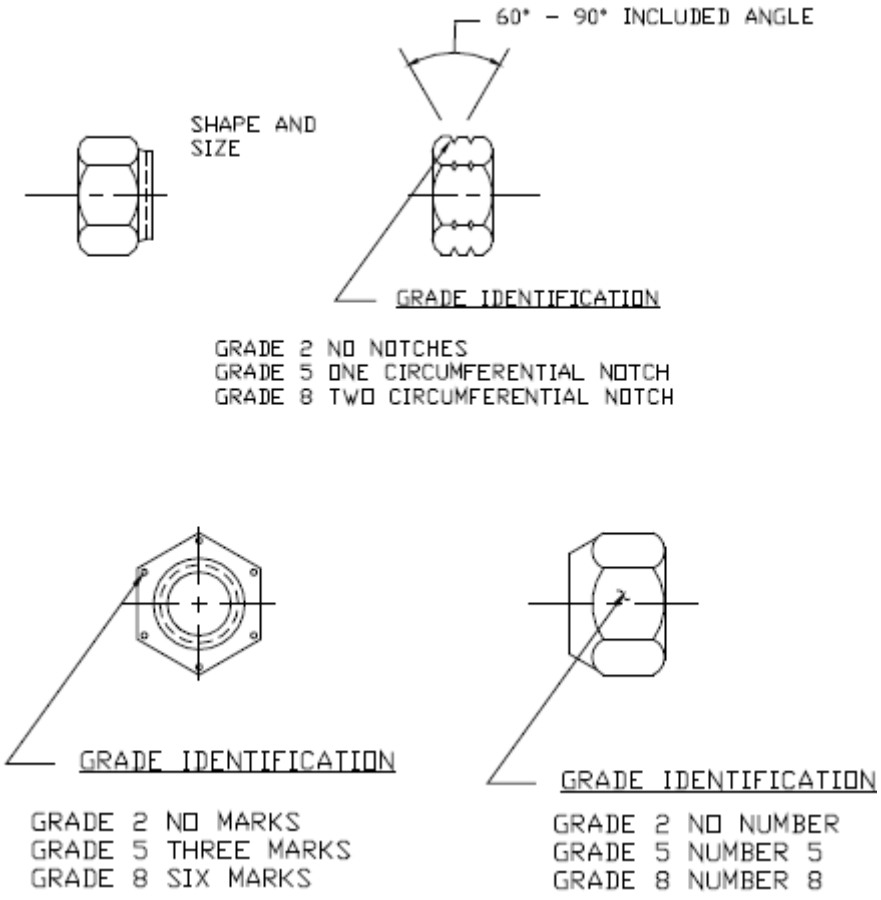


FIGURE 1. Grade indicators.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T04:10Z
Check the source to verify that this is the current version before use.

TABLE II. Prevailing torque.

Locknut Nominal Size and Threads Per Inch	Grade 2 Nuts							Grade 5 Nuts							Grade 8 Nuts						
			Prevailing Torque							Prevailing Torque							Prevailing Torque				
				First Removal		Fifth Removal					First Removal		Fifth Removal					First Removal		Fifth Removal	
	Proof Load Lb.	Clamp Load Lb.	First Install In Lb. Max	Highest Reading Min In. Lb.	Lowest Reading Min In. Lb.	Highest Reading Min In. Lb.	Lowest Reading Min In. Lb.	Proof Load Lb.	Clamp Load Lb.	First Install In. Lb. Max	Highest Reading Min In. Lb.	Lowest Reading Min In. Lb.	Highest Reading Min In. Lb.	Lowest Reading Min In. Lb.	Proof Load Lb.	Clamp Load Lb.	First Install In. Lb. Max	Highest Reading Min In. Lb.	Lowest Reading Min In. Lb.	Highest Reading Min In. Lb.	Lowest Reading Min In. Lb.
Coarse Thread Series																					
.0730-64																					
.0860-56																					
.0990-48																					
.1120-40	540	250	3.0	1.0	.5	.5	.2	720	380	3.0	1.0	.5	.5	.2	910	550	4.0	1.0	.5	.5	.2
.1250-40																					
.1380-32	820	370	6.0	1.5	.5	1.0	.5	1,100	580	8.0	1.5	.5	1.0	.5	1,350	810	8.0	2.0	1.0	1.5	.5
.1640-32	1,250	580	9.0	2.0	1.0	1.5	.5	1,700	900	12.0	2.0	1.0	1.5	.5	2,100	1,250	12	2.5	1.0	2.0	1.0
.1900-24	1,550	720	13	2.5	1.0	2.0	1.0	2,100	1,100	13	2.5	1.0	2.0	1.0	2,600	1,550	17	3.5	1.5	2.5	1.0
.2160-24	2,200	1,000	20	3.5	1.5	2.5	1.0	2,900	1,550	20	3.5	1.5	2.5	1.0	3,650	2,200	27	4.5	2	3.0	1.5
.2500-20	2,900	1,300	30	5.0	2.5	3.5	1.5	3,800	2,000	30	5.0	2.5	3.5	1.5	4,750	2,850	40	6.0	3	4.5	2
.3125-18	4,700	2,150	60	8.0	4	5.5	2.5	6,300	3,350	60	8.0	4	5.5	2.5	7,850	4,700	80	10.5	5	7.5	3
.3750.16	7,000	3,200	80	12	5	8.5	4	9,300	4,950	80	12	5	8.5	4	11,600	6,950	110	16	7.5	11.5	5
.4375-14	9,550	4,400	100	17	7.5	12	5	12,800	6,800	100	17	7.5	12	5	15,900	9,600	135	23	10	16	7.5
.5000-13	12,800	5,850	150	22	10	15	7.5	17,000	9,050	150	22	10	15	7.5	21,300	12,800	17	30	15	20	10
			* ft lb.							* ft lb.							*ft lb.				
.5625-12	16,400	7,550	17*	30	15	21	10	21,800	11,600	17*	30	15	21	10	27,300	16,400	25*	40	20	28	12.5
.6250-11	20,300	9,300	25*	39	17.5	27	12.5	27,200	14,500	25*	39	17.5	27	12.5	33,900	20,300	35*	52	25	36	15
.7500-10	30,000	13,800	35*	58	25	41	20	40,100	21,300	35*	58	25	41	20	50,100	30,100	45*	78	35	54	25
.8750-9	41,600	11,400	50*	88	40	62	30	55,400	29,500	50*	88	40	62	30	69,300	41,600	70*	117	50	82	40
1.000-8	54,500	15,000	70*	120	60	84	40	72,700	38,700	70*	120	60	84	40	90,900	54,600	90*	160	80	112	50
1.1250-7	68,700	18,900	75*	150	70	105	50	80,100	42,100	75*	150	70	105	50	115,000	69,000	100*	200	100	140	70
1.2500-7	87,200	24,000	85*	188	90	132	60	101,700	53,500	85*	188	90	132	60	145,000	87,000	110*	250	120	176	80
1.3750-6	104,000	28,700	100*	220	110	154	70	121,300	63,800	100*	220	110	154	70	173,000	104,000	135*	293	140	205	100
1.5000.6	126,000	34,800	110*	260	130	182	90	147,500	77,600	110*	260	130	182	90	211,000	127,000	150*	346	170	242	120
Fine Thread Series																					
.0600-80																					
.0730-72																					
.0860-64																					
.0990-56																					
.1120-48	600	270	3.0	1.0	.5	.5	.2	790	420	3.0	1.0	.5	.5	.2	990	600	4.0	1.0	.5	.5	.2
.1250-44																					
.1380-40	900	420	6.0	1.5	.5	1.0	.5	1,200	640	8.0	1.5	.5	1.0	.5	1,500	900	8.0	2.0	1.0	1.0	.5
.1640-36	1,350		9.0	2.0	1.0	1.5	.5	1,750	930	12	2.0	1.0	1.5	.5	2,200	1,300	12	2.5	1.0	2.0	1.0
.1900-32	1,800	840	13	2.5	1.0	2.0	1.0	2,400	1,300	13	2.5	1.5	2.0	1.0	3,000	1,800	17	3.5	1.5	2.5	1.0
.2160-28	2,300	1,050	20	3.5	1.5	2.5	1.0	3,100	1,650	20	3.5	1.5	2.5	1.0	3,900	2,350	27	4.5	2	3.0	1.5
.2500-28	3,300	1,500	30	5	2.5	3.5	1.5	4,350	2,300	30	5.0	2.5	3.5	1.5	5,450	3,250	40	6.0	3	4.5	2
.3125-24	5,200	2,400	60	8	4	5.5	2.5	6,950	3,700	60	8.0	4	5.5	2.5	8,700	5,200	80	10.5	5	7.5	3
.3750-24	7,900	3,600	80	12	5	8.5	4	10,500	5,600	80	12	5	8.5	4	13,200	7,900	110	16	7.5	11.5	5
.4375-20	10,700	4,900	100	17	7.5	12	5	14,200	7,550	100	17	7.5	12	5	17,800	10,700	135	23	10	16	7.5
.5000-20	14,400	6,550	150	22	10	15	7.5	19,200	10,200	150	22	10	15	7.5	24,000	14,400	17	30	15	20	10
			* ft lb.							* ft lb.							*ft lb.				
.5625-18	18,300	8,350	17*	30	15	21	10	24,400	13,000	17*	30	15	21	10	30,400	18,300	25*	40	20	28	12.5
.6250-18	22,900	10,500	25*	39	17.5	27	12.5	30,700	16,300	25*	39	17.5	27	12.5	38,400	23,000	35*	52	25	36	15
.7500-16	33,600	15,400	35*	58	25	41	20	44,800	23,800	35*	58	25	41	20	56,000	33,600	45*	78	35	54	25
.8750-14	45,800	12,600	50*	88	40	62	30	61,100	32,400	50*	88	40	62	30	76,400	45,800	70*	117	50	82	40
1.0000-14	61,100	16,800	70*	120	60	84	40	81,500	43,300	70*	120	60	84	40	101,900	61,100	90*	160	80	112	50
1.0000-12	59,700	16,400	70*	120	60	84	40	79,600	42,300	70*	120	60	84	40	99,500	59,700	90*	160	80	112	50
1.1250-12	76,900	21,200	75*	150	70	105	50	89,900	47,500	75*	150	70	105	50	128,000	76,800	100*	200	100	140	70
1.2500-12	96,600	26,600	85*	188	90	132	60	113,000	59,700	85*	188	90	132	60	161,000	96,600	110*	250	120	176	80
1.3750-12	118,000	32,500	100*	220	110	154	70	138,000	72,900	100*	220	110	154	70	197,000	118,000	135*	293	140	205	100
1.5000-12	142,000	39,100	110*	260	130	182	90	166,000	87,700	110*	260	130	182	90	237,000	142,000	150*	346	170	242	120

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T04:10Z
Check the source to verify that this is the current version before use.

CONCLUDING MATERIAL

Custodians:
Army - AT
Navy - OS
Air Force - 71
DLA - GS

Preparing activity:
Army - AT

(Project 5310-2024-005)

Review activities:
Army - AV, CR, MI
Navy - SH

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T04:10Z
Check the source to verify that this is the current version before use.