MIL-C-19145B(MC)
8 September 1983
SUPERSEDING
MIL-C-19145A(MC)
12 May 1966

MILITARY SPECIFICATION

COVERALL, WADING

This specification is approved for use by U. S. Marine Corps, Department of the Navy, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers a one-piece coverall including hood, with gusset closure and drawcord, suitable for affording complete protection of the wearer from water, including feet and hand.

1.2 Classification. Coveralls shall be of one type in the following sizes as specified (see 6.2):

Schedule of sizes

Short	(for wearer's height)	5'6''/5'9''
Regular	(for wearer's height)	5'10''/6'1''
Long	(for wearer's height)	6'2''/6'6''

2. APPLICABLE DOCUMENT

2.1 Government documents.

2.1.1 Specifications, standards, and handboods. Unless otherwise specified, the following specifications, standards, and handbooks of the issue listed in that issue of the Department of Defense Index of Specifications and Standards (DODISS) specified in the solicitation form a part of this specification to the extent specified herein.

SPECIFICATIONS

FEDERAL

V-T-276	- Thread, Cotton
UU-P-268	- Paper, Kraft, Wrapping
CCC-C-446	- Cloth, Muslin, Cotton
DDD-L-20	- Label: For Clothing, Equipage, and Tentage (General Use)

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to the Commandant of the Marine Corps (LMA-1), Headquarters, U. S. Marine Corps, Washington, D. C. 20380, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

MILITARY

MIL-B-371	- Braid, Textile, Tubular
MIL-C-577	- Cloth, Twill, Nylon; 1.6 and 3.0 Ounce
MIL-T-3530	- Thread and twine, Mildew Resistant or Water Repellent Treated
MIL-F-10884	- Fasteners, Snap
MIL-G-16491	- Grommets, Metallic
MIL-B-17757	- Boxes, Fiber, Fiberboard (Modular Sizes)
MIL-T-43566	- Tape, Textile, Cotton, General Purpose, Natural or in Colors

STANDARDS

FEDERAL

FED-STD-191	- Textile Test Methods
FED-STD-751	- Stitches, Seams, and Stitchings

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	- Marking for Shipment and Storage
MS27980	- Fasteners, Snap, Style 2 (Regular Wire Spring Clamp type)

(Copies of specifications, standards, handbooks, drawings, and publications required by manufacturers in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer).

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. The issues of the documents which are indicated as DOD adopted shall be the issue listed in the current DODISS and the supplement thereto, if applicable.

UNIFORM CLASSIFICATION COMMITTEE
Uniform Freight Classification Rules

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, Illinois 60606.)

LAWS AND REGULATIONS

U. S. Postal Service Manual

(Application for copies should be addressed to the Superintendent of Documents, U. S. Government Printing Office, Washington, D. C. 20402.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

NATIONAL MOTOR FREIGHT TRAFFIC ASSOCIATION, INC., AGENT

National Motor Freight Classification

(Application for copies should be addressed to The American Trucking Association Inc., Tariff Order Section, 1616 P. Street, N. W., Washington, D. C. 20036.)

Department of Defense (DOD) Standard Color Card of
Official Standardized Shades for Sewing Threads 1968

(Application for copies may be obtained from The Color Association of the United States Inc., 200 Madison Avenue, New York, New York 10016.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence.

3. REQUIREMENTS

3.1 Sample. Samples are furnished solely for guidance and information to the contrator (see 6.3). Variation from the specification may appear in the sample in which case the specification shall govern.

3.2 First article. Unless otherwise specified (see 6.2), before production is commenced, the first article consisting of the number of finished coveralls specified by the procuring activity (see 6.2) shall be submitted, or made available to the contracting officer or his authorized representative for approval. The approval of the first article authorizes the commencement of production, but does not relieve the supplier of responsibility for compliance with all provisions of the specification. The first article shall be manufactured by the supplier in the same facilities to be used for the manufacture of the production items.

3.3 Materials.

3.3.1 Basic material.

3.3.1.1 Basic fabric. The basic fabric for the coveralls, except the stockings, shall be cloth, cotton, muslin, conforming to type II, class 2 or class 3 of CCC-C-446 with bleached finish or any other finish that facilitates the coating process in accordance with this specification. The finished fabric shall contain not more than 0.005 percent copper and 0.001 percent manganese, when tested as specified in Section 4, Table I.

3.3.1.2 Coating compound. The compound used for coating the cotton fabric shall be natural or synthetic rubber, suitably compounded and pigmented to produce an approved shade of olive green NO. 107 (see 6.3) when tested as specified in Section 4, Table I. Reclaimed rubber shall not be used.

3.3.1.3 Coated fabric. The coating compound shall be applied to one side of the cotton fabric only. The coated fabric shall be free of pinholes and shall have a dull finish, free from excessive tendency to whiten in handling. The coated side of the fabric shall be on the outside of the garment. The coated fabric shall

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

conform to the following requirements when tested as specified in Section 4, Table I.

	Minimum	Maximum
Weight of coating, ozs per sq yd	5.0	7.0
Breaking strength, warp, pounds	35	-
Breaking strength, filler, pounds	15	-
Hydrostatic, pounds (fabric)	25	-
Hydrostatic, centimeters (seams)	25	-
Adhesion, pounds (fabric)	6.0	-
Adhesion, pounds (seams)	3.0	
Accelerated aging (O_2 bomb-14 days, 158°)	Not soft and tacky or hard and brittle	
Accelerated weathering (96 hours)	Not soft and tacky or hard and brittle	
Low temperature resistance (-20°F.)	Shall not crack	

3.3.2 Cement. The compound used for cementing the seams shall be natural or synthetic rubber cement completely compatible with the coating on the fabric with which it is being used, shall have good adhesion and flexibility, be pigmented olive green 207 and have all other characteristics equal to the requirements for the coating of the fabric. Reclaimed rubber shall not be used. The cement used with the coated cotton fabric shall be so compounded as to be heat-vulcanizing and have the same vulcanizing characteristics as the coating compound of the cotton fabric with which it is being used. Cement shall be tested requirements specified in Section 4, Table I.

3.3.3 Coated nylon fabric.

3.3.3.1 Basic fabric. The basic material for the stockings shall be cloth, twill, nylon, conforming to type II of MIL-C-577.

3.3.3.2 Coating compound. The compound used for coating the nylon fabric shall be a properly plasticized chloroprene rubber, pigmented to produce an approved shade of olive green NO. 107 (see 6.3) when tested as specified in Section 4, Table I. It shall be nontoxic, nonirritant, and free of objectionable odor.

3.3.3.3 Coated fabric. The coating compound shall be applied to one side of the nylon fabric only, shall have good adhesion to the fabric, and shall not impair the strength of the basic fabric. The coated cloth shall be flexible, free of tackiness, and resistant to abrasion and scratching. The coated fabric shall conform to the following requirements when tested as specified in Section 4 Table I.

	Minimum	Maximum
Weight, ozs per sq yd	6.0	7.0
Tearing strength, grams, warp	1200	-
Tearing strength, grams, filling	1280	-
Hydrostatic pressure, lbs-initial	80	-
Hydrostatic pressure, lbs-after 40 hrs weatherometer	70	-
Hydrostatic pressure, lbs-after low temperature resistance	64	-
Adhesion:		
coating	8.0	-
seams	3.0	-

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

3.3.3.3.1 Resistance to heat. The coated cloth shall show no exudation, tackiness, or loss of flexibility.

3.3.3.3.2 Resistance to low temperature. The coated cloth shall maintain its flexibility and show no signs of cracking or flaking.

3.3.4 Dusting material. Dusting material for finishing coated fabrics and for treating cemented seams or reinforcement patches to avoid blocking shall be inert mineral dusting powder which shall be acceptable for toxicity in accordance with prescribed standards, when tested as specified in Section 4, Table I.

3.3.5 Rifle strap webbing. Webbing shall be cotton, 1 inch wide, vat dyed OG 107, mildew and water resistant treated, conforming to requirements of type I, class 4 of MIL-T-43566.

3.3.6 Drawcord. The drawcord shall be cotton, tubular, braided, vat dyed, olive green NO. 107, plastic tipped, water-repellent treated, conforming to type II, class 2 of MIL-B-371.

3.3.7 Cord. The cord used for reinforcing the tear-strip shall be No. 9 Lincoln cord, or equal, suitable impregnated with cement to ensure good adhesion to the suit material.

3.3.8 Elastic webbing. Elastic webbing for the hood and wrist shall be cotton, 1 inch wide for the hood and 1/4 inch wide for the wrists.

3.3.9 Slide keeper. The slide keeper shall be rectangular plastic, olive drab No. 107, 1-1/4 inches by 3/4 inch by 1/8 inch, with two 1/4-inch round holes. Each hole shall be centered on the center line parallel to the 3/4-inch dimension, one hole being centered 5/16 inch from each end of the keeper. The rectangular keeper shall be of such flexibility as to make it suitable for the purpose.

3.3.10 Grommets. The grommets shall be brass, plain type, black chemical finish, No. 0, with toothed washer, conforming to type II, class 3 of MIL-G-16491.

3.3.11 Fasteners, snap. Snap fasteners shall be brass, black finish conforming to style 2, finish 2, construction A, of MIL-F-10884 and part Nos. 3B, 6B, 7B, and 8B of MS27980. The fastener components shall consist of a button, socket, stud, and eyelet (size 1).

3.3.12 Thread. Thread shall be cotton, machine, 30/4, glazed finish, conforming to type IB3 of V-T-276. The thread shall be vat dyed shade S-1, cable No. 66022. (See DOD Standard Color Card of Official Standardized Shades for Sewing Threads 1968).

3.3.12.1 Treatment. The thread, after mildew resistant treatment, shall conform to type I, class 2 of MIL-T-3530.

3.3.13 Label. Each coverall shall be provided with an identification-size label conforming to type IV of DDD-L-20. The format and content shall be as follows:

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

Nomenclature (item identification)
Contract Number
Name of contractor
Size
Stock Number

Note: Size of characters for "Name of contractor" shall be minimum 6 point (approximately 1/16 inch).

Unless otherwise specified, the labels shall be fast only to the laundering transference test (Method 5610) specified in DDD-L-20, except that colorfastness of labels is not required. If the labels are clearly legible after laundering, they shall be rated satisfactory.

3.4 Design. The coveralls shall be the U. S. Marine Corps design shown in Figures 1 through 3.

3.5 Patterns. The patterns for cutting all parts of the coverall wading shall be furnished by the contractor and shall be of the proper proporations to provide good fitting and meet the requirements of the specification.

3.6 Construction.

3.6.1 Stitches, seams, and stitchings. Stitch, seam, and stitching types specified shall conform to FED-STD-751. The needle shall be the smallest possible size which can be used with the specified thread in order to minimize the size of the hole made in the fabric by the needle. All cemented seams shall be full-cemented, lapped, and securely rolled to ensure good adhesion. Whenever it is necessary to dust any finished seams of the suits to avoid blocking, powdered chalk, whiting, talc, or other similar inorganic material shall be used, as specified in 3.3.4.

3.6.2 Vulcanization. The coated cotton fabric components of the coveralls shall be assembled from uncured stocks and vulcanized in their entirety after assembly. The coated nylon fabric stockings shall be assembled to the legs of the vulcanized coveralls.

3.6.3 Body. The body of the coverall shall consist of four pieces with center seam at front and back of both the top and bottom halves and leg seams cemented and lapped not less than 1/2 inch. The suit shall have raglan shoulders. The junction of the seams at the crotch shall be reinforced with a circular patch not less than 1-1/8 inches in diameter securely cemented to the outside.

3.6.4 Front gusset. The gusset shall be of one piece and shall be securely cemented to the front of the upper body 1/2 inch, enlarging the neck. The bottom of the gusset at its junction with the front body seam shall be reinforced with a circular patch, not less than 1-1/8 inches in diameter, securely cemented to the outside.

3.6.5 Sleeves. The sleeves shall be raglan style, cut in one piece, with the seam cemented and lapped not less than 1/2 inch. The bottom of the sleeve shall be hemmed to the outside and stitched 3/8 inch with a 1/4-inch elastic inserted into

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

the hem so as to draw the sleeve tightly at the wrist. The sleeve shall have a gusset at the underarm cemented and lapped not less than 1/2 inch. The sleeve shall be inserted into the armhole, cemented and lapped not less than 1/2 inch.

3.6.6 Neck tunnel. The tunnel shall consist of two pieces with the ends cemented and lapped not less than 1 inch at the front and 1/2 inch at the back. A grommet shall be attached through the front seam. A cord 85 inches long shall be inserted with the ends protruding from the grommet. The tunnel shall have the two edges cemented together 1 inch and shall be cemented and lapped to the periphery of the neck, from the inside, not less than 1/2 inch.

3.6.7 Hood. The hood shall be cut in two pieces with the seam butted together and covered both on the inside and outside with 1/2-inch strips of body material securely cemented to it. The bottom front corners shall be cemented 2-1/2 inches along neck, 1 inch wide, and the front edge folded over 1-1/4 inches. The hood shall be cemented and attached to the neck tunnel 1 inch, even with the bottom inside edge of the tunnel and centered over the back seam of the upper body. After the suit is cured, a 1 inch wide elastic 21 inches long shall be inserted into the front of the hood and the hood hemmed 1-1/4 inches with two rows of stitching fastening down the inner edge and the folded edge. The bottom ends of the elastic shall be sewed to the hood with a rectangular stitching 1/4 inch apart across elastic.

3.6.8 Stockings. The stocking is designed to be worn inside the cold weather rubber insulated boot, and to extend above the top of the boot to permit rapid removal of the coverall by means of a rip tab, without removing the cold weather boot. Stockings shall be made of the coated nylon fabric in three sizes, as follows:

Small	- 6-1/2 to 8
Medium	- 8-1/2 to 10
Large	- 10-1/2 to 13

The stockings shall be made in three pieces, one piece for the leg and top part of foot, one piece for the innersole, and one piece for the outersole. The leg and foot piece shall be formed by lapping and securely cementing together edges of front edges with the coated side of the fabric to the inside of the stocking. A 3/8 inch-wide strip of the coated nylon fabric shall be cemented over the inside of front seam and a 3/4 inch-wide strip of the same material shall be cemented over the outside of front seam. The innersole shall be securely cemented to the inside of the stocking and the outersole securely cemented to the outside of the stocking, with the coated side of the outersole placed next to the uncoated side of the insole.

3.6.8.1 Rip tab. The rip tab for removal of lower portion of coverall from stockings shall be made of the coated nylon fabric. Rip tabs shall be cut 1-1/2 inches wide and shall be sufficiently long to encircle the leg and to overlap itself approximately 2 inches.

3.6.8.2 Assemble stocking. The top edge of the stocking shall be butted to the lower edge of the trouser leg (not overlapped) and the rip tab placed evenly over both edges and securely cemented to the trouser leg and stocking to form a water-tight seal. The 2-inch overlap of the tab shall not be cemented down but shall remain free to provide a pull tab.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

3.6.9 Rifle strap. The strap shall be cut in one piece 14 inches long. One end shall be turned 1-1/2 inches and stitched across the raw edge. The other end shall be turned under and stitched to a semicircular stay with a rectangular stitching following the edges of the webbing and stopping about 1/2 inch from the edges of the stay. The webbing shall be securely cemented to the right side of the upper body with the loose end of the webbing extending to the rear. The cap of the snap fastener shall be attached at the end of the webbing for attachment to the stud about 9 inches to the back from the rifle strap stay. The stud stay consists of two circular pieces, one 2 inches in diameter and the other 1-1/2 inches in diameter, securely cemented together and to the coverall. The stud is attached before the stays are secured to the coverall.

3.6.10 Tear strip. The tear strip is cut into two pieces on the warp of the material. Each piece is securely cemented 1/2 inch to the top of the lower body before the crotch seams are joined. The 3/4-inch extension is then securely cemented to the upper body 1/2 inch with the edge of the upper body folded back 1/2 inch and remaining loose. A 1/4-inch space of the tear strip is left exposed around the periphery of the coverall. The tear cord is securely attached in the center of this space with the ends protruding through a slit at the back. A stay 1 inch in diameter is solid-cemented over the slit from the inside.

3.6.11 Cord tunnel. The tunnel is cut into two pieces on the warp of the material. Each piece is hemmed 7/8 inch to the gum side and stitched its length 3/4 inch from the fold. The tunnel shall then be securely cemented to the upper body above the stitching so that the folded edge is placed directly along the tear cord. The two tunnel pieces butt at back where cord protrudes. After cure, a 3/16-inch cord 20 inches long is tied to the protruding tear cord, inserted into the cord tunnel, and knotted at the front end. The cord tunnels are cut 1/2 inch at fold at rear.

3.6.12 Waterproofness. Coveralls shall be waterproof when tested as specified in 4.6.1.

3.7 Marking. Each coverall shall have the identification-size label stamped on the inside of the suit just below the neck.

3.8 Workmanship. The coveralls shall be clean, well finished, thoroughly waterproof and free from any defects which may affect its appearance or serviceability.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the government. The government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

4.1.1 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Classification of inspection. The inspection requirements specified herein are classified as follows:

1. First article inspection (see 4.4).
2. Ouality conformance inspection (see 4.5).

4.3 Inspection conditions. Unless otherwise specified, inspection shall be in accordance with MIL-STD-105.

4.4 First article inspection. When first article is required, inspection shall be performed on a completely fabricated coverall for conformance to all provisions of this specification.

4.5 Ouality conformance inspections.

4.5.1 In-process inspection. In-process inspection shall be performed whenever the nonperformance of any operation or omission of any component cannot be determined during examination of the completed end item. Evidence of supplier's noncompliance with requirements of the specification disclosed during in-process inspection may be cause for rejection of all items where noted deficiencies are suspected to exist. Final determination of suspected noncompliance shall be accomplished, at the discretion of the Government, by partial or complete disassembly of the coverall, or coveralls, in question.

4.5.2 Testing of components. In addition to the quality assurance provisions of the subsidiary specifications and figures, inspection shall be performed on components and materials listed in Table I for the characteristics shown. The inspection level for all test characteristics of each component shall be S-1. The acceptable quality level, applicable to sample unit requirements, shall be 6.5 of MIL-STD-105. The method of testing specified in FED-STD-191, wherever applicable, and as listed in Table I, shall be followed.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

Table I. - Testing of components

Component	Characteristic	Rqmt. para.	Test method	Rqmt. appl. to S/U	Det. per S/U	Results reported as;
Cloth, cotton muslin	Copper	3.3.1.1	2051	X	1	Pass or fail
	Manganese	3.3.1.1	Std.comm'l	X	1	Pass or fail
Coating compound	Composition 1/	3.3.1.2 and	Std.comm'l	X	1	Pass or fail
	Color 1/	3.3.3.2	Visual	X	1	Pass or fail
Coated cloth	Weight	3.3.1.3	Std.comm'l	X	1	Pass or fail
	Breaking strength	3.3.1.3	5100	X		
	-warp				5	Avg. of 5 det. in each direction
	-filling				5	
	Accelerated aging 2/	3.3.1.3	5852	X	5	Pass or fail
	Water resistance 3/ fabric	3.3.1.3 and 3.3.3.3	5512	X	5	Avg. of 5 det. to nearest lb. per sq. in. Avg. of 5 det. to nearest cm or 1/2 inch.
	Adhesion -coating	3.3.1.3 and 3.3.3.3	5970 4/	X	3	Avg. of 3 det. to nearest 0.1 lb. for 2 inch width.
	-seams	3.3.3.3	5960 or 5962	X	5	Avg.of 5 det. to nearest 0.1 lb.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

Table I. - Testing of components (cont'd)

Component	Characteristic	Rqmt. para.	Test method	Rqmt. appl. to S/U	Det. per S/U	Results reported as;
	Accelerated weathering 5/	3.3.1.3 and 3.3.1.3	5670	X	6/	Pass or fail
	Weight (per sq yd)	3.3.3.3	5041	X	5	Avg. of det. nearest 0.1 oz sq yd
	Tearing strength 7/	3.3.3.3	5132	X		
	-warp				5	Avg. of 5 det. in each direction to the nearest gm.
	-filling				5	
	Resistance to heat	3.3.3.3.1	4.4	X	1	Pass or fail
	Resistance to low temperature 8/	3.3.1.3 and 3.3.3.3.2	5874	X	3	Pass or fail
Cement	Composition	3.3.2	Std.comm'l	X	1	Pass or fail
	Color	3.3.2	Visual	X	1	Pass or fail
	Heat-vulcanizing	3.3.2	Std.comm'l	X	1	Pass or fail
Dusting material 1/	Nontoxic	3.3.2	Std.comm'l	X	1	Pass or fail

1/ A certificate of compliance is acceptable for this characteristic.
2/ For a period of 14 days, determination of the loss in tensile strength is not required.
3/ Water pressure shall be applied to the coated side of the cotton fabric and to the cloth side of the nylon fabric.
4/ Except the test specimen shall be 2 inches wide.
5/ The coated side to the arc.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

Table I. - Testing of components (cont'd)

Component	Characteristic	Rqmt. para.	Test method	Rqmt. appl. to S/U	Det. per S/U	Results reported as;

6/ One sample for the cotton fabric and five samples for the nylon cloth.
7/ The standard instrument with NBS augmenting weight shall be used.
8/ The nylon cloth shall be subjected to -40°F for 2 hours prior to creasing.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

4.5.3 Examination of end item. The end item shall be examined for the defects listed in 4.5.3.1 and 4.5.3.2. The sample unit shall be one coverall.

4.5.3.1 General defects. General defects shall be classified as follows:

EXAMINE	DEFECT	CLASSIFICATION		
		MAJOR	MINOR	
			A	B
Finish and color (applicable to all components) Cleanliness	Not as specified or definite variation.	X		
	a. Spot or stain clearly visible.		X	
	b. Cement line extends more than 1/4 inch.		X	
Design	Any characteristic not in accordance with specified requirement (unless otherwise indicated herein).	X		
Material (general)	Any component not fabricated of specified material (unless otherwise indicated herein).			
Coated fabric	a. Any hole, cut, tear, or rip through material.	X		
	b. Any evidence of separation through material.	X		
	c. Any area of no coating.	X		
	d. Any brittle area which cracks when bent.	X		
	e. Area of excess coating, e.g., solid run, ridge, or lump.		X	
	f. Any abraded area exposing base fabric	X		
	g. Tacky coating, e.g., improper vulcanization.			

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

EXAMINE	DEFECT	CLASSIFICATION		
		MAJOR	MINOR	
			A	B
	h. Any imbedded foreign matter which results in a through hole, or base fabric exposed when removed.	X		
	i. Any imbedded foreign matter not removable or, if removable, does not expose base fabric.		X	
	j. Permanent crease, weak or thin spot, blister, or tunnel.	X		
Construction and workmanship (applicable to all components unless otherwise indicated herein).	a. Any component omitted, damaged, misplaced, operation omitted, or not properly performed.	X		
	b. Any patch.		X	
	c. Any component or assembly malformed.	X		
Seams and stitching (as applicable)	a. Any stitching omitted.		X	
	b. Twisted, puckered, or pleated seam.	X		
	c. Any open seam which may result in leakage through the seam.		X	
Strapped and cemented seams (as applicable)	a. Any open seam.	X		
	b. Strapping not securely affixed, i.e., strapping not properly cemented so that it can be readily pulled off with little resistance.	X		
	c. Any blister or delamination in central area of strapping but edges are securely affixed, affecting serviceability but not seriously.			X
	d. Any cemented seam not adequately dusted to avoid blocking.			X
Elastic webbing	a. Ensecurely attached.		X	
	b. Not gathered at hood or sleeve hem.		X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

EXAMINE	DEFECT	CLASSIFICATION		
		MAJOR	MINOR	
			A	B
	c. Caught in hem stitching			
Gusset	a. Any not securely cemented at edges.	X		
	b. Any not constructed as specified.	X		
Marking	Missing, incorrect, misplaced, illegible, not specified size or color, or not accomplished in specified manner.			X
Reinforcement patches	Any reinforcement omitted.	X		

4.5.3.2 Dimensional examination of coveralls. The coveralls shall be examined for dimensional defects. Any dimensions that are not within the established tolerance shall be classified a defect.

4.5.3.3 Inspection levels and acceptable quality levels (AQLs). The inspection levels and acceptable quality levels, expressed in defects per hundred units (DHU), shall be as follows:

Examination	Inspection level	AQL	
		Major	Total
4.5.3.1	II	1.5	10.0
4.5.3.2	S-3	-	4.0
4.5.4	S-2	-	2.5

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

4.5.4 Examination of packaging requirements. An examination shall be made to determine that packaging, packing, and marking requirements of Section 5 of this specification are compiled with. Defects shall be scored in accordance with list below. The sample unit shall be one shipping container fully prepared for delivery with the exception that it need not be sealed. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The applicable inspection level and the AQL shall be indicated in 4.5.3.3.

Examine	Defect
Marking (exterior	Omitted; incorrect; illegible; of improper size, location, sequence or method of application.
Materials	Any nonconforming component; component missing, damaged, or otherwise defective, affecting serviceability.
Workmanship	Inadequate application of components, such as incomplete closure of case liners and container flaps, loose strapping and inadequate stapling. Bulging or distortion of containers.
Contents	Number of coveralls per container is more or less than required.
Weights	Gross or net weight exceeds requirements.

4.6 Tests

4.6.1 Testing for leakage. The end item shall be tested for leakage in accordance with the following requirements. The sample unit shall be one completely fabricated coverall.

Rqmt. para.	Test method	No. of det. per S/U	Results reported as	Insp. levels
3.6.12	1/	1	Pass or fail	2/

1/ The coveralls shall be tested by having a man don the garment and wade in a tank of water for 3 minutes with the water level at the armpits. Leaks shall be localized by air pressure and soap solutiom method.

2/ One-hundred percent testing shall be performed for leakage. Any coveralls found to contain a leak shall be rejected, repaired, and retested. Patches will not be permitted. At its discretion, the Government may verify the results of the supplier's examination by 100 percent examination or by sampling inspection.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

4.6.2 Test for resistance to heat. The sample unit shall be placed in an oven at 160° ±2° F for 120 hours.

5. PACKAGING

5.1 Packing. Packing shall be level A, B, or commercial as specified (see 6.2).

5.1.1 Level A.

5.1.1.1 Method 1. Fifteen coveralls, of one size only, shall be packed in a fiberboard shipping container with liner, conforming to class-weather resistant, size No. 3A of MIL-B-17757 and assembled, closed, and reinforced in accordance with appendix thereto. The fiberboard used in fabricating the liner shall be grade 275. In addition, each container shall have the contents completely covered on the top and bottom with a sheet of 60 pound minimum basis weight kraft paper conforming to grade B of UU-P-268. Toward the end of the contract, or when there is less than the required amount per container of the same size, mixed sizes may be packed within the same container.

5.1.1.2 Method 2. When specified (see 6.2), three level B shipping containers (45 coveralls) of one size only shall be packed in a fiberboard shipping container conforming to class-weather resistant, size No. 4 of MIL-B-17757. Shipping containers shall be reinforced as specified in the appendix thereto. Toward the end of the contract, or when there is less than the required amount per container of the same size, mixed sizes may be packed within the same container.

5.1.2 Level B. Fifteen coveralls, of one size only, shall be packed in a fiberboard shipping container with liner, conforming to class domestic, size No. 3A of MIL-B-17757 and assembled, closed, and reinforced in accordance with the appendix thereto. The fiberboard used in fabricating the box and the liner shall be grade 275. In addition, each container shall have the contents completely covered on the top and bottom with a sheet of 60-pound minimum basis weight kraft paper conforming to grade B of UU-P-268. Towards the end of the contract, or when there is less than the required amount per container of the same size, mixed sizes may be packed within the same container.

5.1.3 Commercial. The coveralls shall be packed in a manner to ensure carrier acceptance and safe delivery at destination. Containers shall be in accordance with Uniform Freight Classification Rules, U. S. Postal Service Manual, or National Motor Freight Classification Rules, as applicable.

5.2 Marking. In addition to any special marking required by the contract or order, shipping containers shall be marked in accordance with the requirements of MIL-STD-129.

5.2.1 Mixed sizes. Each shipping container which is packed with mixed sizes shall have securely attached to the end and side, directly under the printing or

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

stenciling, a white paper label 5 X 4 inches with the words "MIXED SIZES" plainly stamped or printed thereon, and under these words shall be legibly printed the correct quantity of each size contained therein.

6. NOTES

6.1 Intended use. The coverall described herein is intended for wear during amphibious landing operations.

6.2 Ordering data. Purchasers should exercise any desired options offered herein, and procurement documents should specify the following:

6.2.1 Procurement requirements.

(a) Title, number, and date of this specification.
(b) Size required (see 1.2).
(c) Whether first article is required (see 3.2).
(d) Number of coveralls in first article (see 3.2).
(e) Selection of applicable levels of packing (see 5.1).
(f) When level A, method 2, packing is required (see 5.1.1.2).

6.2.2 Contract data requirements. Data conforming to Data Item Descriptions DI-R-4803, DI-R-4805, DI-T-4901, DI-T-4902, DI-T-4903, and DI-T-4904 will usually be required for delivery in connection with this specification. When so required, such data will be specified for delivery on a DD Form 1423 included in the contract.

6.3 Samples and shade samples. For information regarding availability of sample coveralls and standard shades specified, address inquiry to the procuring activity issuing the invitation for bids.

6.4 First article. First article examination, test, and approval shall be as specified by the contracting officer (see 3.2).

6.5 Figures. Figures 1 through 3 show general design of the coveralls with assembly details and measurements. In the event of conflict between these figures and the text of this specification, the text of this specification shall govern.

6.6 Marginal notations. Asterisks are not used in this revision to identify changes with respect to the previous issue, due to the extensiveness of the changes.

Preparing Activity
Navy-MC
Proj. No. 8415-N264

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

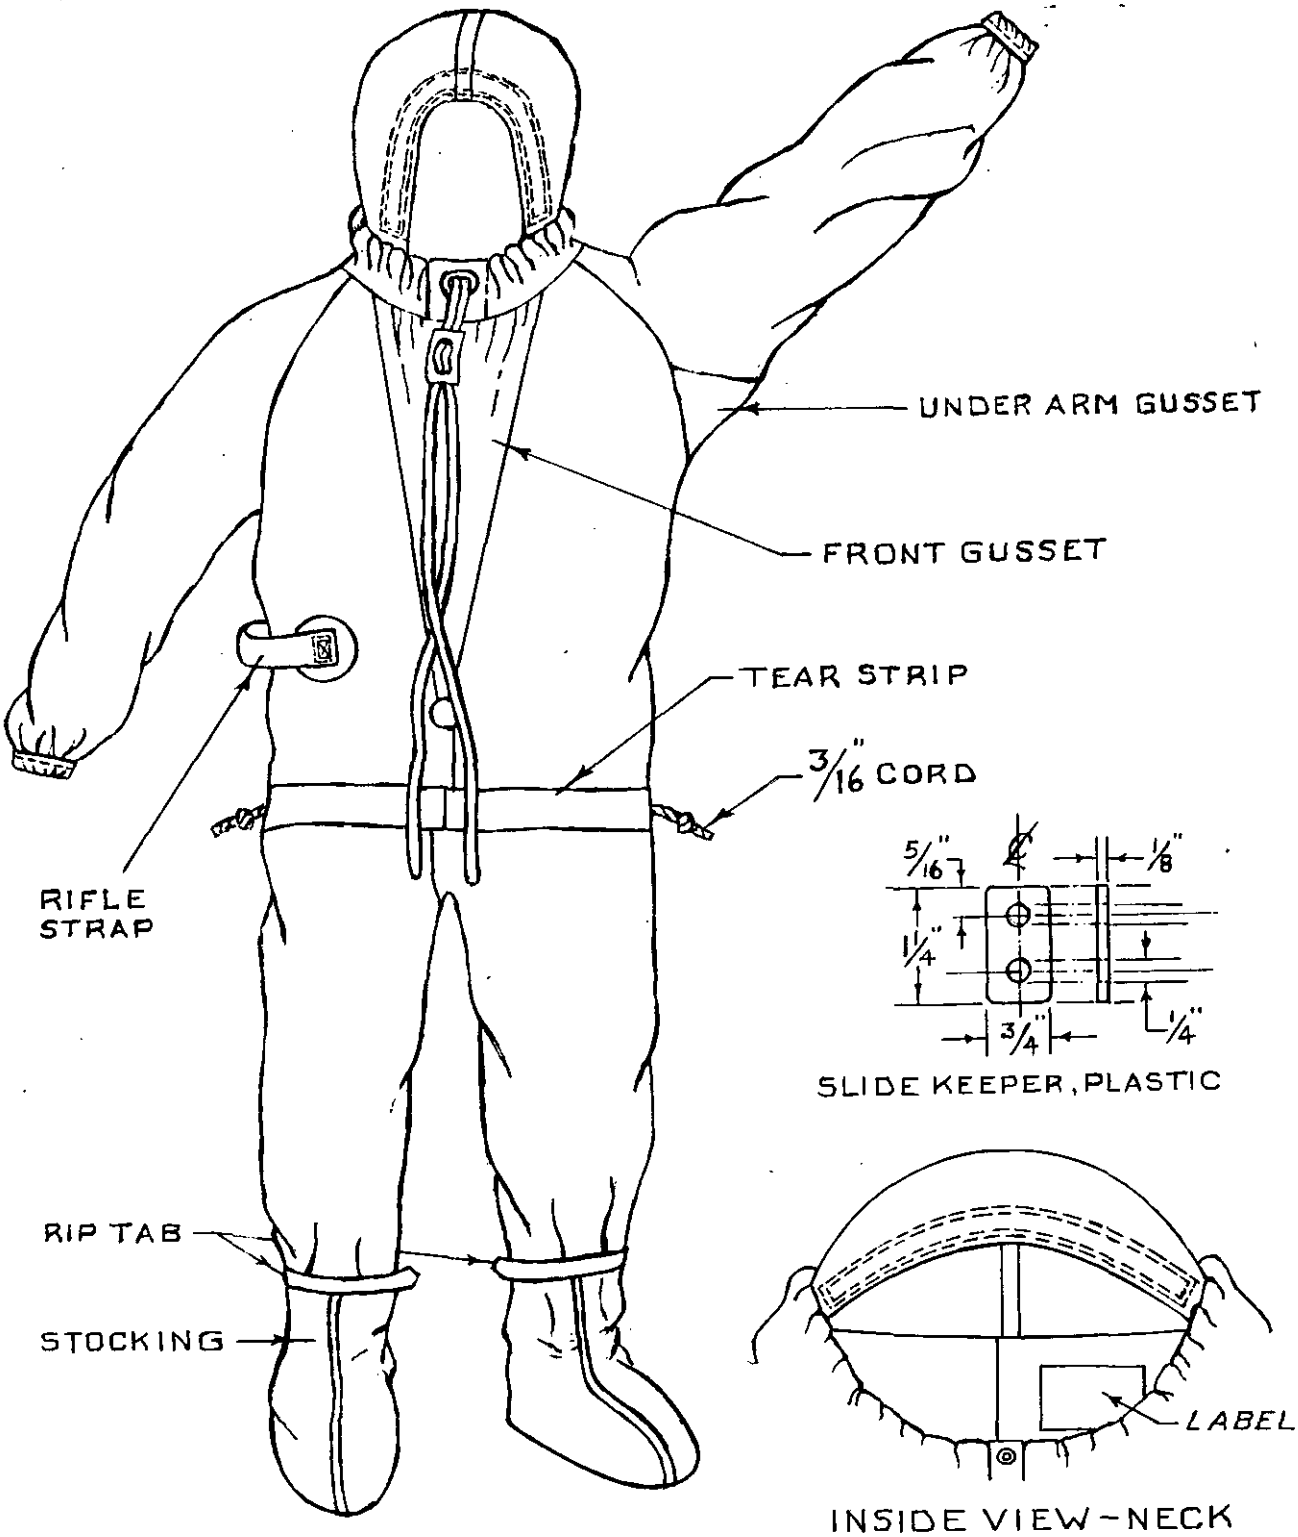


FIGURE 1. COVERALL, WADING

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.


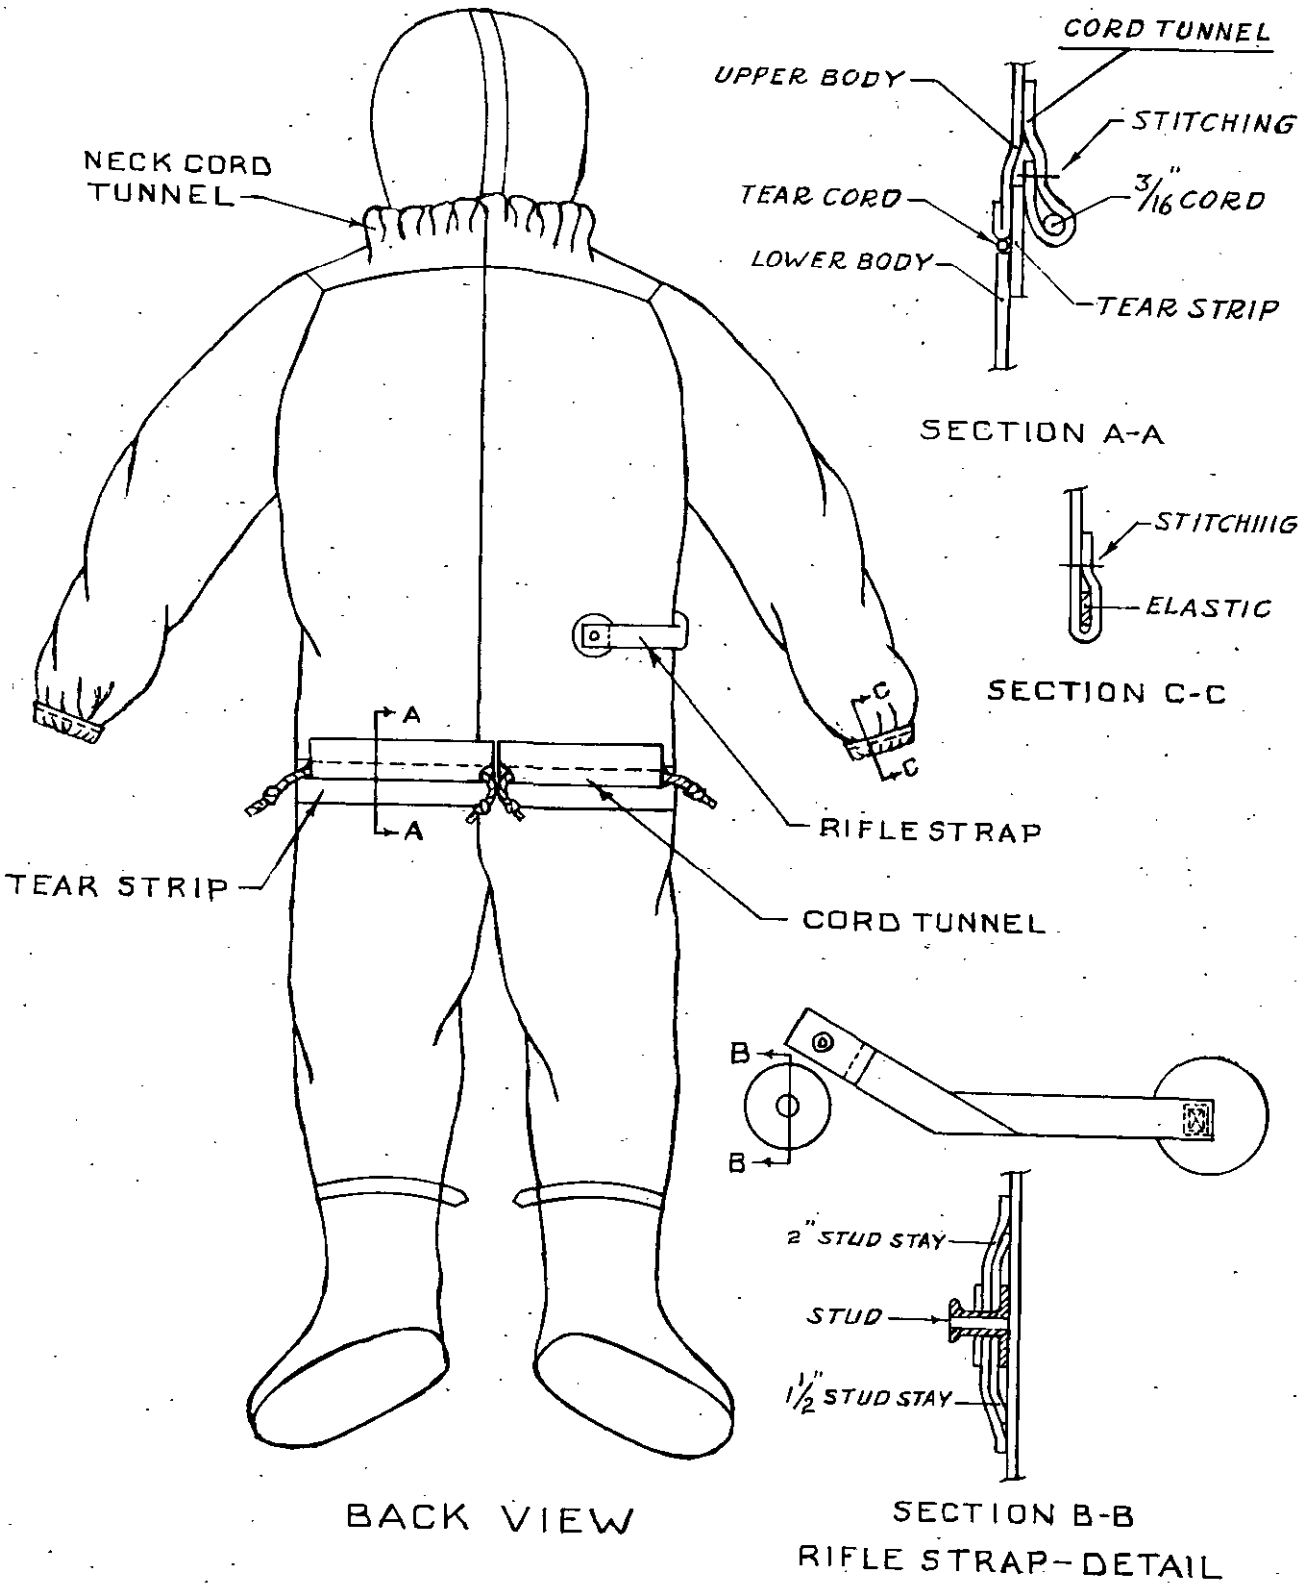



FIGURE 2. COVERALL, WADING

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

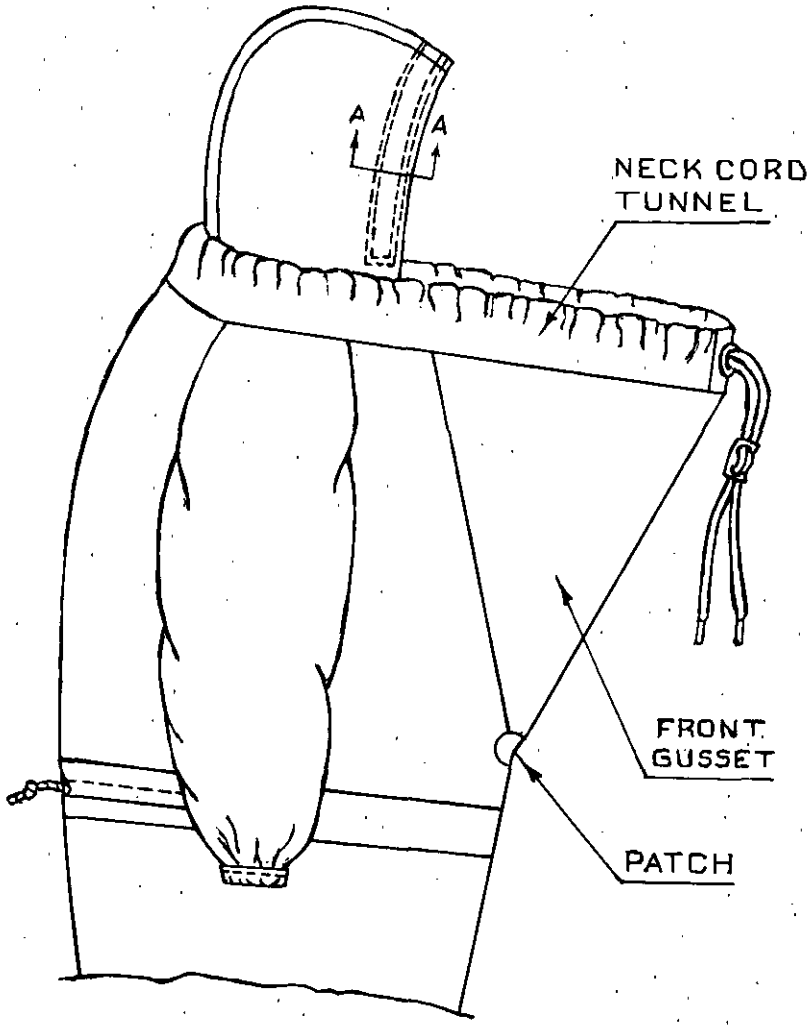


SIDE VIEW – RIGHT


SHOWING NECK TUNNEL AND FRONT GUSSET EXTENDED

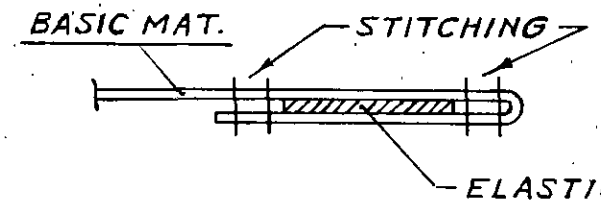

SECTION A-A

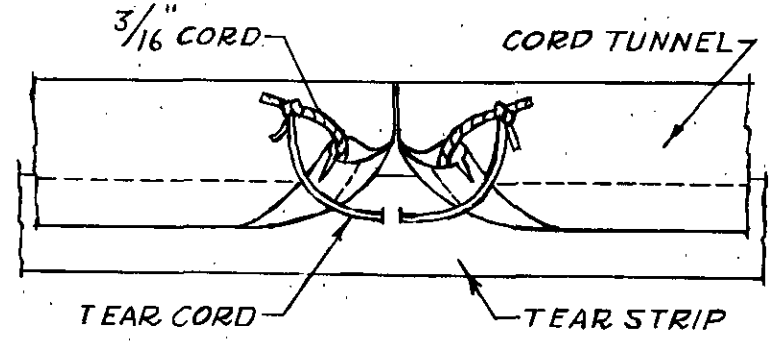

OUTSIDE VIEW

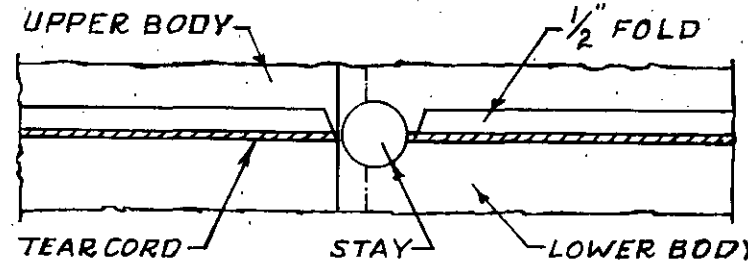

INSIDE VIEW

CORD TUNNEL AND TEAR STRIP – DETAIL

FIGURE 3. COVERALL, WADING

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

FOLD

DEPARTMENT OF THE NAVY
HEADQUARTERS, U. S. MARINE CORPS
WASHINGTON, D.C. 20380

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

Commandant of the Marine Corps
Headquarters, U. S. Marine Corps
Attn: LMA-1
Washington, D. C. 20380

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

OMB Approval
No. 22-R255

INSTRUCTIONS: The purpose of this form is to solicit beneficial comments which will help achieve procurement of suitable products at reasonable cost and minimum delay, or will otherwise enhance use of the document. DoD contractors, government activities, or manufacturers/ vendors who are prospective suppliers of the product are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements. Attach any pertinent data which may be of use in improving this document. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity.

DOCUMENT IDENTIFIER AND TITLE

MIL-C-19145B(MC) Coverall, Wading

NAME OF ORGANIZATION AND ADDRESS

CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY DOCUMENT REQUIREMENT CONSIDERED TOO RIGID

3. IS THE DOCUMENT RESTRICTIVE?

☐ YES ☐ NO *(If "Yes", in what way?)*

4. REMARKS

SUBMITTED BY *(Printed or typed name and address - Optional)*

TELEPHONE NO.

DATE

DD FORM 1 JAN 72 1426 REPLACES EDITION OF 1 JAN 66 WHICH MAY BE USED S/N 0102-LF-014-1802

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:19Z
Check the source to verify that this is the current version before use.