INCH-POUND

MIL-DTL-17/192D
2 July 2007
SUPERSEDING
MIL-C-17/192C
15 March 1993

DETAIL SPECIFICATION SHEET

CABLE, RADIO FREQUENCY, FLEXIBLE, COAXIAL, 50 OHMS, LOW SMOKE, M17/192-00001, M17/192-00002 (TEMPERATURE STABILIZED) AND M17/192-00003 (WATER BLOCKED)

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-DTL-17.

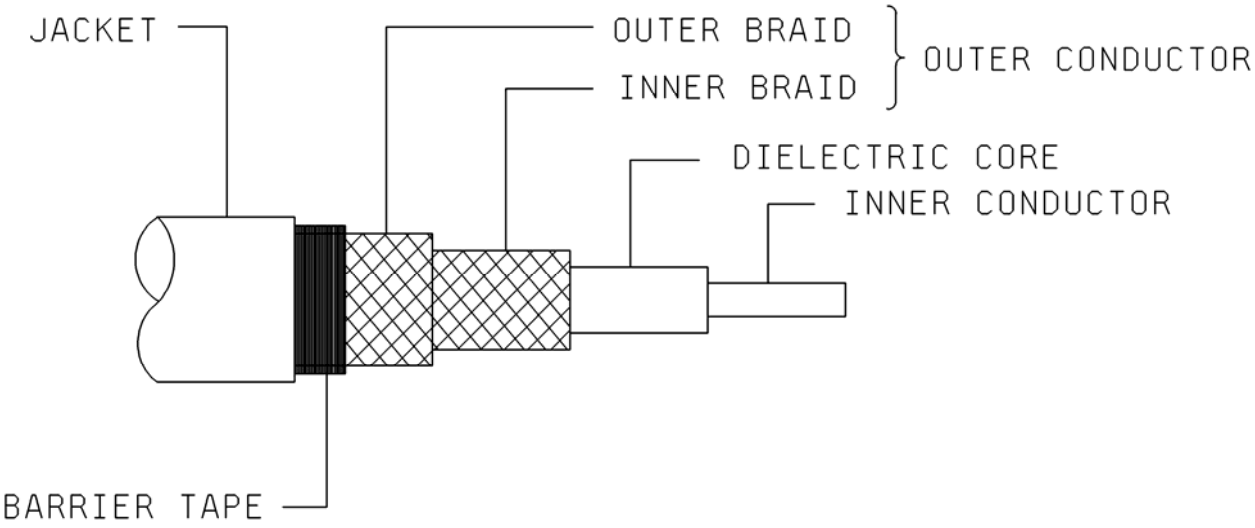


FIGURE 1. General configuration.

AMSC N/A

FSC 6145

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:28Z
Check the source to verify that this is the current version before use.

TABLE I. Description. 1/

Component	Construction
Inner conductor	Solid bare copper wire. Diameter: .106 inch ±0.001
Dielectric core	Type A-I: Solid polyethylene Diameter: .370 inch ± 0.010
Outer conductor	Double braid of AWG No. 33, bare copper wire. Diameter: .445 inch, maximum.
Inner braid	Coverage: 94.8% nominal Carriers: 24 Ends: 10 Picks/inch: 5.4 ±10%
Outer braid	Coverage: 93.6% nominal Carriers: 24 Ends: 8 Picks/inch: 10.6 ±10%
Barrier tape	A .001 inch thick polyester tape faced with a .002 inch thick layer of aluminum. The tape will be applied with a 50% overlap. Aluminum face toward the outer conductor. Diameter: .455 inch maximum.
Jacket	Cross linked polyolefin. Diameter: .545 inch ±.010

1/ Free strippable blocking compound needed where necessary to meet hydrostatic test. The inner shield may be partially imbedded in the dielectric. Applicable to water blocked cables only.

ENGINEERING INFORMATION

Continuous working voltage: 5,200 V rms, maximum.

Operating frequency: 1 GHz, maximum.

Velocity of propagation: 65.9 percent, nominal.

General configuration: See figure 1.

Power rating: See figure 2.

Operating temperature range: -30°C to +85°C

Inner conductor properties:

DC resistance (maximum at 20°C): 0.0941 ohm per 100 feet.

Elongation: 25 percent, minimum.

Tensile strength: Not applicable.

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:28Z
Check the source to verify that this is the current version before use.

Engineering notes: This cable is useful in general purpose applications, medium low temperature applications. (See connector series “N” and “SC” in accordance with MIL-PRF-39012.) These cables were redesigned to meet the vertical flame test. A water blocked cable option has also been included.

REQUIREMENTS

Dimensions, configuration, and description: See figure 1 and table I.

Environmental and mechanical:

Visual and mechanical examination: Applicable.

Out-of-roundness: Applicable.

Eccentricity: 10 percent, maximum.

Adhesion of conductors:

Inner conductor to core: 7 pounds, minimum; 70 pounds, maximum.

Aging stability: +98ºC ±2ºC.

Stress crack resistance: Not applicable.

Outer conductor integrity: Not applicable.

Cold bend: -30ºC ±2ºC.

Dimensional stability: +85°C ± 2°C.

Inner conductor from core: .125 inch, maximum.

Inner conductor from jacket: .250 inch, maximum.

Temperature stabilization: (Applicable to M17/192-00002 cable only). 1/

Temperature cycle at -28ºC within 0ºC and -5ºC, for 24 hours.

Temperature cycle at +65ºC within +5ºC and -0ºC, for 24 hours.

Contamination: Not applicable.

Bendability: Not applicable.

Flame propagation: Applicable.

Acid gas generation: 2.0 percent, maximum.

1/ The cable (1,000 feet) to be treated shall be wound on a spool having a 12 inch minimum barrel diameter before, during and after cycling. The temperature cycling shall be repeated 3 times. The time between cycling shall not exceed 30 minutes. This cable must be able to pass the dimensional stability test following temperature cycling.

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:28Z
Check the source to verify that this is the current version before use.

Halogen content: 0.2 percent, maximum.

Immersion test:

Tensile strength, percent of unaged minimum: 50.

Elongation, percent of unaged minimum: 50.

Smoke index: 25 maximum.

Toxicity index: 5 maximum.

Durometer hardness: (type A) 80 minimum.

Weathering: Applicable

Abrasion resistance: 75 cycles minimum (jacket only).

Tear strength: 35 pounds per inch minimum.

Heat distortion: 30 percent maximum distortion.

Physical tests on unaged jacket:

Tensile strength: 1,300 psi, minimum.

Elongation: 160 percent, minimum.

Physical tests on aged jacket:

Air oven:

Tensile strength, percent minimum: 60.

Elongation, percent minimum: 60.

Hot oil immersion: Applicable

Tensile strength, percent minimum: 50.

Elongation, percent minimum: 50.

Tensile strength and elongation: 1,300 psi, 160 percent, minimum.

Weight: 24.8 pounds per 100 feet, maximum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:28Z
Check the source to verify that this is the current version before use.

Watertightness (Applicable to M17/192-00003, only): One end of a five foot length of completed cable shall be placed in a terminal fitting which will allow water pressure to be applied directly to the exposed cross-sectional area of the end of the cable. Exposure of the sides of the cable to water shall be kept to a minimum, and the fitting shall not exert radial compression against the cable. Unless otherwise approved by the qualifying activity, the sealer used for the packing gland in the terminal fitting shall be a metal alloy having a maximum melting point of 88°C. The specimen shall be subjected to a water pressure of 25 lb_f/in^2 for a period of 6 hours. Any evidence of water leakage shall be cause for rejection.

Hydrostatic (open end) (Applicable to M17/192-00003, only): A 5-foot specimen of completed cable shall be fitted into a gland similar to USL 44500B-12. The cable shall be capable of withstanding 1,000 lb_f/in^2 applied to the gland end of the specimen for a period of 2 hours. Any evidence of water leakage shall be cause for rejection.

Electrical:

Continuity: Applicable.

Spark test: 8,000 V rms, minimum.

Voltage withstanding: 12,000 V rms, minimum

Insulation resistance: Not applicable.

Corona extinction voltage: 7,000 V rms, minimum.

Characteristic impedance: 50 ohms ± 2.

Attenuation: See figure 2.

Structural return loss: See figure 3.

Capacitance: 32.2 pF per foot, maximum.

Capacitance stability: Not applicable.

Capacitance unbalance: Not applicable.

Transmission unbalance: Not applicable.

Mechanically induced noise voltage: Not applicable.

Time delay: Not applicable.

Part or Identifying Number (PIN): See table II.


TABLE II. Cross-reference of PIN.

PIN	Type
M17/192-00001	Low smoke
M17/192-00002	Low smoke, temperature stabilized
M17/192-00003	Low smoke, water blocked

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:28Z
Check the source to verify that this is the current version before use.

Attenuation maximum (dB per 100 feet)

Power in Watts

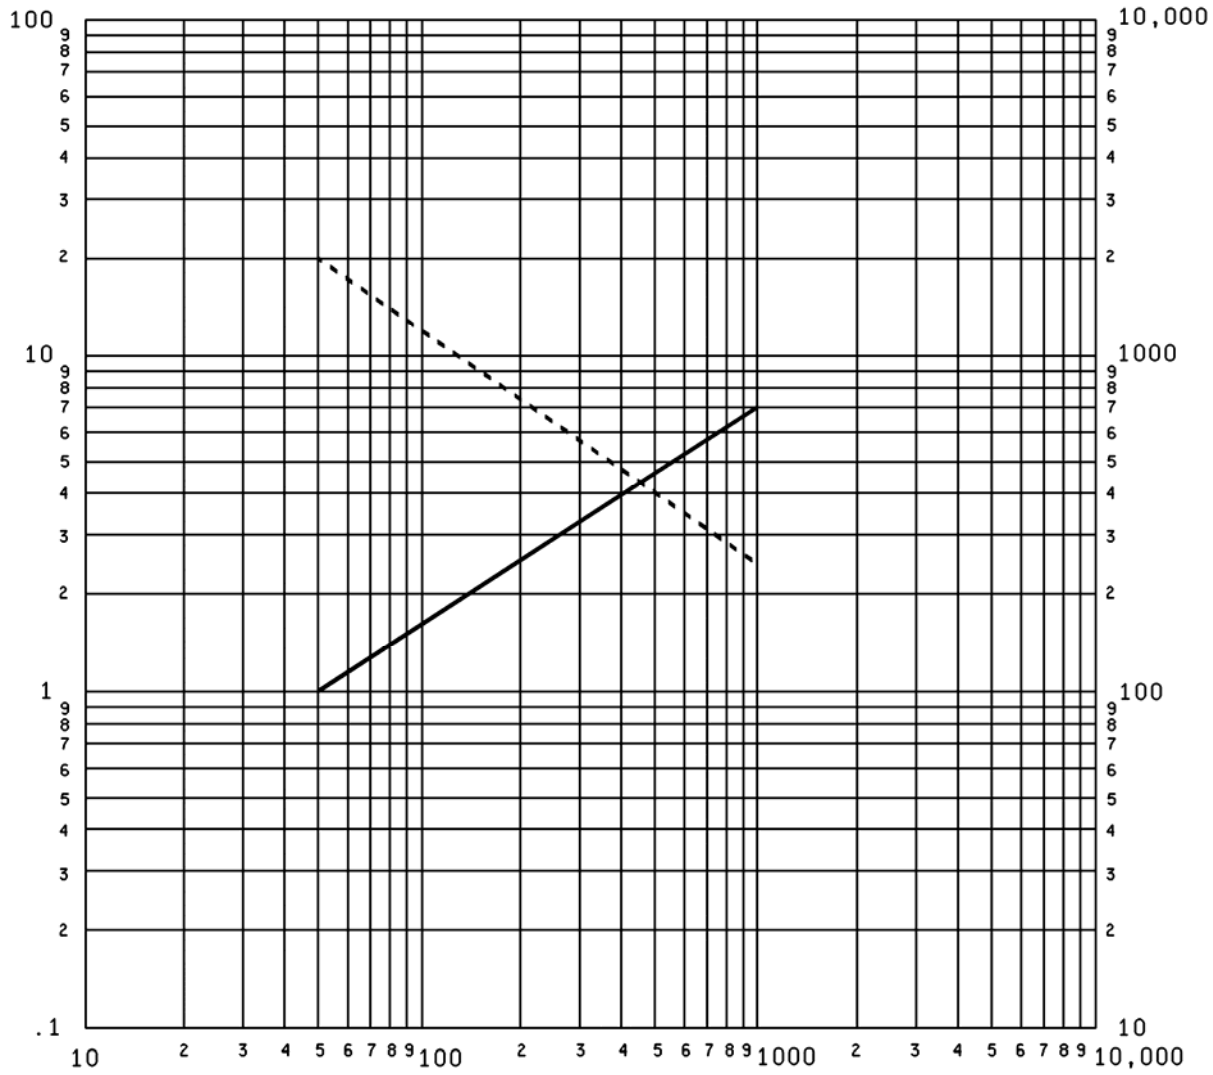

FREQUENCY IN MHz

Maximum power (at 25°C sea level) - - - - - - - - - - - - - -

Maximum attenuation ————————


Test requirements shall be noted as line indicated on graph.

Frequency MHz	Attenuation dB	Watts dB
50	1	2,000
100	1.5	1,200
1000	7	250

FIGURE 2. Power rating and attenuation.

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:28Z
Check the source to verify that this is the current version before use.

Minimum return loss
(in dB)

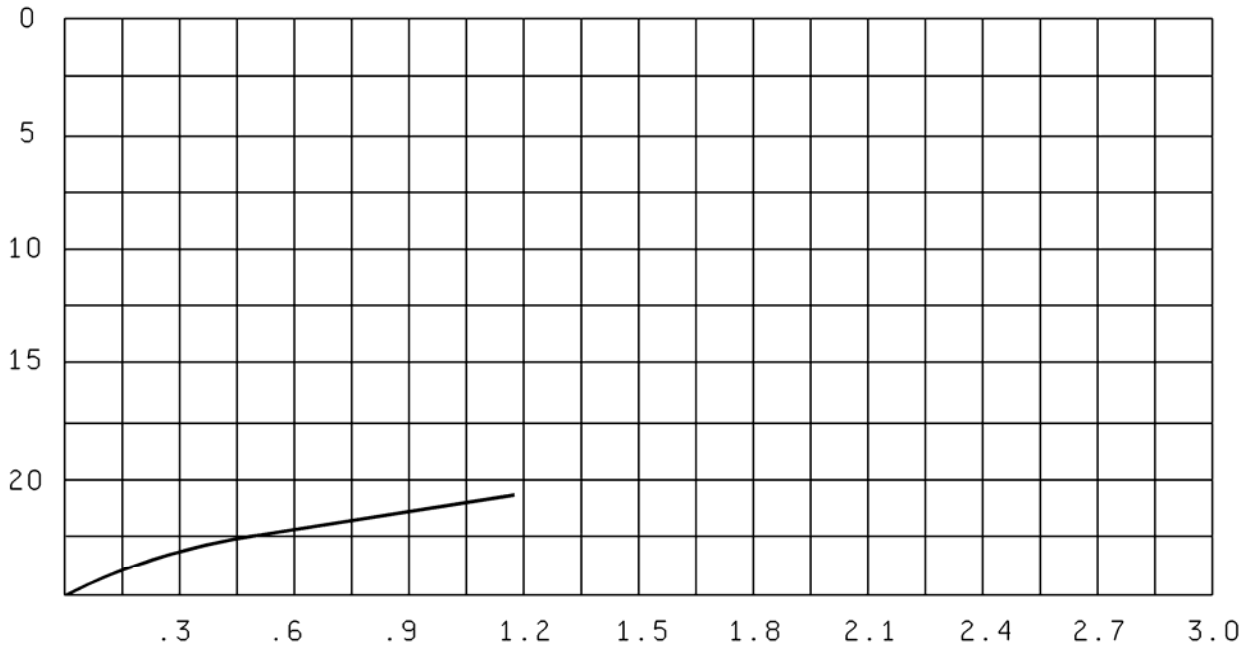

FREQUENCY IN GHz

SWR	Reflection coefficient	Return loss dB	SWR	Reflection coefficient	Return loss dB
17.3910	.8913	1	1.3767	.1585	16
8.7242	.7943	2	1.3290	.1413	17
5.8480	.7079	3	1.2880	.1259	18
4.4194	.6310	4	1.2528	.1122	19
3.5698	.5623	5	1.2222	.1000	20
3.0095	.5012	6	1.1957	.0891	21
2.6146	.4467	7	1.1726	.0794	22
2.3229	.3981	8	1.1524	.0708	23
2.0999	.3548	9	1.1347	.0631	24
1.9250	.3162	10	1.1192	.0562	25
1.7849	.2818	11	1.1055	.0501	26
1.6709	.2512	12	1.0935	.0447	27
1.5769	.2239	13	1.0829	.0398	28
1.4985	.1995	14	1.0736	.0355	29
1.4326	.1778	15	1.0653	.0316	30

FIGURE 3. Structural return loss.

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:28Z
Check the source to verify that this is the current version before use.

Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

Referenced documents. In addition to MIL-DTL-17, this document references the following:

MIL-PRF-39012

CONCLUDING MATERIAL

Custodians:
Army - CR
Navy - EC
Air Force - 11
DLA - CC

Preparing activity
DLA - CC

(Project 6145-2007-036)

Review activities:
Army - AR, AT, CR4, MI
Navy - AS, MC, OS, SH
Air Force - 19, 71, 99

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at http://assist.daps.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:28Z
Check the source to verify that this is the current version before use.