MIL-D-19458A(SHIPS)
14 August 1964
SUPERSEDING
MIL-D-19458(SHIPS)
27 June 1956
(See 6.3)

MILITARY SPECIFICATION

DIVER'S DRESS, SWIM SUIT

1. SCOPE

1.1 This specification covers swim suit, rubber coated, in five sizes as specified (see 3.6).

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of the specification to the extent specified herein:

SPECIFICATIONS

FEDERAL
V-T-276 - Thread, Cotton.
CCC-T-191 - Textile Test Methods.

STANDARDS

FEDERAL
FED-STD-601 - Rubber: Sampling and Testing.
FED-STD-751 - Stitches; Seams; and Stitchings.

MILITARY
MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

3. REQUIREMENTS

3.1 Preproduction sampling.- Before production is started, a finished swim suit of each size, including accessory parts, shall be submitted to the Officer-in-Charge, Experimental Diving Unit, Washington Navy Yard, Washington 25, D. C., for the tests specified in 4.2 (see 6.2).

3.2 Materials.- Unless otherwise specified (see 6.1), the following materials shall be used in the manufacture of the swim suits.

3.2.1 Fabric.- The fabric shall be cotton, ribbed knit, (Cooper or Wildman knit will be acceptable), having the physical characteristics specified in table I.

Table I - Physical characteristics of the fabric.

	Standard	Minimum	Maximum
Finished width (inches)	54	52	56
Weight-ounces per square yard (see 4.7.9.2)	3.0	2.73	3.3
Strength-bursting (Scott) pounds (see 4.7.9.3)	52	48	---
Wales per inch (see 4.7.9.4)	25	23.5	26.5

FSC 4220

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

Table I - Physical characteristics of the fabric. (continued)

	Standard	Minimum	Maximum
Courses per inch-face (see 4.7.9.4)	35	33	37
Courses per inch-back (see 4.7.9.4)	35	33	37
Yarn-face	40/1 Combed Peeler-Single thread (S.T.)		
Construction	S.T. ribbed knit needles per inch-18		
Diameter of knitting head (inches)	29	---	---
Piece dyed, brown (satisfactory to the bureau or agency concerned	---	---	---
Stretch - length percent (see 4.7.9.5)	15	12	18
Stretch - width percent (see 4.7.9.5	130	104	156

3.2.1.1 The pH of the fabric shall be not lower than 7.0 when tested in accordance with 4.7.9.1.

3.2.1.2 The dyed and finished fabric shall contain not more than 0.005 percent copper or 0.001 percent manganese.

3.2.2 Coating compound. - The compound used for coating the fabric shall be made from good quality natural rubber containing not less than 60 percent by weight of natural rubber. The coating compound shall be of a shade of grey-green satisfactory to the bureau or agency concerned.

3.2.2.1 The coating compound shall have the physical properties specified in table II as determined by testing mold-cured test slabs when tested in accordance with 4.7.5.2, 4.7.6 and 4.7.8.

Table II - Physical properties of the coating compound.

	Minimum	Maximum
Tensile strength, initial, (p.s.i.)	1800	---
Elongation, initial, (percent)	500 percent	---
Tensile strength, after aging	Not less than 75 percent of unaged value	
Permanent set	---	5 percent

3.2.3 Coated fabric. - The coated fabric prepared in accordance with 3.3.4 shall have the physical properties specified in table III, when tested in accordance with 4.7.1, 4.7.2, 4.7.3, 4.7.4, 4.7.5.1 and 4.7.10.

Table III - Physical properties of coated fabric.

	Minimum	Maximum
Weight of coating (ounces per square yard)	10.0	13.0
Bursting strength (ball burst)	47.0	---
Hydrostatic (Mullen) (pounds)	40	---
Adhesion (coating to fabric per 1 inch strip) (pounds)	5	---
Percent stretch (length) percent	30	---
Percent stretch (width) percent	180	---

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

3.2.4 Sheet rubber. - The rubber material used in seam straps, shall be made from good quality rubber compound containing not less than 75 percent by weight of natural rubber and shall be of a shade of grey-green satisfactory to the bureau or agency concerned. The rubber material shall be calendered to a thickness of not less than 0.025 inch and not more than 0.028 inch and shall have the physical properties specified in table IV when tested in accordance with 4.7.5.2, 4.7.6, 4.7.7, and 4.7.8.

Table IV - Physical properties of rubber material.

	Minimum	Maximum
Tensile strength, initial, (p.s.i.)	1800	---
Elongation, initial, (percent)	500 percent	---
Tensile strength, after aging	Not less than 75 percent of unaged value	
Permanent set	---	5 percent.
Tear resistance (Graves)	70 pounds	---

3.2.5 Cement. - The cement used for assembly of the garment shall be made from natural rubber and shall be completely compatible with the coating and components with which it is used, shall have good adhesion, flexibility, and all other characteristics equal to the physical properties of the coated fabric used in the suit. The cement used for assembly of uncured parts shall be so compounded as to be heat curing, and shall have the same curing characteristics as the compounds with which it is used. Rubber cement used for operations performed after vulcanizing shall be so compounded as to be self-curing.

3.2.6 Insole material. - The material used for insoles shall be made of same material as the body of the dress.

3.2.7 Cloth strapping. - The cloth strapping used for attachment of latex waist bands, facepiece, and cuffs shall be the same material as the suit body.

3.2.8 The facepiece, cuffs, and bands for attaching to the jumper and pants shall be made of dipped latex and have the following physical characteristics when tested in accordance with 4.7.5.2 and 4.7.6:

Tensile strength, initial p.s.i. ---------- 3500 minimum
Elongation, initial, percent ---------- 700 minimum
Tensile strength (after aging) ---------- Not less than 70 percent of initial value.

3.2.9 Exhaust valve cushion. - The exhaust valve cushion material shall be 1/8 inch natural rubber unicellular sponge.

3.2.10 Gloves. - The gloves shall be dipped rubber latex and shall have the physical properties specified in table V when tested in accordance with 4.7.6.

Table V - Physical properties of gloves.

	Minimum	Maximum
Thickness (inch)	0.018	0.025
Weight (pounds per 100 pairs)	35	---
Tensile strength (p.s.i.)	2500	---
Elongation, percent	600	---
Tensile strength, p.s.i. (after 46 hours water soak at 70°C.)	1500	---

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

3.2.11 Thread. - The thread shall be 3-cord No. 40 cotton sewing thread dyed black (type IB3 of V-T-276).

3.3 Design and construction. - The suit shall consist of 3 pieces which will cover the entire body with the exception of the face opening. The top, or jumper, shall cover the body from the waist up with the exception of the hands and face opening. At the bottom of the jumper shall be attached a latex band that will extend up under the arms. The jumper shall have a skirt on the inside to cover the section between the latex bands after assembly with the pants. To the arms of the jumper shall be attached dipped latex cuffs. A skirt under the cuff shall also be provided.

3.3.1 The bottom or pants section shall cover the wearer from the waist down. At the top of the pants shall be a dipped latex band that will extend up under the arms and match the latex band of the jumper.

3.3.2 By folding the two bands of the waist and by overlaying the cuffs, and in conjunction with the molded rings, a watertight seal shall be effected at the waist and wrist.

3.3.3 The suit shall be constructed with the seams stitched and gum-strapped on the outside before vulcanization. The garment shall be vulcanized in its entirety after assembly, except that the facepiece, cuffs, latex waist bands, and exhaust valve may be attached after cure.

3.3.4 Coated fabric. - The coating compound shall be calendered to the outside of the fabric with not less than 10.0 ounces per square yard and not more than 13.0 ounces per square yard of coating compound. The coated fabric shall be sufficiently soft and pliable and of such modulus as to be entirely suitable for the purpose. There shall be no appreciable signs of deterioration of the coated fabric when tested in accordance with 4.7.5.1.

3.3.5 Facepiece. - The facepiece shall be made on a full face form. To the outside periphery of the facepiece there shall be cemented a 1-inch strip of the suit material attached with the coated side to the outside of the facepiece and the lining side exposed. The thickness of the finished facepiece shall be not less than 0.023 inch in the thinnest areas and not more than 0.028 inch in the thickest areas. Physical properties of the finished facepiece shall conform to 3.2.8.

3.3.6 Cuffs. - The cuffs shall be made from one ply of the 0.025 inch dipped latex. The thickness of the finished cuff shall be not less than 0.020 inch and not more than 0.030 inch.

3.3.7 Waist band. - The waist band shall be made from one ply of 0.025 inch dipped latex. The thickness of the finished waistband shall be not less than 0.020 inch and not more than 0.030 inch. The waist band shall be attached to inside waist of both the jumper and leg portions of the suit and strapped with body material on the inside.

3.3.8 Cutting. - To provide maximum mobility, the direction of maximum stretch in the material is of prime importance in the cutting of the parts of the suit. The front body panel, back panel, the sleeves, the upper leg sections, the lower leg sections, and neck band shall be cut so that the maximum stretch is in the horizontal plane. The hood shall be cut to have the stretch in vertical plane.

3.3.9 Stitches, seams and stitching. - Stitches, stitching and formation of stitched seams shall conform to FED-STD-751, and shall be made with stitch type 401. The seam type shall be in accordance with type SSa-1 except that the seams shall also be cemented and gum strapped on the outside with 3/4-inch gum strapping centered on the seam.

3.3.10 Waterproofness of seams. - All seams shall be completely waterproof and shall be equal to the waterproof requirements for the coated material. When tested as specified in 4.7.2, the adhesion of the gum strap to the seam shall be not less than 3.5 pounds, and the strength of the seam, when subjected to crosswise sheer pull, shall be equal to the suit material.

3.3.11 The gloves shall be size 10, 13-3/4 inches to 14-1/2 inches long. They shall have roughened fingers.

3.4 Detail construction. -

3.4.1 Suit. - The jumper portion of the suit shall be constructed with a two-piece body consisting of one piece front and back panels. The leg portion of the suit shall consist of one section and crotch and a

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

foot. The leg sections shall be seamed at the back and joined together with a seam at the back of leg. The foot section shall consist of two pieces (each foot) on the instep, an outsole and an insole. The sleeves shall be made in one piece (each sleeve) seamed at inseam and joined to body with square shoulders. The hood portion shall consist of a neck band and a three-piece helmet type head section. All seaming and joining shall be done in accordance with 3.3.9. Cutting shall be in accordance with 3.3.8.

3.4.2 Hood straps. - To the back of the hood shall be attached two straps with quick take-up buckles, in order to obtain proper tightness on the facepiece to make a watertight seal.

3.4.3 Facepiece. - The facepiece shall be made in accordance with 3.3.5 and shall be attached by cementing around the outside of the opening in the hood and strapping on the outside with 1-inch strapping of suit material.

3.4.4 Hood. - The hood shall be equipped with two straps approximately 3/4 inch wide attached at each side in back. Quick take-up buckles shall be furnished.

3.4.5 Cuffs. - The cuffs shall be made in accordance with 3.3.6 and shall be attached inside each sleeve with a single hinge of 1-1/2-inch suit material.

3.4.6 Molded rings. - There shall be a set of molded rings for the wrist and waist. A set shall consist of two rings. The inner ring shall be positioned between the wearer and the suit, and shall be sufficiently rigid so that when the folded portion of the jumper and pants are folded over it, plus the outer ring, it will not collapse. The outer ring shall be an "O" ring type and shall then fit over the suit closure folds with sufficient elasticity to make a watertight seal. The waist inner ring shall be adjustable to the point that any amount up to 4 inches can be removed.

3.4.7 Exhaust valves. - The suit shall have one exhaust valve. Valves shall be attached over a 3/8 inch circular hole which shall be reinforced with oval stays of suit material cemented to the outside. The exhaust valve (see figure 1) shall be located on the centerline of the chest so that the center of its base is 3 inches below the seam between the hood and suit. It shall be oriented so that the stem of the valve is up and over at the base of the neck and the mouthpiece is easily accessible to the swimmer. Near the neck seams and shoulder junction shall be attached a triple fold loop with ends hinged into a reinforced oval stay to hold down the valve tube.

3.4.8 Exhaust valve cushions. - The exhaust valve cushion shall be cemented on the inside of the suit.

3.4.9 Insoles (feet). - The insoles shall be solid cemented to the lining side of the soles of feet after the suit is vulcanized.

3.4.10 Outsoles and foxing. - The gum foxing and outsole shall be made from material rubber compound and calendered to a gage of 0.075 $\pm$ .005. The gum shall be knurled on one side. The outsole shall be constructed as follows:

> Cement bottom of leg 1 inch wide; cement smooth side of foxing. Place foxing around periphery of foot, starting at inside arch overlapping ends 1 inch. Cement complete insole and 1/2 inch onto foxing; cement smooth side of outsole. Position outsole on bottom of foot, outer edges overlapping foxing 3/8 inch. Bevel-roll all edges.

3.5 Marking. - The following information shall be legibly stamped with indelible ink on inside top of jumper and pants, in letters approximately 1 inch high:

(a) Manufacturer's name.
(b) Contract number.
(c) Suit size.
(d) Bureau of Ships stock number.
(e) Date of manufacture.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

3.6 Measurements. - The measurements, in inches, shall conform to table VI.

Table VI - Swim suit measurements.

Suit size	M-short	M	M-long	Large	X-large
	Inches	Inches	Inches	Inches	Inches
Chest, expanded	39-1/2	41-1/2	41-1/2	43-1/2	45-1/2
Waist	32-1/2	34-1/2	34-1/2	36-1/2	38-1/2
Arm length	23	25	27	25	25
Arm circumference	13	14	14	15	16
Wrist	6-3/4	6-3/4	6-3/4	7-1/4	7-3/4
Head	22	23	23	23	24
Neck	15-1/2	15-1/2	15-1/2	16-1/2	16-1/2
Butt	37-1/2	39-1/2	39-1/2	41-1/2	43-1/2
Leg, inseam	30-1/2	33-1/2	36-1/2	34-1/2	35-1/2
Leg, circumference	14	15	15	16	17
Leg at crotch	22-1/2	24	24	25-1/2	27
Ankle	9-1/2	10-1/2	10-1/2	11-1/2	11-1/2
Feet	10	11	11	12	12

3.7 Repair parts. - The following repair parts shall be furnished:

1 piece of cured body material, 18 inches by 18 inches.
2 waist straps 2 inches by 46 inches.
2 wrist straps 1 inch by 16 inches.
2 extra cuffs
1 extra facepiece.
2 extra latex waistbands.
1 extra waist snap ring.
1 extra pair gloves.
4 one-ounce tubes of cement.
Grater.
Instruction sheet.
Label on cement cans.

3.8 Workmanship. - The suits shall be clean, well finished, thoroughly waterproof, and free from any defects which may affect serviceability. Suits with patches shall be acceptable up to 10 percent of the quantity specified by the contract or order, provided there are not more than two patches per suit and that patches are applied in such a manner that the serviceability of the suit will not be affected.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. - Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification, where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Preproduction inspection. - The sample suit and accessories submitted in accordance with 3.1 shall be visually and dimensionally examined for conformance with this specification. The suit shall be subjected to an actual swim test to determine suitability for the purpose intended.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

4.3 Sampling. - Samples of any materials or components entering into the manufacture of the articles may be selected from time to time by the Government inspector, carefully examined, and tests made to determine compliance with this specification.

4.4 Contractor's inspection. - The contractor shall inspect all finished swim suit units for compliance with this specification prior to submitting them for final inspection.

4.4.1 Contractor's inspection for waterproofness. - The contractor shall conduct waterproofness test on each finished garment by donning and immersing in a tank of water for a period of 5 minutes.

4.5 Sampling for quality conformance inspection. -

4.5.1 Inspection lot. - All swim suits of one size offered for delivery at one time shall be considered a lot for purposes of inspection.

4.5.2 Sampling for visual and dimensional examination and waterproofness test. - A random sample of swim suits shall be selected from each lot offered for examination in accordance with MIL-STD-105 at inspection level III. The Acceptable Quality Level shall be 1.0 percent defective.

4.5.3 Material for tests. - The contractor shall provide sufficient specimens of material to perform the tests specified in 4.7. The specimens of material shall have been manufactured in the same calendar run as the material used in the inspection lot.

4.6 Visual and dimensional examination and waterproofness test. - Each of the sample suits selected in accordance with 4.5.2 shall be visually and dimensionally examined to verify compliance with this specification not requiring tests and shall be subjected to the waterproofness test. Any suit in the sample containing one or more visual or dimensional defects shall not be offered for delivery, and if the number of defective suits in any sample exceeds the acceptance number for that sample, this shall be cause for rejection of the lot represented by the sample.

4.6.1 Examination may be made throughout the entire process of manufacture. The passing as satisfactory of any detail of construction or materials shall not relieve the contractor of responsibility for faulty workmanship or materials which may be discovered at any time prior to final acceptance. Final examination of the finished article shall be made either at point of production or at point of delivery. In case of factory examination, every facility shall be afforded Government inspectors, by the manufacturer, for the prosecution of their work.

4.7 Test procedures. - The following tests shall be conducted by the contractor under the surveillance of the inspector:

4.7.1 Bursting strength. - The coated fabric shall be tested in accordance with method 5120 of CCC-T-191.

4.7.2 Hydrostatic. - The coated fabric and seams shall be hydrostatically tested in accordance with method 5512 of CCC-T-191, with water pressure applied to the coated side of the fabric and held for one minute.

4.7.3 Adhesion. -

4.7.3.1 The coated fabric shall be tested in accordance with method 5970 of CCC-T-191.

4.7.3.2 Strapped seams shall be tested in accordance with method 5962 of CCC-T-191.

4.7.4 Weight of coated fabric. - The weight of the coated fabric shall be determined in accordance with method 5041 of CCC-T-191.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

4.7.5 Accelerated aging. -

4.7.5.1 Coated fabric. - A specimen shall be tested in accordance with method 5850 of CCC-T-191 for a period of 7 days.

4.7.5.2 Rubber. - Specimens shall be tested in accordance with method 7221 of FED-STD-601 except that the temperature shall be 194 ± 2°F. (90 ± 1.1°C.) and the length of time shall be 46 hours.

4.7.6 Tensile strength and elongation. - Tensile strength and elongation of rubber shall be determined in accordance with methods 4111 and 4121 of FED-STD-601.

4.7.7 Tear resistance. - The tear resistance of the rubber shall be determined in accordance with method 4211 of FED-STD-601 using die C.

4.7.8 Permanent set. - The permanent set of the rubber shall be determined in accordance with method 4411 of FED-STD-601, except that the specimen shall be elongated 100 percent.

4.7.9 Fabric. -

4.7.9.1 The pH of the fabric shall be determined in accordance with method 2810 of CCC-T-191.

4.7.9.2 The weight of the fabric shall be determined by method 5041 of CCC-T-191.

4.7.9.3 The strength of the fabric shall be determined in accordance with method 5120 of CCC-T-191.

4.7.9.4 The wales and courses per inch of the fabric shall be determined in accordance with method 5070 of CCC-T-191.

4.7.9.5 The stretch of the fabric shall be determined in accordance with the following test method:

(a) The portion of the fabric to be tested shall be representative of the piece and shall not be less than 1/2 yard from the end of the roll nor nearer either edge than 15 percent of the width of the piece. The portion to be tested shall be 2 inches in width and not less than 5 inches in length; and cut so that the longer edges of the sample shall be parallel to the courses of the fabric for width stretch and parallel to the wales for length stretch. Clamps, 2 inches in width, and weighing not more than 3/4 ounce each shall be attached to samples so that the fabric between them shall measure 2 inches in width and 4 inches in length. One of the clamps shall be suspended so that the other will hang vertically and freely, and to the lower clamp shall be attached a one pound weight. After being suspended in this manner for 10 minutes, the distance between the two clamps shall be measured at the joints of contact with the fabric, and this measurement less 4 inches, divided by 4 expressed in terms of percent equals the percent of stretch. The average of five tests in the direction of the wales shall be the percent stretch in the length of the fabric, and the average of five tests in the direction of the courses shall be the percent stretch in width of the fabric.

4.7.10 Stretch of coated fabric. - The stretch of the coated fabric shall be determined in accordance with method 5100 of CCC-T-191.

5. PREPARATION FOR DELIVERY

5.1 Domestic shipment and early installation. -

5.1.1 Packaging. - Packaging shall be sufficient to afford adequate protection against corrosion, deterioration and physical damage during shipment from the supply source to the using activity and until early installation.

5.1.2 Packing. - Packing shall be accomplished in a manner which will insure acceptance by common carrier and will afford protection against physical or mechanical damage during direct shipment from the supply source to the using activity for early installation. The shipping containers or method of packing

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

shall conform to the Uniform Freight Classification Rules and Regulations or other carrier regulations as applicable to the mode of transportation.

5. 1. 3 Marking. - Shipment marking information shall be provided on interior packages and exterior shipping containers in accordance with the contractor's commercial practice. The information shall include nomenclature, Federal stock number or manufacturer's part number, contract or order number, contractor's name and destination.

5. 2 Domestic shipment and storage or overseas shipment. - The requirements and levels of packaging, packing and marking for shipment shall be specified by the procuring activity (see 6. 1).

5. 2. 1 The following provides various levels of protection during domestic shipment and storage or overseas shipment, which may be required when procurement is made.

5. 2. 1. 1 Packaging. -

5. 2. 1. 1. 1 Level A. - Each unit swim suit (jumper, bottom, waist ring, wrist ring, and gloves) and repair parts shall be folded and packaged individually in a corrugated fiberboard box conforming to PPP-B-636 of such dimensions as to accommodate the articles packaged therein without excess of wrinkling or shifting. The repair parts specified in 3. 7 shall be packaged in a separate carton. Fiberboard boxes shall have all joints and seams sealed with pressure-sensitive tape as specified in PPP-B-636.

5. 2. 1. 1. 2 Level C. - Packaging shall be in accordance with the manufacturer's commercial practice.

5. 2. 1. 2 Packing. -

5. 2. 1. 2. 1 Level A. - Swim suits and accessories packaged as specified shall be packed in wood-cleated fiberboard, wood-cleated plywood, wirebound wood, or fiberboard boxes conforming to PPP-B-585, PPP-B-591, PP-B-601, or PP-B-636. Whenever practicable, suits of one size only shall be packed in the same box for shipment. The gross weight of wood or wood-cleated containers shall not exceed approximately 200 pounds.

5. 2. 1. 2. 2 Level B. - Swim suits and accessories packaged as specified shall be packed in wood-cleated fiberboard, wood-cleated plywood, wirebound wood, or fiberboard boxes conforming to PPP-B-591, PPP-B-601, PPP-B-585 or the special requirements of PPP-B-636. Whenever practicable, suits of one size only shall be packed in the same box for shipment. The gross weight of wood or wood-cleated containers shall not exceed approximately 200 pounds.

5. 2. 1. 2. 3 Level C. - Swim suits with accessories packaged as specified shall be packed for shipment in standard commercial containers so constructed as to insure acceptance by common or other carrier for safe transportation, at the lowest rate, to the point of delivery. Whenever practicable, suits of one size only shall be packed in the same box for shipment. Not less than 6 nor more than 12 packages shall be packed in one case for shipment.

5. 2. 1. 3 Marking. - In addition to any special marking required, interior packages and exterior shipping containers shall be marked in accordance with MIL-STD-129.)

6. NOTES

6. 1 Ordering data. - Procurement documents should specify the following:

(a) Title, number, and date of this specification.
(b) Material, if different (see 3. 2).
(c) Packaging, packing or marking requirements other than those required by paragraph 5. 1 (see 5. 2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

6.2 Preproduction. -

6.2.1 Invitations for bids should provide that the Government reserves the right to waive the requirement for preproduction samples as to those bidders offering a product which has been previously procured or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending procurement.

6.3 CHANGES FROM PREVIOUS ISSUE. THE EXTENT OF CHANGES (DELETIONS, ADDITIONS, ETC.) PRECLUDE THE ANNOTATION OF THE INDIVIDUAL CHANGES FROM THE PREVIOUS ISSUE OF THIS DOCUMENT.

Preparing activity:
Navy - Ships
(Project 4220-N048Sh)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

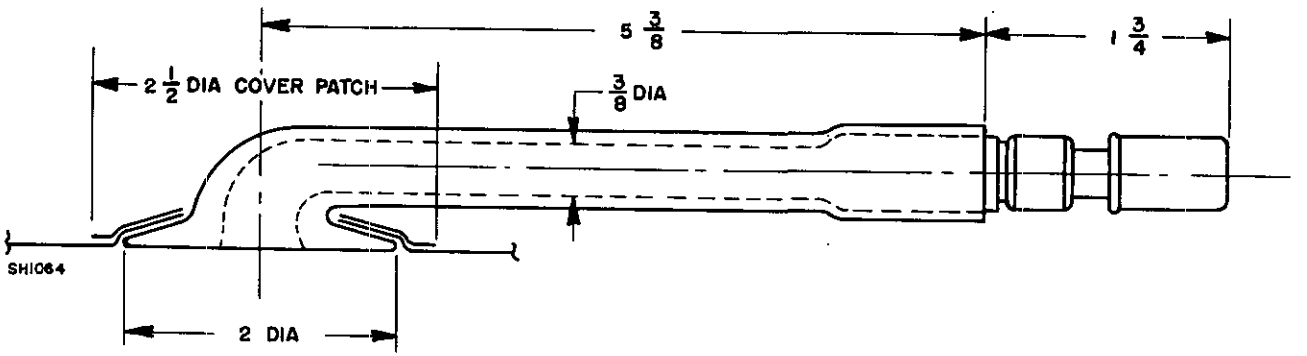


Figure 1 - Exhaust valve.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.

SPECIFICATION ANALYSIS SHEET

Form Approved Budget Bureau No. 119-R004

INSTRUCTIONS

This sheet is to be filled out by personnel either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of *delay and at the least cost*. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity.

SPECIFICATION

ORGANIZATION | CITY AND STATE

CONTRACT NO. | QUANTITY OF ITEMS PROCURED | DOLLAR AMOUNT $

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?
   A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES.

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?

☐ YES ☐ NO IF "YES", IN WHAT WAY?

4. REMARKS *(Attach any pertinent data which may be of use in improving this specification. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity)*

SUBMITTED BY *(Printed or typed name and activity)* | DATE

DD FORM 1 APR 63 1426 REPLACES NAVSHIPS FORM 4863, WHICH IS OBSOLETE

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T12:52Z
Check the source to verify that this is the current version before use.