MILITARY SPECIFICATION

WATER REPELLENT, WINDOW AND WINDSHIELD, GLASS AND PLASTIC

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for one type of water repellent compound.

2. APPLICABLE DOCUMENTS

2.1 Issues of documents. The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein.

SPECIFICATIONS

FEDERAL

QQ-A-250/5	- Aluminum Alloy, Alclad 2024, Plate and Sheet
TT-N-95	- Naphtha, Aliphatic
CCC-C-458	- Cloth, Flannel, Cotton
PPP-B-636	- Box, Fiberboard
PPP-C-186	- Containers, Packaging and Packing for Drugs, Chemicals, and Pharmaceuticals

MILITARY

MIL-P-5425	- Plastic, Sheet Acrylic, Heat Resistant

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Engineering Specifications and Standards Department (Code 93), Naval Air Engineering Center, Lakehurst, NJ 08733, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

Source: https://assist.dla.mil -- Downloaded: 202610-17T07:39Z
Check the source to verify that this is the current version before use.

MILITARY (continued)

MIL-T-5624	- Turbine Fuel, Aviation, Grades JP-4 and JP-5
MIL-C-22750	- Coating, Epoxy-Polyamide
MIL-P-25690	- Plastic, Sheets and Parts, Modified Acrylic Base, Monolithic, Crack Propagation Resistant
MIL-L-81352	- Lacquer, Acrylic (For Naval Weapons Systems)
MIL-C-81773	- Coating, Polyurethane, Aliphatic, Weather Resistant

STANDARDS

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	- Marking for Shipment and Storage

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

3. REQUIREMENTS

3.1 Qualification. The water repellent furnished under this specification shall be a product which is qualified for listing on the applicable qualified products list at the time of opening of bids (see 4.2.1 and 6.3). In addition, the retention of qualification for the water repellent on the applicable qualified products list shall be dependent on periodic verification of continued compliance with the requirements of this specification (see 4.2.1.2).

3.1.1 Service tests. The water repellent shall perform as well as or better than the control formula product (4.5.6.2) when both are tested on an airplane in flight under rain conditions (see 4.2.1.1).

3.1.2 Changes requiring requalification. Any changes in the formulation of the water repellent compound or its container will require proof of compliance with all applicable requirements of this specification (see 4.2.1.1).

3.2 Materials. There are no restrictions on the compositon of the water repellent compound, other than those imposed by the technical requirements specified herein.

Source: https://assist.dla.mil -- Downloaded: 202610-17T07:39Z
Check the source to verify that this is the current version before use.

3.2.1 Toxicity. The material shall have no adverse effect on the health of personnel when used for its intended purpose. Questions pertinent to this effect shall be referred by the procuring activity to the appropriate departmental medical service who will act as an advisor to the procuring agency (see 6.4).

3.2.2 Deleterious effects on adjacent surfaces. The water repellent compound, when used in accordance with specified instructions shall have no deleterious effect on the adjacent surfaces (see 4.5.11).

3.3 Coverage. When the water repellent is applied as specified, it will apply a film on glass or plastic surfaces in a one step operation.

3.4 Resistance to temperature cycling. The weight and appearance of the water repellent compound and its container shall be unchanged by temperatures varying from 39oF (4oC) to 120oF (49oC) when tested as specified in 4.5.1.

3.5 Application of film. The water repellent compound shall be capable of being applied and reapplied at 39oF (4oC) and also at 90oF (32oC) as specified in 4.5.2. The resulting film shall be clear, continuous, and free from granular structure.

3.6 Abrasion and staining. The water repellent compound shall not scratch or stain transparent glass or plastic when applied as specified in 4.5.3.

3.7 Visibility. After application of the water repellent in accordance with manufacturer's instructions, there shall be no marked decrease in visibility, nor any evidence of distortion, when observations are made as specified in 4.5.4.

3.8 Roll angle. When determined in accordance with 4.5.5, the roll angle of a drop of water on glass or plastic to which the water repellent has been applied shall be less than 20 degrees.

3.9 Effectiveness and durability. When the water repellent is tested as specified in 4.5.6, water shall not form a continuous film, but shall be in the form of discrete droplets on the surface of the water repellent film. A single application of water repellent shall be capable of lasting for 6 consecutive hours of simultaneous exposure to wind erosion at 500 ±10 miles per hour and to 1 inch of rainfall per hour, and visibility shall not be impaired. The reading on the chart of the visibility comparator (during the application of air and water) shall at all times be less than half the initial setting for untreated glass or plastic.

3.9.1 Jet fuel and de-icing fluid resistance. After the water repellent film has been applied in accordance with the manufacturer's directions, the glass shall be wiped with a cloth dampened with JP-4 fuel, and then with a

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

cloth dampened with isopropyl alcohol and tested as specified in 4.5.6.1. The decrease in effectiveness and durability, as measured with the visibility comparator shall be not more than 10 percent.

3.9.2 Control tests. The effectiveness and durability exhibited by the test material shall be at least as good as that exhibited by a control film prepared as specified in 4.5.6.2.

3.10 Light transmission. The water repellent film shall not decrease the light transmission, as determined in 4.5.7, of the glass or plastic to which it has been applied.

3.11 Refractive index. There shall be no change in the refractive index, as specified in 4.5.8, when the glass or plastic has been coated with the water repellent.

3.12 Low temperature visibility. When panels, to which water repellent has been applied, are exposed in accordance with 4.5.9 to a temperature of -65°F (-54°C) for 1 hour, there shall be no marked decrease in visibility when the panel is at -65°F (-54°C) and upon return to room temperature.

3.13 High temperature visibility. When a panel, to which water repellent has been applied, is exposed in accordance with 4.5.10 to a temperature of 200°F (93°C) for 1 hour, there shall be no marked decrease in visibility when the panel is at 200°F (93°C) and upon return to room temperature.

3.14 Compatibility. When the water repellent film is applied in accordance with 4.5.11 to coated and non-coated metals, it shall cause no corrosion of the metal, and no softening or discoloration of the coatings. The water repellent shall not cause corrosion of plated or unplated ferrous alloys and standard non-ferrous alloy parts such as fittings and attaching hardware.

3.15 Effect on acrylic plastics. Acrylic plastic panels coated with water repellent shall show no evidence of crazing when tested as specified in 4.5.12.

3.16 Storage stability. The packaging of the water repellent shall not show evidence of deterioration when the water repellent is stored for 1 year as specified in 4.5.13. The stored water repellent shall meet all the other requirements of this specification.

3.17 Workmanship. The water repellent shall, by visual observation, be free from foreign matter (soil, dust, or grease) which impart color or otherwise reduce its effectiveness.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the

Source: https://assist.dla.mil -- Downloaded: 202610-17T07:39Z
Check the source to verify that this is the current version before use.

contract, the contractor may use his own or any other facilities suitable for the performance of inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Compliance. Determination of compliance with provisions of this specification shall include the following;

a. Qualification inspection (see 4.2.1).

b. Quality conformance inspection (see 4.2.2).

4.2.1 Qualification inspection. The qualification inspection performed by the qualification laboratory shall consist of a review for approval of the submitted manufacturer's report, and subjecting the qualification sample (4.3.1) to examination and testing for all the requirements of this specification except the control test which will only be run when necessary to assure that sample conforms to prescribed requirments.

4.2.1.1 Service tests. The service tests performed by a Naval establishment selected by the activity responsible for qualification shall consist of field evaluation of service test sample (4.3.1.1) under service condition, including conditions of rain, on aircraft selected at random to determine suitability of the product for Military use. The control formula product specified in 4.5.6.2 shall be used as a criterion of effectiveness in these tests.

4.2.1.2 Requalification. Items requiring requalification (see 3.1.1) shall be subjected to examination and tests, as determined by the responsible representative of the procuring activity, whenever the conditions defined in paragraph 3.1.1 occur.

4.2.1.3 Retention of qualification. The retention of qualification of products approved for listing in the Qualified Products List (QPL) shall be maintained by periodic verification to determine compliance of qualified water repellent with the requirements of this specification. Periodic verification may be made by certification unless otherwise specified by the activity responsible for Qualified Products List and shall be at intervals of no more than 2 years.

4.2.2 Quality conformance (lot by lot inspection). The quality conformance inspection shall include examining and testing the quality conformance samples as follows:

a. Visual examination (4.4.1).

b. Examination of filled containers (4.4.2).

Source: https://assist.dla.mil -- Downloaded: 202610-17T07:39Z
Check the source to verify that this is the current version before use.

c. Application of film (4.5.2).

d. Abrasion and staining (4.5.3).

e. Visibility (4.5.4).

f. Effect on acrylic plastics (4.5.12).

4.3 Sampling.

4.3.1 Qualification samples. The qualification sample shall consist of twelve 8 oz. containers for which qualification is desired together with instructions for use. The sample shall be accompanied by a report from the manufacturer or a commercial laboratory. The report shall show individual and average results for all requirements of this specification and shall refer specifically to the applicable paragraphs in the specification. The contractor shall furnish toxicological data required to evaluate the safety of the material for the proposed use. The samples and reports shall be forwarded to the Naval Air Development Center (Code 30222), Warminster, Pennsylvania 18974. The samples shall be plainly identified by securely attached durable tags or labels marked with the following information:

Sample for qualification inspection
WATER REPELLENT, WINDOW AND WINDSHIELD, GLASS AND PLASTIC
Name of manufacturer
Product code number
Date of manufacture
Submitted by (name) (date) for qualification inspection in accordance with the requirements of MIL-W-6882F under authorization of (reference authorizing letter) (see 6.3).

4.3.1.1 Pending completion of the storage stability tests, and after a product has met all other qualification requirements, the manufacturer shall furnish service test samples as requested and in accordance with instructions provided by the qualifying activity.

4.3.2 Quality conformance samples and acceptability criteria.

4.3.2.1 Inspection lots. An inspection lot shall consist of all water repellent made from the same batches of ingredients and offered for inspection at the same time.

4.3.2.2 For visual inspection. A random sample of water repellent shall be selected from each lot in accordance with MIL-STD-105 at Inspection Level I. The AQL = 1.0 percent defective.

4.3.2.3 For examination of filled containers. A random sample of water repellent and a sample of shipping containers fully prepared for delivery shall be selected from each lot of water repellent at Inspection Level I and Acceptable Quality Level (AQL) = 2.5 percent defective.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

4.3.2.4 For tests. A random sample of water repellent shall be selected from each lot in accordance with MIL-STD-105, Inspection Level S3. The acceptance number is zero. If any of the specimens representing a lot fails one or more of these tests, the inspection lot shall be rejected.

4.4 Examinations.

4.4.1 Visual examinations. Visual examination shall verify conformance to requirements for workmanship and any other requirements not specifically covered by tests.

4.4.2 Examination of filled containers. Each filled container and sample shipping container shall be examined for defects of construction of the container and the closure, evidence of leakage, unsatisfactory markings, and the net contents.

4.5 Test methods. Unless otherwise specified, prior to and during tests, specimens shall be subjected to a temperature in the range of 75 $\pm 5^{\circ}$F (24 $\pm 3^{\circ}$C).

4.5.1 Resistance to temperature cycling. This test will be performed before any others. Four, unopened water repellent containers shall be weighed. Each shall then be exposed to three successive cycles, each cycle consisting of exposure for 1 hour at 39°F (4°C) followed immediately by exposure for 1 hour at 120°F (49°C). The weight of the containers and condition of their contents shall be noted after each cycle.

4.5.2 Application of film. This test shall be conducted at 39 $\pm 2^{\circ}$F (4 $\pm 1^{\circ}$C) and then at 90 $\pm 2^{\circ}$F (32 $\pm$ 1°C). In each case a new and used 3-inch by 3-inch glass test panel, a new and used plastic panel conforming to MIL-P-5425, and an unopened container of water repellent shall be placed into chambers maintained at the temperature specified above for 1 hour. After the 1 hour period, the water repellent shall be applied and reapplied in accordance with the manufacturer's instructions, to one side of each test panel without removing panel or rain repellent from test chamber. After application, the plate containing the water repellent film shall be examined and compared with a freshly cleaned untreated, identical 3 by 3-inch test panel for clearness, continuity, and freedom from granular structure.

4.5.3 Abrasion and staining. A 3 by 3-inch sheet of transparent glass and 3 by 3-inch sheet of acrylic plastic conforming to MIL-P-5425 shall be cleaned with TT-N-95 rinsed with water and thoroughly dried. The water repellent shall then be applied in accordance with the manufacturer's instructions. The panels shall be observed for evidence of scratches or stains.

4.5.4 Visibility. Panels shall be prepared as in 4.5.3. The observer shall stand 24 inches away and view through a panel, objects which are 100 feet from the far side of the panel. The same observation shall be made viewing the object through an identical, freshly cleaned, untreated panel. A comparison of the two views shall be made.

Source: https://assist.dla.mil -- Downloaded: 202640-17T07:39Z
Check the source to verify that this is the current version before use.

4.5.5 Roll angle. A 3-inch by 3-inch safety glass panel and two 3-inch by 3-inch acrylic panels (one conforming to MIL-P-5425 and the other conforming to MIL-P-25690), shall be cleaned and the water repellent shall be applied in accordance with the manufacturer's instructions. The panels so prepared, shall be placed with coated side up, on a roll angle apparatus shown in Figure 1. A drop of water (approximately 0.10 ml) from a medicine dropper shall be placed on the panel. The panels shall then be tilted slowly and the angle at which the drop just begins to roll shall be recorded as the roll angle measurement.

4.5.6 Effectiveness and durability. New safety glass panels shall be cleaned with water and a suitable detergent. New acrylic plastic panels shall be cleaned with TT-N-95, rinsed with distilled water and dried. The panels shall be tested for wetting with a few drops of water. If the panels are wet by water, the panels shall be allowed to drain until dry and shall be wiped clean. If the panels are not wet by water they shall be cleaned until the water will wet them. Rain repellent shall then be applied and wiped dry. A clean 3 by 3-inch piece of safety glass shall be mounted in the plate holder of the visibility comparator. The plate holder shall be at an angle of 45 degrees from the water stream. With the water and air off, the visibility comparator shall be adjusted as follows: The "Gain" control shall be set at the maximum point. The "Zero" control shall be set at "0" thus balancing out light scattered past the stops. The maximum reading shall be set at 80 for testing. The air jet adjusted at 500 $\pm$10 miles per hour shall be turned on. The panel shall be exposed simultaneously to 500 miles per hour air velocity and 1.0 inch of rainfall per hour for a total of six hours. The reading on the chart shall be compared with the initial setting for untreated glass. The nozzle used for air and water spray in the visibility comparator is shown in Figure 2. Similar tests shall be repeated using separate panels, one conforming to MIL-P-5425 and the other conforming to MIL-P-25690. An abrupt change in the transmission curve during the test is indicative of unsatisfactory performance. Additional information pertaining to construction details of the visibility comparator may be obtained from the Director, Code 30222, Naval Air Development Center, Warminster, PA 18974.

4.5.6.1 Jet fuel and de-icing fluid resistance. Sets of panels having the water repellent applied to the surface shall be run as described in 4.5.6 after having been wiped with a cloth dampened with (1) JP-4 fuel conforming to MIL-T-5624 and (2) with a cloth dampened with isopropyl alcohol. The panels shall be wiped with a clean dry cloth following the application of each liquid.

The percent decrease in effectiveness and durability as measured with the visibility comparator shall be determined by:

$$\text{Decrease} = \frac{R_1 - R_2}{R_1} \times 100$$

R_1 = Reading on chart of panel that has undergone test in 4.5.6
R_2 = Reading on chart of panel that has undergone test in 4.5.6.1

Source: https://assist.dla.mil -- Downloaded: 2026-04-17T07:39Z
Check the source to verify that this is the current version before use.

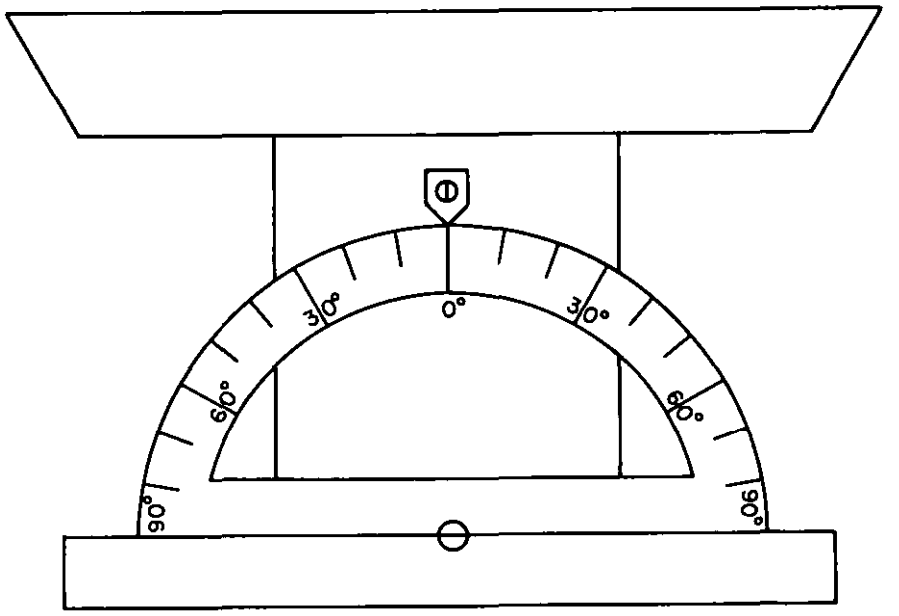


FIGURE 1. Roll angle measurement apparatus.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

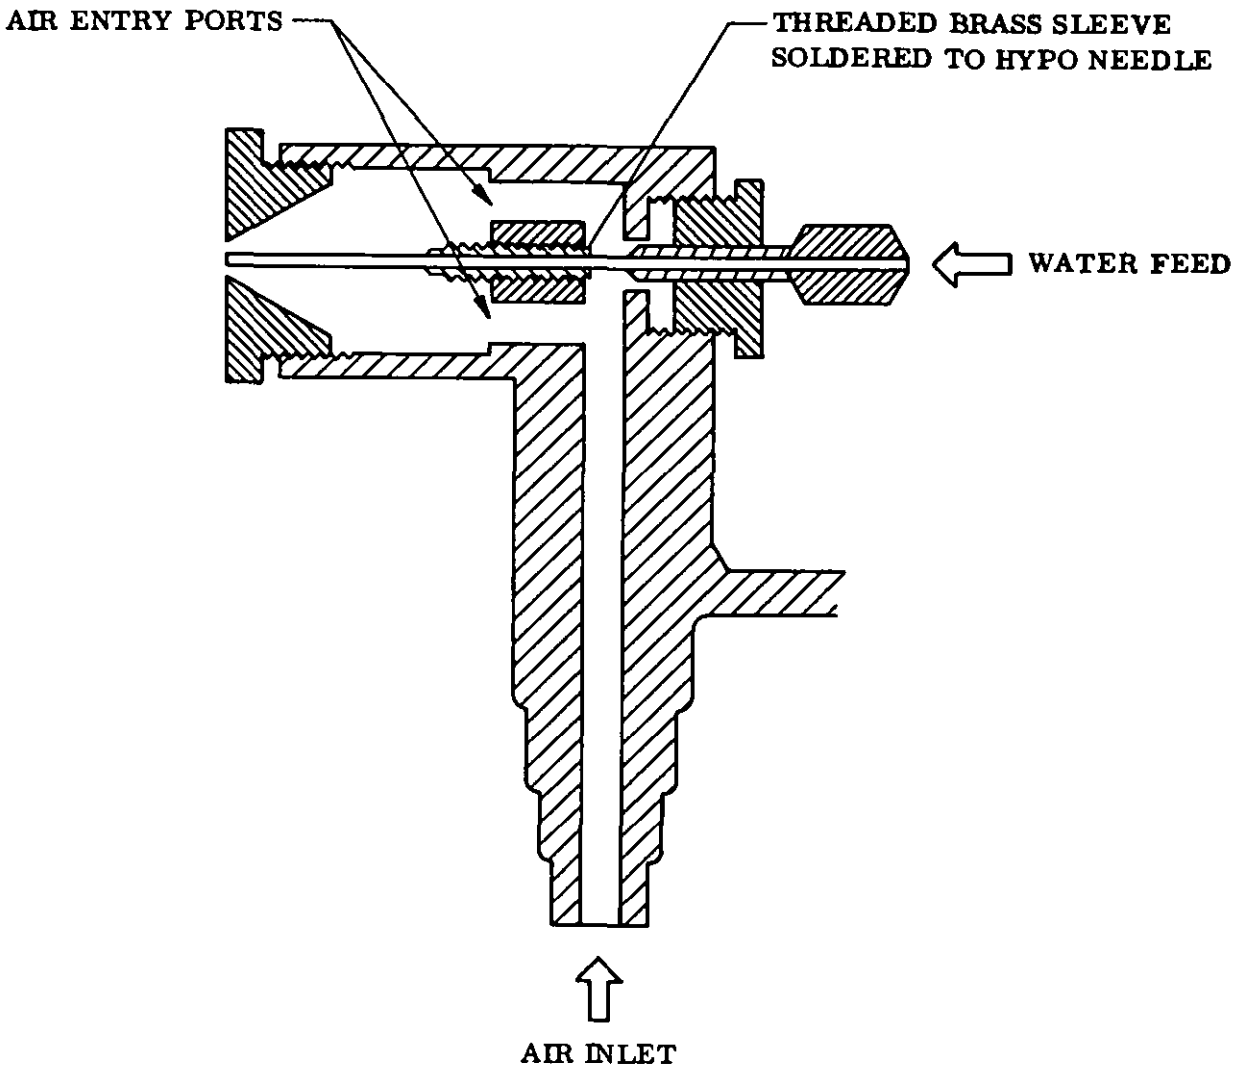


FIGURE 2. Air-Water spray nozzle for visibility comparator.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

4.5.6.2 Control test. Performance results of the water repellent shall be compared with those obtained using the film forming control material containing 19.95 percent (by volume) dimethyldiethoxysilane and 0.05 percent (by volume) of sulfuric acid (96 percent) and 80 percent (by volume) isopropyl alcohol. A previously unused glass panel shall be cleaned thoroughly using TT-N-95. A small amount of fluid shall be applied to a folded cloth conforming to CCC-C-458, and the cloth shall be rubbed over the safety glass surface. The panel shall be polished with a clean cloth rubbing the repellent over the entire surface. Any residual greasiness shall be removed with a clean cloth.

4.5.7 Light transmission. The water repellent shall be applied to safety glass, to a panel conforming to MIL-P-5425, and to a panel conforming to MIL-P-25690, in accordance with manufacturer's instructions. The transmission of light through the panel before and after application shall be determined using a suitable instrument that electronically measures light intensity.

4.5.8 Refractive index. The water repellent shall be applied to safety glass, to a panel conforming to MIL-P-5425, and to a panel conforming to MIL-P-25690, in accordance with the manufacturer's instructions. The refractive index of the panel before and after the application of the water repellent film shall be determined with a suitable refractometer.

4.5.9 Low temperature visibility. A safety glass panel to which water repellent has been applied, and a panel conforming to MIL-P-5425 to which rain repellent has similarly been applied in accordance with 4.5.3, shall be exposed to a temperature of -65°F (-54°C) for 1 hour. At the end of 1 hour and while the panel is still at -65°F (-54°C) the visibility shall be checked. After the panel returns to room temperature, it shall be checked for any decrease in visibility.

4.5.10 High temperature visibility. A safety glass panel to which water repellent has been applied in accordance with 4.5.3 shall be exposed to a temperature of 200°F (93°C) for 1 hour. At the end of 1 hour and while still at 200°F (93°C) the panel shall be checked for visibility. After the panel returns to room temperature, observations shall be made for any decrease in visibility.

4.5.11 Compatibility. One half of a 2 by 6-inch alclad aluminum panel conforming to QQ-A-250/5 shall be coated with an epoxy coating conforming to MIL-C-22750. Similar panels shall be coated with acrylic lacquer conforming to MIL-L-81352, and a polyurethane coating conforming to MIL-C-81773. The uncoated as well as coated portion of the painted panels shall be wiped with

Source: https://assist.dla.mil Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

TT-N-95, followed by immersion in the water repellent. After the panels have been allowed to remain exposed for 168 hours, the panels shall be examined for deleterious effects such as: corrosion of the metal, and softening or discoloration of the coatings. A representative sampling of other standard ferrous and non-ferrous alloys shall be tested in a similar manner.

4.5.12 Effect on acrylic plastics.

4.5.12.1 Apparatus. Three 0.25 by 1 by 7-inch test panels shall be fabricated of acrylic base plastic sheet conforming to MIL-P-5425. A cantilever test rack, as shown in Figure 3, shall be constructed for use in this procedure.

4.5.12.2 Procedure. Three plastic test panels shall be annealed by suspending in an oven maintained at 194° ±4°F (90° ±2°C) for 2 hours. At the end of the annealing period, the temperature of the test panels shall be reduced to room temperature at the rate of 49° ±4°F (9.4 ±2°C) per hour maximum. The annealed test panels shall be conditioned at room temperature for at least 7 days before use. Each of three test panels shall be set up as a cantilever beam under load as shown in Figure 3. The panels shall then be loaded by means of weights or lead shot bags to produce a stress of 2000 pounds per square inch. The load necessary to produce this stress may be determined by use of the following formula:

$$P = \frac{Sbd^2}{6L}$$

where:

S = 2000 = Stress in pounds per square inch

P = Load in pounds


L = Distance in inches from fulcrum to point at which load is applied

b = Width of plastic sheet 1/

d = Thickness of plastic sheet 1/

1/ Measured by means of micrometer to within 0.001 inch.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

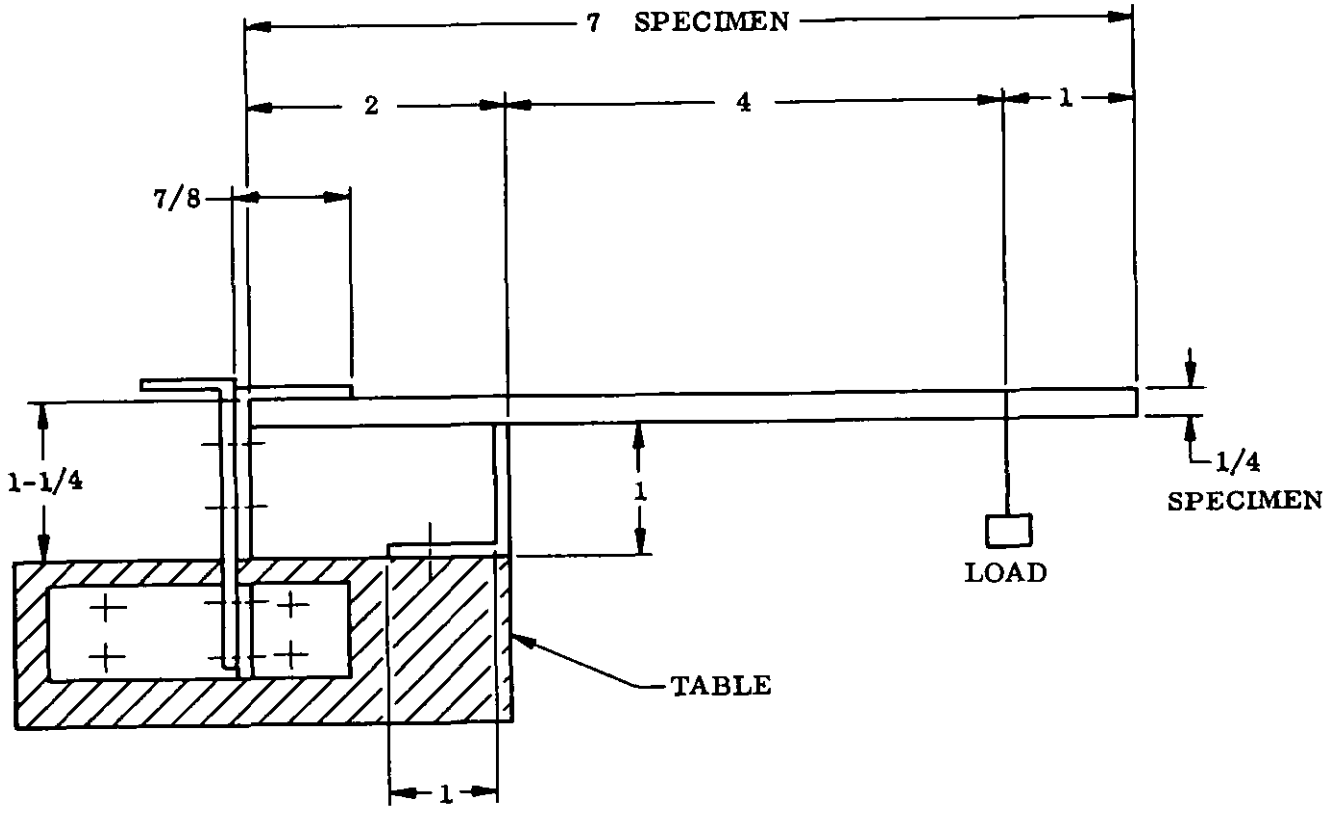

NOTES: 1/8 ANGLE IRON USED AT FULCRUM AND END OF SPECIMEN
ALL DIMENSIONS IN INCHES

FIGURE 3. Test set-up for effect on acrylic plastics.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

After 10 minutes the test panels shall be examined to insure that no crazing has occurred prior to Rain Repellent compound application. While test panels are still under stress, a 1 by 2-inch piece of flannel cloth shall be placed on the top surface of the panel with its long axis parallel to that of the panel and centered over the fulcrum. The flannel shall be wet (using a medicine dropper) with 2 ml of the Rain Repellent compound. The flannel shall be kept wet by applying an additional milliliter of Rain Repellent compound as necessary for 4 hours. At the end of 6 hours, while the panels are still under stress, the flannel cloth shall be removed and the panel inspected for crazing by passing a light under the loaded end of the panel and observing panel at the fulcrum from above. The appearance of bright refractory lines parallel to the fulcrum is evidence of crazing. Lines less than 1/8 of an inch in length touching the sheared edges of the panel shall be disregarded.

4.5.13 Storage stability. The rain repellent shall be stored for 1 year at 100 $\pm 5^{\circ}$F (38 $\pm 3^{\circ}$C). If the container shows no evidence of deterioration, it shall be tested for conformity to the other requirements of this specification.

5. PACKAGING

5.1 Packaging. Packaging shall be Level A or C as specified (see 6.2).

5.1.1 Level A .

5.1.2 Unit packaging. The water repellent shall be packaged in 8 oz. flexible plastic bottles conforming to PPP-C-186, Group A, Class 2, Style 1, Closure J (see 6.2).

5.1.3 Level C. The water repellent shall be packaged in a manner that will afford adequate protection against chemical corrosion/deterioration and physical damage during shipment from the supply source to the first receiving activity. The supplier's commercial practice may be utilized when it conforms to the requirements of this level.

5.2 Packing. Packing shall be Levels A, or C as specified (see 6.2).

5.2.1 Level A. Unless otherwise specified, the water repellent shall be packed twelve unit containers to a shipping container conforming to Type CF or SF, Class weather resistant, Grade W5C of PPP-B-636.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

5.2.2 Level C. The water repellent shall be packed to insure safe transportation at the lowest rates to the point of delivery and shall meet as a minimum, the requirements of the rules and regulations applicable to the mode of transportation selected.

5.3 Marking. In addition to any special marking required by the contract (see 6.2), each unit package, intermediate and exterior container shall be marked in accordance with MIL-STD-129 and shall include the following:

Flash Point (In accordance with ICC Regulations)

5.3.1 Additional markings.

5.3.1.1 Caution markings. Individual unit containers shall be marked as follows, along with any other applicable markings:

"CAUTION - FLAMMABLE MIXTURE
DO NOT USE NEAR FIRE OR FLAME.
USE IN VENTILATED AREA. IF SPLASHED
INTO EYES, FLUSH WITH WATER."

5.3.1.2 Instructions for use. In addition to the markings specified in 5.3 and 5.3.1.1, each unit container shall contain the following instructions for use:

"1. Preclean surface and dry completely.

2. Apply water repellent to a cloth or tissue and thoroughly wipe surface using an overlapping motion.

3. Allow any solvent to evaporate for one minute.

4. Using soft dry cloth or tissue, wipe treated surface until all excess repellent or smears have disappeared."

6. NOTES

6.1 Intended use. The water repellent is intended for ground application of an antiwetting film to glass or acrylic plastic windows and glass or acrylic plastic windshields, to assure good visibility under rain conditions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

6.1.1 Moist surfaces. The material producing the final film should not be applied on excessively moist surfaces because excessive moisture will cause hydrolysis and condensation of the compound before actual contact with surface is made.

6.1.2 Cleaning. Prior to application of the water repellent to a previously unused panel, the glass or acrylic plastic should be cleaned with TT-N-95. Partially deteriorated water repellent films may be removed using P-P-560.

6.2 Ordering data. Procurement documents should specify the following:

a. Title and number of this specification.

b. Total quantity desired.

c. Selection of applicable levels of packaging and packing (see 5.1 and 5.2).

d. Description and size of container, if other than as specified in PPP-C-186.

e. Special markings other than specified (see 5.3).

6.3 Qualification. With respect to products requiring qualification, awards will be made only for such products as have, prior to the time set for opening of bids, qualified for inclusion in the applicable Qualified Products List whether or not such products have actually been so listed by that date. The attention of contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. The activity responsible for the Qualified Products List is the Naval Air Systems Command, Department of the Navy; however, information pertaining to qualification of products may be obtained from the Director, Code 30222, Naval Air Development Center, Warminster, Pennsylvania 18974.

6.4 Any questions raised regarding toxicity should be referred by the procuring agency to the departmental medical authority.

6.5 Supersession data. This specification, MIL-W-6882F, supersedes MIL-W-006882E (AS) dated 19 June 1973 and MIL-W-6882D dated 3 June 1971.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

Water repellent furnished under MIL-W-006882E(AS) is interchangeable with the water repellent furnished under MIL-W-6882F. Type I and Type II kits furnished under MIL-W-6882D are no longer required by the military and their requirements have been omitted in MIL-W-6882F.

6.6 Changes from previous issue. Asterisks are not used in this revision to identify changes with respect to the previous issue, due to the extensiveness of the changes.

Custodians:
Army - EA
Navy - AS
Air Force - 11

Review activities:
Army - EA, AV
Air Force - 82

User activities:
Navy - MC, CG

Preparing activity:
Navy - AS
(Project No. 6850-0596)

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T07:39Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

OMB Approval
No. 22-R255

INSTRUCTIONS: The purpose of this form is to solicit beneficial comments which will help achieve procurement of suitable products at reasonable cost and minimum delay, or will otherwise enhance use of the document. DoD contractors, government activities, or manufacturers/vendors who are prospective suppliers of the product are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements. Attach any pertinent data which may be of use in improving this document. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity.

DOCUMENT IDENTIFIER AND TITLE

MIL-W-6882F - WATER REPELLENT, WINDOW AND WINDSHIELD, GLASS AND PLASTIC

NAME OF ORGANIZATION AND ADDRESS

CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY DOCUMENT REQUIREMENT CONSIDERED TOO RIGID

3. IS THE DOCUMENT RESTRICTIVE?

☐ YES ☐ NO (If "Yes", in what way?)

4. REMARKS

SUBMITTED BY (Printed or typed name and address - Optional)

TELEPHONE NO.

DATE

DD FORM 1 JAN 72 1426 REPLACES EDITION OF 1 JAN 66 WHICH MAY BE USED

Source: https://assist.dla.mil -- Downloaded: 202610-17T07:39Z
Check the source to verify that this is the current version before use.