MIL-B-9225 (USAF)
2 March 1954
Superseding
No. 32587-A
12 April 1949

MILITARY SPECIFICATION

BATTERY, STORAGE, AIRCRAFT, HIGH RATE DISCHARGE, 12 VOLTS, 540 AMPERES FOR 3.75 MINUTES, TYPE K-1

1. SCOPE

1.1 This specification covers one type of 12V, lead acid, high rate discharge, quick disconnect battery, designated Type K-1.

2. APPLICABLE SPECIFICATIONS, STANDARDS, DRAWINGS, AND PUBLICATIONS

2.1 The following specifications, standards, drawings, and publication, of the issue in effect on the date of invitation for bids, form a part of this specification to the extent specified herein:

SPECIFICATIONS

FEDERAL

NN-B-591	Boxes, Fiberboard, Wood-Cleated (For Domestic Shipment)
NN-B-601	Boxes, Wood-Cleated-Plywood, For Domestic Shipment
NN-B-621	Boxes, Wood, Nailed and Lock-Corner
NN-B-631	Boxes; Wood, Wirebound, For Domestic Shipment
QQ-C-502	Copper Bars, Rods, and Shapes
QQ-C-576	Copper Plates, Sawed Bars, Sheets, and Strips
UU-C-843	Cushioning Materials, Cellulosic
LLL-B-631	Boxes; Fiber Corrugated (For Domestic Shipment)
LLL-B-636	Boxes; Fiber, Solid, (For Domestic Shipment)
LLL-F-291	Fiberboard; Corrugated, Single Face, (Flexible)

MILITARY

JAN-P-105	Packaging and Packing for Overseas Shipment, Boxes, Wood, Cleated, Plywood
JAN-P-106	Boxes; Wood, Nailed, (Overseas Type)
MIL-B-107	Boxes; Wood, Wirebound, (Military Type)
JAN-P-108	Boxes, Fiberboard, Corrugated and Solid (Military Type)
MIL-P-3827	Plastic, Polystyrene, Modified, Molding Material and Molded Parts
MIL-D-5028	Drawings and Data Lists; Preparation Of (For Engines, Accessories and Other Auxiliary Equipment)
MIL-E-5272	Environmental Testing, Aeronautical and Associated Equipment, General Specification For
MIL-S-7742	Screw Threads; Standard, Aeronautical

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

STANDARDS

MILITARY

MIL-STD-129	Marking of Shipments
MIL-STD-130	Identification Marking of U. S. Military Property

DRAWINGS

U. S. AIR FORCE

47A6209	Terminal - Battery
53A7110	Terminal, Lug, Battery

PUBLICATION

AIR FORCE-NAVY AERONAUTICAL BULLETIN

143	Specifications and Standards; Use of

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific procurement functions should be obtained from the procuring agency or as directed by the contracting officer.)

3. REQUIREMENTS

3.1 Material:

3.1.1 Specifications and standards.- Specifications and standards for all materials, parts, and Government certification and approval of processes and equipment, which are not specifically designated herein and which are necessary for the execution of this specification, shall be selected in accordance with Bulletin No. 143, except as provided in the following paragraph:

3.1.1.1 Standard parts.- AN or MIL standard parts shall be used wherever they are suitable for the purpose, and shall be identified by their part numbers. Commercial utility parts such as screws, bolts, nuts, cotter pins, et cetera, may be used, provided they have suitable properties and are replaceable by the AN or MIL standard parts without alteration, and provided the corresponding AN or MIL part numbers are referenced on the drawings and in the parts lists. In applications for which no suitable corresponding AN or MIL part is in effect on date of invitation for bids, commercial parts may be used provided they conform to the requirements of this specification.

3.1.2 Rubber and rubber compounds.- Rubber and rubber compounds shall be free from any and all materials soluble in sulphuric acid solution of 1.3 specific gravity of 71°C.

3.1.3 Battery case.- The material used in the fabrication of the battery case shall be modified polystyrene and shall conform to the requirements of Specification MIL-P-3827, Type II. If materials other than that specified above are used, they shall be approved by the procuring agency.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

3.1.4 Protective treatment.- When materials are used in the construction of the battery that are subject to deterioration when exposed to climatic and environmental conditions likely to occur during service usage, they shall be protected against such deterioration in a manner that will in no way prevent compliance with the performance requirements of this specification. The use of any protective coating that will crack, chip, or scale with age or extremes of climatic and environmental conditions shall be avoided.

3.2 Design.- The battery shall consist of six cells contained in one case. Cells shall contain the necessary plates, terminal posts, and separators, and shall be secured so that any motion of the plates will not cause structural failure in the plates or separators. The specific gravity of battery electrolyte when fully charged shall be between 1275 and 1300 at 27°C. The entire battery shall be designed with a non-spill feature, to provide for maximum capacity, and for a minimum weight consistent with the requirements of this specification.

3.3 Construction:

3.3.1 Plates.- The grids shall be free from open sections or such evidence of cold-pouring as cracks, blow holes, or other imperfections which may affect their structural strength. Breaks in those parts of the grids which are used to merely retain the active material shall be permissible only when the situation of the breaks does not modify the strength of the grid or permit the active material to become loosened or separated from the plate. A plate shall not contain more than two adjacent broken horizontal bars nor more than three broken vertical or horizontal bars in a grid.

3.3.2 Active material.- Active material shall be incorporated in grids in accordance with high grade commercial practice. Grids incorporating active material reclaimed or reworked from other batteries shall not be acceptable.

3.3.3 Separators.- Separators shall be of an approved type free from flaws, cracks, and other imperfections likely to permit mossing or short circuits. They shall be made of any material suitable for the purpose which has been approved by the procuring agency.

3.3.4 Baffles.- A perforated or slotted baffle of hard rubber, or any acceptable substitute, shall be provided in each cell to prevent any injury to the separators caused by instruments inserted through the filler opening in the cell cover. Each baffle shall be at least 1/32 inch thick and shall be securely held in place without resting or bearing on the plates.

3.3.5 Cell connectors.- The cell connectors shall be constructed of copper, in accordance with Specification QQ-C-502 or QQ-C-576, or sufficient cross section to withstand without failure or excessive heating any discharge rate which the battery will produce. Cell connector screws shall be tight and locked by means approved by the procuring agency.

3.3.6 Cell terminal posts.- Cell terminal posts shall be constructed of lead, antimony alloy, or antimony-lead alloy with copper or brass inserts. They shall adequately conduct any current which the battery is capable of delivering.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

3.3.7 Vents.- Each cell shall have a vent tube connected to a common manifold on the side of the battery case opposite to that which contains the quick disconnect terminals. The vents shall prevent leakage of electrolyte but permit free venting or escape of gas when the battery is in any position from 0 to 180 degrees and in any direction from normal upright position. The venting manifold openings shall be 1/2-13NC 2B threads. One end of the manifold shall be fitted with a removable threaded plug which shall be flush with the battery surface when inserted. The other end shall be fitted with a removable vent nozzle in accordance with Figure 1.

3.3.8 Battery terminals.- Battery terminals shall be as shown on Figure 2.

3.3.9 Unless otherwise specified, the batteries shall be furnished without electrolyte.

3.4 Performance:

3.4.1 The discharge capacities and cutoff voltages of the battery at the various required discharge rates are shown in Table I. Conformance of the battery to these requirements shall be determined during the initial discharge characteristic cycles specified in 4.2.2. The battery shall not develop less than 100 percent rated capacity at each of the specified rates during the initial discharge characteristic cycles.

TABLE I


Discharge Time	Minimum Cutoff Voltage (27°C)	Rate of Discharge Amp	Rated Capacity Amp Hour (Nominal)
5 Hours	10.50	15	75
5 Seconds	9.90	540	—
3.75 Minutes	7.80	540	34
5 seconds	7.80	1125	—
1.3 Minutes	5.00	1125	24

3.4.2 Retention of charge.- The battery shall be supplied with charged plates and dry separators which will permit storage for a period of not less than one year. At the end of this period, the battery shall be filled with electrolyte as recommended by the manufacturer and shall be capable of meeting the performance requirements of 3.4.1.

3.4.3 Life.- The battery shall have a minimum cycle life of 75 charge and discharge cycles. The test shall be conducted as specified in 4.4.2 in an ambient temperature of 20 to 35°C with all four sides of the battery exposed to free air circulation.

3.5 Dimensions.- The battery shall conform to the dimensions shown on Figure 2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

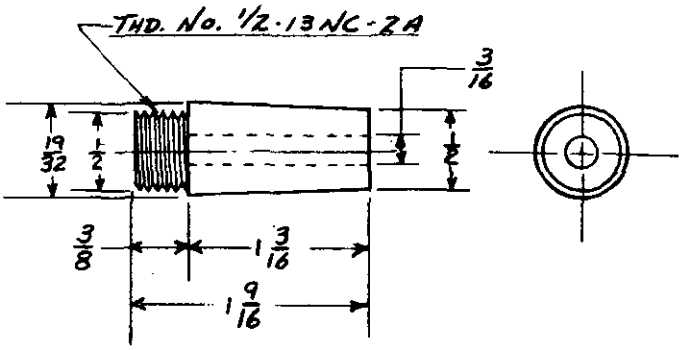

NOZZLE FOR VENT DUCT

DIMENSIONS IN INCHES.
UNLESS OTHERWISE SPECIFIED,
TOLERANCES:
FRACTIONS ± 1/64

FIGURE 1

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

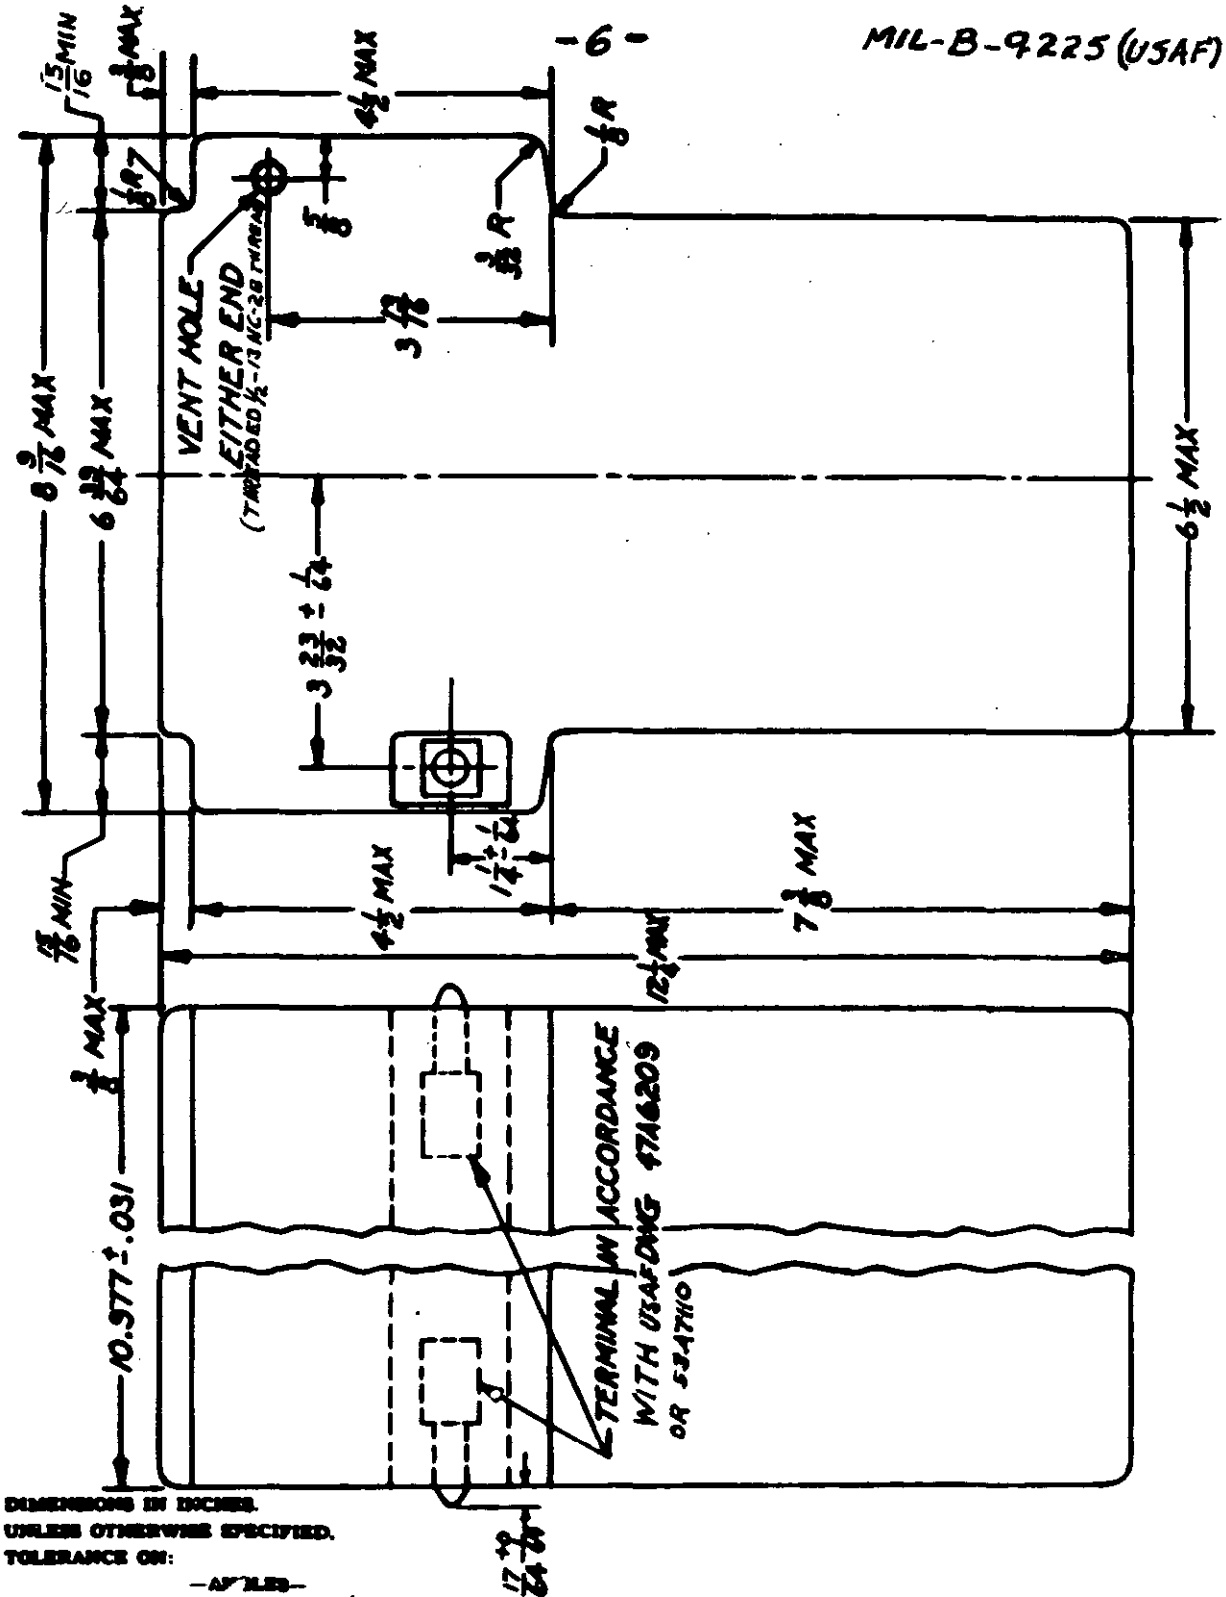


FIGURE 2

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

3.6 Battery case.- The battery case shall not crack, craze, sag, blister, or show any appreciable change in hardness under the following conditions or natural combination of conditions:

3.6.1 Temperature.- Temperature range of -54° to +71°C with case exposed to 1.300 specific gravity sulphuric acid.

3.6.2 Altitude.- Barometric pressure ranging from 30 to 3.5 inches Hg (approximating an altitude range of sea level to 50,000 feet).

3.6.3 Fungus.- When exposed to fungus growth as encountered in tropical climates.

3.6.4 Sunshine or rain.- Under conditions of natural summer sunshine or rain.

3.6.5 Vibration.- Under the vibration, mechanical shocks, and stresses incident to continuous use in aircraft.

3.7 Gas-tightness of cells.- The cells shall be capable of withstanding an internal air pressure of 5 psi at 27°C for a period of not less than 5 minutes without leakage.

3.8 Weight.- The weight of the battery filled with electrolyte to the normal height shall not exceed 74 pounds.

3.9 Screw threads.- Screw threads shall be in accordance with Specification MIL-S-7742.

3.10 Interchangeability.- All parts having the same manufacturer's part number shall be directly and completely interchangeable with each other with respect to installation and performance. Changes in manufacturer's part numbers shall be governed by the drawing number requirements of Specification MIL-D-5028.

3.11 Identification of product.- Equipment, assemblies, and parts shall be marked for identification in accordance with Standard MIL-STD-130, except that the "Serial No." shall be omitted and the following information shall be included:

Date of Manufacture (month and year) *

*Applicable data shall be entered by the contractor.

3.11.1 Container marking.- One side of the container shall be marked with "US" in letters approximately 1 inch high.

3.11.2 Terminal marking.- The polarity of the terminal posts shall be marked with "+" in red, or other color acceptable to the procuring agency, for positive and "-" for negative.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

3.12 Workmanship.- The battery, including all parts, shall be fabricated and finished in a thoroughly workmanlike manner. Particular attention shall be given to freedom from blemishes, defects, burrs and sharp edges; accuracy of dimensions and marking of parts; et cetera.

4. SAMPLING, INSPECTION, AND TEST PROCEDURES

4.1 Classification of tests.- The inspection and testing of batteries shall be classified as follows:

4.1.1 Qualification tests.- Qualification tests are those tests accomplished on samples submitted for qualification as a satisfactory product.

4.1.2 Inspection tests.- Inspection tests are those tests accomplished on batteries submitted for acceptance under contract.

4.2 Test conditions:

4.2.1 Capacity.- Capacity test shall be run at an initial electrolyte temperature of 27 ± 1°C.

4.2.2 Cycling.- Cycling shall consist of a series of cycles of charge and discharge, as specified below, all of which shall be counted as life cycles. The initial discharge characteristic cycles shall be cycles 1 through 4 inclusive and they shall serve to demonstrate conformance of the battery to the capacity requirements specified in 3.4.1. Charging shall be done by constant current method. Initial charge shall be in accordance with the manufacturer's instructions.

Cycles	Rate - Amp	Duration
1st (discharge)	15	5 hours
(recharge)	15	4 hours
(recharge)	5	(see Note 1)
2nd (discharge)	1125	1.3 minutes
(recharge)	9.5	2 hours
(recharge)	9.5	(see Note 1)
2(a) (discharge)	1125	1.3 minutes
(recharge)	9.5	2 hours
(recharge)	9.5	(see Note 1)
2(b) (discharge)	15	5 hours
(recharge)	15	4 hours
(recharge)	5	(see Note 1)
2(c) (discharge)	1125	1.3 minutes
(recharge)	9.5	2 hours
(recharge)	5.5	(see Note 1)
2(d) (discharge)	1125	1.3 minutes
(recharge)	9.5	2 hours
(recharge)	5.5	(see Note 1)

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

Cycles	Rate - Amp	Duration
3rd (discharge)	540	3.75 minutes
(recharge)	13.5	2 hours
(recharge)	5.5	(see Note 1)
4th (discharge)	26	2 hours
(recharge)	12	3.25 hours
(recharge)	6	(see Note 1)
Life cycling (discharge)	26	2 hours
(recharge)	12	3.25 hours
(recharge)	6	3.75 hours
75th cycle (discharge)	15	4 hours

End of life cycle test

NOTE: 1. The recharge period shall be of sufficient duration to recharge the battery with 120 percent of the total ampere hours removed on the previous discharge.

2. Cycles 1 through 4 (including 2(a) through 2(d) are referred to in this specification as the initial discharge characteristic cycles. These cycles shall demonstrate conformance of the battery to the capacity requirements of Table I.

3. If the battery fails to meet the capacity requirements of Cycle 2, up to four repeat tests, cycles 2(a), 2(b), 2(c), and 2(d), run in the specified order are permitted to demonstrate conformance to the capacity requirements of Table I. If any of these optional cycles are run, they shall be counted among the total number of life cycles and the succeeding cycles shall be renumbered accordingly.

4. Upon completion of the initial discharge characteristic cycles, the fully charged battery shall be placed on life cycling with the discharges and recharges indicated in the above schedule. The cycles shall be repeated through the 74th cycle. The 75th cycle, run in accordance with the above schedule shall then be run to determine compliance with the requirements of 4.4.3.5. Prior to the 75th cycle, and all other 5-hour discharge periods required during the life cycle test, recharging not to exceed 120 percent of the total ampere hours removed from the battery on the previous discharge shall be permitted. Throughout the life cycling 5 cycles, in addition to the 75th cycles, and similar to the 75th cycle shall be conducted. These 5-hour discharges shall be as evenly spaced throughout the life cycle schedule as is consistent with commercial testing practice.

4.3 Qualification tests:

4.3.1 Prior qualification.- Unless otherwise specified by the procuring agency, batteries which have not previously passed a qualification test, or which have passed the qualification test and have been modified in any manner shall satisfactorily pass a qualification test prior to the acceptance of any batteries.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

4.3.2 Qualification test samples.- Qualification test samples shall consist of two batteries. Samples shall be appropriately identified with the manufacturer's own part number and any additional identification required by the authorizing letter.

4.3.3 The qualification test shall consist of the inspection tests and the following tests:

4.3.3.1 Environmental.- The tests below shall be conducted in accordance with the specified procedures of Specification MIL-E-5272. Upon completion of the tests and unless otherwise specified, no sagging, cracking, crazing, or blistering of the battery case shall occur.

4.3.3.1.1 High temperature.- Procedure I.

4.3.3.1.2 Low temperature.- Procedure II.

4.3.3.1.3 High altitude.- Procedure II. A fully charged battery shall be used for this test. The battery shall be subjected to a charging current of 3 amp during the entire testing period and it shall remain at the reduced pressure specified for a period of 1 hour. The pressure transition periods (i. e. atmospheric to 50,000 feet and vice versa) shall be accomplished in not more than 10 minutes. No visible evidence of leakage of electrolyte from the battery case or battery venting system shall occur.

4.3.3.1.4 Fungus resistance.- Procedure I, except that distilled or demineralized water having a pH value between 5.8 and 7.4 at 25°C shall be used. No deterioration of the battery case or terminals shall occur.

4.3.3.1.5 Sunshine.- Procedure I for a period of 100 hours.

4.3.3.1.6 Rain.- Procedure I.

4.4 Inspection tests:

4.4.1 Individual tests.- Each battery shall be subjected to the following test:

4.4.1.1 Examination of product.- Each battery shall be inspected to determine compliance with the requirements specified herein with respect to dimensions, materials, workmanship, and marking.

4.4.2 Sampling tests.- One battery shall be selected at random from each lot or fraction thereof on the order and subjected to the following tests:

4.4.2.1 Lot.- A lot shall consist of five hundred batteries or fraction thereof manufactured under essentially the same conditions and submitted for inspection at substantially the same time.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

4.4.2.2 When sampling tests are specified on a number of items that are selected as representative of the lot, and one or more of this number fails to meet the specified tests, acceptance of all items in the lot will be withheld until the extent and cause of failure is determined. For operational reasons, individual tests may be continued pending investigation of a sampling test failure, but final acceptance of the entire lot is contingent upon the inspector's decision regarding the over-all conformance of the lot to specification requirements. When corrective action has been accomplished, all necessary tests shall be repeated. If investigation indicates that the defects may exist on lots previously accepted, full particulars concerning the defects found, including recommendations for correction, shall be furnished to the contracting officer.

4.4.2.3 Cell terminal posts, cell connectors, and terminal connectors.- Fully charged batteries shall be heated and then maintained for a period of at least 2 hours at 38°C prior to being discharged at 1500 amps for 30 seconds. The discharge may be maintained to any terminal voltage necessary for the successful completion of the discharge. For convenience in testing, the rate may be maintained by a booster battery or motor generator set. The cell terminal post, inter-cell connectors, and terminal connectors under test shall withstand this discharge without showing evidence of failure. Fusing of any part, detachment of any part or parts, and any sign of physical change shall provide cause for rejection.

4.4.2.4 Capacity.- The battery shall be discharged from the fully charged condition with a maximum specific gravity of electrolyte in any cell not in excess of 1.300 corrected for 27°C. The ratings shall be as specified in Table I. Failure to meet the cut-off voltage, as specified, shall be cause for rejection.

4.4.2.5 Life.- The battery shall be subjected to not less than 75 cycles of charge and discharge as outlined in 4.2.2. On the 75th cycle the battery shall be capable of delivering not less than 4.0 hours to a cutoff voltage of 10.5V when discharged at 15 amps.

4.4.3 Special tests.- One battery shall be selected from every sixth lot and subjected to the following test:

4.4.3.1 Vibration and gas-tightness of cells.- The battery shall be placed in an oven at 68°C and maintained at this temperature for at least 6 hours. The battery shall be allowed to cool to 27°C and the specified internal air pressure shall be applied to cells of the battery through the vent manifold and maintained constant for the specified length of time to determine compliance with the requirements specified in 3.7. Upon the successful completion of this part of the test, the battery shall be cooled to -34°C with all cells filled with electrolyte of the required specific gravity. The battery shall be vibrated at 1975 to 2000 cps with a displacement of 0.125 to 0.135 inch (total excusion) for 2 hours. The temperature of the battery at start shall be -34°C and allowed to warm during the vibration period in ambient temperature of 21 to 32°C. At the end of this time, visual inspection shall show no signs of compound fracture nor shall a repetition of the air pressure test at 27°C reveal any leak from the cell terminal post seal or any other part of the cell.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

4.5 All parts, specimens, or assemblies destroyed in making tests required by this specification and drawings, to determine compliance with the specification and drawings, shall be in addition to the quantity specified in the contract or purchase order and shall be furnished without increasing the cost of the contract or order.

5. PREPARATION FOR DELIVERY

5.1 General.- The requirements specified herein apply only to direct purchases by or direct shipment to the Government.

5.2 Filling caps.- All filling caps shall be tightened.

5.2.1 Cleaning.- The exterior of the battery shall be free from dirt and grease when packed for shipment.

5.3 Unit packaging.- Each battery shall be unit packaged in a container conforming to Specification LLL-B-631, LLL-B-636, or JAN-P-108.

5.4 Exterior containers:

5.4.1 Cushioning.- All exterior containers shall have a sufficient amount of cushioning material conforming to Specification UU-C-843, LLL-F-291, or JAN-P-108 to protect the batteries against the effects of shock and impact caused by rough handling.

5.4.2 Domestic.- For domestic shipment, batteries packaged as specified in 5.3 shall be packed in containers conforming to Specification NN-B-591, NN-B-601, NN-B-621, or NN-B-631.

5.4.3 Export.- For export shipment, batteries packaged as specified in 5.3 shall be packed in containers conforming to Specification JAN-P-105, JAN-P-106, or MIL-B-107. Plywood when used shall be Type II, Class 2.

5.5 Test.- One completed package prepared for shipment shall be dropped corner wise from a height of 30 inches onto a solid steel or concrete surface in such a manner that the corner of the container absorbs the full force of the fall. This test shall be repeated until each of the eight corners of the container has received a fall. (The height of 30 inches refers to the distance from the steel or concrete surface to the nearest corner of the container when suspended prior to the fall.) No damage to the battery shall occur as a result of this test.

5.6 Marking of shipments.- Interior packages and exterior shipping containers shall be marked in accordance with Standard MIL-STD-129. The nomenclature shall be as follows:

Battery, Storage, Aircraft, High Rate Discharge,
12 Volts, 540 Amperes for 3.75 Minutes
Type K-1
Specification MIL-B-9225
Mfr's. Part No. *

*Applicable data shall be entered by the contractor.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

6. NOTES

6.1 Use.- The Type K-1 battery covered by this specification is intended for use in aircraft equipped with the J-33 (I-40) and the J-35 (TG-180) engines.

6.2 Definitions:

6.2.1 Battery capacity.- Battery capacity is the discharge measured quantitatively in ampere hours at the specified discharge rate.

6.3 Qualification tests.- In the procurement of products requiring qualification, the right is reserved to reject bids on products that have not been subjected to the required tests and found satisfactory for inclusion on a Qualified Products List. The attention of suppliers is called to this requirement, and manufacturers are urged to communicate with the Wright Air Development Center and arrange to have the products that they propose to offer to the Air Force tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from the Commander, Wright Air Development Center, Wright-Patterson Air Force Base, Ohio, Attention: WCLE.

NOTICE: When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

FOLD

DEPARTMENT OF THE NAVY

POSTAGE AND FEES PAID
NAVY DEPARTMENT

OFFICIAL BUSINESS

COMMANDER
CATALOGING OFFICE
ATTN: AFLC (SGEBA)
WRIGHT-PATTERSON AFB, OHIO 45433

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.

SPECIFICATION ANALYSIS SHEET

Form Approved
Budget Bureau No. 119-R004

INSTRUCTIONS

This sheet is to be filled out by personnel either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity *(as indicated on reverse hereof)*.

SPECIFICATION

ORGANIZATION *(Of submitter)* | CITY AND STATE

CONTRACT NO. | QUANTITY OF ITEMS PROCURED | DOLLAR AMOUNT
$

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES.

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?

☐ YES ☐ NO IF "YES", IN WHAT WAY?

4. REMARKS *(Attach any pertinent data which may be of use in improving this specification. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity)*

SUBMITTED BY *(Printed or typed name and activity)* | DATE

DD FORM 1 APR 63 1426 REPLACES NAVSHIPS FORM 4863, WHICH IS OBSOLETE PLATE NO. 15419

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T12:05Z
Check the source to verify that this is the current version before use.