
MIL-W-16878/24(NAVY)
10 August 1981
SUPERSEDING
MIL-W-16878/6A(NAVY) (IN PART)
5 July 1961
(See supersession data herein)

MILITARY SPECIFICATION SHEET

WIRE, ELECTRICAL, POLYTETRAFLUOROETHYLENE (PTFE) INSULATED, 260°C, 250 VOLTS, WRAPPED INSULATION

This specification sheet is approved for use by the Naval Sea Systems Command, Department of the Navy, and is available for use by all Departments and Agencies of the Department of Defense.

The complete requirements for acquiring the wire described herein shall consist of this document and the latest issue of MIL-W-16878.

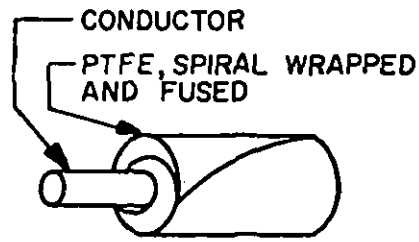

SH 11884

FIGURE 1. Construction.

TABLE I. Construction details.

Wire size	Stranding	Conductor		Conductor diameter (nominal) (inch)	Finished wire	
		Material 2/ 3/	Coating		Diameter (inch)	
					Min	Max
32	7 X 40	Copper	Nickel	0.010	0.020	0.024
32	7 X 40	H.S.C.A.	Nickel	.010	.020	.024
32	7 X 40	C.C. Steel	Nickel	.010	.020	.024

See footnotes at end of table.

FSC 6145

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:31Z
Check the source to verify that this is the current version before use.

TABLE I. Construction details. - Continued

Wire size	Stranding	Conductor		Conductor diameter (nominal) (inch)	Finished wire	
					Diameter (inch)	
		Material 2/ 3/	Coating		Min	Max
30	1 X 30	Copper	Nickel	0.0100	0.020	0.024
30	1 X 30	H.S.C.A.	Nickel	.0100	.020	.024
30	1 X 30	C.C. Steel	Nickel	.0100	.020	.024
30	7 X 38	Copper	Nickel	.012	.022	.026
30	7 X 38	H.S.C.A.	Nickel	.012	.022	.026
28	1 X 28	Copper	Nickel	.0126	.023	.027
28	1 X 28	H.S.C.A.	Nickel	.0126	.023	.027
28	1 X 28	C.C. Steel	Nickel	.0126	.023	.027
28	7 X 36	Copper	Nickel	.015	.025	.029
28	7 X 36	H.S.C.A.	Nickel	.015	.025	.029
26	1 X 26	Copper	Nickel	.0159	.026	.030
26	1 X 26	H.S.C.A.	Nickel	.0159	.026	.030
26	1 X 26	C.C. Steel	Nickel	.0159	.026	.030
26	7 X 34	Copper	Nickel	.019	.029	.033
26	7 X 34	H.S.C.A.	Nickel	.019	.029	.033
26	19 X 38	Copper	Nickel	.020	.029	.033
26	19 X 38	H.S.C.A.	Nickel	.020	.029	.033
24	1 X 24	Copper	Nickel	.0201	.030	.034
24	1 X 24	H.S.C.A.	Nickel	.0201	.030	.034
1/ 24	1 X 24	C.C. Steel	Nickel	.0201	.030	.034
24	7 X 32	Copper	Nickel	.024	.034	.038
24	7 X 32	H.S.C.A.	Nickel	.024	.034	.038
24	19 X 36	Copper	Nickel	.025	.034	.038
24	19 X 36	H.S.C.A.	Nickel	.025	.034	.038
22	1 X 22	Copper	Nickel	.0254	.035	.040
22	1 X 22	H.S.C.A	Nickel	.0254	.035	.040
1/ 22	1 X 22	C.C. Steel	Nickel	.0254	.035	.040
22	7 X 30	Copper	Nickel	.030	.040	.044
22	7 X 30	H.S.C.A.	Nickel	.030	.040	.044
22	19 X 34	Copper	Nickel	.032	.040	.044
22	19 X 34	H.S.C.A.	Nickel	.032	.040	.044
20	1 X 20	Copper	Nickel	.0320	.042	.046
20	1 X 20	H.S.C.A.	Nickel	.0320	.042	.046
20	7 X 28	Copper	Nickel	.038	.048	.052
20	7 X 28	H.S.C.A.	Nickel	.038	.048	.052
20	19 X 32	Copper	Nickel	.040	.048	.052
20	19 X 32	H.S.C.A.	Nickel	.040	.048	.052

1/ Inactive for new design.
2/ H.S.C.A. stands for high strength copper alloy.
3/ C.C. Steel stands for copper clad steel.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:31Z
Check the source to verify that this is the current version before use.

REQUIREMENTS:

Visual and mechanical inspection: Applicable.
Spark test: 2.5 kilovolts (kV).
Impulse dielectric test: 4.0 kV.
Tank test: 1.5 kV.
Dielectric withstanding voltage: 1.5 kV.
Insulation resistance: $IR = K \log_{10} D/d$

Where: IR = Minimum insulation resistance in megohms per 1000 feet at 20 °C
K = 50,000
D = Maximum average diameter of finished wire
d = Conductor diameter

Cold bend: Condition 4 hours at minus 65°C ± 1°C (see table II).


TABLE II. Cold bend mandrel sizes.

Wire size	Cold bend mandrel (maximum diameter) (inches)
32 through 20	1

Concentricity: 70 percent (minimum).
Surface resistance: 5 megohms (minimum).
Wrap back: Applicable.
Heat resistance: Condition at 290°C.
Flammability: Not applicable.
Soldering: Applicable.
Heat aging: Not applicable.
Insulation tensile strength: 3000 pounds force per square inch (minimum).
Insulation elongation: 150 percent (minimum).
Stripe durability: Applicable.
Fungus resistance: Applicable.
Maximum direct current resistance of finished wire: See table I of MIL-W-16878.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:31Z
Check the source to verify that this is the current version before use.

Military part number (see MIL-W-16878):

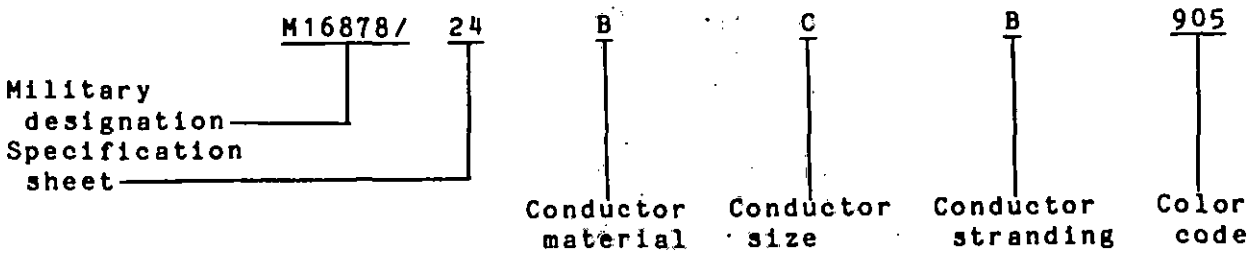

Supersession data: The wire covered by this specification sheet supersedes MIL-W-16878/6A(NAVY), type ET, 260°C rated, with tape wrapped insulation.

Review activities:
Navy - AS, EC
User activities:
Navy - OS, MC

Preparing activity:
Navy - SH
(Project 6145-N300-23)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:31Z
Check the source to verify that this is the current version before use.