MILITARY SPECIFICATION

BELTING, FLAT: CONVEYOR, RUBBER INDUSTRIAL

SYNTHETIC REINFORCEMENT

1. SCOPE

1.1 Scope. This specification covers rubber textile-reinforced conveyor belting made for uninterrupted transportation of packaged articles and bulk materials.

1.2 Classification. Conveyor belting shall be of any combination of the following types and grades as specified (see 6.2):

Type:

A - Smooth rubber cover, both sides.
B - Smooth rubber cover on pulley side, stucco or molded finish cover on carrying side.
C - Friction surface on both sides.
D - Friction surface on pulley side, stucco or molded finish cover on carrying side.

Grade:

210 rated tension (pounds per inch of belt width)
315 rated tension (pounds per inch of belt width)
420 rated tension (pounds per inch of belt width)
525 rated tension (pounds per inch of belt width)

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal form a part of this specification to the extent specified herein:

SPECIFICATIONS

Federal

QQ-S-781	- Strapping, Steel, Flat and Seals.
CCC-C-467	- Cloth, Burlap, Jute (or Kenaf).
PPP-B-601	- Boxes, Wood, Cleated-Plywood.
PPP-B-621	- Boxes, Wood, Nailed and Lock-Corner.

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:10Z
Check the source to verify that this is the current version before use.

STANDARDS

Federal

FED. TEST METHOD STD. No. 601 - Rubber: Sampling and Testing.

Military

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.

MIL-STD-129 - Marking for Shipment and Storage.

(Copies of specifications and standards required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

AMERICAN SOCIETY FOR TESTING AND MATERIALS

D378 - Standard Methods of Testing Flat Rubber Belting.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

UNIFORM CLASSIFICATION COMMITTEE, AGENT

Uniform Freight Classification.

(Application for copies should be addressed to the Uniform Classification Committee, ATTN: Tariff Publishing Officer, Room 1106, 222 South Riverside Plaza, Chicago, IL 60606.)

NATIONAL MOTOR FREIGHT TRAFFIC ASSOCIATION, INC., AGENT

National Motor Freight Classification.

(Application for copies should be addressed to the American Trucking Associations, Inc., ATTN: Tariff Order Section, 1616 P Street, NW, Washington, DC 20036.)

(Technical society and technical association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 Description. The flat, rubber, conveyor belting (hereinafter called belt or belting) shall consist of a carcass, a top or carrying surface, and a bottom or pulley surface.

3.2 Material. Material shall be as specified herein. Material not specified shall be selected by the supplier and shall be subject to all provisions of this specification.

3.2.1 Rubber. Rubber shall be natural or synthetic or a combination of natural and synthetic. The belt top and bottom shall be the same rubber compound.

3.2.2 Fabric. The fabric shall be all nylon, all polyester, or a combination of nylon and polyester.

3.3 Construction.

3.3.1 Carcass. The belt carcass shall be one or more plies of fabric thoroughly impregnated with rubber.

3.3.2 Belt edges. The belt edges shall be cut or rubber covered. Rubber covered edges shall be of the same rubber compound as the top and bottom.

3.3.3 Longitudinal seams. Longitudinal seams shall be at least 4 inches from the edge of the belt and each longitudinal seam shall be at least 12 inches from any other longitudinal seam in the same ply. In addition, each longitudinal seam shall be at least 4 inches, laterally, from any longitudinal seam in any other ply. The number of longitudinal seams in belt plies shall be not more than the number specified in table I.

Table I. Number of longitudinal seams

Belt Width Inches	Maximum number of longitudinal seams, outer ply	Maximum number of longitudinal seams, inner ply
	Cut edge	
10 thru 48	0	1
over 48 thru 60	1	2
over 60 thru 72	2	2
	Rubber covered edge	
10 thru 26	1	1
over 26 thru 48	2	1
over 48 thru 60	2	2
over 60 thru 72	3	2

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

3.3.4 Transverse seams. Transverse seams shall be at a 45 degree to 75 degree angle to the belt centerline. There shall be no more than one transverse seam per ply per 100 feet of belt, except there shall be no transverse seams in belts of 1 or 2 ply. Each transverse seam shall be separated from all other transverse seams by a longitudinal distance of at least 15 feet.

3.3.5 Skim coats. Each fabric ply shall be separated from all other fabric plies by a rubber skim coat. The minimum skim coat thickness shall be 0.030 inch for 2 ply, 0.015 inch for 3 ply and 0.012 inch for 4 and 5 ply.

3.4 **Dimensions.**

3.4.1 Lengths. The minimum length of the belting shall be as specified (see 6.2), plus sufficient additional belting for testing. When specified (see 6.2), length tolerance shall be minus 0, plus 2 percent.

3.4.2 Width. The belt width shall be as specified (see 6.2 and 6.4).

3.4.2.1 Width tolerance, rubber covered edge. The tolerance for widths of 24 inches or less shall be plus or minus 0.25 inch. The tolerance for widths over 24 inches shall be plus or minus 1 percent of belt nominal width.

3.4.2.2 Width tolerance, cut edge. The tolerance for widths of 24 inches or less shall be plus or minus 0.125 inch. The tolerance for widths over 24 inches shall be plus or minus 0.5 percent of belt nominal width.

3.5 Types and grades. Unless otherwise specified, the physical requirements of all belt types and grades shall be in accordance with table II. When specified (see 6.2), the warp minimum breaking strength shall be in accordance with table III.

3.5.1 Type A. The belting shall have a smooth rubber cover on both the pulley side and the carrying side. Unless otherwise specified (see 6.2), the thickness of the rubber cover shall be as specified in table II.

3.5.2 Type B. The rubber cover on the carrying side of the belting shall have an approved molded or approved stucco surface design. The supplier shall secure approval of his particular type of surface design on the cover of the belting which he proposes to submit by furnishing a sample to the contracting officer. The pulley side rubber cover shall be smooth. Unless otherwise specified (see 6.2), the thickness of the rubber cover shall be as specified in table II.

3.5.3 Type C. The belt outer cover shall consist of a friction surface formed by the rubber impregnating compound during the frictioning process.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

3.5.4 Type D. The rubber cover on the carrying side shall have an approved molded or approved stucco surface design. The supplier shall secure approval of the particular type of surface design on the cover of the belting which he proposes to submit by furnishing a sample to the contracting officer. The cover on the pulley side shall be a friction surface formed by the rubber impregnating compound during the frictioning process. Unless otherwise specified (see 6.2), the cover thickness shall be as specified in table II.

3.6 Marking. Belting shall be molded with the supplier's name or trade mark, the grade of belting and the last two digits of the year of manufacture repeated at intervals of 50 feet or less.

3.7 Workmanship. The belting shall be free of defects that may impair its serviceability.

Table II. Cover and belting physical requirements

	Type				Method of test
	A	B	C	D	
Rubber cover:					
Tensile strength, carrying side, minimum, lb./sq. in.	2000	2000	-----	2000	4.4.2.3
Ultimate elongation, carrying side, minimum:					
Original, percent	400	400	-----	400	4.4.2.3
After aging, percent	300	300	-----	300	4.4.2.4 & 4.4.2.3
Thickness, minimum, inch:					4.4.2.1.3
Carrying side:					
Overall	0.060	0.060	-----	0.060	
Thinnest portion	-----	0.030	-----	0.030	
Pulley side	0.030	0.030	-----	-----	
Equivalent weight of cover with molded surface design at specific gravity of 1, minimum, lb./sq. ft.	-----	0.43	-----	0.43	4.4.2.2
Belting:					
Warp elongation at rated tension, maximum percent	3	3	3	3	4.4.2.5
Warp elongation at break, minimum percent	10	10	10	10	4.4.2.5
Warp minimum breaking strength, lb. per inch of belt					4.4.2.5
Grade 210	1680	1680	1680	1680	
Grade 315	2520	2520	2520	2520	
Grade 420	3360	3360	3360	3360	
Grade 525	4200	4200	4200	4200	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

Table II. Cover and belting physical requirements (Cont'd)

	Type A	Type B	Type C	Type D	Method of test
Fill minimum breaking strength, lbs. per inch of belt					4.4.2.5
Grade 210	1000	1000	1000	1000	
Grade 315	1500	1500	1500	1500	
Grade 420	2000	2000	2000	2000	
Grade 525	2500	2500	2500	2500	
Adhesion between cover and ply or plies, minimum:					
Carrying cover lb/in.	24	24	24	24	4.4.2.6
After aging, lb/in or percent of original whichever is greater	18 60	18 60	18 60	18 60	4.4.2.7 & 4.4.2.6
Bottom cover lb/in.	20	20	20	20	4.4.2.6
After aging lb/in. or percent of original whichever is greater	15 60	15 60	15 60	15 60	4.4.2.6 & 4.4.2.7
Plies lb/in.	30	30	30	30	4.4.2.6
After aging lb/in. or percent of original whichever is greater	22.5 60	22.5 60	22.5 60	22.5 60	4.4.2.7 & 4.4.2.6
Thickness (less cover), inch minimum					4.4.2.1.2
Grade 210	.130	.130	.130	.130	
Grade 315	.160	.160	.160	.160	
Grade 420	.235	.235	.235	.235	
Grade 525	.295	.295	.295	.295	

Table III. Warp breaking strength (when specified)

	Type A	Type B	Type C	Type D	Method of test
Warp min. breaking strength lb/in. of belt					4.4.2.5
Grade 210	2400	2400	2400	2400	
Grade 315	3600	3600	3600	3600	
Grade 420	4800	4800	4800	4800	
Grade 525	6000	6000	6000	6000	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Acceptability criteria. Conveyor belting which conforms to all requirements in sections 3 and 5 of this specification and pass all examination and tests in section 4 of this specification will be considered acceptable by the Government.

4.2 Classification of inspection. Inspection shall be classified as follows:

(a) Quality conformance inspection (see 4.3).
(b) Inspection of preparation for delivery (see 4.5).

4.3 Quality conformance inspection.

4.3.1 Sampling.

4.3.1.1 Lot. A lot shall consist of all conveyor belting of one type and grade presented for delivery at one time.

4.3.1.2 Sampling for examination. Unless otherwise specified (see 6.2), the sample for inspection shall be taken from a lot as described in table I, section 6 of FED. TEST METHOD STD. No. 601. For the purpose of inspection, a unit shall be one belt.

4.3.1.3 Sampling for test. Unless otherwise specified (see 6.2), the sample for test shall be taken from the lot as specified in table IV. For the purpose of tests, a test unit shall be a full width of belting equal in area to 3 square feet.

4.3.2 Examination. Samples selected in accordance with 4.3.1.2 shall be examined in accordance with 4.4.1. If the number of defective units in the sample equals or exceeds the "Rejection Number R" in table I of section 6 of FED. TEST METHOD STD No. 601, the lot shall be rejected.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

Table IV. Sampling for test

Lot size		Sample size	Rejection
From	To	(Number of test units)	number
Yards	Yards		
0	500	1	1
501	1,000	2	1
1,001	2,000	3	1
2,001	3,500	4	1
3,501	5,000	5	1
5,001	7,000	6	1
7,001	10,000	7	1

4.3.3 Tests. Samples selected in accordance with 4.3.1.3 shall be tested as specified in 4.4.2. Failure of any test shall be cause for rejection.

4.4 Inspection procedure.

4.4.1 Examination. The belting shall be examined for the following defects:

101. Type not as specified.
102. Width not as specified (see 4.4.1.1).
103. Length not as specified (see 4.4.1.2).
104. Workmanship not as specified.

4.4.1.1 Width. The width of the belting shall be determined at 50 foot intervals in accordance with method 2121 of FED. TEST METHOD STD. No. 601.

4.4.1.2 Length. The length of the belting shall be determined in accordance with method 2111 of FED. TEST METHOD STD. No. 601, using either a steel tape graduated to 1/8 inch or less or a length recording device accurate to 1/8 inch.

4.4.2 Tests.

4.4.2.1 Thickness.

4.4.2.1.1 Skim coats. A specimen of the belting with the full cross-section cut perpendicular to the principal surface of the material shall be examined for the required skim coat between plies. In case of dispute, method 2031 of FED. TEST METHOD STD. No. 601 shall be used to determine the correct thickness. Nonconformance to 3.3.5 shall constitute failure of this test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

4.4.2.1.2 Belting. A specimen of the belting with the full cross-section cut perpendicular to the principal surface of the material shall be examined for the required thickness. In case of dispute, method 2031 of FED. TEST METHOD STD. No. 601 shall be used to determine the correct thickness. A thickness that is less than the belting thickness (less cover) specified in table II plus the cover thickness specified in table II, if applicable, shall constitute failure of this test.

4.4.2.1.3 Covers. The thickness of rubber covers shall be determined as specified in method 2011 or 2031 of FED. TEST METHOD STD. No. 601. Only in case of dispute will method 2031 be used. When method 2011 is used, the thickness of the cover shall be the difference between the reading for the entire specimen, including the cover, and the thickness after the cover has been removed. Nonconformance to table II shall constitute failure of this test.

4.4.2.2 Equivalent weight of covers with molded surface design. The equivalent weight of types "B" and "D" covers shall be determined by stripping the rubber cover from a specimen of the belting at least 4 inches square in area. The rubber stripped from the belting shall be weighed, its specific gravity determined, and the equivalent weight at a specific gravity of 1 calculated as follows:

$$\text{Equivalent weight at specific gravity of 1} = \frac{W}{S}$$

where:

W = weight in grams of 4 by 4 inch of rubber specimen;
S = specific gravity of 4 by 4 inch of rubber specimen;

and,

$$\text{Equivalent weight in pounds per square foot} = \frac{W}{S} \times 0.02$$

An equivalent weight, in pounds per square foot, that is less than 0.43 shall constitute failure of this test.

4.4.2.3 Tensile strength and ultimate elongation of cover on carrying side, types A, B, and D. The tensile strength and ultimate elongation of the rubber cover on the carrying side of the belting shall be determined as described in methods 4111 and 4121, respectively, of FED. TEST METHOD STD. No. 601. Die III shall be used for cutting the specimens. A tensile strength and ultimate elongation less than specified in table II shall constitute failure of this test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

4.4.2.4 Resistance of cover on carrying side to aging, types A, B, and D. The resistance of the rubber on the carrying side of the belting to aging shall be determined as described in method 7221 of FED. TEST METHOD STD. No. 601. An ultimate elongation after aging that is less than specified in table II shall constitute failure of this test.

4.4.2.5 Carcass breaking strength and elongation.

4.4.2.5.1 Sample preparation. The breaking strength and ultimate elongation specimens shall be a portion of the test sample having the full belt carcass thickness, except a 2-ply portion may be used for belts of 2 or more plies. The elongation at rated tension specimens shall be portions of the sample having the full belt thickness. Elongation at rated tension specimens shall be cut with a die conforming to figure 1. Breaking strength and ultimate elongation specimens shall be cut from a die conforming to figure 1 or shall be prepared in accordance with ASTM D378. The breaking strength test shall be performed on three warp and three fill specimens. The elongation at rated tension and ultimate elongation tests shall be performed on three warp specimens. Specimens that break outside the reduced section shall be discarded and replaced.

4.4.2.5.2 Test procedure. The breaking strength and elongation shall be determined in accordance with methods 4111 and 4121, respectively, of FED. TEST METHOD STD. No. 601, except as specified herein. Grips similar to those shown in figure 2 shall be used. The specimens shall be conditioned for at least 24 hours at a temperature of 23° C. plus or minus 3° C. (73.4° F. plus or minus 9° F.) and a relative humidity between 45 and 70 percent. In case of dispute, the specimens shall be conditioned for at least 72 hours at the above specified temperature with a relative humidity of 50 percent plus or minus 5 percent. The rate of grip separation shall be 1 inch per minute for elongation at rated tension and 4 inches per minute for ultimate elongation and breaking strength. When an extensometer is used to measure ultimate elongation, it shall be fixed or held on the specimen with the pointers on the 4-inch reference line and the scale set at zero. Breaking strength shall be calculated as follows:

$$BF = \frac{F \times N_1}{N_2 \times W}$$

Where:

BF = Breaking strength in pounds per inch of belt width.
F = Specimen breaking force recorded in pounds.
N_1 = Number of plies in belt carcass.
N_2 = Number of plies in sample.
W = Width of specimens (inches) at narrowest point, prior to testing.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

Nonconformance to the elongation at rated tension, ultimate elongation or breaking strength requirements listed in table II and table III (if applicable) shall constitute failure of this test.

4.4.2.6 Adhesion between cover and plies. The adhesion between cover and plies shall be determined as described in method 6011 of FED. TEST METHOD STD. No. 601 with the following exceptions:

(a) Specimen. The specimen shall consist of a portion of the test sample 1 inch in width and uniform within 0.010 inch. The specimen shall be long enough to permit separation for a sufficient distance to indicate the adhesion value. A distance of separation of at least 4 inches is recommended. When adhesion between rubber layer and fabric is required, the specimen shall consist of the rubber and 1 ply of fabric with all other layers removed. When adhesion between fabric layers is required, the specimen shall consist of 2 plies of fabric with all other layers removed.

(b) Procedure. The specimen shall be separated at one end for a distance of about 1.500 inches into its two component parts and each free end clamped in one of the grips of the testing machine. The remainder of the procedure shall be as described in method 6011. When a testing machine is equipped with an integrator that determines the area under the force separation curve, the average force may be determined by dividing the area by the length of separation.

(c) One specimen shall be tested for each adhesive bond in the test unit and the adhesive strength for each bond recorded to the nearest 0.500 pound per inch of width.

(d) Nonconformance to table II shall constitute failure of this test.

4.4.2.7 Resistance of adhesive to aging. The specimen shall be as described in 4.4.2.6. The specimen shall be aged as specified in method 7221 of FED. TEST METHOD STD. No. 601. The adhesion after aging shall be determined as specified in 4.4.2.6 and percentage of original adhesion calculated. An adhesion that is less than specified in table II shall constitute failure of this test.

4.5 Inspection of preparation for delivery.

4.5.1 Quality conformance inspection of pack.

4.5.1.1 Unit of product. For the purposes of inspection, a completed pack prepared for shipment shall be considered a unit of product.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

4.5.1.2 Sampling. Sampling for examination shall be in accordance with MIL-STD-105.

4.5.1.3 Examination. Samples selected in accordance with 4.5.1.2 shall be examined for the following defects. AQL shall be 2.5 percent defective.

105.	Materials and containers not as specified for level A or B. Each incorrect material or container shall be considered one defect.
106.	Belting not rolled and roll secured as required.
107.	Belting not individually packed, as specified.
108.	Strapping not zinc coated for level A.
109.	Strapping not applied as specified for level A or B.
110.	Marking missing, illegible, incorrect, or incomplete.

5. PREPARATION FOR DELIVERY

5.1 Packaging (see 6.5). The belting shall be rolled and the roll secured to prevent unwinding or telescoping in a manner that will not damage the belting in accordance with the manufacturer's recommendations.

5.2 Packing. Packing shall be level A, B, or C as specified (see 6.2).

5.2.1 Level A.

5.2.1.1 Rolls of belting with a gross weight less than 900 pounds. Rolls of belting weighing 900 pounds or less shall be wrapped in 1 ply of 7-1/2 ounce burlap conforming to CCC-C-467 with the ends constrained with wire ties or sewn in place. Stencil "Use No Hooks" on the burlap cover. Each roll of belting shall then be placed in a close-fitting box conforming to PPP-B-621, class 2, style 2. Box closure and strapping shall be in accordance with the appendix to the applicable box specification. Strapping shall be zinc coated and on boxes provided with skids, the strapping shall be parallel and adjacent to the skids.

5.2.1.2 Rolls of belting with a gross weight exceeding 900 pounds and less than 2,000 pounds. Rolls of belting weighing between 900 and 2,000 pounds shall be packed in cylindrical wood crates. The crate heads shall be made of 2 plies of 1 inch nominal, No. 3 grade, S-4-S, random widths of soft woods with the boards in each ply running at right angles to each other. The crate heads shall have a 6-inch square hole in the center of the head. Slats shall be single ply of 1-inch nominal, No. 3 grade, S-4-S, 4-inch width nailed solid around the crate heads. The slats shall be nailed to the crate heads by 2-inch leg staples or 7d cement coated sinker nails driven into both faces of each head. One wide perforated steel strapping conforming to QQ-S-781, type II, class B shall be applied over each slat and nailed into the heads. In addition, 1-1/4 inch by 0.035 inch solid steel strapping conforming to QQ-S-781, type IV, class B shall be applied securely

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

over the slats approximately 4 inches from each end. When the distance between the straps exceeds 24 inches, one or more intermediate straps, as required, shall be applied.

5.2.1.3 Rolls of belting with a gross weight exceeding 2000 pounds. Rolls of belting exceeding 2000 pounds shall be packed as specified in 5.2.1.2 with the following exceptions: The crate heads shall be constructed of 3 plies of lumber with the outside plies running at right angles to the center ply. Slats shall be 2 plies.

5.2.2 Level B. Belting shall be packed as specified in 5.2.1 for level A with the following exceptions: No box will be required for belting with a gross weight of less than 900 pounds. Strapping shall be class A.

5.2.3 Level C. Rolls of belting, secured as specified in 5.1 shall be individually packed in a manner to assure carrier acceptance and safe delivery to lowest ratings in compliance with Uniform Freight Classification rules or National Motor Freight Classification rules.

5.3 Marking. Marking for shipment and storage shall be in accordance with MIL-STD-129.

6. NOTES

6.1 Intended use.

6.1.1 Types A and B belting are intended for carrying various classes of mail and parcel post under conditions of exposure to the atmosphere or to other extreme conditions making it necessary to protect the carcass with a rubber cover. They are also intended for use in conveying bulk materials such as coal, sand, gravel, etc., where abrasion or moisture conditions make necessary the use of a rubber cover. The B belting is also intended for carrying mail or other packages inside a post office or similar building on inclines of sufficient grade to make necessary the use of a molded surface design construction.

6.1.2 Types C and D are intended for carrying mail, parcel post, packages, etc., under all conditions except where exposure to the elements or abrasion requires the use of a rubber cover. Type D is intended for use where the necessity for an increased coefficient of friction, due to the incline of the belt, requires a molded surface rubber cover.

6.2 Ordering data. Procurement documents should specify the following:

(a) Title, number, and date of this specification.
(b) Type and grade of belting (see 1.2).
(c) Length of belting (see 3.4.1).
(d) When length tolerance shall be minus 0, plus 2 percent (see 3.4.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

(e) Width of belting (see 3.4.2 and 6.4).
(f) When warp and fill breaking strength must conform to table III instead of table II (see 3.5).
(g) When thickness of cover shall be other than as specified (see 3.5.1, 3.5.2, 3.5.4 and 6.3).
(h) When sampling for inspection shall be other than as specified (see 4.3.1.2).
(i) When sampling for test shall be other than as specified (see 4.3.1.3).
(j) Level of packing required (see 5.2).

6.3 Recommended cover thickness for type A belting.

Usage	Belt Width	Cover Thickness Top	Bottom
Indoor	18" to 20" / 24" to 36"	1/16" / 1/8"	1/32" / 1/16"
Outdoor	18" to 24" / 30" to 36"	1/8" / 3/16"	1/16" / 1/16"

6.4 Standard widths. Standard widths in inches are 10, 12, 14, 16, 18, 20, 24, 26, 30, 36, 42, 48, 54, 60, and 72. Other widths are available at premium price.

6.5 Rated tension. When splicing conforms to the belt manufacturer's recommendations, the spliced joint shall have the same tension rating as the belt.

6.6 Levels of packaging have not been included as securing of the roll is the only requirement applicable and is required for all levels.

Custodian:

Army - ME

User activities:

Army - GL, AT

Preparing activity:

Army - ME

Project No. 3030-A003

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

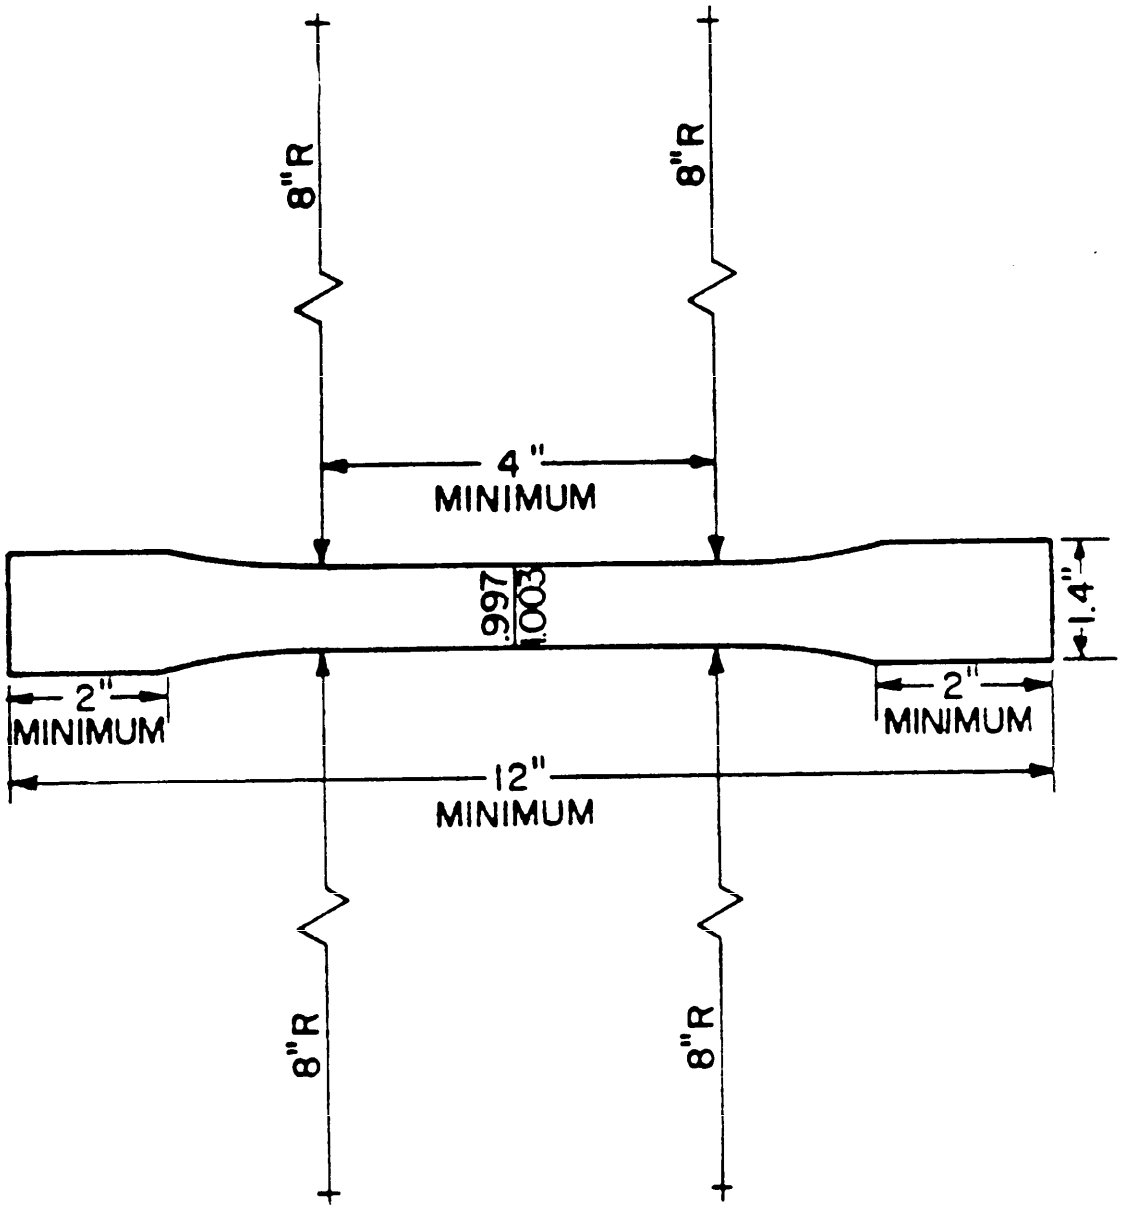


FIGURE 1. DIE FOR DUMBELL SPECIMEN.

X-2302

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:10Z
Check the source to verify that this is the current version before use.

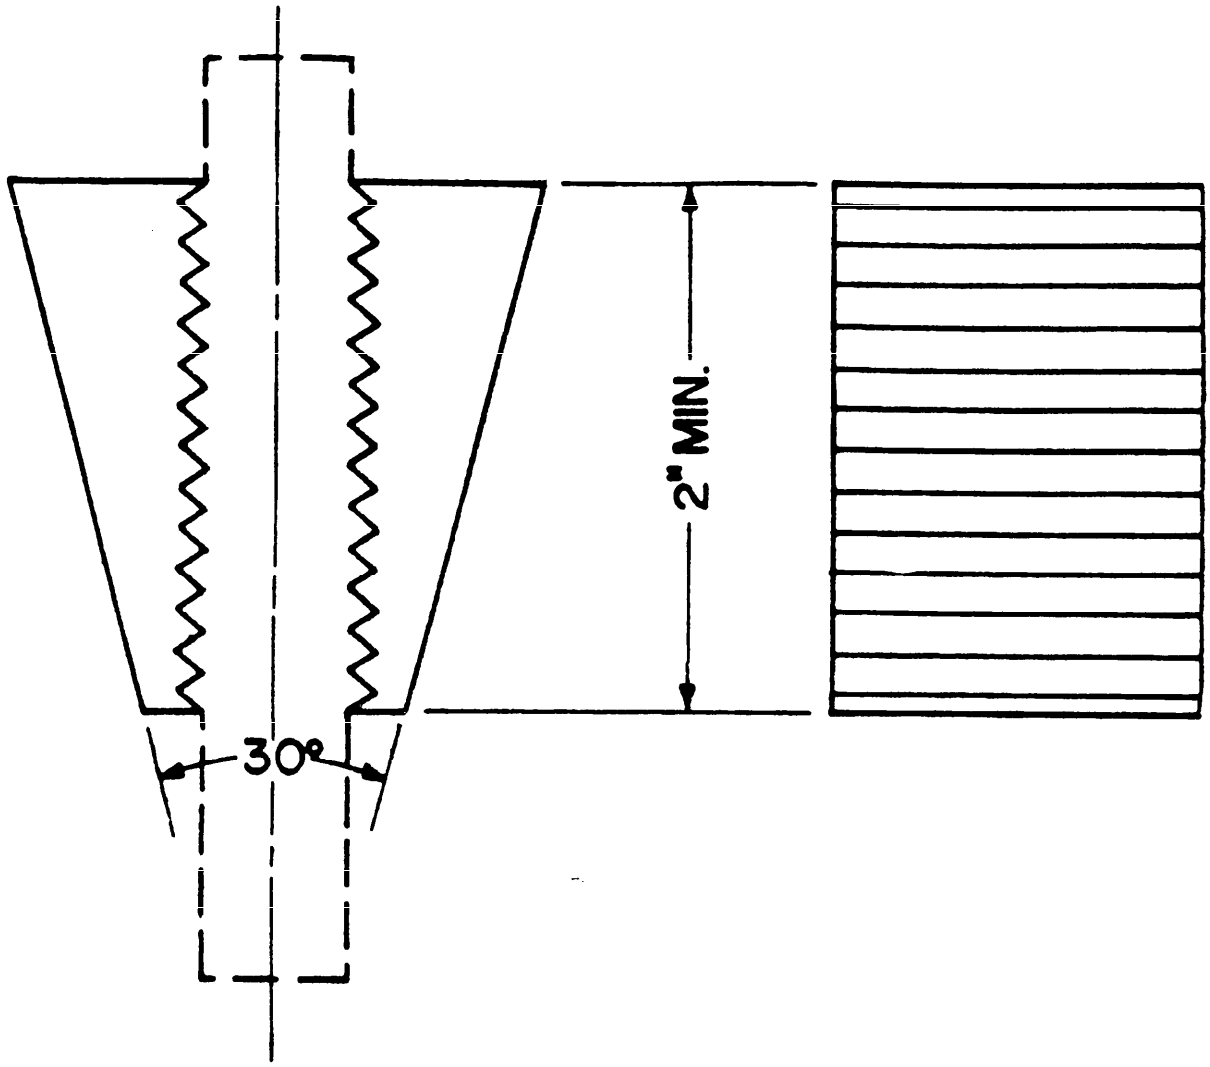


FIGURE 2. GRIP

X-2303

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

Form Approved
Budget Bureau No. 22-R255

INSTRUCTIONS: This sheet is to be filled out by personnel, either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments and suggestions submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or serve to amend contractual requirements.

SPECIFICATION: MIL-B-52761(ME) Belting, Flat: Conveyor, Rubber Industrial Synthetic Reinforcement

ORGANIZATION

CITY AND STATE

CONTRACT NUMBER

MATERIAL PROCURED UNDER A
— DIRECT GOVERNMENT CONTRACT — SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?

☐ YES ☐ NO (If "yes", in what way?)

4. REMARKS (Attach any pertinent data which may be of use in improving this specification. If there are additional papers attach to form and place both in an envelope addressed to preparing activity.)

SUBMITTED BY (Printed or typed name and activity - Optional)

DATE

DD FORM 1426
11 Oct 72 (Rev)

REPLACES EDITION OF 1 OCT 64 WHICH MAY BE USED

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.

FOLD

DEPARTMENT OF THE ARMY
U. S. ARMY MOBILITY EQUIPMENT
RESEARCH, DEVELOPMENT
CENTER
FORT BELVOIR, VIRGINIA 22060

OFFICIAL BUSINESS

AMSME-RZD-S

POSTAGE AND FEES PAID
DOD-314

COMMANDER
U. S. ARMY MOBILITY EQUIPMENT
RESEARCH, DEVELOPMENT CENTER
ATTN: AMSME-RZD-S
FORT BELVOIR, VIRGINIA 22060

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:10Z
Check the source to verify that this is the current version before use.