MIL-M-52599A
17 March 1983
SUPERSEDING
MIL-M-52599
12 January 1968

MILITARY SPECIFICATION

MEMBRANE SURFACING: RUNWAYS,

TAXIWAYS, HELIPADS AND SPLICING

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers three types of coated fabric membrane.

1.2 Classification. The membrane shall be the following types, as specified (see 6.2).

Type I - Runway membrane
Type II - Taxiway membrane
Type III - Splicing membrane

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. Unless otherwise specified, the following specifications and standards of the issue listed in that issue of the Department of Defense Index of Specifications and Standards (DoDISS) specified in the solicitation form a part of this specification to the extent specified herein.

Benefical comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: US Army Mobility Equipment Research and Development Command, ATTN: DRDME-DS, Fort Belvior, VA 22060 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

FSC 5680

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:09Z
Check the source to verify that this is the current version before use.

SPECIFICATIONS

FEDERAL

FF-N-105	- Nails, Brads, Staples and Spikes, Wire, Cut and Wrought.
NN-P-530	- Plywood, Flat Panel.
QQ-S-781	- Strapping, Steel, and Seals.
PPP-B-601	- Boxes, Wood, Cleated Plywood.
PPP-B-1055	- Barrier Material, Waterproofed, Flexible.
PPP-S-760	- Strapping, Nonmetallic (and Connectors).
PPP-T-60	- Tape, Packaging, Waterproof.

MILITARY

MIL-T-5624	- Turbine Fuel, Aviation, Grades JP-4 and JP-5.
MIL-B-22191	- Barrier Materials, Transparent, Flexible, Heat Sealable.

STANDARDS

FEDERAL

FED-STD-191	- Textile Test Methods.

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129	- Marking for Shipment and Storage.
MIL-STD-130	- Identification Marking of U.S. Military Property.
MIL-STD-731	- Quality of Wood Members for Containers and Pallets.

2.1.2 Other government publications. The following other Government publications form a part of this specification to the extent specified herein.

U.S. DEPARTMENT OF COMMERCE

PS-1	- Construction and Industrial Plywood.
PS-51	- Hardwood and Decorative Plywood.

(Application for copies should be addressed to the Superintendent of Documents, U.S. Government Printing Office, Washington, D.C. 20402.)

(Copies of specifications, standards, and publications required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:09Z
Check the source to verify that this is the current version before use.

2.2 Other publications. The following document(s) form a part of this specification to the extent specified herein. The issues of the documents which are indicated as DoD adopted shall be the issue listed in the current DoDISS and the supplement thereto, if applicable.

AMERICAN NATIONAL STANDARDS INSTITUTE (ANSI)

ANSI/ASTM D 789 - Nylon Injection Molding and Extrusion Materials.
ANSI/ASTM D 903 - Peel or Stripping Strength of Adhesive Bonds.
ANSI/ASTM D 1151 - Effect of Moisture and Temperature on Adhesive Bonds.
ANSI/ASTM D 1682 - Breaking Load and Elongation of Textile Fabrics.

(Application for copies should be addressed to the American National Standards Institute, Inc., 1430 Broadway, New York, NY 10018.)

(Industry association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence.

3. REQUIREMENTS

3.1 Description. The membrane shall be a jointed panel or roll of 2-ply runs of impregnated, bonded and coated base fabric.

3.2 First article. When specified (see 6.2), a sample shall be subjected to first article inspection (see 4.3 and 6.3).

3.3 Material. Material shall be as specified herein. Materials not specified shall be selected by the contractor and shall conform to the requirements specified herein (see 6.7).

3.3.1 Base fabric. The base fabric shall be a plain weave, single ply fabric woven from an 840 denier, continuous filament, high tenacity nylon yarn (polyamide of polyhexamethylene adipimide). The base fabric shall conform to the physical requirements shown in table I.

TABLE I. Physical requirements of base fabric.

Property	Requirements	
	Maximum	Minimum
Weight per sq. yd.; ounces	4.8	4.2
Melting point, yarns; ^{o} F	492	472
Yarns per inch, warp and fill	-	22
Breaking strength (grab), warp and fill; pounds.	-	325

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:09Z
Check the source to verify that this is the current version before use.

3.3.2 Coated laminate.

3.3.2.1 Coating. Coated laminate shall be fabricated by applying a compounded chloroprene synthetic rubber coating to two plies of base fabric. The coating shall contain no ingredient deleterious to nylon and shall be applied to the base fabric so as to thoroughly impregnate the fabrics, bond the two plies, and completely and evenly coat the outer surfaces of the laminate.

3.3.2.2 Physical requirements. The coated laminate shall be fabricated so that the edges do not deviate more than 12 inches from a perpendicular line drawn from corner to adjacent corner of the run. The coated laminate shall also conform to the physical requirements shown in table II.

TABLE II. Physical requirements of coated laminate.

Property	Requirements	
	Maximum	Minimum
Weight per sq. yd.; ounces	48.0	42.0
Breaking strength; pounds		
Warp direction	-	900
Fill direction	-	800
Elongation, warp and fill; percent	35	25
Tear strength, warp and fill; pounds		
Warp direction	-	100
Fill direction	-	90
Joint peel strength after 72 hours at 212° F, ± 2° F. (pounds per inch)	-	10
Joint peel strength after 48 hours in distilled water at 77° F (pounds per inch)	-	10
Jet fuel resistance; retained strength and elongation; percent	-	90
Flame resistance;		
After flame time; seconds	5	-
Length of char; inches	2	-
Heat resistance, after 5 minutes at 350° F., retained breaking strength and elongation, percent	-	90
Hydrostatic pressure resistance, for 10 minutes at a 20-inch head	no leakage	
Extreme temperature resistance;		
after 2 hours at 180° F.	no blocking or tackiness	
after 4 hours at -40° F.	no cracking or flaking of the coating	
Joint breaking strength; wet or dry	equal to laminate without joint	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:09Z
Check the source to verify that this is the current version before use.

3.4 Membrane fabrication. Type I and II membrane shall be fabricated by joining runs of coated laminate into specified membrane sizes. The edges of all membranes shall be cut so that they do not deviate more than 6 inches from a perpendicular line drawn from corner to adjacent corner.

3.4.1 Joints. All joints shall be single lap joints which are vulcanized, or bonded with adhesive. Membrane shall be cleaned of any excess adhesive resulting from lap joint construction.

3.4.1.1 Joint width. The width of all joints shall be not less than 3 inches nor more than 4 inches.

3.4.1.2 Joint directions. Joints used in the fabrication of the membrane shall be constructed parallel to the length of the membrane except that not more than 2 transverse joints may be constructed in any 100 continuous feet of laminate between parallel joints (single run of coated fabric). However, no transverse joint shall be constructed within 15 feet of any other transverse joint and no transverse joint shall be constructed in an area 36 feet wide by 100 feet long, located symmetrically about the longitudinal center line of the type I panel.

3.4.1.3 Joint strength. Joint peel and breaking strengths shall conform to the requirements as prescribed for coated laminate joints in table II.

3.5 Color. The color of the finished membrane shall be black.

3.6 Marking. The membrane shall be identified in accordance with MIL-STD-130. In addition, each dimension of the membrane shall be clearly marked to the nearest foot with 4 inch high numerals and arrows indicating the length and direction of the dimension. Dimensional markings shall be placed on the uppermost horizontal surface of the folded (prepared for delivery) membrane. All markings shall be made with white, waterproof ink.

3.7 Dimensions. Membrane dimensions shall be as shown in table III.

TABLE III. Membrane dimensions (in feet).

Dimension	Runway membrane type I		Taxiway membrane type II		Splicing membrane type III	
	Mininum	Maximum	Minimum	Maximum	Minimum	Maximum
Width	66	67	36	37	2.98	3.02
Length	100	101	100	101	180	195

3.8 Type I, runway membrane. The runway membrane shall be furnished as a one-piece panel and shall contain not more than 23 longitudinal joints nor more than 8 transverse joints.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:09Z
Check the source to verify that this is the current version before use.

3.9 Type II, taxiway membrane. The taxiway membrane shall be furnished as a one-piece panel and shall contain not more than 12 longitudinal joints nor more than 4 transverse joints.

3.10 Type III, splicing membrane. The splicing membrane shall be furnished in a compact and uniformly wound roll and shall contain not more than 2 transverse joints. However, unjoined pieces of splicing membrane may be used to form a roll, provided no single piece is less than 75 feet in length. The dimensions of the roll shall be as shown in table III.

3.11 Workmanship. The finished membrane surface shall contain no excess adhesive and shall be free from bubbles, blisters, and wrinkles. The membrane shall have no holes or cracks in the surface. Except for joints and patches, the surface shall show no evidence of laps, laminations or included foreign material. The membrane surfaces shall be free of talc, oil, grease, dirt and other foreign matter and shall show no evidence of tackiness when tested as prescribed in 4.5.2.3.2.2.

3.11.1 Patches. Type I membrane shall contain not more than six patches in any one panel, except that no patches will be permitted in an area 36 feet wide by 100 feet long located symmetrically about the longitudinal center line of the panel. Type II membrane shall contain not more than four patches. Type III membrane shall contain no patches.

3.11.1.1 Patching. The maximum size of a patched area, where permitted, shall be not more than 150 square inches. Patches shall overlap the damaged area not less than 3 inches and the adhesion strength shall be equal to that specified for membrane joints. Holes, cuts, and tears shall be patched on both sides of the membrane. Scuffs and abrasions shall be patched on the damaged side only.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Classification of inspections. Inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3).

b. Quality conformance inspection (see 4.4).

c. Inspection of packaging (see 4.6).

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:09Z
Check the source to verify that this is the currentversion before use.

4.3 First article inspection.

4.3.1 Examination. The first article membrane shall be examined as specified in 4.5.1. Presence of one or more defects shall be cause for rejection.

4.3.2 Tests. The first article base fabric, coated laminate, and membrane shall be tested as specified in 4.5.2. Failure of any test shall be cause for rejection.

4.4 Quality conformance inspection.

4.4.1 Sampling. Sampling for examination and tests shall be in accordance with 4.4.1.1, 4.4.1.2, and 4.4.1.3.

4.4.1.1 Base fabric. A sample of base fabric shall consist of 2 randomly chosen strips. Each strip shall be 3 feet long and full mill width. The samples shall be selected from each 5,000 square yards, or fraction thereof, of base fabric used in the manufacture of the membrane.

4.4.1.2 Coated laminate. The sample and lot of coated laminate shall be as specified for the base fabric (see 4.4.1.1), except that the sample shall be 9 feet long, and when the laminate is being used in the fabrication of types I and II membranes, one strip shall contain a transverse joint midlength of the strip.

4.4.1.3 Membrane.

4.4.1.3.1 Unit of product. For purposes of inspection a completed type I, II or III membrane shall be considered a unit of product.

4.4.1.3.2 Sampling. Sampling for examination and tests of the membrane shall be in accordance with MIL-STD-105, inspection level S-4.

4.4.2 Examination.

4.4.2.1 Coated laminate. Samples selected in accordance with 4.4.1.2 shall be examined in accordance with 4.5.1. One major defect or two minor defects shall be cause for rejection of the material represented by the sample.

4.4.2.2 Membrane. Samples selected in accordance with 4.4.1.3.2 shall be examined as specified in 4.5.1. AQL shall be 0.4 percent defective for major defects and 1.0 percent defective for minor defects.

4.4.3 Tests.

4.4.3.1 Base fabric. Samples of the base fabric selected in accordance with 4.4.1.1 shall be tested as specified in 4.5.2.1. Failure of any test shall be cause for rejection of the entire lot represented by the sample.

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:09Z
Check the source to verify that this is the current version before use.

4.4.3.2 Coated laminate. Samples of coated laminate selected in accordance with 4.4.1.2 shall be tested as specified in 4.5.2.2. Failure of any test shall be cause for rejection of the entire lot represented by the sample.

4.4.3.3 Membrane. Samples of the membrane selected in accordance with 4.4.1.3.2 shall be tested as specified in 4.5.2.3. Failure of any test shall be cause for rejection of the entire lot represented by the sample.

4.5 Inspection procedure.

4.5.1 Examination. Each sample of coated laminate and membrane shall be examined for the defects marked "X" in the appropriate column of table IV.

TABLE IV. Examination schedule.

Coated laminate	Membrane		Defect	Requirement paragraph
	Panels	Rolls		
	Types I and II	Type III		
			Major	
X	X	X	101. Material not as specified.	3.3
-	X	X	102. Membrane not fabricated as a lamination.	3.3, 3.3.2
X	X	X	103. Coating not even, complete or properly cured.	3.3, 3.3.2.1
-	X	-	104. Deviation of edges more than as specified.	3.4
-	X	X	105. Joints not fabricated as specified.	3.4.1
-	X	X	106. Joint width less than minimum specified.	3.4.1.1
X	X	X	107. Color not as specified.	3.5
-	X	X	108. Marking not as specified.	3.6
-	X	X	109. Dimensions not as specified.	Table III
-	X	X	110. Quantity of joints more than specified.	3.4, 3.8, 3.9 & 3.10
X	X	X	111. Workmanship not as specified.	3.11
			Minor	
-	X	X	201. Transverse joint proximity less than specified.	3.4.1.2
-	X	X	202. Excess adhesive on joints or membrane not properly treated or cured.	3.4
-	-	X	203. Rolled membrane not compactly and uniformly wound.	3.10

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:09Z
Check the source to verify that this is the current version before use.

4.5.2 Tests.

4.5.2.1 Base fabric. Each sample of base fabric shall be tested in accordance with Fed. Test Method Std. No. 191 by the methods shown on table V, except as noted. Failure to conform to any of the applicable physical requirements of table I shall constitute failure of the corresponding test.

TABLE V. Tests of base fabric.

Property	Test method
Weight	5041
Melting point of yarns	ANSI/ASTM D 789
Yarns per inch	5050
Breaking strength (grab)	5100

4.5.2.2 Coated laminate.

4.5.2.2.1 Preparation of specimens. Join the 2 strips with a longitudinal joint. The joint shall be formed by joining two warpwise edges of the coated laminate strips. Test specimens shall be cut from the interior area of the piece formed by the joining of the strips. Six joint strength specimens shall be cut from the joint area only and each specimen shall be a 4 inch by 9 inch rectangle with the joint at the center of the 9-inch dimension. Three of the joint specimens shall be immersed for 48 hours in distilled water maintained at 77° F. and then blotted dry to prevent slippage in the clamps just prior to test. The other three specimens shall be aged for 72 hours at 212° F ± 2° F, allowed to cool to room temperature, and the peel strength determined. A segment of the formed piece at least 3 feet long and full mill width (from either longitudinal edge to longitudinal joint) shall be completely immersed for 24 hours in JP-4 jet fuel conforming to MIL-T-5624. Test specimens shall then be cut from the interior area of the segment. All specimens, except jet fuel resistance, wet joint strength, and peel strength specimens, shall be conditioned before test as specified in Fed. Test Method Std. No. 191.

4.5.2.2.2 Test methods. The specimens shall be tested in accordance with Fed. Test Method Std. No. 191, as shown in table VI, unless otherwise indicated. Failure of any specimen to conform to any physical requirement of table II shall constitute failure of the test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:09Z
Check the source to verify that this is the current version before use.

TABLE VI. Coated laminate test methods.

Property	Test method
Weight	5041
Breaking strength[1/]	5100
Elongation	5100
Tear strength	5134
Jet fuel resistance (modified grab method)	ANSI/ASTM D 1682
Flame resistance	5903
Heat resistance	5100
Hydrostatic pressure resistance	5516
Blocking resistance: High temperature	5872
Cracking resistance: Low temperature	5874
Peel strength: Dry[2/]	ANSI/ASTM D 1151 & D 903
Wet	ANSI/ASTM D 903

1/ Except that the distance between the clamps shall be 6 inches at the start of the test when testing joints.
2/ Test after 72 hours at 212° F. plus or minus 2° F.

4.5.2.3 Membrane.

4.5.2.3.1 Preparation of specimens. Specimens for use in determining joint breaking and peel strength shall be obtained from the joint area and shall be 4 inches by 9 inches. Specimens for use in determining tackiness shall be 3 inches by 6 inches and shall not be obtained from joint areas of the membrane.

4.5.2.3.2 Test methods.

4.5.2.3.2.1 Breaking and peel strength. Specimens shall be tested in accordance with the procedures prescribed for breaking and peel strength in table VI.

4.5.2.3.2.2 Tack. The tackiness of the membrane shall be determined by folding the specimen upon itself and applying a pressure of 2 pounds per square inch at 160° F., plus or minus, 2° F. for 4 hours. When the pressure is released at the end of this time the material shall be examined. Evidence of the material adhering to itself shall constitute failure of this test.

4.6 Inspection of packaging.

4.6.1 Preproduction pack inspection.

4.6.1.1 Examination. Examine the preproduction pack for the defects specified in 4.6.2.3. Presence of one or more defects shall be cause for rejection.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:09Z
Check the source to verify that this is the current version before use.

4.6.2 Quality conformance inspection of pack.

4.6.2.1 Unit of product. For the purpose of inspection, a completely processed membrane prepared for shipment, shall be considered a unit of product.

4.6.2.2 Sampling. Sampling for examination shall be in accordance with MIL-STD-105.

4.6.2.3 Examination. Samples selected in accordance with 4.6.2.2 shall be examined for the following defects. The inspection level shall be S-2. AQL shall be 4.0 percent defective.

112.	Materials, methods and containers not as specified. Each incorrect material, method or container shall be considered one defect.
113.	Weight and size of shipping container exceeds weight and size limitations of applicable container specification.
114.	Marking illegible, incorrect or incomplete.
115.	Types I and II membranes not folded and pleated as specified.
116.	Types I and II membrane ends not sealed as specified.
117.	Strapping and tape not as specified.

5. PACKAGING

5.1 Preproduction pack. The contractor shall furnish a preproduction pack for examination and test within the time frame specified (see 6.2) to prove, prior to starting production packaging, that the applied preservation, packing, and marking comply with the packaging requirements of this specification (see 6.4). Examination shall be as specified herein and shall be subject to the surveillance and approval by the Government (see 6.4).

5.2 Preservation.

5.2.1 Type I, runway membrane, 66 by 100 feet. (NSN 5680-00-921-5809). Areas 3 feet wide on both sides of each end of the membrane for the full width of the membrane (66 feet) shall be cleaned of all dirt, powders, curing compounds and other foreign materials that constitute a hindrance to the construction of adhesive joints. The cleaned areas shall be covered with paper conforming to PPP-B-1055, class E-1. The paper shall be sealed to the membrane at all edges with tape conforming to PPP-T-60, class 1. The membrane shall be accordion pleated in pleats 43 inches plus or minus 2 inches wide in the direction that parallels the 100 foot dimension. The folded membrane runway shall be accordion pleated in pleats 43 inches plus or minus 2 inches wide in the direction that parallels the 66 foot dimension to form a compact 43 inches plus or minus 2 inches by 43 inches plus or minus 2 inches bundle. The folded and pleated bundle shall then be restrained with two lengthwise and two girthwise straps conforming to PPP-S-760, type II, 5/8-inch by 0.030-inch and secured with a metal sealed joint or buckle type seal to form a compact bundle of minimum cube.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:09Z
Check the source to verify that this is the current version before use.

5.2.2 Type II, taxiway membrane, 36 by 100 feet. (NSN 5680-00-921-5810). The membrane shall be cleaned, covered, folded, pleated and strapped as specified in 5.2.1.

5.2.3 Type III, splicing membrane, 3 by 180 feet. (NSN 5680-00-921-6512). The membrane shall be cleaned of all dirt, powders, curing compounds and other foreign materials. The membrane shall be compactly and uniformly wound on a wood core having an inside diameter of 3 inches plus 1/16 inch, minus 0 inch, with a 1 inch inside diameter hollow core. The length of the core shall be equal to the finished width of the membrane. The roll shall be secured with four strips of tape conforming to PPP-T-60, class 1, 2-inch width. Tape shall be of 12-inch length, with 6 inches on each side of the end of the roll and shall be uniformly spaced over the width of the roll. The taped roll shall be completely wrapped in barrier material conforming to MIL-B-22191, type III, 6 mil. thickness. Seams shall be sealed with tape conforming to PPP-T-60.

5.3 Packing.

5.3.1 Membrane runway and membrane taxiway. The membrane runway and membrane taxiway preserved as specified in 5.2, shall be packed in a container as shown in figure 1.

5.3.2 Membrane splicing roll. The membrane splicing roll, preserved as specified in 5.2 shall be packed in a nailed wood cleated-plywood box conforming to PPP-B-601, overseas type, style optional, in quantities not to exceed the weight limitation of the containers.

5.4 Marking. Marking shall be in accordance with MIL-STD-129. For purposes of preservation and packing level marking, level A/A shall be used (see 6.5).

6. NOTES

6.1 Intended use. The membrane surfacing, is intended for use as a temporary dustproof, waterproof airfield surfacing material. Type I membrane is intended for surfacing runways; type II is for surfacing taxiways; and type III is for joining runway or taxiway sections and for patching holes or tears in the membrane.

6.2 Ordering data. Acquisition documents should specify the following:

a. Title, number and date of this specification.

b. Type of membrane, surfacing required (see 1.2).

c. When a first article is required for inspection and approval and the number of units required (see 3.2, 4.3 and 6.3).

d. Time frame required for submission of preproduction pack (see 5.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:09Z
Check the source to verify that this is the current version before use.

6.3 First article. When a first article inspection is required, the item will be tested and should be a first produced model. The first article should consist of one or more units. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examinations, tests, and approval of the first article.

6.4 Preproduction pack. Any changes or deviations of production packs from the approved preproduction pack will be subject to the approval of the contracting officer. Approval of the preproduction pack will not relieve the contractor of his obligation to preserve, pack, and mark the membranes in accordance with this specification.

6.5 Preservation and packing levels. The nature of these items is such that only a single level of preservation, and packing is required. This A/A level represents both the maximum and minimum acceptable level of protection.

6.6 Accessories. DA Supply Catalog 5680-97-CL-E01 should be consulted for accessories required for use with the types of membranes described in this specification.

6.7 Recycled material. It is encouraged that recycled material be used, when practical, as long as it meets the requirements of this specification (see 3.3).

Custodians:
Army - ME
Navy - YD
Air Force - 99

Review activity:
Air Force - 84

User activity:
Army - CE

Preparing activity:
Army - ME

Project 5680-0103

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:09Z
Check the source to verify that this is the current version before use.

FIND NO.	QTY	NOMENCLATURE
1	1	BASE, PLYWOOD NN-P-530; GROUPS A OR B, CONFORMING TO PS-51
		TYPE I, GRADE 3-4 OR PS 1 WITH EXTERIOR GLUE, GRADE C-D; 3/4
		INCH THICKNESS.
2	2	SKID LUMBER MIL-STD-731 CL II 3 X 4 NOM. SIZE (2 X 4 PLUS
		1 X 4 RUBBING STRIP ACCEPTABLE) BEVEL LOWER 3/4 INCH ON 45°
3	1	CAP CONFORMING TO PPP-B-601 OVERSEAS TYPE, STYLE A WITH
		FOLLOWING EXCEPTIONS OF FIND NO'S 4 AND 5 DESCRIBED BELOW.
4	5	ALL PLYWOOD PANELS NN-P-530; GROUPS A OR B, CONFORMING
		TO PS-51 TYPE I GRADE 3-4 OR PS 1 WITH EXTERIOR GLUE, GRADE
		C-D; 3/8 INCH THICKNESS.
5	25	ALL CLEATS ON END PANELS, SIDES, AND TOP TO BE NOM. 1 X 4.
6	6	STRAPPING QQ-S-781 TYPE I, HEAVY DUTY, FINISH B, 1-1/4" x CL 031"
7	AR	STAPLES, 1-3/8" CROWN WIDTH, 3/4" LONG, GALVANIZED STEEL.
8	AR	7d (MIN.) CEMENT COATED COOLERS OR SINKERS, FF-N-105 TYPE II
		STYLE 7 OR 8.
9	AR	8d CEMENT COATED COOLERS OR SINKERS — SEE NOTE 5 BELOW.

NOTES:
1. CONSTRUCTION OF PANELS IN ACCORDANCE WITH REQUIREMENTS OF PPP-B-601.
2. HEIGHT TO BE DEPENDENT UPON MEMBRANE CONTAINED.
3. CONTAINER FOR RUNWAY WILL APPROXIMATE 35 INCHES IN HEIGHT I.D., CONTAINER FOR TAXIWAY WILL APPROXIMATE 22 INCHES IN HEIGHT I.D.
4. NET WT. OF CONTENTS: (NOMINAL) RUNWAY, 2060 LBS, TAXIWAY, 1060 LBS.
5. NAILING OF BASE TO SKIDS; CEMENT COATED COOLERS OR SINKERS OF SUFFICIENT LENGTH TO ALLOW CLINCH OF MIN 1/8 INCH. IF SKIDS ARE MADE OF TWO PIECE CONSTRUCTION, SECURE BEVELED RUBBING STRIP TO NOM. 2 X 4 SKID WITH 8d CEMENT COATED COOLERS OR SINKERS.
6. TOP PANEL SECURED IN PLACE WITH CLEATS ON INSIDE.
7. STRAPPING SHALL BE DRAWN TO MAXIMUM PERMISSIBLE TENSION FOR ALL BANDS.
8. STRAPPING SHALL BE CENTERED ON 1 X 4 CLEATS.

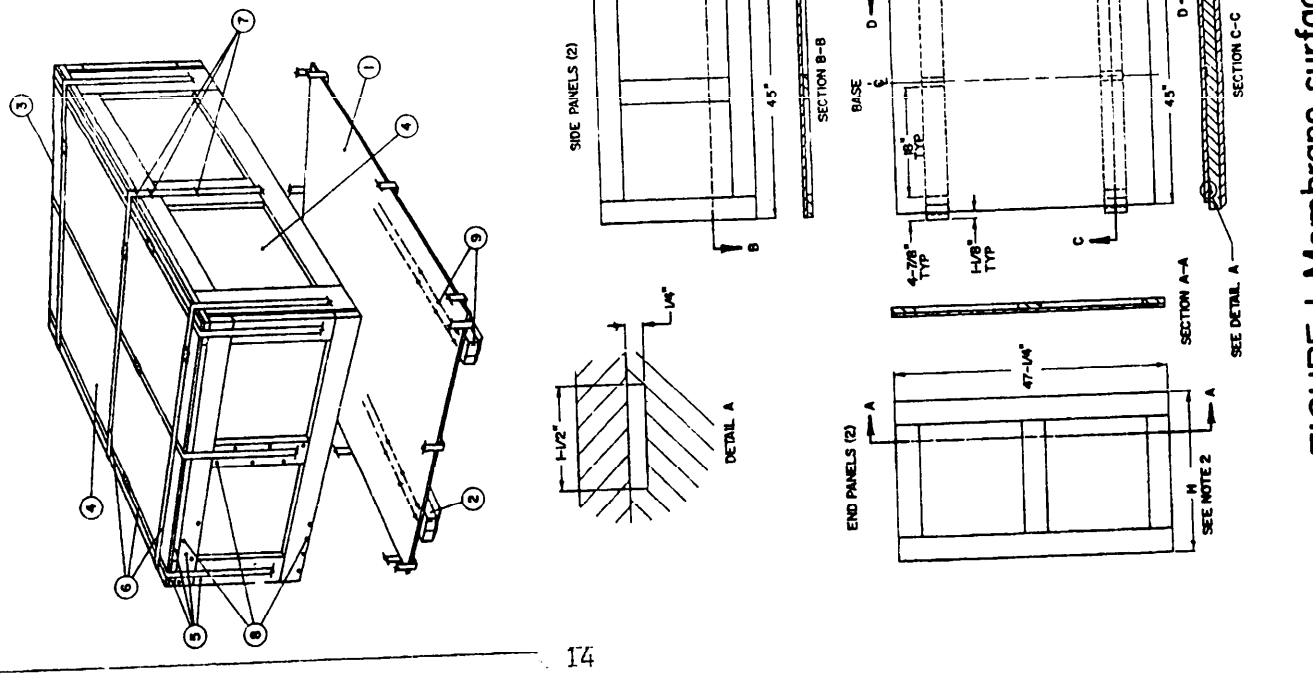


FIGURE 1. Membrane surfacing level A pack.

X-1597B

Source: https://assist.dla.mil -- Downloaded: 202610-26T04:09Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
US Army Mobility Equipment Research & Development Command
ATTN: DRDME-DS
Fort Belvoir, VA 22060

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:09Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ USER
	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:09Z
Check the source to verify that this is the current version before use.