DDD-B-421d
JANUARY 6, 1960
SUPERSEDING
Int. Fed. Spec. DDD–B–00421c(GSA–FSS)
November 4, 1959 and
DDD–B–421b
August 21, 1953

FEDERAL SPECIFICATION

BLANKET, BED, OTHER THAN ALL WOOL

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope.—This specification covers the requirements for blankets other than all wool.

1.2 Classification.

1.2.1 *Types, classes and sizes.* — Blankets covered by this specification shall be of the following types, classes, and sizes, as specified (see 6.3):

Type I.—All cotton
Class 1.—Twill (double filling)
Sizes:
1.—30 by 40 inches
2.—60 by 84 inches
3.—66 by 84 inches
4.—66 by 90 inches
Class 2.—Plain (single filling)
Sizes:
1.—70 by 84 inches
2.—72 by 90 inches

Type II.—Cotton warp—wool filling
Class 1.—Twill (double filling)
Sizes:
1.—60 by 80 inches
2.—66 by 90 inches
3.—72 by 90 inches
4.—66 by 84 inches

Type III. — Blended nylon-wool-rayon-cotton and other fibers
Class 1.—Twill (double filling)
Sizes:
1.—60 by 80 inches
2.—66 by 90 inches
3.—72 by 90 inches
4.—66 by 84 inches

2. APPLICABLE SPECIFICATIONS, STANDARDS, AND OTHER PUBLICATIONS

2.1 Specifications and standards.—The following specifications and standards of the issues in effect on date of invitation for bids form a part of this specification:

Federal Specifications:

L–P–406 — Plastics, Organic; General Specifications, Test Methods.
R–N–91 — Naphthalene; Balls and Flakes.
V–T–276—Thread, Cotton.
CCC–T–191—Textile Test Methods.
DDD–L–20—Label, Cotton (Woven General Use).
PPP–B–591 — Boxes, Fiberboard, Wood Cleated.
PPP–B–601—Boxes, Wood, Cleated Plywood.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

PPP–B–621—Boxes, Wood, Nailed and Lock-Corner.

PPP–B–636—Boxes, Fiber.

PPP–T–60 — Tape; Pressure Sensitive Adhesive Waterproof—For Packaging and Sealing.

Federal Standards:

Fed. Std. No. 102—Preservation, Packaging and Packing Levels (Civilian Agencies).

Fed. Std. No. 123—Marking for Domestic Shipment (Civilian Agencies).

Fed. Std. No. 751—Stitches; Seams; and Stitching.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications, Standards, and Handbooks and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington 25, D. C.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, Los Angeles, Seattle, and Washington, D. C.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications, Standards, and Handbooks from established distribution points in their agencies.)

Military Specifications:

MIL–B–10377—Box, Wood, Cleated, Veneer, Paper Overlaid.

MIL–L–10547 — Liners, Case, Waterproof.

MIL–P–3803 — Plastic, Polyethylene, Molded and Extruded Shapes, Sheets and Tubing.

Military Standards:

MIL–STD–105 — Sampling Procedures and Tables for Inspection by Attributes.

MIL–STD–129 — Marking for Shipment and Storage.

MS16686—Medical Services Symbol.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 **Other publications.** — The following publication forms a part of this specification. Unless otherwise indicated, the issue in effect on date of invitation for bids shall apply.

Color Association of the United States, Inc.

U. S. Army Standard Color Card for the Official Colors for Arms and Services.

(Application for copies should be addressed to the Color Association of the United States, Inc., 200 Madison Avenue, New York 16, N. Y.)

Rules and Regulations under the Wool Products Labeling Act of 1939.

(Application for copies should be addressed to the Superintendent of Documents, Government Printing Office, Washington 25, D. C. Price may be obtained from the Superintendent of Documents.)

3. REQUIREMENTS

3.1 Standard sample. — Unless otherwise specified, the blankets shall be equal to the standard sample in all respects not specifically covered by this specification (see 6.2).

3.2 Preproduction sample.—Unless otherwise specified, before production is commenced the contractor shall submit for approval to the contracting officer a sample finished blanket he proposes to furnish (see 6.3).

3.3 Materials.

3.3.1 *Cotton yarns.*—The cotton yarns shall be evenly spun from cleaned cotton of a grade and length of staple to meet the requirements for the finished blankets.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

3.3.2 *Wool yarns.*—The wool yarns for type II blankets shall be made from cleaned fleece, pulled, reprocessed wools or wool noils or any combination thereof and shall be of a grade not lower than 44s U. S. Standard. The wool content of the filling yarn, when tested as specified, shall analyze not less than 99 percent.

3.3.3 *Yarns of nylon-wool-rayon-cotton and other fibers.* — The blended fiber yarns for type III blankets shall be made from cleaned fleece, pulled, reprocessed wools or wool noils, nylon, rayon, cotton and other fibers as follows: Not less than 80 percent wool not lower in grade than 44s U. S. Standard. The reprocessed-wool content shall not exceed 50 percent of the wool used in the blend. Not less than 10 percent nylon fibers and not more than 10 percent rayon, cotton and other fibers.

3.3.4 *Thread.*

3.3.4.1 *Thread for overedge stitching and attaching labels.*—The thread for overedge stitching the blanket and stitching on labels shall be cotton thread conforming to the requirements for type IC1 or IC2, ticket number B, 3-ply of Federal Specification V–T–276.

3.3.4.2 *Thread for binding stitching.* — When binding is specified (see 6.3), the thread used for stitching binding shall be thread, cotton, ticket No. 0, 3-ply, conforming to type IC1 or IC2 of Federal Specification V–T–276.

3.3.4.3 *Color, thread.* — The color of the thread shall match the color of the standard sample blanket and the colorfastness shall be as specified in 3.4.4.3.

3.3.5 *Binding.* — When fabric binding is specified (see 6.3) the binding shall be rayon or acetate satin weighing not less than 4 ounces per square yard. The binding shall be not less than 4 inches wide when finished, with uniformly constructed edges on both sides, or shall have edges cut parallel to the warp and shall be of sufficient width to meet the requirements of 3.12.1.2.2. The color of the binding shall approximate that of the standard shade blanket. The colorfastness shall be as specified in 3.4.4.3.

3.3.6 *Markings.*

3.3.6.1 All markings specified herein shall show colorfastness as specified in 3.4.4.3 and shall show good fastness to one laundering when tested as specified in 4.4.

3.3.6.2 *Letters "U" and "S".*—When specified (see 6.3), each blanket shall have the letters "US" in outline block letters, 4 inches ± ⅛ inch high by 3¼ inches ± ⅛ inch wide in the center. The overall width of the lettering shall be 7¼ inches ± ¼ inch.

3.3.6.3 *Caduceus.* — When specified (see 6.3), each blanket shall have a caduceus 6 inches ± ⅛ inch high by 6¼ inches ± ⅛ inch wide, centered between the block letters "U" and "S" 2 inches ± ⅛ inch high by 1½ inches ± ⅛ inch wide conforming to Military Standard MS 16686 (see 2.1).

3.3.6.4 *Color of letters and caduceus.*

3.3.6.4.1 *Color of letters and caduceus for type I, class 1, size 1 blankets.*—The color shall be cable No. 65017 as shown in the U.S. Army Color Card for the Official Colors for Arms and Services (see 2.2). Colors shall be stencilled with a marking medium and the colorfastness shall be as specified in 3.4.4.3.

3.3.6.4.2 *Color of letters and caduceus for all other types, classes and sizes.*—The color shall be applied by direct printing, stamping, or stencilling with a black marking medium. The colorfastness shall be as specified in 3.4.4.3.

3.3.6.5 *Identification label.*—Each blanket shall have a 2-inch ± ¼-inch by 3-inch ± ¼-inch label attached 2 inches by ½ inch from

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

each edge, on the back of the right-hand corner of the blanket as the blanket is viewed face up. The label shall be attached by stitching, using a 301 stitch type, and there shall be not less than 10 stitches per inch. The label shall be in accordance with Federal Specification DDD–L–20 except that mildew resistance is not required. The label shall contain the following information with size of letters as indicated:

Nomenclature (10-point letters)
Contract number (8-point letters)

In addition, each blanket shall be labelled in accordance with the Wool Products Labeling Act of 1939. The legend may be incorporated in the identification label.

3.4 Color.

3.4.1 *Type I blankets.*—Blankets shall be bleached, white, or dyed, as specified (see 6.3).

3.4.2 *Types II and III blankets.*—When white is specified, the color shall be unbleached white consistent with the best mill practice for good grade white wool. The wool shall be so selected as to avoid the presence of black hairs. The black-hair content of the finished blanket shall be not more than that shown by the standard sample. When color is required, it shall be as specified (see 6.3).

3.4.3 *Color matching.*—The color of all dyed textile components shall match the approved standard shade under natural (north sky) daylight or artificial daylight having a color temperature of 7500° Kelvin and shall be a good approximation to the standard shade under incandescent lamplight at 2800° Kelvin.

3.4.4 *Colorfastness.*

3.4.4.1 *Type I blankets (fabric).*—When colors are specified, the finished blanket shall show fastness to laundering, bleaching, and crocking equal to or better than the standard sample. If no standard sample is available for colorfastness, the blanket shall show good fastness to laundering, bleaching and crocking. Fastness shall be determined as specified in 4.4.


3.4.4.2 *Types II and III blankets (fabric).*—When colors are specified, the finished blanket shall show fastness to laundering and crocking equal to or better than the standard sample or if no standard sample is available for colorfastness, the blanket shall show good fastness to laundering and crocking. Fastness shall be determined as specified in 4.4.

3.4.4.3 *Component materials.*—The colorfastness properties for the component materials used, as applicable, thread, binding and marking, shall be equal to those required for the blanket with which they are used.

3.5 Physical requirements. — The finished blanket shall conform to the requirements specified in table I.

3.6 Weave.

3.6.1 *Class 1.*—Class 1 blankets shall be double woven, having a twill face of one up, three down and a twill back of three up, one down using two sets of filling yarns and one set of warp yarns (see fig. 1). All class 1 blankets shall have woven selvages ¼, + ⅛ – 0 inch.

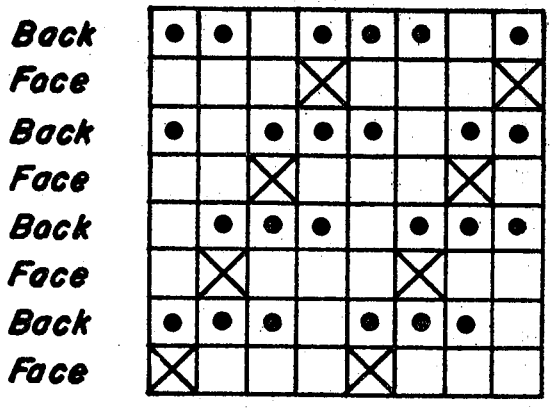

–Weave diagram

FIGURE 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

TABLE I.—*Physical requirements*

Type	Class	Size	Fiber	Blanket size, minimum		Weight per blanket		Yarns per inch, minimum		Breaking strength, grab method, minimum	
				Width	Length	Maximum	Minimum	Warp	Filling	Warp	Filling
				Inches	*Inches*					*Pounds*	*Pounds*
I	1	1	Cotton	30	40	9.0 ozs.	7.8 ozs.	30	35	23	15
	1	2		60	84	3.2 lbs.	3.0 lbs.	37	36	30	25
	1	3		66	84	3.5 lbs.	3.3 lbs.	37	36	30	25
	1	4		66	90	3.7 lbs.	3.4 lbs.	37	36	30	25
	2	1		70	84	1.3 lbs.	1.2 lbs.	35	24	28	15
	2	2		72	90	1.7 lbs.	1.5 lbs.	27	28	27	17
II	1	1	Cotton warp, wool filling	60	80	3.45 lbs.	3.3 lbs.	52	40	38	36
	1	2		66	90	4.3 lbs.	4.1 lbs.	52	40	38	36
	1	3		72	90	4.6 lbs.	4.4 lbs.	52	40	38	36
	1	4		66	84	4.0 lbs.	3.8 lbs.	52	40	38	36
III	1	1	Blended: Wool-rayon-cotton and other fibers	60	80	3.4 lbs.	3.3 lbs.	22	20	35	30
	1	2		66	90	4.4 lbs.	4.1 lbs.	22	20	35	30
	1	3		72	90	4.6 lbs.	4.4 lbs.	22	20	35	30
	1	4		66	84	4.0 lbs.	3.8 lbs.	22	20	35	30

3.6.2 *Class 2.*—Class 2 blankets shall have a plain weave with one warp and one filling, woven with selvages on the side ¼, + ⅛ – 0 inch.

3.7 Shrinkage.

3.7.1 *Type I blankets.*—The total shrinkage for type I blankets shall not exceed 11 percent in the warp and 6 percent in the filling, when a sample is subjected to laundering and then to dry cleaning when tested as specified in 4.4.

3.7.2 *Types II and III blankets.*—The total shrinkage for types II and III blankets shall not exceed 10 percent in either the warp or filling direction when a sample is subject to laundering and then to dry cleaning when tested as specified in 4.4.

3.8 Fiber content.

3.8.1 *Type I blankets.*—The fiber content of type I blankets shall be 100 percent cotton.

3.8.2 *Type II blankets.*—The fiber content of type II blankets shall be not less than 80 percent wool of any combination thereof and not more than 20 percent cotton when tested as specified in 4.4.

3.8.3 *Type III blankets.*—The fiber content of type III blanket shall be not less than 80 percent wool, not more than 10 percent rayon, cotton and other fibers, and not less than 10 percent nylon when tested as specified in 4.4.

3.9 Nonfibrous materials. — Sizing, finishing, and other nonfibrous materials shall not exceed 5 percent when tested as specified in 4.4.

3.10 Moth repellency.—The blankets shall have a properly applied silicofluoride moth-

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

repellent treatment so that the animal fiber will have a minimum of 0.5 percent fluorine when tested as specified in 4.4.

3.11 Finish.—The blankets of all types and classes shall have a finish equal to the standard sample with respect to nap and hand.

3.12 Construction.

3.12.1 *Stitches, seams, and stitching.*

3.12.1.1 *Type I blankets.*—Unless otherwise specified, type I blankets shall be cut to size and the corners slightly rounded. The edges shall be overstitched ¼ inch wide with 16 to 20 stitches per inch of thread, cotton, ticket No. B, 3-ply, conforming to Federal Specification V–T–276 stitch-type 505 and stitching type EFd–1 conforming to Federal Standard No. 751. The ends of the overedge stitching shall be locked.

3.12.1.2 *Types II and type III blankets.*—The cut ends of the blankets shall be finished by overedge stitching, binding with fabric, or by turning under and hemming (binding) ½ inch as specified (see 6.3).

3.12.1.2.1 *Overedge stitching for types II and III blankets.*—When specified (see 6.3), the cut edges of the finished blankets shall be overedge stitched ¼ inch wide with 16 to 20 stitches per inch of thread, cotton, ticket No. B, 3-ply, conforming to Federal Specification V–T–276 and stitch type 505 and stitching type EFd–1 conforming to Federal Standard No. 751. The ends of the overedge stitching shall be locked.

3.12.1.2.2 *Binding stitching.*—Satin binding, when specified (see 6.3), shall be as specified in 3.3.5 and shall be attached with two rows of stitching ¼ inch apart, 1/16 to ⅛ inch from edge, using 6 to 8 stitches per inch of thread, cotton, ticket No. 0, 3 ply, conforming to Federal Specification V–T–276 stitch type 301 conforming to Federal Standard No. 751. Seam type shall be BSa2 when a binding with woven edges is used, and type BSc-2 on cut binding with stitches ⅛ to 3/16 inch from edge. The turnunder shall be ¼ inch wide and shall be caught in the outer row of stitching, and the finished binding shall finish 4 inches of total exposed width. The ends of the binding shall have a 1- ± ⅛-inch turnunder. The stitching shall be backstitched ½ to 1 inch at the ends.

3.12.1.2.3 *Turned-end and hemmed stitching for types II and III blankets.*—The ends shall be turned under ½ ± ⅛ inch, hemmed ½ ± ⅛ inch and sewn with 2 rows of stitching ¼ inch apart using 6 to 8 stitches per inch of thread, cotton, ticket No. 0, 3 ply, conforming to Federal Specification V–T–276 stitch type 301 specified in Federal Standard No. 751. The stitching shall be backstitched ½ to 1 inch at the ends.

3.13 Workmanship.—The finished blanket shall conform to the quality and grade of product established by this specification. Occurrence of defects shall not exceed the levels set by the applicable acceptable quality levels.

4. SAMPLING, INSPECTION, AND TEST PROCEDURES

4.1 Contractor's inspection responsibility.—Unless otherwise specified herein, the supplier is responsible for the performance of all inspection requirements prior to submission for Government inspection and acceptance. Except as otherwise specified, the supplier may utilize his own facilities or any other commercial laboratory acceptable to the Government. Inspection records of the examination and tests shall be kept complete and available to the Government as specified in the contract or order.

4.2 Preacceptance inspection.

4.2.1 *Preproduction sample inspection.*—The preproduction sample submitted in accordance with 3.2 shall be visually inspected for appearance, color, and finish. If required

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

by the contracting officer, the sample shall be tested for physical and chemical properties in accordance with the methods shown in table IV.

4.3 Inspection for acceptance. — Except when otherwise specified by Civil agencies, inspection shall be in accordance with Military Standard MIL–STD–105 except where otherwise indicated.

4.3.1 *Inspection of components.*—In addition to the quality assurance provisions of the subsidiary specifications, inspection shall be performed on components and materials listed in 4.3.1.1 and 4.3.1.2.

4.3.1.1 *Examination of components.*

4.3.1.1.1 *Wool.* — Examination for grade shall be performed visually by comparison with the applicable U. S. Standard. In the event of a dispute resulting from the above comparison, the grade shall be determined by a width (wedge) method approved by the Government.

4.3.1.1.2 *Fleece or pulled wool.* — These wools shall be examined in scoured form prior to dyeing, picking, or carding. The examination for grade shall be performed on a composite sample of 1 pound of the component for each 10,000 pounds or fraction thereof in the lot. The composite sample shall be selected from not less than 10 percent of the bales or bags in the lot. The lot shall be unacceptable if the sample does not conform to the requirements of 3.3.2.

4.3.1.1.3 *Noils.*—Noils shall be examined prior to dyeing. The examination for grade shall be performed on a composite sample of 1 pound of the component for each 10,000 pounds or fraction thereof in the lot. Sampling shall be accomplished in the same manner as specified in 4.3.1.1.2.

4.3.1.1.4 *Reprocessed wool.*—These wools shall be examined for grade when reduced to a fibrous state prior to blending with other component fibers. Method of sampling and sample size shall be as specified in 4.3.1.1.2.

4.3.1.2 *Testing of components.* — Unless otherwise specified, testing shall be performed on the following components for the characteristics indicated, in accordance with Federal Specification CCC–T–191 wherever applicable and as listed in table III. The physical and chemical values specified in section 3 apply to the average of the determinations made on a unit of product for test purposes as specified in the applicable test method. The sample size shall be in accordance with table II. The lot shall be unacceptable if one or more units fail to meet any requirements specified.

TABLE II.

Lot size	Sample size
Less than 800	2
801 to 22,000	3
22,001 and over	5

4.3.1.2.1 *Filling yarn (type II blankets).*— The unit of product for test purposes shall be 2 ounces of the yarn. The lot size shall be expressed in units of 1 pound each.

4.3.1.2.2 *Thread (for binding and label).*— The unit of product for test purposes shall be 1 cone or spool of the thread. The lot size shall be expressed in units of 1 pound each.

4.3.1.2.3 *Satin binding material.*—The unit of product for test purposes shall be 9 linear yards of binding. The lot size shall be expressed in units of 1 linear yard each.

4.3.1.2.4 *Marking (caduceus).*—The markings shall be tested for colorfastness in accordance with colorfastness tests for the finished blanket specified in 4.4. The unit of product for test purposes shall be a caduceus applied to a piece of finished blanket fabric under same conditions as in production.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

TABLE III.

Characteristic	Specification reference	Test method	Number of determinations per sample unit	Results reported as
Thread:				
Material identification	3.3.4	Std. comm'l	1	Report material as found
Breaking strength	3.3.4	4100	20	Average of the 20 determinations to the nearest 0.1 pound
Thread:				
Color fastness to:				
(dyed thread only)				
Laundering	3.3.4.3	4610–4614	1	*Standard sample*—Satisfactory or unsatisfactory
Bleaching	3.3.4.3	5600	1	
Crocking	3.3.4.3	4650	1	
Filling yarn:				
(Type II Blankets)				
Wool content	3.3.2	2101	2	Average of the 2 determinations to the nearest 0.1 percent
(Type III Blankets)				
Wool content	3.3.3	[1]		
Satin binding material:				
Material identification	3.3.5	1500, 1510	1	Report material as found
Weave	satin (any repeat) 3.3.5	Visual	1	Pass or fail
Weight ozs. per sq. yd.	3.3.5	5041 [2]	5	Average of the 5 determinations to the nearest 0.1 ounce.
Color fastness to:				
(dyed binding only)				
Laundering	3.3.5	5614	1	When standard sample available—Satisfactory or unsatisfactory. No standard sample—Excellent, good, fair or poor
Bleaching	3.3.5	5600	1	
Crocking	3.3.5	5651	1	

[1] The contractor shall submit a certification with each lot that new cotton, rayon or nylon fibers were used and that percent and type of fiber content is in accordance with the requirements of this specification.

[2] Except that the specimen shall be any size of 2 square inches or more, without the limitations of method 5041.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

4.3.2 *In-process inspection.* — Inspection shall be made at any point or any phase of the manufacturing process to determine that:

(*a*) Only approved components are used.

(*b*) Fiber materials are blended in the proportions specified.

The Government reserves the right to exclude from consideration for acceptance any blankets for which in-process inspection has indicated nonconformance.

4.3.3 *Inspection of the end item.*

4.3.3.1 *Examination of the end item.*—Defects found during this examination shall be classified in accordance with list shown in 4.3.3.1.1, 4.3.3.1.2 and 4.3.3.1.3.

4.3.3.1.1 *Examination for workmanship.*—Each blanket shall be examined on both sides and visual defects classified as listed below. Each blanket shall be given a through-lighting examination toward a light source for holes, thin or weak areas. The defects found shall be counted regardless of their proximity to each other, except where two or more defects represent a single local condition of the cloth, in which case, only the more serious defect shall be counted. The unit of product for this examination shall be one blanket. The acceptable quality levels (AQL's) for this examination shall be 1.0 major and 4.0 total defects (major and minor combined) per 100 units (blankets). The sample size shall be based on level I, table III-A of Military Standard MIL–STD–105. The lot size shall be expressed in units of one blanket.

Defect	Classification	
	Major	Minor
Fabric defects:		
Hole, cut, or tear—Any	X	
Smash or clearly visible* mend—Any	X	
Broken or missing yarns—		
Two or more contiguous, 2 inches or more in length	X	
Two contiguous less than 2 inches in length or single more than 4 inches in length		X
Black hair content in excess of those contained in standard sample (applicable to types II and III white blankets only)	X	
Float or skips—		
Multiple, ½ inch or more in combined warp and filling directions	X	
Single, more than 4 inches long		X
Skips, any sequence of two or more, regardless of length		X
Thin, light, or open place—clearly visible*	X	
Abrasion mark, weak place—clearly visible*	X	
Coarse filling bar, heavy place—clearly visible*	X	
Coarse yarns, slub, slough-off, jerked-in filling—clearly visible*		X
Knot, large, extending from surface of blanket or resulting in clearly noticeable hard spot or bunch		X
Burr, shive, sisal or specks—clearly visible*		X
Selvage edge missing on either side	X	
Shade bar or dye streak, mixed filling—clearly visible*	X	
Spot or stain—		
1 inch or more in combined dimensions and clearly visible*	X	
Less than 1 inch in combined dimensions and clearly visible*		X
Tight yarn or edges—clearly noticeable tight areas or waviness		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

Defect	Classification	
	Major	Minor
Workmanship defects:		
Unfinished either one or both ends	X	
Needle chews—resulting in a weak place	X	
Seam or splice—blanket composed of two or more parts	X	
Scorch or burn—clearly visible*	X	
Wrong seam or stitch type		X
Loose stitch tension—resulting in an insecure or unsightly end	X	
Run-off—		
More than 1 inch	X	
One half inch but not more than 1 inch		X
Raw edge (including binding)—		
One inch or more	X	
Less than 1 inch		X
Finished ends:		
When overedge stitching is specified:		
Overedge stitching more than 5/16 inch or less than 3/16 inch		X
Less than sixteen overedge stitches per inch		X
Corners not rounded (type I blankets only)		X
When satin binding is specified:		
Stitching overrun, not securely anchored in binding		X
Note.—(Should be trimmed to ¾ inch and pulled back under binding).		
Less than two rows of stitching	X	
Stitching gage less than 3/16 inch or more than 5/16 inch		X
Binding not adequately turned under (when without woven edges)		X
Turnunder not caught in stitching		X
Less than eight stitches per inch		X
Total exposed width of binding less than 4 inches		X
When turnedunder ends are specified,		
Turnedunder less than ½ inch		X
Less than two rows of stitching	X	
Stitch gage less than 3/16 inch or more than 5/16 inch		X
Less than eight stitches per inch		X
Edge of binding on either corner of blanket not turned under at least 2 inches		X
Markings, and insignia (as specified):		
Missing, incorrect, illegible or wrong color	X	
Misplaced by more than 2 inches		X
Label insecurely attached or misplaced by more than 1 inch		X
Not labeled in accordance with the Wool Products Labeling Act		X
Shade and finishing defects:		
Off shade—blanket not within acceptable range	X	
Mottled or cloudy		X
Color of binding or thread does not blend with color of blanket		X
Degree and character of finish not equal to standard	X	
Unevenly napped, clearly visible*	X	
Resistance of nap to lifting with needle not equal to standard sample		X
Rancid or other objectionable odor	X	
Hand of blanket not equal to standard sample		X
Threads not trimmed		X
Unclean overall appearance		X

* At normal inspection distance (approximately 3 feet).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

4.3.3.1.2 *Examination for dimensions.* — Defects found during this examination shall be classified in accordance with the following list. The unit of product shall be 1 blanket. The acceptable quality level (AQL) shall be 1.5 major and 4.0 total defects per 100 units. The inspection level (sample size) shall be L–7, table III–B of Military Standard MIL–STD–105. The lot size shall be expressed in units of 1 blanket. An approximate equal number of blankets shall be drawn from each shipping container selected for visual examination (4.3.3.1.1).

Dimensions	Defects	Classification	
		Major	Minor
Size (30 by 40 inches)	Less than 40 inches long but not less than 39 inches		X
	Less than 39 inches	X	
	More than 42 inches		X
	Less than 30 inches wide but not less than 29 inches		X
	Less than 29 inches wide	X	
	More than 31 inches wide		X
Size (60 by 80 inches)	Less than 80 inches long but not less than 78 inches		X
	Less than 78 inches long	X	
	More than 83 inches long		X
	Less than 60 inches wide but not less than 58 inches		X
	Less than 58 inches wide	X	
	More than 62 inches wide		X
Size (60 by 84 inches)	Less than 84 inches long but not less than 82 inches		X
	Less than 82 inches long	X	
	More than 87 inches long		X
	Less than 60 inches wide but not less than 58 inches		X
	Less than 58 inches wide	X	
	More than 62 inches wide		X
Size (66 by 84 inches)	Less than 84 inches long but not less than 82 inches		X
	Less than 82 inches long	X	
	More than 87 inches long		X
	Less than 66 inches wide but not less than 64 inches		X
	Less than 64 inches wide	X	
	More than 68 inches wide		X
Size (66 by 90 inches)	Less than 90 inches long but not less than 88 inches		X
	Less than 88 inches long	X	
	More than 93 inches long		X
	Less than 66 inches wide but not less than 64 inches		X
	Less than 64 inches wide	X	
	More than 68 inches wide		X
Size (70 by 84 inches)	Less than 84 inches long but not less than 82 inches		X
	Less than 82 inches long	X	
	More than 87 inches long		X
	Less than 70 inches wide but not less than 68 inches		X
	Less than 68 inches wide	X	
	More than 72 inches wide		X
Size (72 by 90 inches)	Less than 90 inches long but not less than 88 inches		X
	Less than 88 inches long	X	
	More than 93 inches long		X
	Less than 72 inches wide but not less than 70 inches		X
	Less than 70 inches wide	X	
	More than 74 inches wide		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

TABLE IV.—*Tests*

Characteristic	Specification reference requirement	Test method	Number of determinations per sample unit	Results reported as
Yarns per inch:				
Warp	Table I	5050	5	Average of five determinations to the nearest whole number
Filling	Table I	5050	5	
Breaking strength:				
Warp	Table I	5100	5	Average of five determinations to the nearest 1.0 pound
Filling	Table I	5100	5	
Weave:				
Class 1	3.6.1	Visual	1	Pass or fail
Class 2	3.6.2	Visual	1	Pass or fail
Shrinkage:				
Type I:				
Warp	3.7.1	5550 [1]	3	Average of three determinations to the nearest 0.1 percent
Filling	3.7.1	and 5580	3	
Types II and III:				
Warp	3.7.2	5552 [1]	3	Average of three determinations to nearest 0.1 percent
Filling	3.7.2	and 5580	3	
Wool content:				
(Types II and III)	3.8.2—3.8.3	2101	2	Average of two determinations to nearest 1.0 percent
Nylon content:				
(Type III)	3.8.3	2530	2	Average of two determinations to the nearest 1.0 percent
Nonfibrous material	3.9	2611	2	Average of two determinations to nearest 0.1 percent
Moth repellency	3.10	(see 4.4.1)	2	Average of two determinations to nearest 0.01 percent
Colorfastness to:				
Laundering	3.4.4	5614	1	Standard sample—Satisfactory or unsatisfactory. No standard sample—Excellent, good, fair or poor
Crocking	3.4.4	5651	1	
Bleaching	3.4.4	5600	1	

[1] Except that evaluation, calculation of results and report of test methods 5550 and 5552 apply only after pressing operation of test method 5580.

4.3.3.1.3 *Examination for weight.* — The samples for this examination shall be those selected for dimensional examination. The lot shall be considered unacceptable if the average weight of the blankets in the sample is less than specified minimum weight.

4.3.3.1.4 *Inspection for preparation for delivery.*—Examination shall be made of preservation, packaging, packing and marking, to determine compliance with section 5.

4.4 Testing of the end item.—The methods of testing specified in Federal Specification

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

CCC–T–191, wherever applicable, and as listed in table IV shall be followed. The physical and chemical values specified in section 3 apply to the average of the determinations made on a unit of product for test purposes as specified in the applicable test method. The lot size shall be expressed in units of 1 blanket. The unit of product for test purposes shall be one finished blanket. The sample size for each characteristic shall be in accordance with table II. The lot shall be unacceptable if one or more units fail to meet any requirements specified.

4.4.1 *Moth-repellent test.*—The percentage of fluorine shall be determined as follows:

4.4.1.1 *Chemicals, reagents, and indicator used shall be:*

Chemicals and reagents:

50 percent sulfuric acid (H_2SO_4) in distilled water (by volume)

N/100 thorium nitrate ($Th(NO_3)_4$) solution (standardized against a standard NaF solution)

N/10 hydrochloric acid (HCl) solution

10 percent sodium hydroxide (NaOH) solution

Indicator:

0.05 percent aqueous solution sodium alizarin sulfonate

4.4.1.2 *Procedure.* — Separate the animal fiber from the vegetable fiber in the specimen, retaining only the animal fibers. Weigh out 0.5 g. sample of the animal fibers and cut into small pieces. Transfer to a concave bottom 300 ml. flask with a No. 40/50 joint (or No. 6430 fluorine determination apparatus manufactured by Ace Glass, Inc., Vineland, N.J., or equivalent apparatus) and, add 40 ml. of 50 percent sulfuric acid. Connect flask to fluorine apparatus and, after first heating gradually to dissolve animal fiber, start distillation with strong flame. Immerse lower end of condenser in 20 ml. distilled water in receiving beaker to insure solution of gases. Avoid localized overheating by protecting flask with asbestos sheeting having a relatively small hole placed directly under the bottom of flask. Maintain liquor temperature between 135° and 140°C. by dropping distilled water from separatory funnel inserted in one neck of flask. Collect 200 ml. or a minimum of 175 ml. of distillate, then make up to exactly 200 ml. in volumetric flask. (The distillation can be shortened by heating the upper portion of the distillation apparatus with an infrared bulb or heating tape. A heating mantle may be used instead of the flame with stirring by means of a magnetic stirrer). After shaking well, allow to rise to surface in neck of volumetric flask any fats or waxes which may have distilled over from which point they are readily shaken out. For titration, take two 20 ml. aliquot parts, add two drops sodium alizarin indicator, one drop of 10 percent NaOH, neutralized with N/10 HCl and add 5 drops in excess. Titrate to a faint but definite pink coloration with N/100 Th $(NO_3)_4$ solution.

4.4.1.3 *Calculation:*

Percentage fluorine = ml. × 0.038 (based on 100% wool sample) where:

ml. = total number mls. N/100 Th $(NO_3)_4$ required for 0.5 g. sample (extrapolated from 20 ml. aliquot titration).

Note 1.—Twenty ml. aliquot of distillate should never require more than one drop 10 percent NaOH solution for neutralization. When more is required, contamination of the distillate by decomposition products is indicated. These products interfere with the titration.

Note 2.—The pH of the solution taken for titration is important. The pH provided by the addition of five drops excess N/10 HCl is ideal (i.e. 3.2). The use of buffers is not recommended because the end point is not well defined even in the absence of a buffer.

Note 3.—Sodium ion concentration in the distillate should be kept

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

to a minimum since these ions cause erroneous (high) results.

4.4.1.4 *Report.*—Two specimens shall be tested from each unit-of-product. The fluorine contents of unit-of-product shall be the average of the results obtained from the two specimens tested and shall be reported to the nearest 0.01 percent.

5. PREPARATION FOR DELIVERY

For civil agency procurement Federal Standard No. 102 shall be referred to for definitions and applications of the various levels of packaging and packing protection for supplies and equipment.

5.1 Packaging.—Packaging shall be level A, B, or C as specified (see 6.3).

5.1.1 *Level A or B.*—Each blanket shall be neatly folded and individually packaged in a polyethylene bag. When specified, three type I, class 1, size 1 blankets shall be packaged in a polyethylene bag. The polyethylene flexible film shall be 0.003 inch thick conforming to grade 1, tables I and IV, and specific gravity of table III of Military Specification MIL–P–3803, except that ultimate elongation in cross direction in table IV shall be 350. The polyethylene shall withstand the tests specified in method 1013, method B of Federal Specification L–P–406, and the seams and closures shall withstand 60 percent of the force required for the breaking strength of the film. All seams and closures shall be effected by heat sealing. Prior to or during the final heat sealing operation, excess air within the bag shall be expelled. When blankets are not moth-repellent treated, a sufficient quantity of naphthalene flakes conforming to Federal Specification R–N–91 shall be evenly distributed throughout each blanket containing wool.

5.1.2 *Level C.*—Blankets shall be packaged in accordance with the manufacturer's commercial practice.

5.2 Packing.—Packing shall be level A, B, or C as specified (see 6.3).

5.2.1 *Level A.*—Seventy-two type I, class 1, size 1 identical blankets; 35 type I, class 2, sizes 1 and 2 identical blankets; or 15 identical blankets of all other types, classes, and sizes, packaged as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container conforming to class 2, V3c or V3s, style RSC–L of Federal Specification PPP–B–636. The inside of each fiberboard shipping container shall be fitted with a taped one-piece double-faced corrugated fiberboard liner conforming to compliance symbol V3c of Federal Specification PPP–B–636. Alternatively, shipping containers may be used that conform to overseas type of Federal Specification PPP–B–591, PPP–B–601 or Military Specification MIL–B–10377; or class 2, style 2 or 4 of Federal Specification PPP–B–621. Each shipping container (except fiberboard) shall be provided with type I or II, grade B or C, class 2 sealed case liner conforming to Military Specification MIL–L–10547. Each shipping container shall be closed and strapped in accordance with the appendix of the applicable container specification, except that fiberboard containers shall not be strapped and, in addition, shall have all seams, corners, and joints sealed by the application of a 3-inch cloth tape conforming to type II, class 1, olive-drab color of Federal Specification PPP–T–60.

5.2.2 *Level B.*—Seventy-two type I, class 1, size 1 identical blankets; 35 type I, class 2, sizes 1 and 2 identical blankets; or 15 identical blankets of all other types, classes, and sizes, packaged as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container conforming to type I or II, class 1, style RSC–L of Federal Specification PPP–B–636, except that the minimum bursting strength of the fiberboard shall be 275 p.s.i. The inside of each fiberboard container shall be fitted with a taped one-piece double-faced corrugated fiberboard liner having a minimum bursting strength of 275 p.s.i. All flaps of the fiberboard shipping containers shall be securely sealed with an adhesive commercially used for the specific product being packed by

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.

application throughout the entire area of contact between the flaps, or by a combination of metal stitching the bottom flaps and sealing the top flaps with adhesive. Alternatively, shipping containers may be used that conform to domestic type, style A or B of Federal Specification PPP–B–591, PPP–B–601, or Military Specification MIL–B–10377; or class 1, style 2 or 4 of Federal Specification PPP–B–621.

5.2.3 *Level C.* — Blankets, packaged as specified in 5.1, shall be packed in a manner to insure carrier acceptance and safe delivery at destination. Containers shall be in accordance with Uniform Freight Classification Rules or regulations of other carriers applicable to the mode of transportation.

5.3 Marking.

5.3.1 *Civil agencies.*—In addition to any special marking required by the contract or order, interior packages and shipping containers shall be marked in accordance with Federal Standard No. 123. Polyethylene bagged packages shall have the required information legibly printed or stamped directly on the bag or on a paper label inserted within the bag so as to permit ready identification.

5.3.2 *Military agencies.*—In addition to any special marking required by the contract or order, interior packages and shipping containers shall be marked in accordance with Military Standard MIL–STD–129. Polyethylene bagged packages shall have the required information legibly printed or stamped directly on the bag or on a paper label inserted within the bag so as to permit ready identification.

6. NOTES

6.1 **Intended use.**—Type I, class 1, size 1 blanket is intended for infants' use in hospitals and nurseries. Other types and classes are primarily used as bed covering. Type I, class 2 blankets are also used as sheet and bath blankets.

6.2 **Standard sample.** — For access to a standard sample address the procuring office issuing the invitation for bids.

6.3 **Ordering data.**—Purchasers should exercise any desired options offered herein, and procurement documents should specify the following:

(*a*) Title, number, and date of this specification.
(*b*) Type, class, size, and color of blanket required.
(c) When preproduction sample is required (see 3.2).
(*d*) When satin (finish) binding is required (see 3.3.5).
(*e*) When moth repellency treatment is required (see 3.10).
(*f*) Finish end and edges required (see 3.12.1.1).
(*g*) Selection of applicable levels of packaging and packing (see 5.1 and 5.2).
(*h*) Marking for identification (see 3.3.6).
(*i*) That only one type, style, and size shipping container should be used for any one item for a specific level of shipment (see 5.2.1 and 5.2.2).

Notice. — When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

MILITARY INTERESTS:
Army—M Q
Navy—Md
Air Force—MOAMA.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:35Z
Check the source to verify that this is the current version before use.