The documentation and process conversion measures necessary to comply with this revision shall be completed by 4 August 2005.

INCH-POUND

MIL-PRF-19500/553B
4 May 2005
SUPERSEDING
MIL-PRF-19500/553A
27 June 1997

PERFORMANCE SPECIFICATION SHEET

SEMICONDUCTOR DEVICE, DIODE, SILICON, SCHOTTKY BARRIER,
FAST RECOVERY, TYPE 1N6391, JAN, JANTX, JANTXV, JANS, AND JANHC

This specification is approved for use by all Departments and Agencies of the Department of Defense.

* The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-PRF-19500.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for a silicon, fast recovery, schottky barrier semiconductor diode, intended for use as a power rectifier in rectifier recovery circuits, or as a flyback diode in power switching applications. Four levels of product assurance are provided for each encapsulated device type as specified in MIL-PRF-19500. One level of product assurance is provided for each unencapsulated device type.

* 1.2 Physical dimensions. See figure 1 (DO-4) and figure 2 (JANHC die).

* 1.3 Maximum ratings.

Type	V_{RRM} and V_{RWM} (1)	V_{RSM}	V_R (1)	I_{FM} (2) (4)	I_O (3)	I_{FSM}	T_J
				T_C = +125°C	T_C = 125°C		
	V(pk)	V(pk)	V dc	A dc	A dc	A (pk)	°C
1N6391	45	54	45	25	22.5	600	-55 to +175

(1) Full rated V_{RRM} and V_{RWM} is applicable over the range of T_C = -55°C to +165°C for I_{FM} = 0. Full rated V_R is applicable over the temperature range of T_C = -55 to +155°C. When V_R = 45 V dc and T_C = +155°C, then T_J = 175°C.

(2) Average current with a 50 percent duty cycle square wave including reverse amplitude equal to the magnitude of full rated V_{RWM}. Derate linearly at 0.625 A dc/°C for T_C > +125°C.

(3) Full rated V_{RRM} is applicable over the range T_C = - 55°C to +169°C I_O = 0 and T_J = 175°C.


* 1.4 Primary electrical characteristics. Unless otherwise specified T_C = 25°C.

Type	Max V_{FM1} I_{FM} = 50 A (pk)	Max V_{FM2} I_{FM} = 5 A (pk)	Max I_{RM} V_{RM} 45 V (pk)		Max C_T V_R = 5 V dc	Max $R_{\theta JC}$
			T_J = +175°C	T_J = +25°C		
	V (pk)	V (pk)	mA (pk)	mA (pk)	pF	°C/W
1N6391	0.68	0.50	220	1.5	2,000	2.0

* Comments, suggestions, or questions on this document should be addressed to Defense Supply Center, Columbus, ATTN: DSCC-VAC, P.O. Box 3990, Columbus, OH 43218-3990, or emailed to Semiconductor@dscc.dla.mil . Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at http://assist.daps.dla.mil

AMSC N/A FSC 5961

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

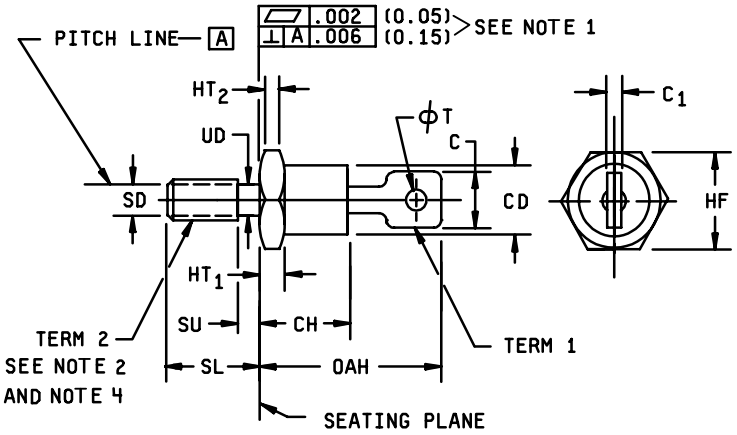


Ltr	Dimensions				Notes
	Inches		Millimeters		
	Min	Max	Min	Max	
C		.250		6.35	7
C_1	.018	.065	0.46	1.65	7
CD	.265	.424	6.74	10.76	8
HF	.403	.437	10.24	11.10	8
HT_1	.075	.175	1.91	4.44	
HT_2	.060		1.53		6
CH	.300	.405	7.62	10.28	
OAH	.600	.800	15.42	20.32	
UD	.163	.189	4.14	4.80	
SD					5
SL	.422	.453	10.72	11.50	
SU		.078		1.98	4
ϕT	.060	.103	1.52	2.62	

NOTES:
1. Dimensions are in inches.
2. Metric equivalents are given for general information only.
3. Units must not be damaged by torque of 15 inch-pounds applied to .10-32 UNF-2B nut assembled on thread.
4. Length of incomplete or undercut threads - SU.
5. Maximum pitch diameter of plated threads shall be basic pitch diameter .1697 inch (4.31 mm) reference (FED-STD-H28, “Screw-Thread Standards for Federal Services”).
6. A chamfer or undercut on one or both ends of the hex portion is optional; minimum base diameter at seating plane .403 inch (10.24 mm).
7. The angular orientation and peripheral configuration of terminal 1 is undefined, however, the major surfaces over dimensions C and C_1 shall be flat.
8. Dimension CD can not exceed dimension HF.
9. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

* FIGURE 1. Physical dimensions (similar to DO-4).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

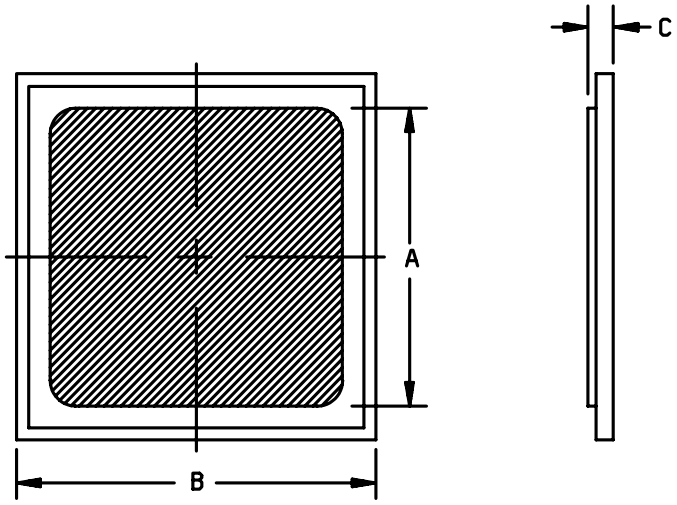

A Version

Ltr	Dimensions			
	Inches		Millimeters	
	Min	Max	Min	Max
A	.167	.177	.53	.63
B	.175	.185	.33	.43
C	.012	.013	.305	.330

NOTES:
1. Dimensions are in inches.
2. Metric equivalents are given for general information only.
3. The metallization characteristics of the die are:

JANHC version:	Anode(front)	Cathode(back)
A	Ag	Ag

4. Dimensions are in accordance with ASME Y14.5M.
5. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

* FIGURE 2. JANHCA die dimensions (A version).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

* 2.1 General. The documents listed in this section are specified in sections 3, 4, or 5 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3, 4, or 5 of this specification, whether or not they are listed.

2.2 Government documents.

* 2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

* DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

* DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-750 - Test Methods for Semiconductor Devices.

* (Copies of these documents are available online at http://assist.daps.dla.mil/quicksearch/ or http://assist.daps.dla.mil or from the Standardization Document Order Desk, 700 Robbins Avenue, Building 4D, Philadelphia, PA 19111-5094.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

* 3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturer's list (QML) before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. The abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500.

* 3.4 Interface and physical dimensions. The interface and physical dimensions shall be as specified in MIL-PRF-19500 and figure 1 (DO-4) and figure 2 (die) herein.

3.4.1 Lead finish. Unless otherwise specified, lead finish shall be solderable in accordance with MIL-PRF-19500, MIL-STD-750, and herein (see 6.2).

3.4.2 Polarity. Devices shall have the cathode electrically connected to the stud.

3.5 Marking. Marking shall be in accordance with MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in paragraph 1.3, 1.4, and table I.

* 3.6.1 Temperature current derating curve.. Temperature current derating curve see figure 3 herein.

3.7 Electrical test requirements. The electrical test requirements shall be the subgroups specified in 4.4.2 and 4.4.3.

3.8 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3).

c. Conformance inspection (see 4.4).

* 4.2 Qualification. Qualification inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

* 4.2.1 Group E qualification. Group E qualification shall be performed herein for qualification or re-qualification only. In case qualification was awarded to a prior revision of the associated specification that did not request the performance of table II tests, the tests specified in table II herein that were not performed in the prior revision shall be performed on the first inspection lot to this revision to maintain qualification.

4.2.2 JANHC devices. Qualification for JANHC devices shall be in accordance with MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

* 4.3 Screening (JANTX, JANTXV, and JANS levels). Screening shall be in accordance with table IV of MIL-PRF-19500, and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen (see table IV of MIL-PRF-19500)	Measurement	
	JANS	JANTX and JANTXV levels
3a	Condition C	Condition C
3b	Surge, see 4.3.2	Surge, see 4.3.2
3c	Thermal impedance, see 4.3.3	Thermal impedance, see 4.3.3
4	Not applicable	Not applicable
(1) (2) 9	Reverse energy test (see 4.5.2), followed by V_{FM1} and I_{RM1} of table I, subgroup 2.	Not applicable
10	Method 1038 of MIL-STD-750, test condition A; t = 48 hrs.	Not applicable
(1) (2) 11	V_{FM1} and I_{RM1} of table 1, subgroup 2 ΔV_{FM1} = 0.05 V(pk), ΔI_{RM1} = ±100 percent or 5 mA dc, whichever is greater.	Reverse energy test (see 4.5.2), followed by V_{FM1} and I_{RM1} of table I subgroup 2.
12	Burn-in, method 1038 of MIL-STD-750, test condition A; see 4.3.4.	Burn-in, method 1038 of MIL-STD-750, test condition A; see 4.3.4.
(1) (2) (3) 13	V_{FM1} and I_{RM1} of table 1, subgroup 2; ΔV_{FM1} = 0.05 V (pk), ΔI_{RM1} = ±100 percent or 5 mA dc, whichever is greater. Scope display evaluation (see 4.5.3).	V_{FM1} and I_{RM1} of table 1, subgroup 2; ΔV_{FM1} = 0.05 V (pk), ΔI_{RM1} = ±100 percent or 5 mA dc, whichever is greater. Scope display evaluation (see 4.5.3).

(1) I_{RM1} shall not be indicative of an open condition.
(2) All JAN level devices shall be subjected to the scope display evaluation and reverse energy tests.
(3) Surge current shall precede thermal response. These tests shall be performed anytime after screen 3 and before screen 10.

4.3.1 Screening (JANHC). Screening of JANHC die shall be in accordance with MIL-PRF-19500.

4.3.2 Surge current. Surge current shall be performed in accordance with method 4066 of MIL-STD-750, with the following conditions: I_{FSM} = 600 A, 6 surges, t_p = 8.3 ms, 1/2 sine wave, or rectangular pulse of equivalent I_{RMS}, I_O = 0A, V_{RWM} = 0, duty factor one percent minimum, T_A = 25°C.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

* 4.3.3 Thermal impedance. Thermal impedance $Z_{\theta JC}$ measurements shall be performed in accordance with method 3101 of MIL-STD-750. Read and record data ($Z_{\theta JC}$) shall be supplied to the qualifying activity on one lot (random sample of 500 devices minimum) prior to shipment. Twenty-two samples shall be serialized and provided to the qualifying activity for test correlation. The following conditions shall apply:

a.) $I_H \geq$ rated I_O.

b.) t_H = 150 to 400 ms.

c.) I_M = 50 mA to 250 mA.

d.) t_{MD} = 50 to 300 μs.

The maximum limit for $Z_{\theta JC}$ under these test conditions is $Z_{\theta JC\ (max)}$ = 2° C/W.

4.3.4 Burn-in. Method 1038 of MIL-STD-750, test condition A, T_C = 165°C, V_{RM} = 36 V (pk), I_O = 0, f = 60 Hz, t = 48 hrs; Alternate test: V_R = 36 V dc and T_C = 165°C, t = 48 hrs.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with MIL-PRF-19500, and table I herein.

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VIa (JANS) and table VIb (JAN, JANTX, and JANTXV) of MIL-PRF-19500, and as follows. Electrical measurements (end-points) shall be V_{FM1} and I_{RM1} of table I, subgroup 2 herein.

* 4.4.2.1 Group B inspection, table VIa (JANS) of MIL-PRF-19500.

Subgroup	Method	Conditions
B3	4066	I_{FSM} = 600 A pk; t_p = 8.3 ms; six 8.3 ms surges; 1 surge/minute maximum; I_O = 22.5 A; V_R = rated (see 1.3); 100°C ≤ T_C ≤ 125°C.
B4	1037	2,000 cycles, 25 percent rated $I_O \leq I_O$ applied ≤ rated I_O (see 4.5.6).
B5	1027	I_F = 20 A Avg at T_C = +130°C, for 340 hours, f = 60 Hz, $V_R = V_{RWM}$ (pk) (see figure 3).
B6	3101 or 4081	$R_{\theta JC}$ = 2.0°C/W; $t_H \geq$ 20 seconds; heating current (I_H) ≥ rated I_O; t_{MD} ≤ 300 μs; measurement current 50 mA ≤ I_M ≤ 250 mA (see 4.5.4).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

4.4.2.2 Group B inspection, table VIb (JAN, JANTX, and JANTXV) of MIL-PRF-19500.

Subgroup	Method	Condition
B3	1027	T_C = 165°C, V_{RM} = 36 V (pk) or V_R = 36 V dc.
B5	4081	See 4.5.4.
B7	4066	I_{FSM} = 600 A (pk); V_{RM} = 45 V (pk), I_O = 22.5 A dc; 10 surges of 8.3 ms each at 1 minute intervals; 100°C < T_C < 125°C; 22 devices, c = 0.

* 4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VII of MIL-PRF-19500, and as follows. Electrical measurements (end-points) shall be V_{FM1} and I_{RM1} of table I, subgroup 2 herein.

Subgroup	Method	Condition
C2	2036	Test condition A, 10 lbs, t = 15 s. Test condition F (method B), 5 pounds, t = 15 s. Test condition D1, 10 oz-in, t = 15 s. Test condition D2, 15 pound-inch, t = 15 s.
C5	4081 or 3101	$R_{\theta JC}$ = 2.0°C/W maximum in accordance with 4.5.4 except t_H = 20 s (minimum). n = 22, c = 0.
C6	1026	I_O = 22.5 A dc, V_{RM} = 36 V (pk), T_C = 125°C ± 3°C.
C7	1037	Operational power cycling (see 4.5.6), I_O = 20 A dc, T_C (low) = 40°C +0, -15°C; T_C (high) = 115°C +5, -0°C; 5000 cycles (may be continued from JANS group B subgroup 4); (15 devices, c = 0).

* 4.4.4 Group E inspection. Group E inspection shall be conducted in accordance with MIL-PRF-19500 and the conditions for subgroup testing in table II herein. Electrical measurements (end-points) shall be in accordance with table I, subgroup 2 herein.

4.5 Methods of inspection. Methods of inspection shall be as specified in appropriate tables and as follows.

4.5.1 Pulse measurements. Conditions for pulse measurements shall be as specified in section 4 of MIL-STD-750.

4.5.2 Peak reverse energy test. The peak reverse energy test is to be performed as on figure 4. The Schottky rectifier under test must be capable of absorbing the reverse energy, as defined, and meet the electrical requirements of table I, subgroup 4 herein.

4.5.3 Scope display evaluation. A curve trace visual display of the reverse characteristics (voltage versus current) shall be made using a calibration of 10 mA for each division vertical sensitivity, and 10 V for each division horizontal sensitivity. Increase the reverse voltage until the reverse current reaches 50 mA minimum to 70 mA maximum. Observe the curve characteristics. Any device with an erratic pattern, such as double trace, other than capacitance effects, intermittence, discontinuities other than zener noise at the knee of the curve, or shorts shall be removed from the lot. Time limit for this test shall be 5 seconds minimum.

This test shall be the last test performed on the device in the 100 percent screening tests. The percent defective result for evaluation against the percent defective allowed (PDA) shall be determined prior to the results of this test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

4.5.4 Thermal resistance. Thermal resistance measurement shall be performed in accordance with method 3101 or 4081 of MIL-STD-750. Read and record data in accordance with group E herein and shall be included in the qualification report.

a. $I_H \geq$ rated I_O

b. t_H = 20 seconds minimum

c. I_M = 50 mA to 250 mA

d. t_{MD} = 300 μs maximum

4.5.5 Reverse current at peak reverse voltage, alternate test. The reverse current at peak reverse voltage test requirement may be satisfied by performing the reverse energy test of 4.5.2 and measuring breakdown voltage to ensure $V_{BR} \geq 54$ V (pk) with I_{RM} = 2.0 A (pk).

* 4.5.6 DC intermittent operation life. Method 1037 of MIL-PRF-19500. A cycle shall consist of an "on" period, when forward current is applied suddenly, not gradually, to the device for the time necessary to achieve an increase (delta) case temperature of +85°C +15°C, -5°C followed by an "off" period, when the current is suddenly removed for cooling, the case through a similar delta temperature. Auxiliary (forced) cooling is permitted during the "off" period only. Forward current or "on" time, within specific limits, and "off" time may be adjusted to achieve the delta case temperature. Heat sinks shall only be used if and to the degree necessary to maintain test samples within the desired delta temperature tolerance. The heating time shall be such that 30 s $\leq t_{heating} \leq$ 180 s. The forward current may be steady-state dc, full-wave rectified dc, or the equivalent half-sine wave dc, of the specified value. The test duration shall be the specified number of cycles. Within the time interval of 50 cycles before and 500 cycles after the termination of the test, the sample units shall be removed from the specified test conditions and allowed to reach room ambient conditions. Specified end-point measurements for qualification and quality conformance inspections shall be completed within 96 hours after removal of sample units from the specified test conditions. Additional readings may be taken at the discretion of the manufacturer.

4.5.7 Inspection conditions. Unless otherwise specified in MIL-PRF-19500 or herein, all inspections shall be conducted at a case temperature (T_C) of 25°C ± 3°C.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 1						
Visual and mechanical inspection	2071					
Subgroup 2						
Thermal impedance	3101	See 4.3.3	$Z_{\theta JC}$		2.0	°C/W
Forward voltage	4011	I_{FM} = 50 A (pk) pulsed (see 4.5.1)	V_{FM1}		0.68	V (pk)
		I_{FM} = 5 A (pk) pulsed (see 4.5.1)	V_{FM2}		0.50	V (pk)
* Reverse current	4016	Pulsed method, (see 4.5.1) V_{RM} = 45 V (pk)	I_{RM1}		1.5	mA (pk)
Subgroup 3						
High temperature operation						
Reverse current leakage	4016	Pulse method, (see 4.5.1) V_{RM} = 45 V (pk).				
		T_J = 175°C T_J = 125°C	I_{RM2} I_{RM3}		220 40	mA(pk) mA(pk)
Low temperature operation		T_C = -55°C				
Reverse current leakage	4016	Pulse method, (see 4.5.1) V_{RM} = 45 V (pk)	I_{RM4}		400	mA(pk)
Forward voltage	4011	Pulsed (see 4.5.1) I_F = 5 A (pk)	V_{FM3}		0.60	V (pk)
* Subgroup 4						
Reverse current leakage at peak reverse voltage	4016	Peak reverse energy test (see 4.5.2). V_{RSM} = 54 V (pk) (alternate test see 4.5.5).	I_{RM5}		2.0	A(pk)
Capacitance	4001	V_R = 5 V dc; f = 1 MHz, 100 KHz ≤ f ≤ 1 MHz	C_T		2000	pF

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 5						
Not applicable						
Subgroup 6						
Forward surge	4066	I_{FSM} = 600 A (pk); 10 surges of 8.3 ms each at 1 minute intervals, superimposed on I_O = 22.5 A dc; V_{RWM} = rated V_{RWM} (see 1.3); T_A = +100°C.				
Electrical end-points		See table I, subgroup 2				
Subgroup 7						
Not applicable						


1/ For sampling plan, see MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

* TABLE II. Group E inspection (all quality levels) for qualification and requalification only.

Inspection	MIL-STD-750		Sampling plan
	Method	Conditions	
Subgroup 1			22 devices c = 0
Thermal shock (temperature cycling)	1056	100 cycles, 0° to 100°C.	
Hermetic seal	1071	Test condition C and H1	
Electrical measurement		See table I, group A, subgroup 2.	
Subgroup 2			22 devices c = 0
Steady-state reverse bias	1038	Test condition A, 1,000 hours.	
Electrical measurement		See table I, subgroup 2	
Subgroup 4			Sample size = N/A
Thermal impedance, curves		Each supplier shall submit their (typical) maximum design thermal impedance curves. In addition, optional test conditions and $Z_{\theta JX}$ limit shall be provided to the qualifying activity in the qualification report.	
Subgroup 5			
Not applicable			

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

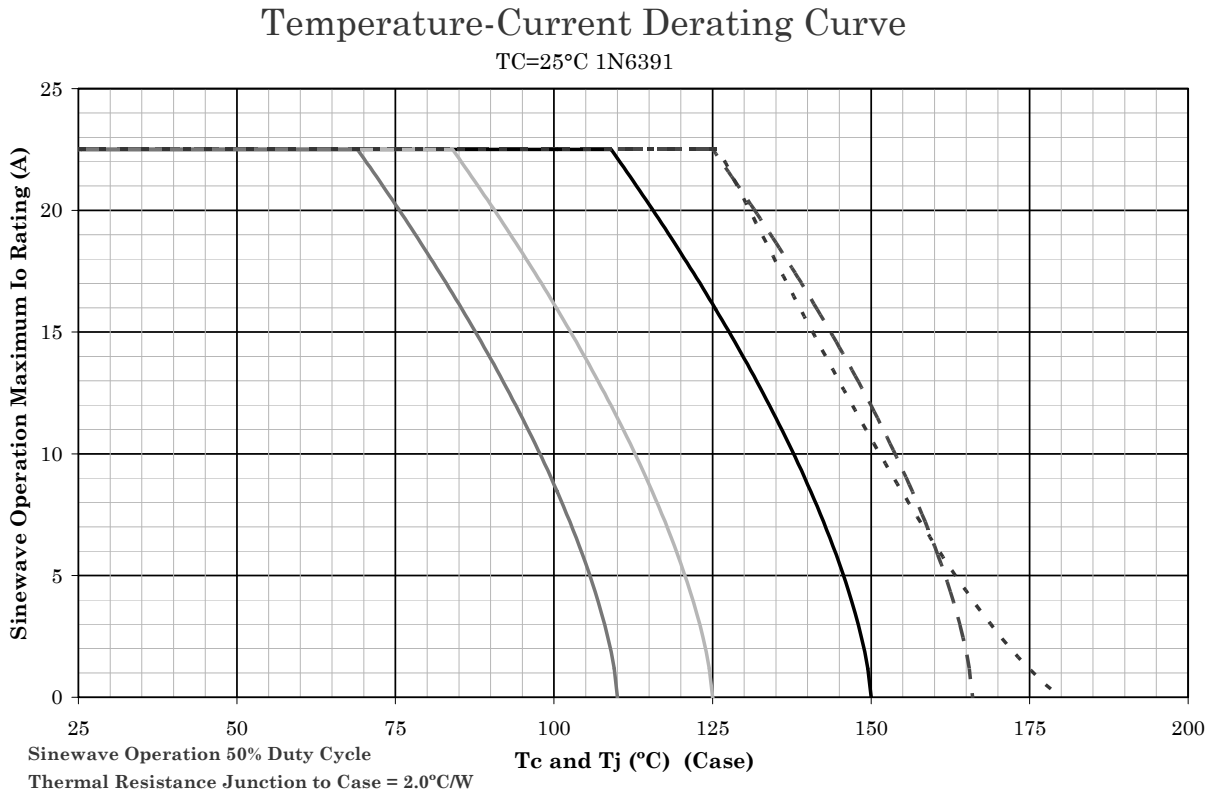

Sine wave operation 50 percent duty cycle
Thermal resistance junction to case = 2°C/W

NOTE: Max finish-alloy temp = 175°C


NOTES:

1. This is the true inverse of the worst case thermal resistance value. All devices are capable of operating at ≤ T_J specified on this curve. Any parallel line to this curve will intersect the appropriate power for the desired maximum T_J allowed.
2. Derate design curve constrained by the maximum junction temperature (T_J ≤ 175°C) and power rating specified. (See 1.3 herein.)
3. Derate design curves chosen at T_J ≤, 150°C, 125°C, and 110°C to show power rating where most users want to limit T_J in their application.

* FIGURE 3 Temperature current derating curve.

,

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

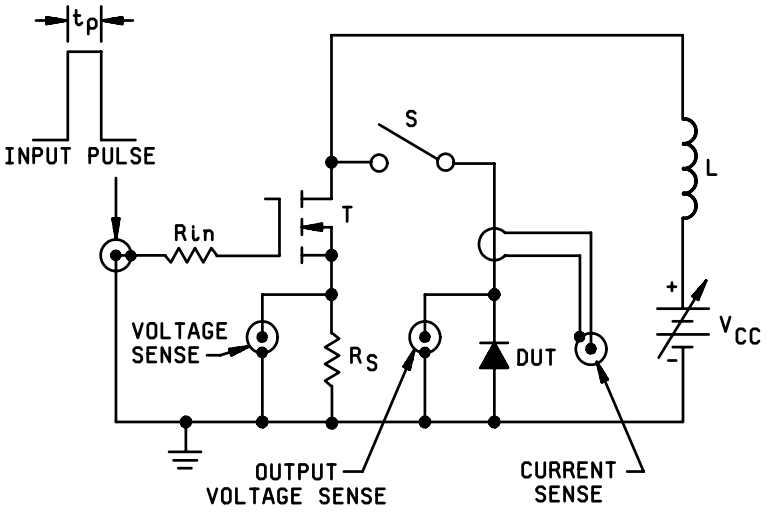

Input pulse	Rin = 50 ohms, 1 watt
V_G = 10 Volts	R_S = 0.1 ohms, 1 watt
R_G = 50 ohms	V_{CC} ≈ 10 volts
P.W.≈ 30 μs	L = 260 μH
Duty cycle ≤ 1%	T = IRF130/2N6756 or equivalent

PROCEDURES:

1. With S open, adjust pulse width to test current of 2 amps across R_S.
2. Close S, verify test current with current sense.
3. Read peak output voltage (see 4.5.5).

FIGURE 4. Peak reverse energy test circuit.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

5. PACKAGING

* 5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the Military Service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The notes specified in MIL-PRF-19500 are applicable to this specification.

* 6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Packaging requirements (see 5.1).

c. Lead finish (see 3.4.1).

d. Product assurance level and type designator.

* 6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List (QML 19500) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Defense Supply Center, Columbus, ATTN: DSCC/VQE, P.O. Box 3990, Columbus, OH 43218-3990 or e-mail vqe.chief@dla.mil.

* 6.4 Suppliers of JANHC die. The qualified JANHC suppliers with the applicable letter version (example, JANHCA1N6391) will be identified on the QML.

JANHC ordering information	
PIN	Manufacturer
	59377
1N6391	JANHCA1N6391

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.

6.5 Changes from previous issue. The margins of this specification are marked with asterisks to indicate where changes from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

Custodians:
Air Force - 11
DLA - CC

Preparing activity:
DLA - CC

Review activities:
Air Force - 19, 99

(Project 5961-2739)

* NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at http://assist.daps.dla.mil .

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:13Z
Check the source to verify that this is the current version before use.