The documentation and process conversion measures necessary to comply with this revision shall be completed by 22 December 2016.

INCH-POUND

MIL-PRF-19500/577D
22 September 2016
SUPERSEDING
MIL-PRF-19500/577C
6 October 2006

PERFORMANCE SPECIFICATION SHEET

SEMICONDUCTOR DEVICE, DIODE, SILICON, POWER RECTIFIER, FAST RECOVERY, HIGH VOLTAGE, AXIAL LEAD, TYPES 1N6528 THROUGH 1N6535, JAN, JANTX, JANTXV, AND JANS

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-PRF-19500.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for silicon, high voltage, fast recovery power rectifier diodes. Four levels of product assurance are provided for each device as specified in MIL-PRF-19500.

* 1.2 Package outlines. The device package for the encapsulated device type are as follows: Axial in accordance with figure 1 (similar to DO-7).

1.3 Maximum ratings. Unless otherwise specified T_A = +25°C.

Types	V_{RWM}	I_O T_A = +55°C	I_O T_A = +100°C	I_{FSM} t_p = 8.3 ms	t_{rr}	T_{STG}	T_J	$R_{\theta JL}$ L = .25 (6.35 mm)
	V dc	mA dc	mA dc	A (pk)	ns	°C	°C	°C/W
1N6528	1,500	250 (1)	125 (1)	10	70	-65	-65	50
1N6529	2,000	250 (1)	125 (1)	10	70	to	to	50
1N6530	2,500	100 (2)	50 (2)	8	70	+200	+175	50
1N6531	3,000	100 (2)	50 (2)	8	70			50
1N6532	4,000	50 (3)	25 (3)	4	70			50
1N6533	5,000	50 (3)	25 (3)	4	70			50
1N6534	7,500	25 (4)	12.5 (4)	2	70			50
1N6535	10,000	25 (4)	12.5 (4)	2	70			50

(1) Derate I_O linearly 2.78 mA/°C for T_A = +55°C to +100°C, and 1.67 mA/°C for T_A = +100°C to 175°C.
(2) Derate I_O linearly 1.11 mA/°C for T_A = +55°C to +100°C, and 0.67 mA/°C for T_A = +100°C to 175°C.
(3) Derate I_O linearly 0.55 mA/°C for T_A = +55°C to +100°C, and 0.33 mA/°C for T_A = +100°C to 175°C.
(4) Derate I_O linearly 0.28 mA/°C for T_A = +55°C to +100°C, and 0.17 mA/°C for T_A = +100°C to 175°C.

* Comments, suggestions, or questions on this document should be addressed to DLA Land and Maritime, ATTN: VAC, P.O. Box 3990, Columbus, OH 43218-3990, or emailed to semiconductor@dla.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A

FSC 5961

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

1.4 Primary electrical characteristics.

Types	V_{RWM}	I_O T_A = +55°C	I_{R1} T_A = +25°C	V_{F1} at I_O	C at V_R = 50 V F_O = 1 kHz	Barometric pressure (reduced) t = 1 minute (minimum)
	V dc	mA dc	µA dc	V (pk)	pF	mmHg
1N6528	1,500	250	0.10	3.0	4.0	8
1N6529	2,000	250	0.10	3.0	4.0	8
1N6530	2,500	100	0.10	7.0	2.0	8
1N6531	3,000	100	0.10	7.0	2.0	8
1N6532	4,000	50	0.10	9.0	1.0	8
1N6533	5,000	50	0.10	9.0	1.0	8
1N6534	7,500	25	0.10	14.0	0.5	8
1N6535	10,000	25	0.10	14.0	0.5	8

* 1.5 Part or Identifying Number (PIN). The PIN is in accordance with MIL-PRF-19500, and as specified herein. See 6.4 for PIN construction example and 6.5 for a list of available PINs.

* n JAN certification mark and quality level.

* 1.5.1.1 Quality level designators for encapsulated devices. The quality level designators for encapsulated devices that are applicable for this specification sheet from the lowest to the highest level are as follows: "JAN", "JANTX", "JANTXV", and "JANS".

* 1.5.2 Device type. The designation system for the device types of semiconductors covered by this specification sheet are as follows.

* 1.5.2.1 First number and first letter symbols. The semiconductors of this specification sheet use the first number and letter symbols "1N".

* 1.5.2.2 Second number symbols. The second number symbols for the semiconductors covered by this specification sheet are as follows: "6528", "6529", "6530", "6531", "6532", "6533", "6534", and "6535".

* 1.5.3 Suffix symbols. Suffix symbols are not applicable to this specification.

* 1.5.4 Lead finish. The lead finishes applicable to this specification sheet are listed on QPDSIS-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

* 2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-19500 - Semiconductor Devices, General Specification for.


DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-750 - Test Methods for Semiconductor Devices.
MIL-STD-1276 - Leads For Electronic Component Parts.

* (Copies of these documents are available online at http://quicksearch.dla.mil.)

2.3 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

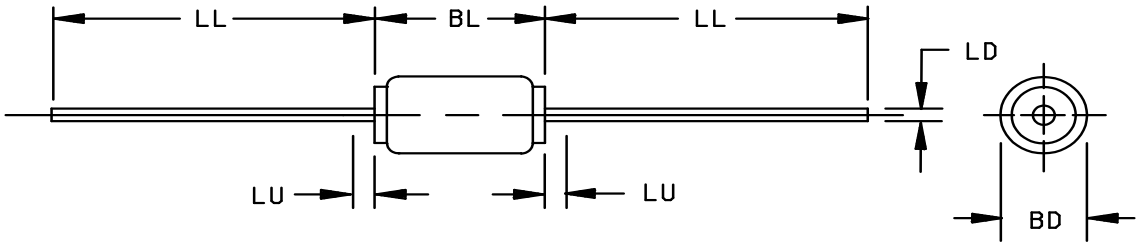

PIN	Dimensions															
	BD				BL				LD				LL			
	Inches		Millimeters		Inches		Millimeters		Inches		Millimeters		Inches		Millimeters	
	Min	Max	Min	Max	Min	Max	Min	Max	Min	Max	Min	Max	Min	Max	Min	Max
1N6528	.065	.125	1.65	3.18	.140	.200	3.56	5.08	.017	.023	0.43	0.58	1.0	1.3	25.4	33.0
1N6529	.065	.125	1.65	3.18	.140	.200	3.56	5.08	.017	.023	0.43	0.58	1.0	1.3	25.4	33.0
1N6530	.065	.125	1.65	3.18	.160	.220	4.06	5.59	.017	.023	0.43	0.58	1.0	1.3	25.4	33.0
1N6531	.065	.125	1.65	3.18	.160	.220	4.06	5.59	.017	.023	0.43	0.58	1.0	1.3	25.4	33.0
1N6532	.065	.125	1.65	3.18	.180	.240	4.57	6.10	.017	.023	0.43	0.58	1.0	1.3	25.4	33.0
1N6533	.065	.125	1.65	3.18	.180	.240	4.57	6.10	.017	.023	0.43	0.58	1.0	1.3	25.4	33.0
1N6534	.065	.125	1.65	3.18	.240	.300	6.10	7.62	.017	.023	0.43	0.58	1.0	1.3	25.4	33.0
1N6535	.065	.125	1.65	3.18	.240	.300	6.10	7.62	.017	.023	0.43	0.58	1.0	1.3	25.4	33.0

NOTES:
1. Dimensions are in inches.
2. Millimeters are given for general information only.
3. The specified lead diameter applies in the zone between .05 inch (1.27 mm) from the body to the end of the lead. Outside of this zone lead shall not exceed the body diameter.
4. Dimension LU defines region of uncontrolled diameter .050 inch max (1.27 mm).
5. In accordance with ASME Y14.5M, diameters are equivalent to Φx symbology.

FIGURE 1. Physical dimensions (similar to DO-7).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturer's list (QML) before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500.

3.4 Interface and physical dimensions. The interface and physical dimensions shall be as specified in MIL-PRF-19500 and on figure 1 herein. Plastic packages are prohibited.

3.4.1 Lead material and finish. Lead material shall be type C, 99.9 percent silver or copper in accordance with MIL-STD-1276. Lead finish shall be in accordance with MIL-PRF-19500 and MIL-STD-750. Where a choice of lead finish is desired, it shall be specified in the acquisition document (see 6.2).

3.4.2 Diode construction. These devices shall be constructed utilizing non-cavity double plug construction with high temperature metallurgical bonding between both sides of the silicon die and terminal pins. Metallurgical bond shall be in accordance with the requirements of category I in MIL-PRF-19500.

3.5 Marking. Devices shall be marked as specified in MIL-PRF-19500. Manufacturer’s identification and date code shall be marked on the devices. The polarity shall be indicated with a contrasting color band to denote the cathode end. The prefixes JAN, JANTX, and JANTXV may be abbreviated as J, JX, and JV, respectively. The part number may be reduced to J6528, JX6528, JV6528 or JS6528. No color coding will be permitted for part numbering.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I herein.

3.7 Electrical test requirements. The electrical test requirements shall be the subgroups specified in and table I herein.

3.8 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3).

c. Conformance inspection (see 4.4).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.2.1 Group E qualification. Group E inspection shall be performed for qualification or re-qualification only. In case qualification was awarded to a prior revision of the specification sheet that did not require the performance of table II tests, the tests specified in table II herein that were not performed in the prior revision shall be performed on the first inspection lot of this revision to maintain qualification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

4.3 Screening (JANS, JANTXV, and JANTX levels only). Screening shall be in accordance with table E-IV of MIL-PRF-19500 and as specified herein. Specified electrical measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen (see table E-IV of MIL-PRF-19500)	Measurement	
	JANS level	JANTX and JANTXV levels
(1)	Surge, see 4.3.2.	Surge, see 4.3.2.
9	I_{R1} and V_{F1}	Not applicable
11	I_{R1} and V_{F1}; ΔI_{R1} and ΔV_{F1}, see table III herein.	I_{R1} and V_{F1}
12	See 4.3.1	See 4.3.1
13	Subgroups 2 and 3 of table I herein: ΔI_{R1} and ΔV_{F1}, see table III. I_{R1} and V_{F1}. Scope display evaluation (see 4.5.4)	Subgroup 2 of table I herein: ΔI_{R1} and ΔV_{F1}, see table III. I_{R1} and V_{F1}. Scope display evaluation (see 4.5.4)

(1) Surge screening shall be performed anytime after screen 3 and before screen 10.

4.3.1 Power burn-in conditions. Power burn-in conditions are as follows: Method 1038 of MIL-STD-750, condition B, T_A = room ambient as defined in the general requirements of 4 of MIL-STD-750; V_R = 1000 Vdc, f = 60Hz.

Types	I_O (mA dc)
1N6528, 1N6529	250
1N6530, 1N6531	100
1N6532, 1N6533	50
1N6534, 1N6535	25

4.3.2 Surge screening. Method 4066 of MIL-STD-750, T_A = +25°C, V_{RWM} = 0. Six surges. Apply 20 x I_O rated at T_A of 55°C, 8.3 ms.

* 4.3.3 Thermal impedance. The thermal impedance measurements shall be performed in accordance with method 3101 or 4081, as applicable, of MIL-STD-750 using the guidelines in that method for determining I_M, I_H, t_H, t_{SW} (V_C and V_H where appropriate). See group E, subgroup 4 herein.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with table E-V of MIL-PRF-19500, and table I herein

* 4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-VIa (JANS) and table E-VIb (JANTX and JANTXV) of MIL-PRF-19500. Delta measurements shall be in accordance with the applicable steps of table III herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

4.4.2.1 Group B inspection, table E-VIa (JANS) of MIL-PRF-19500.

	Subgroup	Method	Conditions
*	B3	4066	Condition A, I_O at T_A = 55°C, I_{FSM} = rated I_{FSM}, see 1.3, one surge, 8.3 ms, V_{RWM} = 0 V.
	B4	1037	See 4.3.1, t_{on} = t_{off} = 3 minutes minimum, 2,000 cycles.
*	B5	1027	T_A = +150°C minimum, I_O = rated I_O (see 1.3) or adjust I_O and T_A as required to achieve T_J = +275°C for a minimum of 96 hours at V_{RWM} = 1,000 V. For irradiated devices, include t_{rr} as an end-point measurement.
	B6	4081	T_A = +25°C; $R_{\theta JL}$ = rated $R_{\theta JL}$ (see 1.3).

4.4.2.2 Group B inspection, table E-VIb (JANTX and JANTXV) of MIL-PRF-19500.

	Subgroup	Method	Conditions
*	B2	4066	Condition A, I_O = I_O at T_A = 55°C one surge, 8.3 ms; I_{FSM} = rated I_{FSM} (see 1.3), V_{RWM} = 0
*	B3	1027	T_A = room ambient as defined in the general requirements in 4.5 of MIL-STD-750 minimum, I_O = rated I_O (see 4.3.1); adjust I_O or T_A as required to achieve $T_J \geq$ +125°C, V_{RWM} = 1,000 V. For irradiated devices, include t_{rr} as an end-point measurement.
	B5	4081	T_A = +25°C; $R_{\theta JL}$ = rated $R_{\theta JL}$ (see 1.3).

* 4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-VII of MIL-PRF-19500 and as follows. Delta measurements shall be in accordance with the applicable steps of table III herein.

4.4.3.1 Group C inspection, appendix E, table VII of MIL-PRF-19500.

	Subgroup	Method	Conditions
	C2	2036	Test condition A, weight = 5 lbs, t = 30s.
*	C6	1027	T_A = +25°C minimum, I_O = rated I_O (see 4.3.1); adjust I_O or T_A as required to achieve $T_J \geq$ +125°C, V_{RWM} = 1,000 V. For irradiated devices, include t_{rr} as an end-point measurement.

* 4.4.4 Group E inspection. Group E inspection shall be conducted in accordance with the tests and conditions specified for subgroup testing in table E-IX of MIL-PRF-19500, and table II herein.

4.5 Methods of inspection. Methods of inspection shall be specified in the appropriate tables and as follows.

4.5.1 Pulse measurements. Conditions for pulse measurement shall be as specified in section 4 of MIL-STD-750.

4.5.2 Inspection of conditions. Unless otherwise specified, all inspections shall be conducted at an ambient temperature, T_A = +25°C ± 3°C.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

4.5.3 Reverse-recovery time. The reverse recovery time shall be measured in the circuit of figure 2 or an equivalent circuit. The recovery conditions shall be 12.5 mA forward current to 25 mA reverse current. The reverse recovery time is defined as the time the rectifier begins to conduct in the reverse direction (crosses I = 0) until the reverse current decays to -6.3 mA. The point of contact on the leads shall be no less than .375 inch (9.52 mm) from the diode body.

4.5.4 Scope display test. Scope display test method 4023 of MIL-STD-750 shall be performed with the following conditions: Test condition B, I_{BR} = 50 μA min.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

	Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
		Method	Conditions		Min	Max	
	Subgroup 1						
	Visual and mechanical examination	2071					
	Subgroup 2						
*	Thermal impedance 2/	3101	See 4.3.3	$Z_{\theta JX}$			°C/W
*	Forward voltage	4011	Condition B, I_F = 25 mA	V_{F1}			
	1N6528, 1N6529					3.0	V dc
	1N6530, 1N6531					7.0	
	1N6532, 1N6533					9.0	
	1N6534, 1N6535					14.0	
	Reverse current leakage	4016	DC method; V_R = rated V_{RWM} (see 1.3)	I_{R1}		0.1	µA dc
	Breakdown voltage	4021	I_R = 50 µA dc	V_{BR}			
	1N6528				1,650		V dc
	1N6529				2,200		
	1N6530				2,750		
	1N6531				3,300		
	1N6532				4,400		
	1N6533				5,500		
	1N6534				8,250		
	1N6535				11,000		
	Subgroup 3						
	High temperature operation:		T_A = 150°C				
	Reverse current Leakage	4016	DC method; V_R = rated V_{RWM} (see 1.3)	I_{R2}		50	µA dc
	Low temperature operation:		T_A = -55°C				
*	Forward voltage	4011	Condition B, I_F = 25 mA	V_{F2}			
	1N6528, 1N6529					4.8	V dc
	1N6530, 1N6531					11.2	
	1N6532, 1N6533					14.4	
	1N6534, 1N6535					22.4	

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 3 - Continued						
Low temperature operation:		T_A = -55°C				
Breakdown voltage	4021	I_R = 50 μA dc	V_{BR}			
1N6528				1,650		V dc
1N6529				2,200		
1N6530				2,750		
1N6531				3,300		
1N6532				4,400		
1N6533				5,500		
1N6534				8,250		
1N6535				11,000		
Subgroup 4						
* Reverse recovery	4031	See 4.5.3 and figure 2	t_{rr}		70	ns
Scope display evaluation	4023	Method 4203 of MIL-STD-750, figures 4023-3, -7, -9, -10 only. (see 4.5.4)				
Capacitance	4001	V_R = 50 V dc, 1 kHz ≤ f ≤ 100 kHz	C			
1N6528, 1N6529					4.0	pF
1N6530, 1N6531					2.0	
1N6532, 1N6533					1.0	
1N6534, 1N6535					0.5	
Subgroups 5, 6 and 7						
Not applicable						

1/ For sampling plan, see MIL-PRF-19500.

* 2/ This test required for the following end-point measurements only:
Group B, subgroups 3, 4 and 5 (JANS).
Group B, subgroups 2 and 3 (JAN, JANTX, JANTXV).
Group C, subgroups 2 and 6.
Group E, subgroup 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

TABLE II. Group E inspection for (all quality levels) for qualification and requalification only.

Inspection	MIL-STD-750		Sampling plan
	Method	Conditions	
Subgroup 1			22 devices, c = 0
Temperature cycling	1051	500 cycles, condition C	
Hermetic seal Gross leak	1071		
Electrical measurements		See table III, steps 1 and 2	
Subgroup 2			22 devices, c = 0
Steady-state dc blocking life	1038	Condition A, t = 1,000 hours	
Electrical measurements		See table III, steps 1 and 2	
Subgroup 3			
Not applicable			
Subgroup 4			
* Thermal impedance curves		See MIL-PRF-19500.	Samples size N/A
Thermal resistance	4081	T_A = +25°C; $R_{\theta JL}$ = rated $R_{\theta JL}$ (see 1.3).	
Subgroup 5			
Barometric pressure	1001	V_R = rated V_{RWM} (see 1.3), pressure = 8mm Hg, t = 1 minute (minimum). Dielectric fluid may be used.	3 devices, c = 0


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

* TABLE III. Screening, groups A, B, C, and E delta measurements. 1/ 2/ 3/

Step	Inspection	MIL-STD-750		Symbol	Limits		Unit
		Method	Conditions		Min	Max	
1.	Forward voltage	4011	Condition B, Pulsed (see 4.5.1), I_F = 25 mA	ΔV_{F1}			V (pk)
	1N6528, 1N6529					±0.2	
	1N6530, 1N6531					±0.4	
	1N6532, 1N6533					±0.8	
	1N6534, 1N6535					±1.2	
2.	Reverse current	4016	DC method	ΔI_{R1}	50 nA or ±100 percent of initial value, whichever is greater.		

1/ Devices which exceed the table I limits for this test shall not be accepted.
2/ The electrical measurements for group B inspections in table E-VIa (JANS) of MIL-PRF-19500 are as follows: Subgroups 3, 4, and 5, see table III herein, steps 1 and 2.
3/ The electrical measurements for group B inspections in table E-VIb (JAN, JANTX, and JANTXV) of MIL-PRF-19500 are as follows: Subgroup 3, see table III herein, steps 1 and 2.
4/ The electrical measurements for group C inspections in table E-VII (all quality levels) of MIL-PRF-19500 are as follows: Subgroups 2 and 6, see table III herein, steps 1 and 2.
5/ The electrical measurements for group E inspections in table E-IX of MIL-PRF-19500 are as follows: Subgroups 1 and 2, see table III herein, steps 1 and 2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

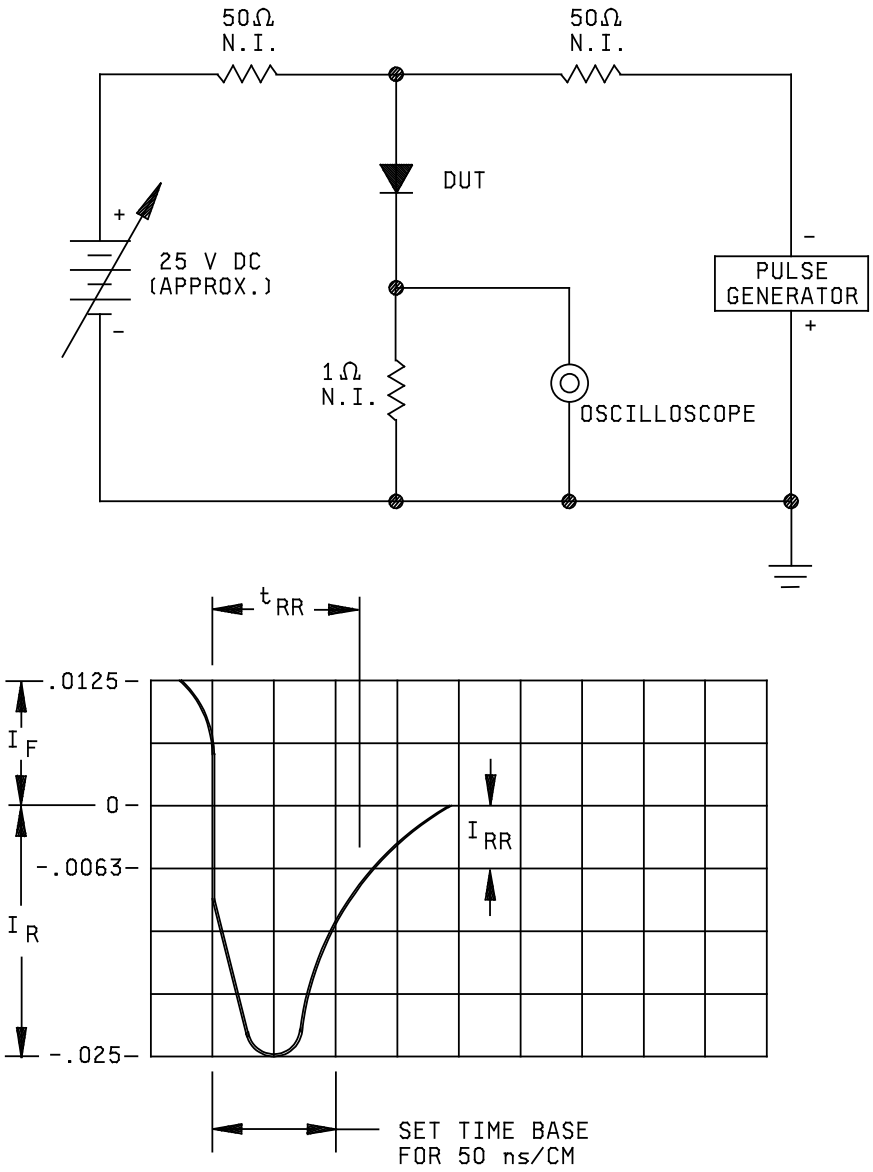

NOTES:

1. Oscilloscope-rise time ≤ 7 ns; input impedance = 1 megohm; 22 pF.
2. Pulse generator - rise time ≤ 10 ns; source impedance 50 ohms.
3. Recovery time shall be measured on the above circuit and with equipment as shown. The pulse generator shall have a pulse repetition frequency of 1 kHz and a pulse width of 200 ns. Recovery conditions: 12.5 A forward current to .25 mA reverse current. Recovery time measured when rectifier recovers to -6.3 mA.

FIGURE 2. Reverse recovery time test circuit and characteristic nomograph.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the Military Service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The notes specified in MIL-PRF-19500 are applicable to this specification.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Packaging requirements (see 5.1).

c. Lead material and finish (see 3.4.1).


* d. The complete PIN, see 1.5.

e. Destructive physical analysis when requested.

* 6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List (QML-19500) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from DLA Land and Maritime, ATTN: VQE, P.O. Box 3990, Columbus, OH 43218-3990 or e-mail vqe.chief@dla.mil. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://assist.dla.mil.

* 6.4 PIN construction example.

* 6.4.1 Encapsulated devices The PINs for encapsulated devices are constructed using the following form.

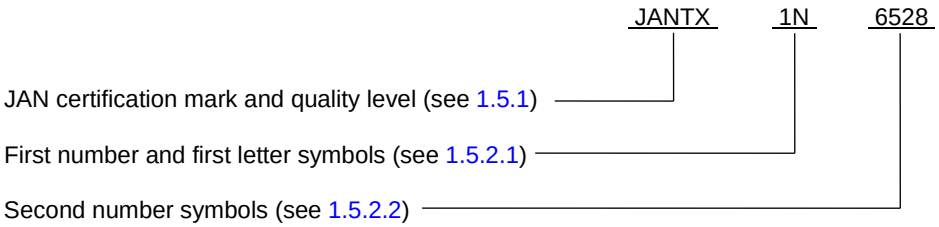

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

* 6.5 List of PINs. The following is a list of possible PINs available on this specification sheet.

	PINs			
Axial Package	JAN1N6528	JANTX1N6528	JANTXV1N6528	JANS1N6528
	JAN1N6529	JANTX1N6529	JANTXV1N6529	JANS1N6529
	JAN1N6530	JANTX1N6530	JANTXV1N6530	JANS1N6530
	JAN1N6531	JANTX1N6531	JANTXV1N6531	JANS1N6531
	JAN1N6532	JANTX1N6532	JANTXV1N6532	JANS1N6532
	JAN1N6533	JANTX1N6533	JANTXV1N6533	JANS1N6533
	JAN1N6534	JANTX1N6534	JANTXV1N6534	JANS1N6534
	JAN1N6535	JANTX1N6535	JANTXV1N6535	JANS1N6535

* 6.6 Substitution information. Devices covered by this specification are substitutable for the manufacturers' and users' Part or Identifying Number (PIN). This information in no way implies that manufacturers' PIN's are suitable as a substitute for the military PIN.

PIN	Manufacturer's CAGE code	Manufacturer's and user's PIN
1N6528	53711 60211	8502234-215 RM115 M15FG M15UFG
1N6529	53711 49956 94117 60211	8502234-220 G339806 194087 RM116 RM135 RM140 M20FG M20UFG
1N6530	53711 60211	8502234-225 RM117 M25FG M25UFG
1N6531	53711 60211	4027428-103 4027428-113 8502234-230 4056502 RA352 RA643 RM118 RM123 M30FG M30UFG
1N6532	53711 23426 60211	8502234-240 28005-12 RM119 RM130 M40FG M40UFG

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

PIN	Manufacturer's CAGE code	Manufacturer's and user's PIN
1N6533	53711 60211	4027428-105 4027428-115 8502234-250 304-1-58A2 RA641 RA644 RM120 RM137 M50FG M50UFG
1N6534	53711 23426 60211	4027428-106 4027428-116 8502234-260 28005-7 RA642 RA645 RM121 RM131 M60FG M60FUFG
1N6535	58260 53711 23426 60211 23426 60211	13084424 8502234-280 8502234-300 28005-8 M100FG RM122 RM109 RM132 M100UFG M80FG M80UFG

6.5 Changes from previous issue. The margins of this specification are marked with asterisks to indicate where changes from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.

Custodians:
Army - CR
Navy - EC
Air Force - 85
NASA - NA
DLA - CC

Preparing activity:
DLA - CC

(Project 5961-2016-095)

Review activities:
Army - AR, AV, MI, SM
Air Force - 19, 99
Navy - AS, MC, OS

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T03:34Z
Check the source to verify that this is the current version before use.