INCH-POUND

The documentation and process conversion measures necessary to comply with this revision shall be completed by: 27 September 2022.

MIL-PRF-19500/420N
w/AMENDMENT 2
26 May 2022
SUPERSEDING
MIL-PRF-19500/420N
w/AMENDMENT 1
25 October 2021

PERFORMANCE SPECIFICATION SHEET

SEMICONDUCTOR DEVICE, DIODE, SILICON, POWER, RECTIFIER, ENCAPSULATED (THROUGH-HOLE AND SURFACE MOUNT PACKAGES), AND UN-ENCAPSULATED, TYPES 1N5550 THROUGH 1N5554, QUALITY LEVELS JAN, JANTX, JANTXV, JANS, JANHC AND JANKC

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-PRF-19500.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for silicon, general purpose, power rectifier semiconductor diodes. The diode is non cavity double plug construction, with high temperature metallurgical bonds (category 1) between both sides of the silicon die and terminal pins. Four levels of product assurance (JAN, JANTX, JANTXV and JANS) are provided for each encapsulated device. Two levels of product assurance (JANHC and JANKC) are provided for each un-encapsulated device type.

1.2 Physical dimensions.

1.2.1 Package outlines. The device package outline are as follows: Axial lead in accordance with figure 1 and square end-cap (US) surface mount in accordance with figure 2 for all encapsulated device types.

1.2.2 Un-encapsulated die characteristics. The dimensions, physical characteristics and topography for JANHC and JANKC un-encapsulated die are in accordance with figures 3, 4, 5, 6 and 7.

1.3 Maximum ratings. Unless otherwise specified, T_A= +25 °C and ratings apply to all package outlines.

1.3.1 Ratings applicable to all types. T_{STG} = T_J = -65 °C to +175 °C.

Comments, suggestions, or questions on this document should be addressed to DLA Land and Maritime, ATTN: VAC, P.O. Box 3990, Columbus, OH 43218-3990, or emailed to Semiconductor@dla.mil . Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A
DISTRIBUTION STATEMENT A. Approved for public release. Distribution is unlimited.
FSC 5961

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

1.3.2 Ratings applicable to individual types.

Col. 1	Col. 2	Col. 3	Col. 4	Col. 5	Col. 6	Col. 7	Col. 8	Col. 9
Type (1)	V_{RWM}	$I_{O(L)}$ T_L = +30°C; T_{EC} = 130°C (2)	I_{O2} T_A = 55°C max (3) (4)	I_{O3} T_A = 100°C (4) (5)	I_{FSM} I_O = 2 A dc tp = 8.3 ms V_{RWM} = rated T_A = 55°C	$R_{\theta JL}$ (2) (6)	$R_{\theta JEC}$ at (2) (7)	$R_{\theta JX}$ (4)
	V dc	A	A	A dc	A(pk)	°C/W	°C/W	°C/W
1N5550, US	200	5	3.0	2.0	100	22	6.5	47
1N5551, US	400	5	3.0	2.0	100	22	6.5	47
1N5552, US	600	5	3.0	2.0	100	22	6.5	47
1N5553, US	800	5	3.0	2.0	100	22	6.5	47
1N5554, US	1,000	5	3.0	2.0	100	22	6.5	47

(1) Barometric pressure reduced: 1N5550, 1N5551, 1N5552: Condition D 8 mm Hg (100,000 feet); 1N5553, 1N5554: Condition C 33 mm Hg (70,000 feet).
(2) L = .375 inch (9.52 mm) for axial leaded devices. L = 0 inch (0 mm) for US suffix devices.
(3) Derate linearly at 22.2 m/A /°C from +55 °C to +100 °C.
(4) For the 3 A rating at 55 °C ambient and the 2 A rating at 100 °C ambient, these I_O ratings are for a thermal mounting methods (PC boards or other) where the lead or end-cap temperatures cannot be maintained as shown in col. 3 and where thermal resistance from mounting point to ambient is still sufficiently controlled where $T_{J(MAX)}$ in 1.3.1 is not exceeded. This equates to $R_{\theta JX} \leq 47$ °C/W in col. 9. Also see application notes in 6.7.2.
(5) Derate linearly at 26.7mA/°C above T_L= +100 °C to +175 °C ambient.
(6) See figure 8.
(7) See figure 9.

1.4 Primary electrical characteristics. Unless otherwise specified, T_A = +25 °C.

Type	V_{F1} at I_F = 9.0 A(pk) 1 percent duty cycle, 8.3 ms max pulse width		I_{R1}, pulsed $V_R \leq$ 20 ms		I_{R2} at T_A = +125 °C, pulsed $V_R \leq$ 20 ms	
	Min V(pk)	Max V(pk)	µA dc (max) at V_R (V dc)		µA dc (max) at V_R (V dc)	
1N5550, US	0.6	1.2	1.0	200	60	200
1N5551, US	0.6	1.2	1.0	400	60	400
1N5552, US	0.6	1.2	1.0	600	60	600
1N5553, US	0.6	1.3	1.0	800	60	800
1N5554, US	0.6	1.3	1.0	1,000	60	1,000

1.5 Part or Identifying Number (PIN). The PIN is in accordance with MIL-PRF-19500, and as specified herein. See 6.4 for PIN construction example and 6.5 for a list of available PINs.

1.5.1 JAN certification mark and quality level

1.5.1.1 Quality level designators for encapsulated devices. The quality level designators for encapsulated devices that are applicable for this specification sheet from the lowest to the highest level are as follows: "JAN", "JANTX", "JANTXV" and "JANS".

1.5.1.2 Quality level designators for unencapsulated devices (die). The quality level designators for unencapsulated devices (die) that are applicable for this specification sheet from the lowest to the highest level are as follows: "JANHC" and "JANKC".

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

1.5.2 Device type. The designation system for the device types of diodes covered by this specification sheet are as follows.


1.5.2.1 First number and first letter symbols. The diodes of this specification sheet use the first number and letter symbols "1N".

1.5.2.2 Second number symbols. The second number symbols for the diodes covered by this specification sheet are as follows: "5550", "5551", "5552", "5553", and "5554".

1.5.3 Suffix letters. No suffix letters are used on devices that are packaged in the axial leaded package of figure 1. The suffix letters "US" are used on devices that are packaged in the surface mount package of figure 2.

1.5.4 Lead finish. The lead finishes applicable to this specification sheet are listed on QPDSIS-19500.

1.5.5 Die identifiers for unencapsulated devices (manufacturers and critical interface identifiers). The manufacturer die identifiers that are applicable for this specification sheet are "A", "B", "C", "D", "E" and "F" (see figures 3, 4, 5, 6, 7 and 6.6).

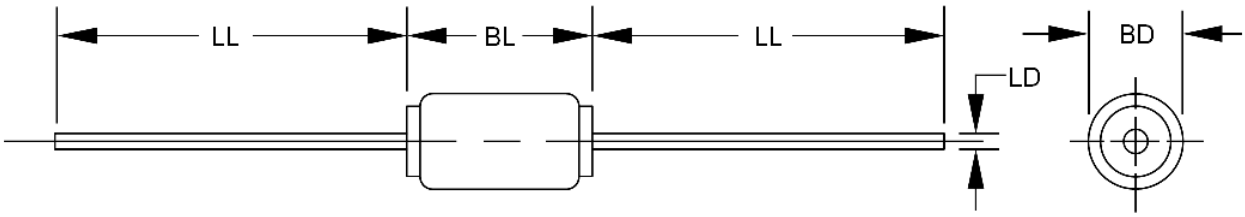


	Dimension				
Symbol	Inches	Inches	mm	mm	Notes
	Min	Max	Min	Max	
BD	.115	.180	2.92	4.57	3
BL	.130	.300	3.30	7.62	4
LD	.036	.042	0.92	1.07	
LL	.900	1.300	22.86	33.02	

NOTES:
1. Dimensions are in inches. Millimeter equivalents are given for general information only.
2. Dimensions are pre-solder dip.
3. Dimension BD shall be measured at the largest diameter.
4. Dimension BL shall include the entire body including slugs and sections of the lead over which the diameter is uncontrolled. This uncontrolled area is defined as the zone between the edge of the diode body and extending .050 inch (1.27 mm) onto the leads.
5. In accordance with ASME Y14.5, diameters are equivalent to øx symbology.

FIGURE 1. Physical dimensions of axial leaded package (1N5550 through 1N5554).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

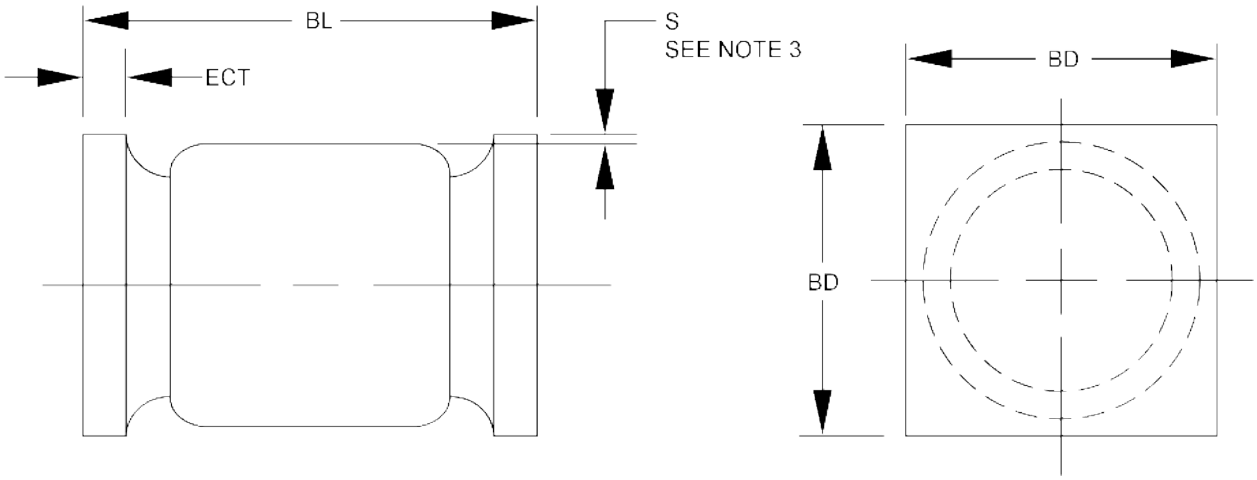


	Dimensions			
Symbol	Inches	Inches	mm	mm
	Min	Max	Min	Max
BL	.200	.275	5.08	6.99
BD	.137	.186	3.48	4.72
ECT	.019	.034	0.48	0.86
S	.003		0.08	

NOTES:
1. Dimensions are in inches. Millimeters are given for general information only.
2. Dimensions are pre-solder dip.
3. Minimum clearance of glass body to mounting surface on all orientations.
4. In accordance with ASME Y14.5, diameters are equivalent to øx symbology.

FIGURE 2. Physical dimensions of square end-cap surface mount (US) package (1N5550US through 1N5554US).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

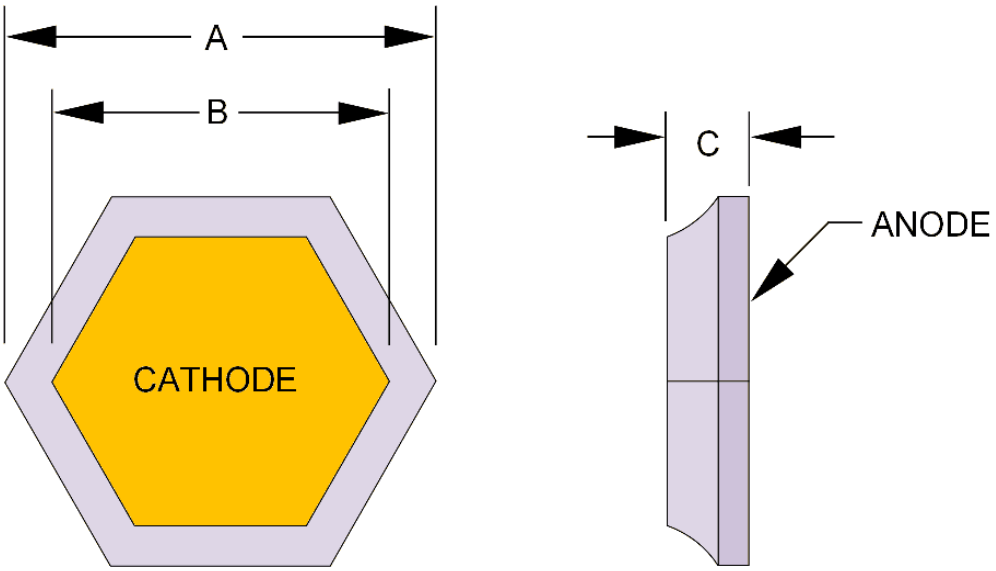


	Dimensions			
Letter	Inches	Inches	mm	mm
	Min	Max	Min	Max
A	.085	.091	2.16	2.31
B	.072	.078	1.83	1.98
C	.008	.014	0.20	0.36

NOTES:
1. Dimensions are in inches. Millimeters are given for general information only.
2. The metallization characteristics are:
   Top (cathode): Au Thickness = 10,000Å minimum,
   Back (anode): Au Thickness = 4,000Å minimum.

FIGURE 3. JANHCA and JANKCA (A-version) die dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

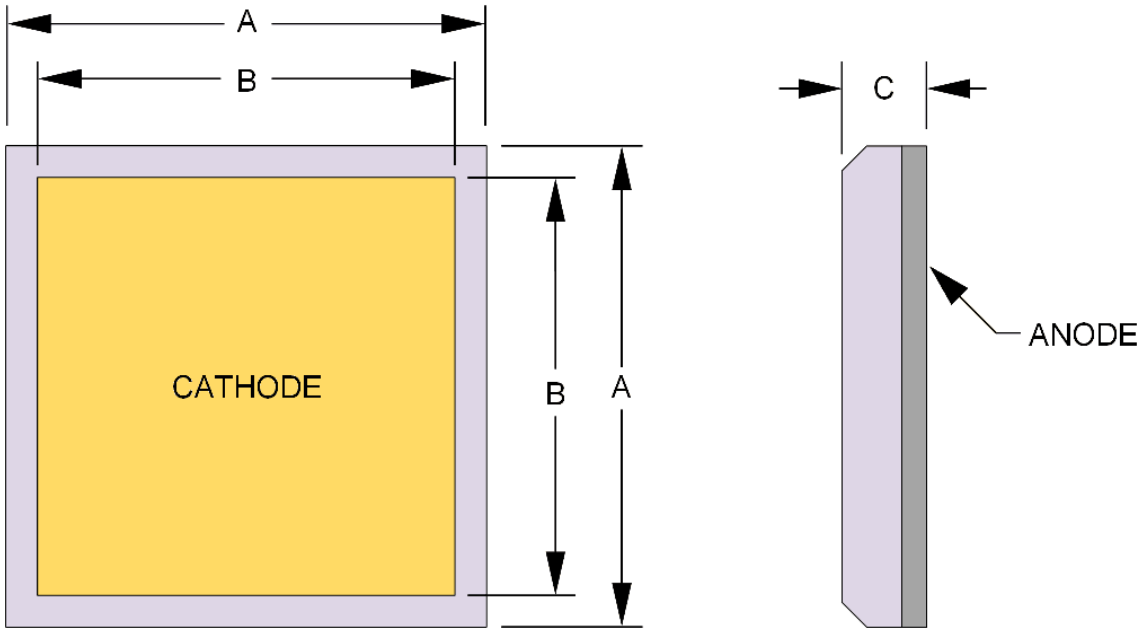


	Dimensions			
Letter	Inches	Inches	mm	mm
	Min	Max	Min	Max
A	.088	.092	2.24	2.34
B	.070	.077	1.78	1.96
C	.007	.035	0.18	0.89

NOTES:
1. Dimensions are in inches. Millimeters are given for general information only.
2. The metallization characteristics are:
   Top (cathode): Au Thickness = 10,000Å minimum,
   Back (anode): Au Thickness = 4,000Å minimum.

FIGURE 4. JANHCB (B-version) die dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

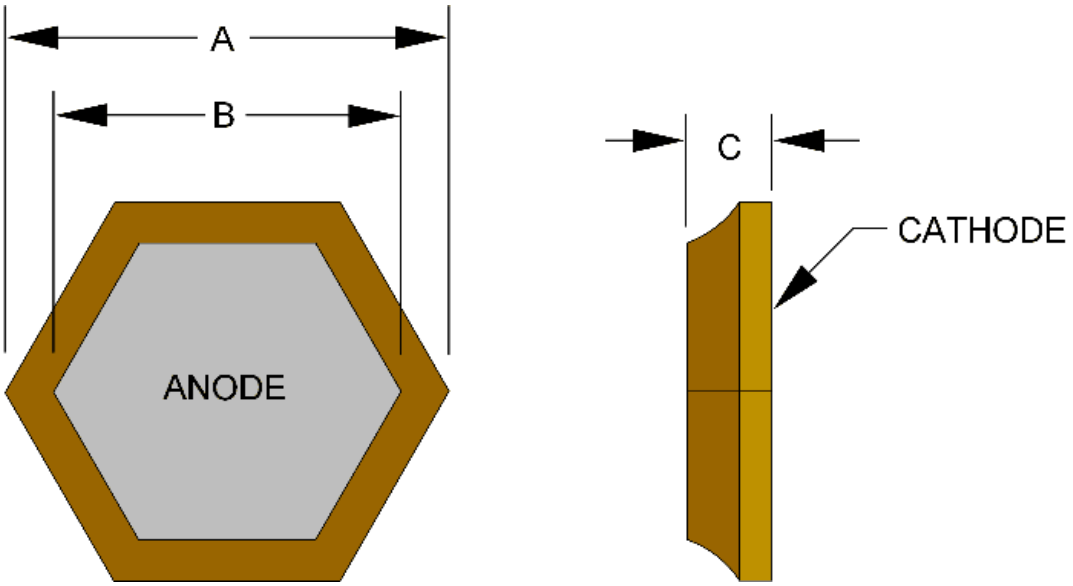


	Dimensions			
Letter	Inches	Inches	mm	mm
	Min	Max	Min	Max
A	0.086	0.092	2.18	2.34
B	0.069	0.075	1.75	1.91
C	0.010	0.014	0.25	0.36

NOTES:
1. Dimensions are in inches. Millimeter equivalents are given for general information only.
2. The metallization characteristics are:
   Top (anode) is Al at 45,000 Å nominal.
   Bottom (cathode) is Ti / Ni / Ag (1,200 Å / 1,800 Å / 30,000 Å) nominal.

FIGURE 5. JANKCC and JANHCC (C-version) die dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

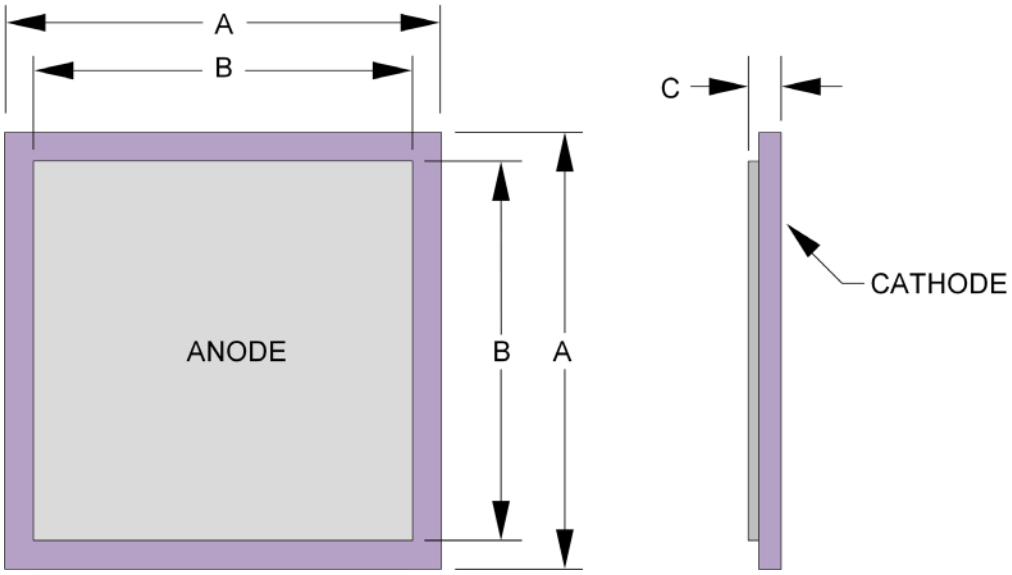


Letter	Dimensions for D and E version			
	Inches	Inches	mm	mm
	Min	Max	Min	Max
A	.081	.087	2.05	2.20
B	.055	.061	1.40	1.55
C	.007	.012	0.18	0.30

NOTES:
1. Dimensions are in inches. Millimeters are given for general information only.
2. The metallization characteristics for the D and E versions are as follows:

Material	D version	E version
Top (anode)	Al	Al
Back (cathode)	Au	Al / Ti / Ni / Ag
Thickness:		
Top (anode)	60,000 Å minimum	25,000 Å minimum
Back (cathode)	2,500 Å minimum	4,000 Å minimum

FIGURE 6. JANHCD, JANKCD, JANHCE and JANKCE (D and E versions) die dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

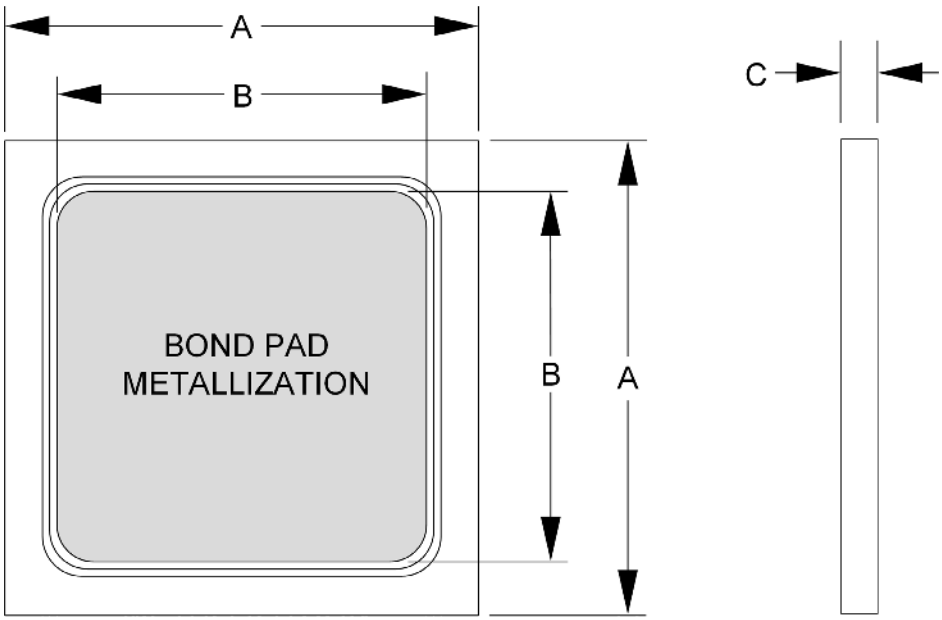

	Dimensions			
Letter	Inches	Inches	mm	mm
	Min	Max	Min	Max
A	0.085	0.095	2.16	2.41
B	0.063	0.073	1.60	1.85
C	0.006	0.016	0.15	0.41

NOTES:
1. Dimensions are in inches.
2. Millimeter equivalents are given for general information only.

FIGURE 7. JANKCF and JANHCF (F-version) die dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-19500 – Semiconductor Devices, General Specification for.

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-750 – Test Methods For Semiconductor Devices.

(Copies of these documents are available online at https://quicksearch.dla.mil.)

2.3 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturer's list (QML) before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500 and as follows.

$I_{O(L)}$ Average rectified output current, as a function of lead temperature at a distance L from the diode body.
P_{RM} Peak reverse power.

3.4 Interface and physical dimensions. The interface and physical dimensions shall be as specified in MIL-PRF-19500 and on figure 1 for 1N5550 through 1N5554, figure 2 for 1N5550US through 1N5554US, and figures 3, 4, 5, 6 and 7 for JANHC and JANKC die.

3.4.1 Lead finish. Unless otherwise specified, lead or end cap finish shall be solderable in accordance with MIL-PRF-19500, MIL-STD-750, and herein. When solder alloy is used for finish the maximum lead temperature is limited to 175 °C maximum. Where a choice of finish is desired, it shall be specified in the acquisition document (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

3.4.2 Diode construction. Axial leaded devices shall be constructed utilizing non-cavity double plug construction with high temperature metallurgical bonding between both sides of the silicon die and terminal pins. Metallurgical bond shall be in accordance with the requirements of category I of appendix A of MIL-PRF-19500. Point contact construction or Silver button Dumet design shall not be acceptable. US version devices shall be structurally identical to the axial leaded devices except for lead terminations.

3.5 Marking. Marking shall be in accordance with MIL-PRF-19500 and herein.

3.5.1 Marking of US version. For US version only, all marking may be omitted from the device except for the polarity marking. All marking which is omitted from the body of the device shall appear on the label of the initial container.

3.5.2 Polarity. The polarity shall be indicated with a contrasting color band to denote the cathode end. Alternately for US version (surface mount devices), a minimum of three evenly spaced contrasting color dots around the periphery of the cathode end may be used. No color coding will be permitted.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I herein.

3.7 Electrical test requirements. The electrical test requirements shall be as specified in table I herein.

3.8 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3).

c. Conformance inspection (see 4.4).

d. Element evaluation of un-encapsulated die (see 4.6).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.2.1 Group E inspection. Group E inspection shall be performed for qualification or requalification only. In case qualification was awarded to a prior revision of the specification sheet that did not request the performance of table II tests, the tests specified in table II herein that were not performed in the prior revision shall be performed on the first inspection lot to this revision to maintain qualification.

4.2.2 Qualification of un-encapsulated die (JANHC and JANKC). Qualification inspection for unencapsulated die shall be in accordance with appendix G of MIL-PRF-19500 and as specified herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

4.3 Screening (quality levels JANS, JANTXV, and JANTX only). Screening shall be in accordance with table E-IV of MIL-PRF-19500, and as specified herein. Specified electrical measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen	Measurements for quality level JANS	Measurements for quality levels JANTXV and JANTX
(1) 3c	Thermal impedance (see 4.3.1 and 4.4.1)	Thermal impedance (see 4.3.1 and 4.4.1)
9	V_{F1} and I_{R1}	Not applicable
10	Method 1038 of MIL-STD-750, condition A	Method 1038 of MIL-STD-750, condition A
(2) 11	V_{F1} and I_{R1}; $\Delta V_{F1} \leq \pm 0.1$ V dc ΔI_{R1} ±250 nA dc or 100 percent of initial value whichever is greater.	V_{F1} and I_{R1}
12	Required, see 4.3.2	Required, see 4.3.2
(2) (3) 13	Subgroups 2 and 3 of table I herein; $\Delta I_{R1} \leq$ 100 percent of initial reading or 250 nA dc, whichever is greater. $\Delta V_{F1} \leq \pm 0.1$ V dc change from initial value. Scope display evaluation (see 4.5.3)	Subgroup 2 of table I herein; $\Delta I_{R1} \leq$ 100 percent of initial reading or 250 nA dc, whichever is greater. $\Delta V_{F1} \leq \pm 0.1$ V dc change from initial value. Scope display evaluation (see 4.5.3)

(1) Thermal impedance shall be performed any time after sealing provided temperature cycling is performed in accordance with MIL-PRF-19500, screen 3 prior to this thermal test.
(2) For JANTX and JANTXV devices, ΔV_{F1} may be omitted if thermal impedance is performed, unless irradiation is used to reduce the carrier lifetime.
(3) $Z_{\theta JX}$ is not required in screen 13, if already previously performed.

4.3.1 Thermal impedance. The thermal impedance measurements shall be performed in accordance with method 3101 of MIL-STD-750 using the guidelines in that method for determining I_M, I_H, t_H, and K factor where appropriate. Measurement delay time (t_{MD}) = 70 µs max. The limit will be statistically derived. See table E-IX, subgroup 4, of MIL-PRF-19500, and table II, subgroup 4 herein.

4.3.2 Free air power burn-in conditions. Free air power burn-in shall be performed in accordance with test condition B of method 1038 of MIL-STD-750. The details of 4.5.2 and those that follows shall apply: I_O = 3 A minimum; T_A = 55°C maximum. Adjust I_O or T_A to achieve the required T_J. T_J = 135°C minimum. With approval of the qualifying activity, alternate burn-in criteria (hours, bias conditions, T_J, mounting conditions) may be used for JANTX and JANTXV quality levels. A justification demonstrating equivalence is required. In addition, the manufacturing site's burn-in data and performance history will be essential criteria for burn-in modification approval.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with table E-V of MIL-PRF-19500 and table I herein. The $Z_{\theta JX}$ end-point shall be derived by the supplier and approved by the qualifying activity. This $Z_{\theta JX}$ end-point shall be documented in the qualification report.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the tests and conditions specified for subgroup testing in table E-VIA (JANS) and table E-VIB (JAN, JANTX, and JANTXV) of MIL-PRF-19500. Delta measurements shall be as specified in table III herein.

4.4.2.1 Quality level JANS. For B5, if a failure occurs, resubmission shall be at the test conditions of the original sample.

Subgroup	Method	Condition
B3	4066	Condition A, I_{FSM} = rated I_{FSM} (see col. 6 of 1.3.2); ten surges of 8.3 ms each at 1 minute intervals, superimposed on I_O = 2 A, V_{RWM} = rated V_{RWM} (see col. 2 of 1.3.2). T_A = +55°C maximum.
B4	1037	I_O = 2.4 A minimum. V_R = rated V_{RWM} (see col. 2 of 1.3.2); 2,000 cycles. T_A = +55°C maximum.
B5	1027	See 4.5.2. I_O = 3 A minimum (see col. 4 of 1.3.2), apply V_R = rated V_{RWM} (see col. 2 of 1.3.2), Adjust I_O or T_A to achieve T_J = 175°C minimum; f = 50 to 60 Hz. T_A = + 55°C maximum. t = 1,000 hours; n = 45, c = 0.
B8	4065	P_{RM} ≥ 636 W for square wave and P_{RM} ≥ 1,000 W for half-sine wave. Test shall be performed on each sublot; sampling plan n = 10, c = 0, electrical end-points, see table I, subgroup 2 herein.

4.4.2.2 Quality levels JAN, JANTX, and JANTXV.

Subgroup	Method	Condition
B3	1027	See 4.5.2. I_O = 3 A minimum (see col. 4 of 1.3.2), adjust I_O or T_A to achieve the required T_J, apply V_R = rated V_{RWM} (see col. 2 of 1.3.2), f = 50 to 60 Hz. T_A =+55 °C maximum. T_J = 150 °C minimum.

4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the tests and conditions specified for subgroup testing in table E-VII of MIL-PRF-19500 and as follows. Delta measurements shall be as specified in table III herein.

Subgroup	Method	Condition
C2	2036	Axial devices only; Tension: Test condition A; weight = 20 pounds (9.1 kg); t = 15 s. Lead fatigue: Test condition E; weight 2 pounds (0.91 kg).
C2	2038	US devices only; Tab pull: Test condition B; weight = 20 pounds (9.1 kg); t = 15 s.
C5	4081	For axial devices; $R_{\theta JL}$ (maximum) ≤ 22 °C/W, L = .375 inch (9.53 mm). For surface mount devices (US version); $R_{\theta JEC}$ < 6.5 °C/W (see 4.5.4).
C6	1026	See 4.5.2. I_O = 3 A minimum (see col. 4 of 1.3.2), adjust I_O or T_A to achieve the required T_J. Apply V_R = rated V_{RWM} (see col. 2 of 1.3.2), f = 50 to 60 Hz. T_A = +55 °C maximum, T_J = 150 °C minimum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

4.4.4 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-IX of MIL-PRF-19500 and as specified herein. Delta measurements shall be as specified in table III herein.

4.5 Methods of inspection. Methods of inspection shall be as specified in appropriate tables and as follows.

4.5.1 Pulse measurements. Conditions for pulse measurement shall be as specified in section 4 of MIL-STD-750.

4.5.2 Burn-in and life tests.

4.5.2.1 Waveforms and currents. These tests shall be conducted with a half-sine waveform of the specified peak voltage impressed across the DUT in the reverse direction followed by a half-sine waveform of the specified average rectified current. The forward conduction angle of the rectified current shall be neither greater than 180 degrees, nor less than 150 degrees.

4.5.2.2 Burn-in. The use of a current limiting or ballast resistor is permitted provided that each DUT still sees the required T_J at full rated I_O and that the minimum required voltage V_{RWM} is maintained throughout the burn-in period. With the approval of the qualifying activity, the supplier may apply T_J = 200°C maximum during burn-in test.

4.5.2.3 Junction temperature measurements. Test method 3100 of MIL-STD-750 to shall be used measure T_J.

4.5.3 Scope display evaluation. Scope display evaluation shall be performed in accordance with condition B (sharp and stable) of method 4023 of MIL-STD-750. Scope display may be performed on ATE (automatic test equipment) for screening only, with the approval of the qualifying activity. Scope display in table I, subgroup 4 shall be performed on a curve tracer. The reverse current (I_{BR}) over the knee shall be 500 µA peak.

4.5.4 Thermal resistance. Thermal resistance measurement shall be performed in accordance with method 4081 of MIL-STD-750 using the guidelines in that method for determining I_M, I_H, t_H, and t_{MD}. See table E-IX, subgroup 4 of MIL-PRF-19500, and figures 8, and 9 herein.

4.5.5 Peak reverse power characterization. The testing to characterize P_{RM} shall be conducted in accordance with method 4065 of MIL-STD-750. The following details shall apply:

a. During the test, the voltage (V_{BR}) shall be monitored to verify it has not collapsed.

b. Any collapse in V_{BR} during or after the test, or rise in leakage current (I_R) after the test that exceeds I_{R1} in table I, shall be considered a failure to that level of applied P_{RM}.

c. Progressively higher levels of P_{RM} shall be applied until failure occurs on all devices within the chosen sample size to characterize each sublot.

4.6 Element evaluation of un-encapsulated die. The element evaluation of un-encapsulated die shall be in accordance with appendix G of MIL-PRF-19500. As a minimum, die shall be 100-percent probed to ensure compliance with table I, subgroup 2. Burn-in duration for the JANKC level follows JANS requirements; the JANHC follows JANTX requirements.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limits	Limits	Unit
	Method	Conditions		Min	Max	
Subgroup 1						
Visual and mechanical examination	2071					
Subgroup 2						
Thermal impedance 2/	3101	See 4.3.1	$Z_{\theta JX}$			°C/W
Forward voltage	4011	Condition B; I_F = 9.0 A, (pulsed see 4.5.1); tp ≤ 8.3 ms; duty cycle ≤ 2 percent	V_{F1}			
1N5550, 1N5550US				0.6	1.2	V
1N5551, 1N5551US				0.6	1.2	V
1N5552, 1N5552US				0.6	1.2	V
1N5553, 1N5553US				0.6	1.3	V
1N5554, 1N5554US				0.6	1.3	V
Forward voltage	4011	Condition B; I_F = 1.5 A	V_{F2}	0.5	1.0	V
Reverse current leakage	4016	Condition A or B	I_{R1}			
1N5550, 1N5550US		V_R = 200 V			1.0	µA
1N5551, 1N5551US		V_R = 400 V			1.0	µA
1N5552, 1N5552US		V_R = 600 V			1.0	µA
1N5553, 1N5553US		V_R = 800 V			1.0	µA
1N5554, 1N5554US		V_R = 1,000 V			1.0	µA
Breakdown voltage (diodes)	4021		V_{BR1}			
1N5550, 1N5550US		I_R = 50 µA		220		V
1N5551, 1N5551US		I_R = 50 µA		440		V
1N5552, 1N5552US		I_R = 50 µA		660		V
1N5553, 1N5553US		I_R = 50 µA		880		V
1N5554, 1N5554US		I_R = 50 µA		1,100		V
Subgroup 3						
High temperature operation:		T_A = +125 °C				
Reverse current leakage	4016	Condition A or B	I_{R2}			
1N5550, 1N5550US		V_R = 200 V			60	µA
1N5551, 1N5551US		V_R = 400 V			60	µA
1N5552, 1N5552US		V_R = 600 V			60	µA
1N5553, 1N5553US		V_R = 800 V			60	µA
1N5554, 1N5554US		V_R = 1,000 V			60	µA

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits	Limits	Unit
	Method	Conditions		Min	Max	
Subgroup 3 - continued						
Forward voltage	4011	Condition B; I_F = 9.0 A, (pulsed see 4.5.1) tp ≤ 8.3 ms; duty cycle ≤ 2 percent	V_{F2}			
1N5550, 1N5550US					1.2	V
1N5551, 1N5551US					1.2	V
1N5552, 1N5552US					1.2	V
1N5553, 1N5553US					1.3	V
1N5554, 1N5554US					1.3	V
Low temperature operation:		T_A = -55 °C				
Forward voltage	4011	Condition B; I_F = 9.0 A, (pulsed see 4.5.1), tp ≤ 8.3 ms; duty cycle ≤ 2 percent	V_{F3}		1.5	V
Forward voltage	4011	Condition B; I_F = 1.5 A	V_{F4}	0.5	1.2	V
Breakdown voltage (diodes)	4021		V_{BR2}			
1N5550, 1N5550US		I_R = 50 µA		200		V
1N5551, 1N5551US		I_R = 50 µA		400		V
1N5552, 1N5552US		I_R = 50 µA		600		V
1N5553, 1N5553US		I_R = 50 µA		800		V
1N5554, 1N5554US		I_R = 50 µA		1,000		V
Subgroup 4						
Reverse recovery time	4031	Condition B1	t_{rr}		2.0	µs
Scope display evaluation	4023	See 4.5.3, condition B, n = 116, c = 0				
Subgroups 5						
Not applicable						
Subgroup 6						
Forward surge current	4066	Condition A; I_{FSM} = rated (see col. 6 of 1.3.2); ten surges of 8.3 ms each at 1 minute intervals, superimposed on I_O = 2 A, V_{RSM} = rated V_{RWM} (see col. 2 of 1.3.2); T_A = +55°C				
Electrical measurement		See table I, subgroup 2.				

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits	Limits	Unit
	Method	Conditions		Min	Max	
Subgroup 7 Not applicable						

1/ For sampling plan, see MIL-PRF-19500.
2/ This test required for the following end-point measurements only:
Group B, subgroups 3, 4, and 5 (JANS).
Group B, subgroups 2 and 3 (JAN, JANTX, and JANTXV).
Group C, subgroup 2 and 6.
Group E, subgroup 1.

TABLE II. Group E inspection (all quality levels) for qualification and requalification only.

Inspection	MIL-STD-750		Sampling plan
	Method	Conditions	
Subgroup 1A			45 devices, c = 0
Temperature cycling (air to air)	1051	20 cycles, low temperature shall be -195°C and high temperature shall be +150°C.	
Hermetic seal	1071	Fine and gross as applicable.	
Electrical measurement		See table I, subgroup 2 and table III herein.	
Subgroup 1B			
Temperature cycling (air to air)	1051	500 cycles, -65°C to +175°C.	45 devices, c = 0
Hermetic seal	1071	Fine and gross as applicable.	
Electrical measurement		See table I, subgroup 2 and table III herein.	
Subgroup 2			22 devices, c = 0
Steady state dc blocking life	1048	1,000 hours, $V_R = V_{RWM}$ (see col. 2 of 1.3).	
Electrical measurements		See table I, subgroup 2 (except $Z_{\theta JX}$ need not be performed) and table III herein.	
Subgroup 4			
Thermal impedance curves		See MIL-PRF-19500.	

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

TABLE II. Group E inspection (all quality levels) for qualification and requalification only - Continued.

Inspection	MIL-STD-750		Sampling plan
	Method	Conditions	
Subgroup 5			22 devices, c = 0
Barometric pressure, (reduced)	1001	Voltage during test shall be V_{RWM} (see col. 2 of 1.3.2); Maximum leakage (I_R) during test shall be 1.0 µA dc; t = 1 minute (minimum). Pressure shall be as follows: Condition D (8 mm Hg) for 1N5550, 1N5551, and 1N5552; Condition C (33 mm Hg) for 1N5553 and 1N5554.	
Subgroup 8			45 devices
Peak reverse power	4065	P_{RM} shall be characterized by the supplier and this data shall be available to the Government. Test shall be performed on each sublot.	
Electrical measurement		See 4.5.5	
Subgroup 9			45 devices
Resistance to glass cracking	1057	Step stress to destruction by increasing cycles or up to a maximum of 25 cycles.	
Subgroup 10			22 devices, c = 0
Forward surge current	4066	Condition A, I_{FSM} = 100 A(pk); ten surges of 8.3 ms each at 1 minute intervals, superimposed on I_O = 2 A dc (see col. 5 of 1.3.2); V_{RWM} = rated V_{RWM} (see col. 2 of 1.3.2). T_A = +55°C.	
Electrical measurement		See table I, subgroup 2 and table III herein.	


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

TABLE III. Groups A, B, C and E delta measurements. 1/ 2/ 3/ 4/ 5/

Step	Inspection	MIL-STD-750		Symbol	Limits	
		Method	Conditions		Min	Max
1	Reverse leakage current change	4016	Condition A or B	ΔI_{R1}		±100 percent of initial value or ±250 nA dc, whichever is greater.
2	Forward voltage change	4011	I_F = 1.5 A dc; condition B, pulsed (see 4.5.1)	ΔV_{F2}		±50 mV dc maximum change from previous measured value.

1/ Devices which exceed table I, subgroup 2 (group A) limits for this test shall not be accepted.
2/ The delta measurements taken during group B inspections for quality level JANS (table E-VIA of MIL-PRF-19500) shall be as follows:
   a. In addition to the measurements specified for subgroup 3, the measurements of step 1 of this table shall also be taken.
   b. In addition to the measurements specified for subgroup 4, the measurements of step 1 of this table shall also be taken.
   c. In addition to the measurements specified for subgroup 5, the measurements of step 1 of this table shall also be taken.
3/ The delta measurements taken during group B inspections for quality levels JAN, JANTX and JANTXV (table E-VIB of MIL-PRF-19500) shall be as follows:
   a. In addition to the measurements specified for subgroup 3, step 1 of this table shall also be taken.
   b. In addition to the measurements specified for subgroup 6, step 1 of this table shall also be taken.
4/ The delta measurements taken during group C inspections for all quality levels (table E-VII of MIL-PRF-19500) shall be as follows:
   a. In addition to the measurements specified for subgroup 2, the measurements of step 1 of this table shall also be taken.
   b. In addition to the measurements specified for subgroup 6, the measurements of step 1 of this table shall also be taken.
5/ The delta measurements taken during group E inspections for all quality levels (table E-IX of MIL-PRF-19500) shall be as follows:
   a. In addition to the measurements specified for subgroup 1, the measurements of steps 1 and 2 of this table shall also be taken.
   b. In addition to the measurements specified for subgroup 2, the measurements of steps 1 and 2 of this table shall also be taken.
   c. In addition to the measurements specified for subgroup 10, the measurements of step 1 of this table shall also be taken

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

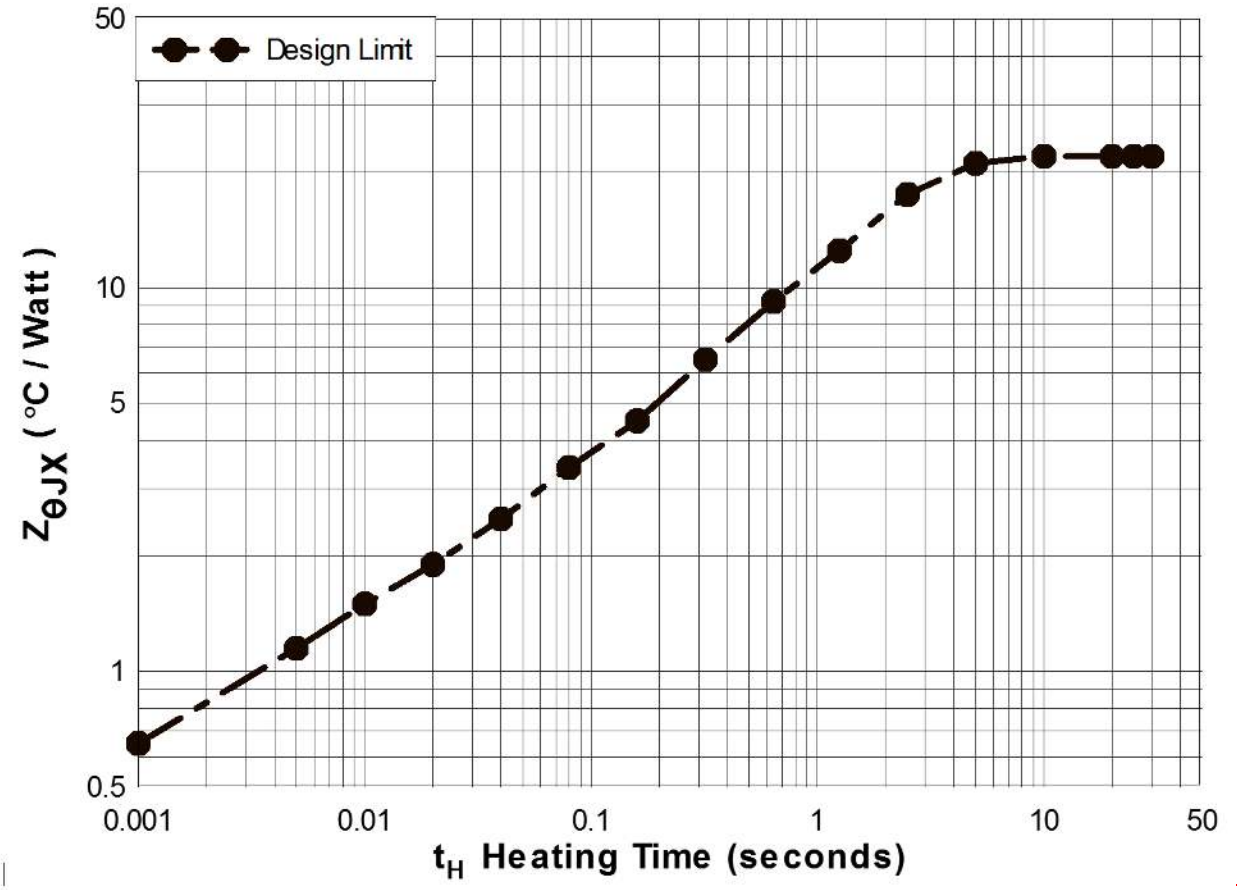


$Z_{\theta JX}$ = 1.5°C/W at 10 ms

$R_{\theta JL}$ = 22°C/W

FIGURE 8. Axial leaded thermal-impedance maximum curve.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

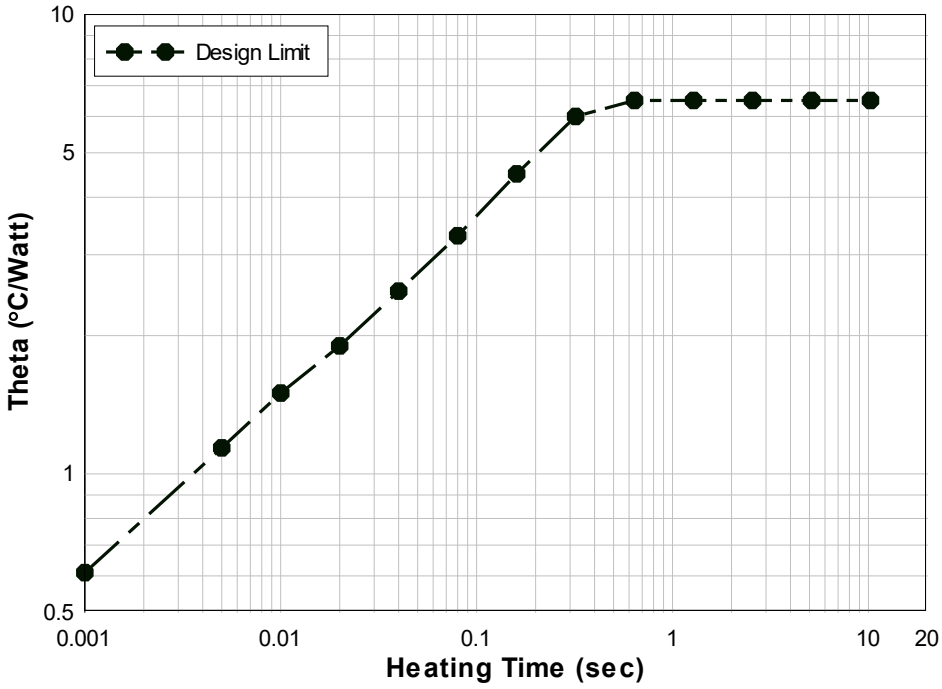

$Z_{\theta JX}$ = 1.5°C/W at 10 ms

$R_{\theta JEC}$ = 6.5°C/W

FIGURE 9. US surface mount thermal-impedance maximum curve.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the Military Service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory. The notes specified in MIL-PRF-19500 are applicable to this specification.)

6.1 Intended use. Semiconductors conforming to this specification are intended for original equipment design applications and logistic support of existing equipment.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Packaging requirements (see 5.1).


c. Lead finish (see 3.4.1).

d. The complete PIN, see 1.5 and 6.5.

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List (QML 19500) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from DLA Land and Maritime, ATTN: VQE, P.O. Box 3990, Columbus, OH 43218-3990 or e-mail vqe.chief@dla.mil. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://qpldocs.dla.mil.


6.4 PIN construction examples.

6.4.1 Encapsulated devices. The PINs for encapsulated devices are construction using the following form.

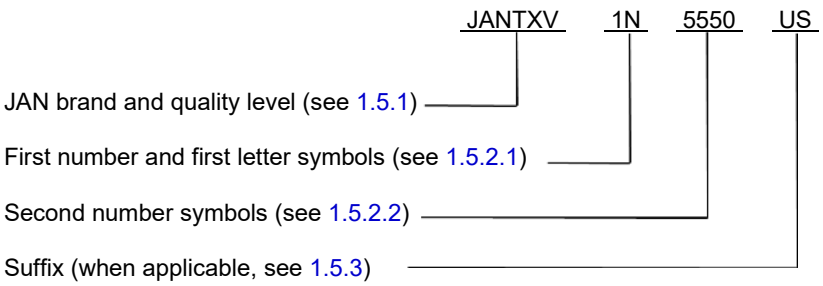

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

6.4.2 Un-encapsulated devices. The PINs for un-encapsulated devices are constructed using the following form.

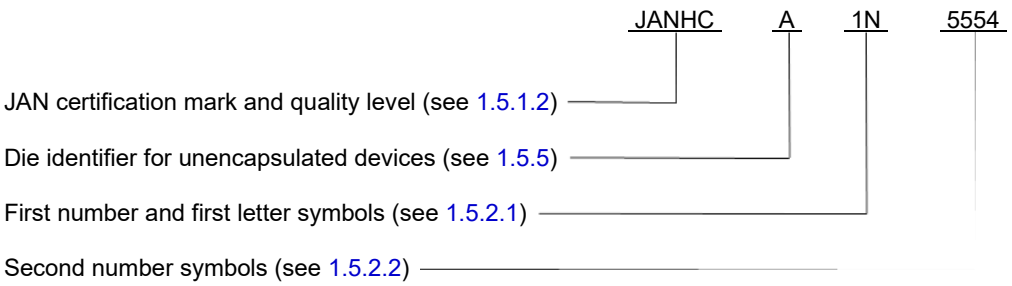

6.5 List of PINs. The following is a list of possible PINs available on this specification sheet.

6.5.1 List of PINs for encapsulated devices. The following is a list of possible PINs for encapsulated devices available on this specification sheet.

Axial lead package of figure 1				Surface mount package of figure 2			
Quality level "JAN"	Quality level "JANTX"	Quality level "JANTXV"	Quality level "JANS"	Quality level "JAN"	Quality level "JANTX"	Quality level "JANTXV"	Quality level "JANS"
JAN1N5550	JANTX1N5550	JANTXV1N5550	JANS1N5550	JAN1N5550US	JANTX1N5550US	JANTXV1N5550US	JANS1N5550US
JAN1N5551	JANTX1N5551	JANTXV1N5551	JANS1N5551	JAN1N5551US	JANTX1N5551US	JANTXV1N5551US	JANS1N5551US
JAN1N5552	JANTX1N5552	JANTXV1N5552	JANS1N5552	JAN1N5552US	JANTX1N5552US	JANTXV1N5552US	JANS1N5552US
JAN1N5553	JANTX1N5553	JANTXV1N5553	JANS1N5553	JAN1N5553US	JANTX1N5553US	JANTXV1N5553US	JANS1N5553US
JAN1N5554	JANTX1N5554	JANTXV1N5554	JANS1N5554	JAN1N5554US	JANTX1N5554US	JANTXV1N5554US	JANS1N5554US

6.5.2 List of PINs for unencapsulated devices. The listing of possible PINs available on this specification sheet is detailed in 6.6. The qualified die suppliers with the applicable letter version (e.g., JANHCA1N5550) will be identified on the QML.


6.6 Suppliers of die. The qualified die suppliers with the applicable letter version (example JANHCA1N5550) will be identified on the QML. JANC ordering information is as follows:

	Manufacturer					
Type	14552	60211	13409	33178	33178	34156
1N5550	JANHCA1N5550 JANKCA1N5550	JANHCB1N5550	JANHCC1N5550 JANKCC1N5550	JANHCD1N5550	JANHCE1N5550	JANHCF1N5550 JANKCF1N5550
1N5551	JANHCA1N5551 JANKCA1N5551	JANHCB1N5551	JANHCC1N5551 JANKCC1N5551	JANHCD1N5551	JANHCE1N5551	JANHCF1N5551 JANKCF1N5551
1N5552	JANHCA1N5552 JANKCA1N5552	JANHCB1N5552	JANHCC1N5552 JANKCC1N5552	JANHCD1N5552	JANHCE1N5552	JANHCF1N5552 JANKCF1N5552
1N5553	JANHCA1N5553 JANKCA1N5553	JANHCB1N5553	JANHCC1N5553 JANKCC1N5553	JANHCD1N5553	JANHCE1N5553	JANHCF1N5553 JANKCF1N5553
1N5554	JANHCA1N5554 JANKCA1N5554	JANHCB1N5554	JANHCC1N5554 JANKCC1N5554	JANHCD1N5554	JANHCE1N5554	JANHCF1N5554 JANKCF1N5554

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

6.7 Applications data.

6.7.1 Maximum power and current as a function of lead temperature curves. See figure 10 for maximum power in watts as a function of lead temperature at a distance "L" from the diode body. Device current capability with lead-dissipators or body forced-air-cooling, may be determined from figure 11, which shows maximum average rectified current versus lead temperature as a function of the distance "L" from the diode body at which lead temperature is measured.

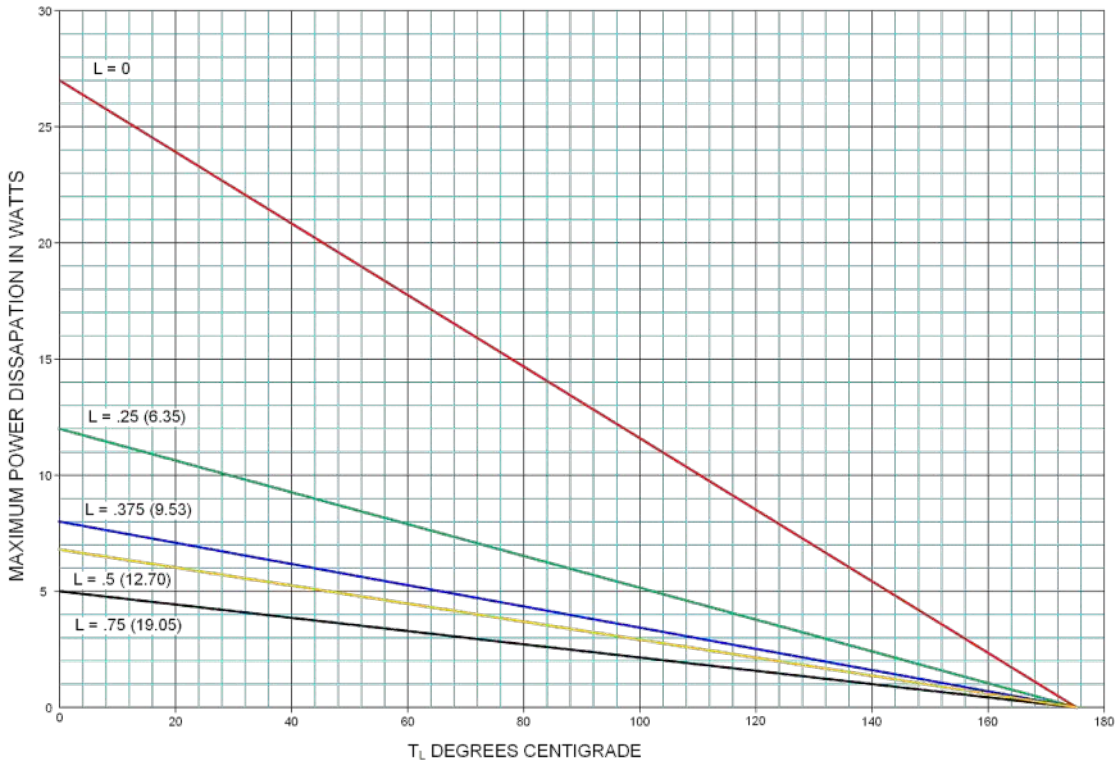


Maximum lead temperature (T_L) in °C at point "L" from diode body (for maximum operating junction temperature of +175°C with equal two-lead conditions).

L		$R_{\theta JL}$
Inches	mm	°C/W
.000	0.00	6.5
.250	6.35	14.5
.375	9.53	22
.500	12.70	26
.750	19.05	35.5

NOTES:
1. Dimensions are in inches. Millimeters are given for general information only.
2. In accordance with ASME Y14.5, diameters are equivalent to øx symbology.

FIGURE 10. Maximum power in watts versus lead temperature.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

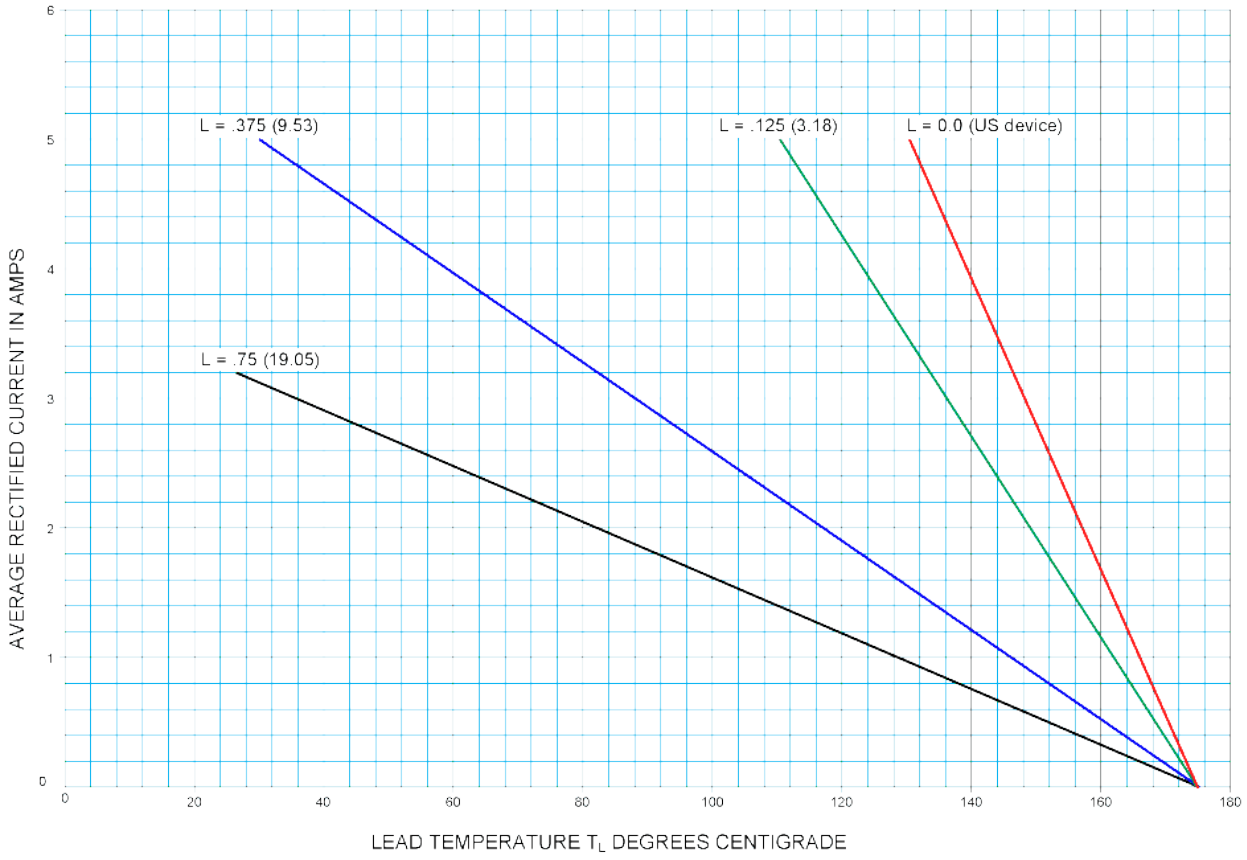

Maximum lead temperature (T_L) in °C at point "L" from diode body (for maximum operating junction temperature of +175°C with equal two-lead conditions).

NOTES
1. Dimensions are in inches. Millimeters are given for general information only.
2. In accordance with ASME Y14.5, diameters are equivalent to øx symbology.

FIGURE 11. Maximum current versus lead temperature.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

6.7.2 PCB mounting with FR4 material for full 3 amp I_O. For a PCB mounting example with FR4 material where the full 3 amp I_O rating (half-sine-wave) is used at a T_J of 175°C and ambient temperature of 55°C, the following steps guide the user in what the PCB pad size will need to be with 1 oz., 2 oz., and 3 oz. copper foil. For axial-leaded devices, the lead length for mounting will be .187 inch (4.76 mm) or less from body to entry point on PCB surface.

a. Use the I_O versus Po curve on figure 12 to look up 3 amps (X-axis) and follow up to the T_J = 175°C curve (lower) for 2.55 watts.

b. Calculate maximum thermal resistance needed (175°C - 55°C) / 2.55 W = 47°C/W.

c. Look up thermal resistance of 47°C/W on Y-axis using a thermal resistance versus pad area plot on one of the three curves on figure 13 for different weights of copper foil and then intersect curve horizontally to get answer. These curves assume still air, horizontal position.

d. In this example, the copper mounting pad sizes for the different copper foil weights would be as follows:

(1) .75 in^2 (483.9 mm^2) for 1 ounce copper foil.

(2) .43 in^2 (277.4 mm^2) for 2 ounce copper foil.

(3) .29 in^2 (187.1 mm^2) for 3 ounce copper foil.

e. Add a conservative guard-band to the pad size (larger) to keep T_J below 175°C.

6.7.3 PCB mounting with FR4 material for 1 amp I_O. For a PCB mounting example with FR4 material to support a 1 amp I_O square wave switching at a 0.50 duty factor (50 percent duty cycle) at T_J = 100°C and ambient temperature of 55°C, the following steps guide the user in what the PCB pad size will need to be with 1 oz., 2 oz., and 3 oz. copper foil.

a. Find size of copper pads on standard FR4 PCB to support operation at 1 amp I_O square wave switching at a 0.50 duty factor (50 percent duty cycle) at T_J = 100°C with T_A = 55°C.

b. Calculate peak I_F = 1A / 0.50 duty factor = 2 amps.

c. Use the V_F versus I_F curve on figure 14 to look up I_F = 2 A (Y-axis) and follow across to the T_J = 100°C curve (middle) for V_F = 0.81 V.

d. Calculate power = I_F x V_F x duty factor = 2 x 0.81 x 0.50 = 0.81 W.

e. Calculate maximum thermal resistance needed (100°C - 55°C) / 0.81 W = 56°C/W.

f. Look up thermal resistance of 56°C/W on the Y-axis using a thermal resistance versus pad area plot on one of the three curves on figure 13 for different weights of copper foil and then intersect curve horizontally to get answer. Curves assume still air, horizontal position.

g. In this example, the copper mounting pad sizes for the different copper foil weights would be as follows:

(1) .45 in^2 (290.3 mm^2) for 1 ounce copper foil.

(2) .25 in^2 (161.3 mm^2) for 1 ounce copper foil.

(3) .17 in^2 (109.7 mm^2) for 1 ounce copper foil.

h. A conservative pad guard-band is optional since T_J is only 100°C. NOTE: With multilayer PCBs, forced air cooling will improve performance. Closed confinement of the PCB will do the opposite. Please use sound thermal management.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

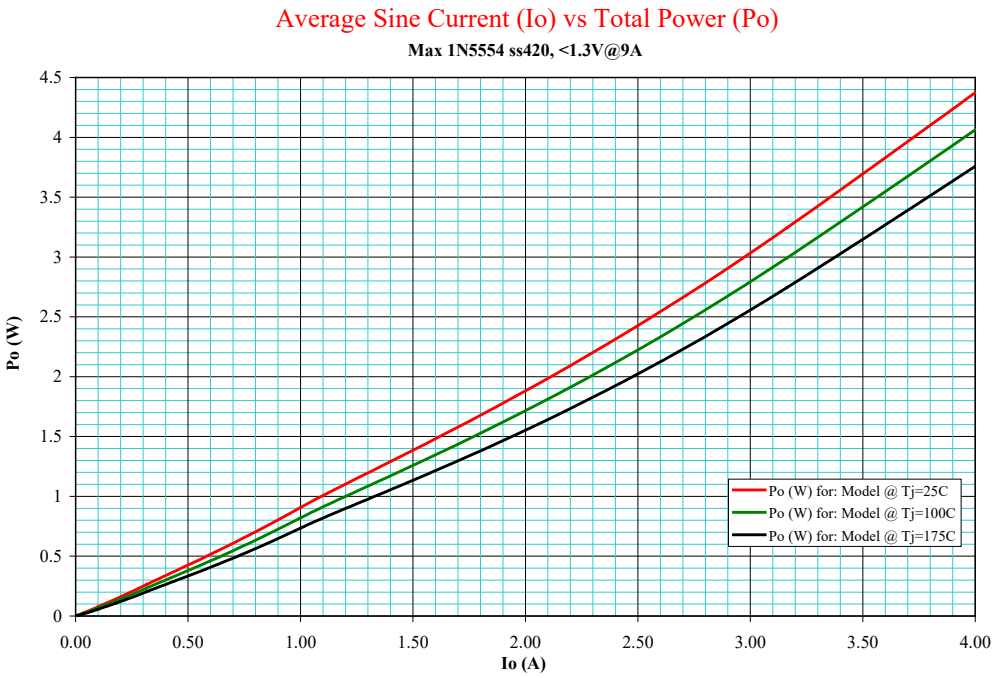


FIGURE 12. Rectifier power versus I_o (average forward current).

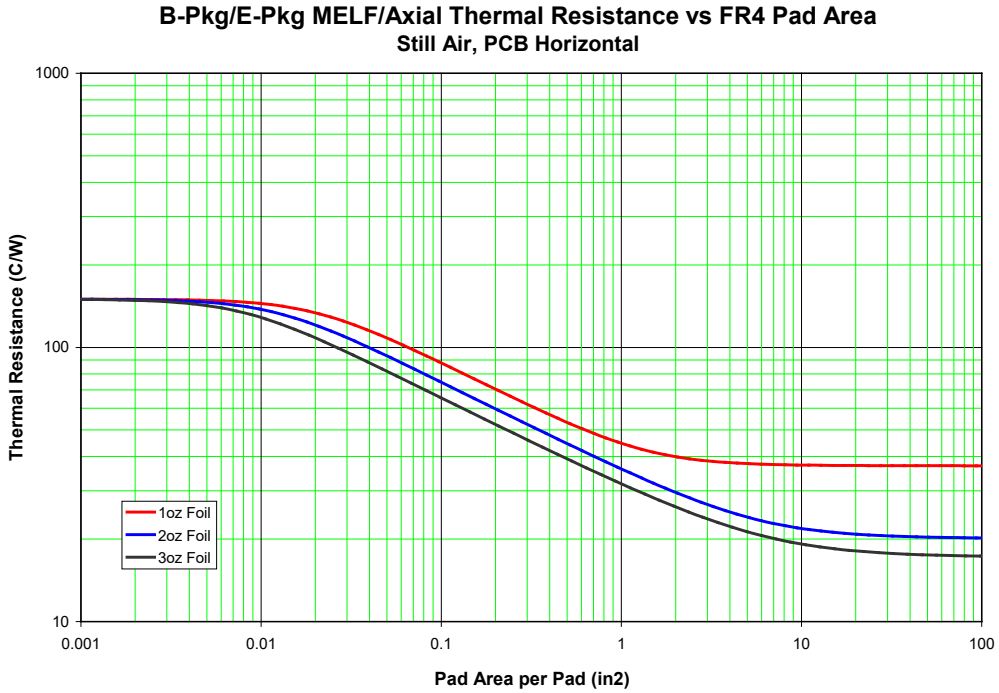


FIGURE 13. Thermal resistance versus pad area (for each pad) with 1, 2 and 3 oz. copper.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

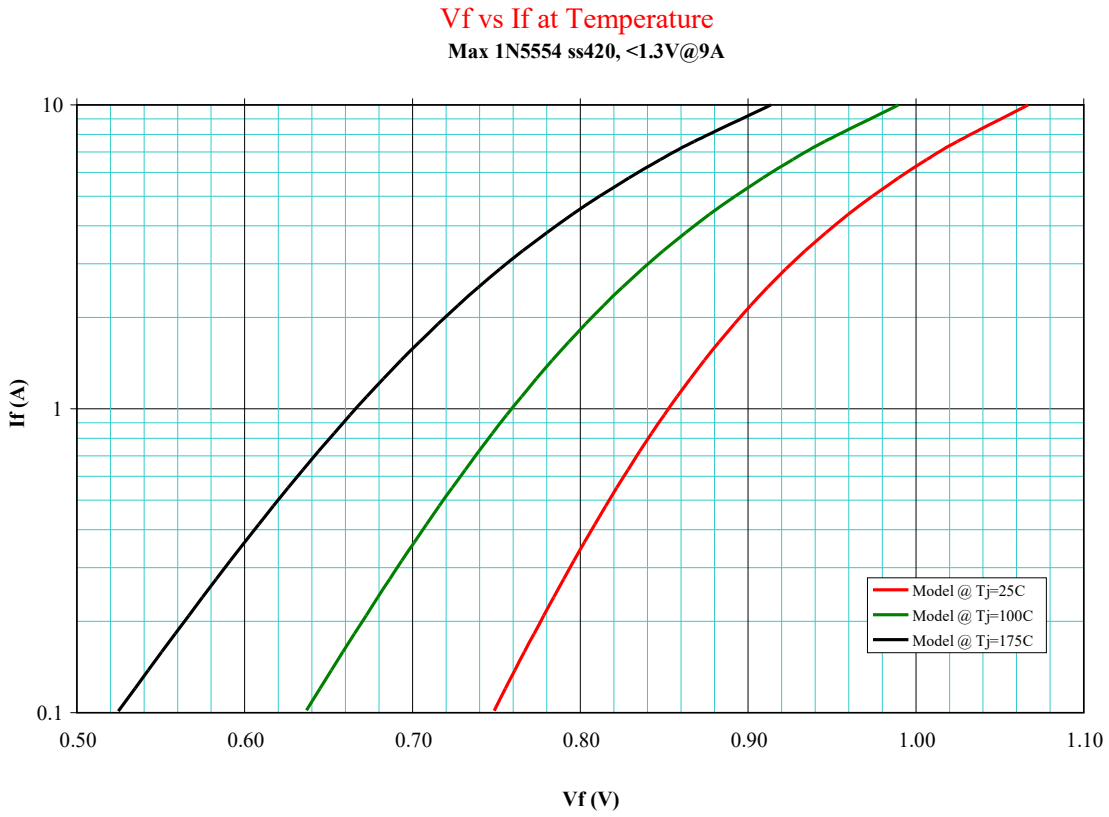


FIGURE 14. Forward voltage versus forward current for 1N5554.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.

6.8 Request for new types and configurations. Requests for new device types or configurations for inclusions in this specification sheet should be submitted to: DLA Land and Maritime, ATTN: VAC, Post Office Box 3990, Columbus, OH 43218−3990 or by electronic mail at Semiconductor@dla.mil .

6.9 Amendment notations. The margins of this specification are marked with vertical lines to indicate modifications generated by this amendment. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

Custodians:
Army − CR
Navy − SH
Air Force − 85
NASA − NA
DLA − CC

Review activities:
Army − AR, MI, SM
Navy − AS, MC
Air Force − 19, 71

Preparing activity:
DLA − CC

(Project 5961-2022-032)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:46Z
Check the source to verify that this is the current version before use.