INCH-POUND

MIL-N-85615/8
15 December 1989

MILITARY SPECIFICATION SHEET

NUT, SELF-SEALING, SELF-LOCKING, ALLOY STEEL,
125 KSI FTU, 250°F AND 450°F

This specification sheet is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and the issue of the following specification listed in that issue of the Department of Defense Index of Specifications and Standards (DODISS) specified in the solicitation: MIL-N-85615.

REQUIREMENTS:

Qualification required.

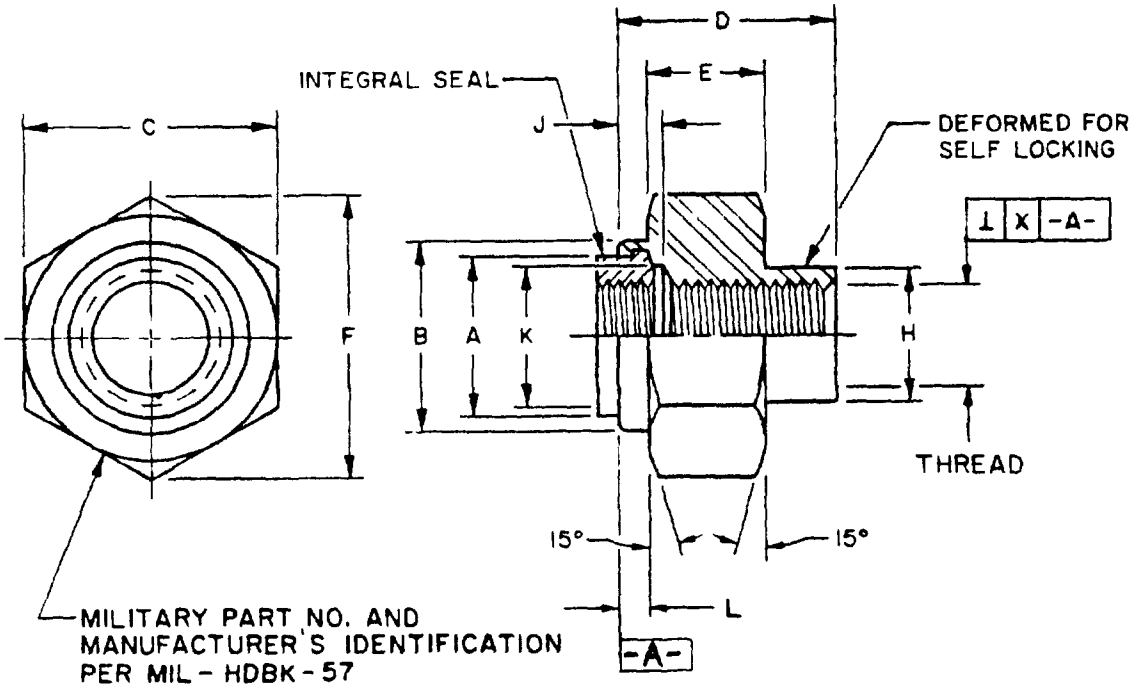



FIGURE 1. Self-sealing locknut.

AMSC N/A FSC 5310

DISTRIBUTION STATEMENT A: Approved for public release; distribution is unlimited.



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:13Z
Check the source to verify that this is the current version before use.

TABLE I. Dimensions and characteristics.

| Size Code | Thread Designation UNJF-3B | Dia A Ref | Dia B ±.005 | Hex Flats C +.005 -.010 | D Max. | E Ref. | Hex Points F Ref. | Bearing Surface Squareness Max X | J** | K** | L Ref |
|---|---|---|---|---|---|---|---|---|---|---|---|
| -3 | .1900-32 | .255 | .364 | .375 | .235 | .092 | .432 | .006 | .122<br>.102 | .206<br>.200 | .055 |
| -4 | .2500-28 | .368 | .489 | .500 | .340 | .138 | .577 | .007 | .127<br>.107 | .268<br>.262 | .062 |
| -5 | .3125-24 | .427 | .547 | .563 | .430 | .178 | .649 | .008 | .137<br>.117 | .331<br>.325 | .067 |
| -6 | .3750-24 | .505 | .686 | .688 | .470 | .216 | .793 | .009 | .137<br>.117 | .393<br>.387 | .092 |
| -7 | .4375-20 | .561 | .744 | .750 | .565 | .255 | .865 | .009 | .152<br>.132 | .471<br>.465 | .100 |
| -8 | .5000-20 | .648 | .841 | .875 | .615 | .326 | 1.010 | .010 | .160<br>.140 | .518<br>.512 | .086 |

**Apply before seal installation, not subject to user inspection.

TABLE II. Axial tensile strength (lbs) alloy steel.

| Size Code | Thread Designation | Axial Tensile Strength (Lbs) Min Alloy Steel (125 KSI) |
|---|---|---|
| -3 | .1900-32 | 2,460 |
| -4 | .2500-28 | 4,580 |
| -5 | .3125-24 | 7,390 |
| -6 | .3750-24 | 11,450 |
| -7 | .4375-20 | 15,450 |
| -8 | .5000-20 | 21,110 |



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:13Z
Check the source to verify that this is the current version before use.

REQUIREMENTS:

1. Material: Nut body - Alloy steel in accordance with AMS 5022 (UNS G11170).

   Seal - Nylon or equivalent in accordance with ASTM D4066. Polytetrafluoroethylene in accordance with ASTM D1710.

2. Threads: Threads shall be in accordance with MIL-S-8879.

3. Finish: Cadmium plate per QQ-P-416, Type II, Class 2, or bright nickel plate per QQ-N-290.

4. Lubrication: Dry film lubricant in accordance with MIL-L-46010, Type I.

5. Surface texture: Measured in accordance with ANSI/ASME B46.1.

6. Pressure range: Wet or dry, pressure or vacuum, 0 to 100 PSI.

NOTES:


1. These nuts are intended for use in applications where a dynamic sealing nut is required to eliminate leak paths at threaded joints in fuel tanks and other applications requiring environmental sealing, or as a reusable seal on threaded adjustments and connections in fluid power systems.

2. Dimensions are in inches.

3. Unless otherwise specified, tolerances are ±.010 for decimals and ±5° for angles.

4. All sharp edges shall be broken and all burrs shall be removed.

Example of a military Part or Identifying Number (PIN):

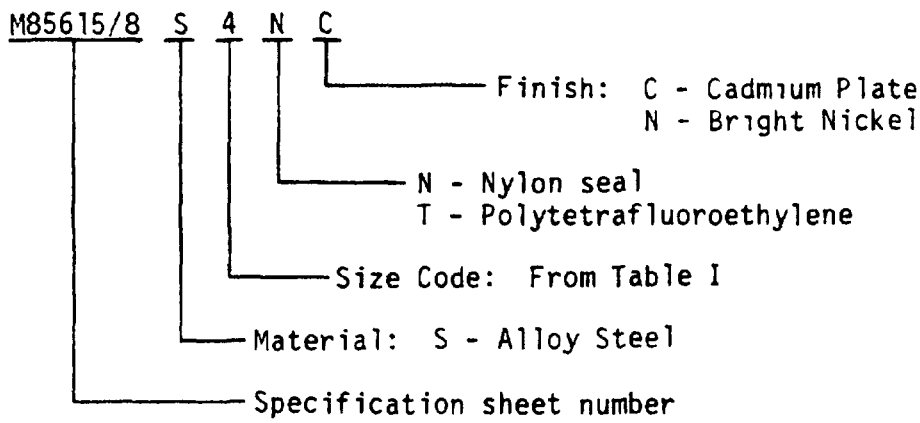




Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:13Z
Check the source to verify that this is the current version before use.

Custodians:
Army - AR
Navy - AS
Air Force - 99

Review Activities:
Army - MI, AV
Navy - SH, OS
DLA - IS

Preparing activity:
Navy - AS
(Project No. 5310-1616)



Source: https://assist.dla.mil -- Downloaded: 2026-10-23T11:13Z
Check the source to verify that this is the current version before use.