The documentation and process conversion measures necessary to comply with this revision shall be completed by 21 March 2005.

INCH-POUND

MIL-PRF-19500/503C
21 December 2004
SUPERSEDING
MIL-PRF-19500/503B
12 September 1997

PERFORMANCE SPECIFICATION SHEET

SEMICONDUCTOR DEVICE, DIODE, SILICON, POWER RECTIFIER,
ULTRA FAST RECOVERY, TYPES 1N6073 THROUGH 1N6081,
JAN, JANTX, JANTXV, AND JANHC

This specification is approved for use by all Departments and Agencies of the Department of Defense.

* The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-PRF-19500.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for three separate series of silicon, ultra fast recovery semiconductor diodes for use as power rectifiers. Three levels of product assurance are provided for each device type as specified in MIL-PRF-19500. One level of product assurance are provided for each unencapsulated device type.

1.2 Physical dimensions. See figures 1 (similar to DO-35) and 2 (die) herein.

* 1.3 Maximum ratings Unless otherwise specified, T_A = +25°C.


Col. 1 Types	Col. 2 V_R	Col. 3 V_{RWM}	Col.4 I_{O1}	Col.5 I_{O2}	Col. 6 t_{rr} (see fig. 3)	Col. 7 T_{STG} and T_J	Col.8 $R_{\theta JL}$	Col. 9 I_{FSM}
			T_A = +55°C (1) (2) (3)	T_L = +70°C (1) (4) (5)	I_F = 0.5 A I_R = -1.0 A I_{RR} = -0.25 A		(1)	t_p = 8.3 ms
	V dc	V (pk)	A dc	A dc	ns	°C	°C/W	A (pk)
1N6073	50	50	.85	3.0	30	-65 to +155	13.0	35
1N6074	100	100	.85	3.0	30	-65 to +155	13.0	35
1N6075	150	150	.85	3.0	30	-65 to +155	13.0	35
1N6076	50	50	1.3	6.0	30	-65 to +155	8.5	75
1N6077	100	100	1.3	6.0	30	-65 to +155	8.5	75
1N6078	150	150	1.3	6.0	30	-65 to +155	8.5	75
1N6079	50	50	2.0	12.0	30	-65 to +155	5.0	175
1N6080	100	100	2.0	12.0	30	-65 to +155	5.0	175
1N6081	150	150	2.0	12.0	30	-65 to +155	5.0	175

(1) Higher I_O rating is allowable provided that T_L and/or T_A is maintained such that $T_J \leq 155°C$.
(2) I_O rating without heat sinking, special mounting or forced air across the device body and/or leads.
(3) Derate I_O rating to zero current linearly, from T_A = +55°C, to +155°C.
(4) I_O and $R_{\theta JL}$ rating at L = 0 and without forced air across the device body and/or leads.
(5) Derate I_O rating to zero current linearly, from T_L = 70°C, to +155°C (see figures 4, 5 and 6).

* Comments, suggestions, or questions on this document should be addressed to Defense Supply Center, Columbus, ATTN: DSCC-VAC, P.O. Box 3990, Columbus, OH 43218-3990, or emailed to Semiconductor@dscc.dla.mil Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at http://assist.daps.dla.mil.

AMSC N/A FSC 5961

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

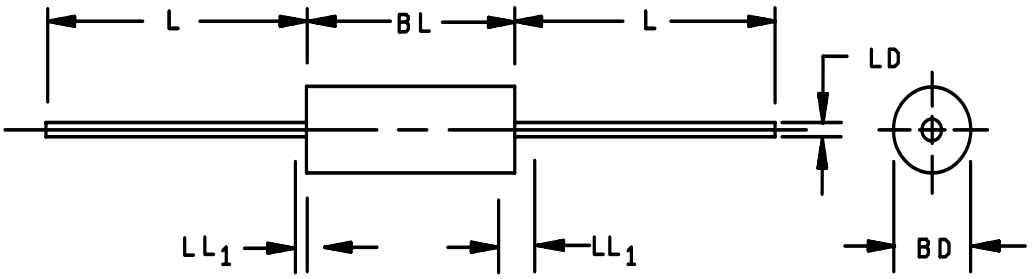


Symbol	Dimensions												Notes
	1N6073 THROUGH 1N6075				1N6076 through 1N6078				1N6079 through 1N6081				
	Inches		Millimeters		Inches		Millimeters		Inches		Millimeters		
	Min	Max	Min	Max	Min	Max	Min	Max	Min	Max	Min	Max	
BD	.055	.083	1.40	2.11	.065	.140	1.65	3.56	.135	.190	3.43	4.83	3
LD	.026	.033	0.66	0.84	.036	.042	0.91	1.07	.036	.042	0.91	1.07	
BL	.140	.225	3.56	5.72	.140	.225	3.56	5.72	.140	.225	3.56	5.72	
L	1.00	1.30	25.4	33.0	.90	1.30	22.90	33.0	.90	1.30	22.9	33.0	
LL_1		.03		0.8		.03		0.8		.03		0.8	4

NOTES:
1. Dimensions are in inches.
2. Millimeters are given for general information only.
3. Dimension BD shall be measured at the largest diameter.
4. The LL1 dimension shall include all uncontrolled areas of the device.
5. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

* FIGURE 1. Physical dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

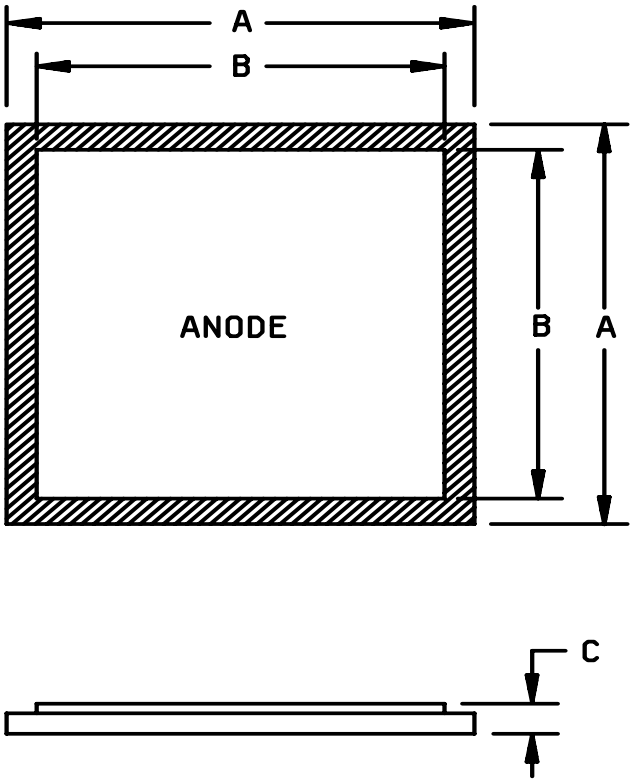

Symbol	Dimensions											
	1N6073 THROUGH 1N6075 (see note 3)				1N6076 through 1N6078 (see note 4)				1N6079 through 1N6081 (see note 4)			
	Inches		Millimeters		Inches		Millimeters		Inches		Millimeters	
	Min	Max	Min	Max	Min	Max	Min	Max	Min	Max	Min	Max
A	.039	.043	0.99	1.09	.066	.070	1.68	1.78	.128	.132	3.25	3.35
B	.031	.035	0.79	0.89	.057	.061	1.45	1.55	.119	.123	3.02	3.12
C	.008	.012	0.20	0.30	.008	.012	0.20	0.30	.008	.012	0.20	0.30

NOTES:
1. Dimensions are in inches.
2. Millimeters are given for general information only.
3. Anode thickness: AL - 45,000 Å minimum; cathode thickness: AU - 2500 Å minimum.
4. Anode thickness: AL - 60,000 Å minimum; cathode thickness: AU - 2500 Å minimum.
5. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

FIGURE 2. Physical dimensions, JANHC (A - version).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

* 2.1 General. The documents listed in this section are specified in sections 3, 4, or 5 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3, 4, or 5 of this specification, whether or not they are listed.

2.2 Government documents.

* 2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

* DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

* DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-750 - Test Methods for Semiconductor Devices.

* (Copies of these documents are available online at http://assist.daps.dla.mil/quicksearch/ or http://assist.daps.dla.mil.or from the Standardization Document Order Desk, 700 Robbins Avenue, Building 4D, Philadelphia, PA 19111-5094.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturer's list (QML) before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions shall be as specified in MIL-PRF-19500.

3.4 Interface and physical dimensions. The Interface and physical dimensions shall be as specified in MIL-PRF-19500, and figures 1 (similar to DO-35) and 2 (die) herein.

3.4.1 Lead finish. Lead finish shall be solderable as defined in MIL-PRF-19500, MIL-STD-750, and as specified herein. Where a choice of lead finish is desired, it shall be specified in the acquisition document (see 6.2).

* 3.5 Diode construction. These devices shall be constructed in a manner and using material which enable the diodes to meet the applicable requirements of MIL-PRF-19500 and this document. The diode shall be metallurgically bonded, non-cavity, double plug construction.

3.6 Marking. Marking shall be in accordance with MIL-PRF-19500. At the option of the manufacturer, the following marking may be omitted from the body of the diode, but shall be retained on the initial container.

3.5.1 Polarity. The polarity of all types shall be indicated with a contrasting color band to denote the cathode end.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4 and table I herein.

3.7 Electrical test requirements. The electrical test requirements shall be the subgroups specified in 4.4.2 and 4.4.3.

3.8 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3).

c. Conformance inspection (see 4.4).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500.

* 4.2.1 Group E qualification. Group E inspection shall be performed for qualification or re-qualification only. In case qualification was awarded to a prior revision of the specification sheet that did not request the performance of table II tests, the tests specified in table II herein that were not performed in the prior revision shall be performed on the first inspection lot of this revision to maintain qualification.

4.2.1 JANHC devices. Qualification for JANHC devices shall be in accordance with MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

* 4.3 Screening (JANTX and JANTXV levels). Screening shall be in accordance with table IV of MIL-PRF-19500, and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen (see table IV of MIL-PRF-19500)	JANTXV and JANTX Level
1a 1b	Not required Required (JANTXV only)
2	Not required
3a (1) 3c	Required Thermal impedance (see 4.3.1)
4	Not applicable
5	Not applicable
6	Not applicable
7a 7b	Not applicable Optional
8	Not required
9	Not applicable
10	T_A = 125°C
11	V_F and I_{R1}
12	Required See 4.3.2
(2) 13	Subgroup 2 of table I herein; ΔV_{F1} = 0.1V dc; ΔI_{R1} = (1) or 100 percent of the initial value, whichever is greater. Scope display evaluation (see 4.5.3).
14a 14b	Not applicable Required
15	Not required
16	Not required

(1) I_{R1} is as follows:
1N6073 through 1N6075 = +0.250 μA dc.
1N6076 through 1N6078 = +1.0 μA dc.
1N6079 through 1N6081 = +5.0 μA dc.

(2) $Z_{\theta JX}$ is not required in screen 13, if already previously performed.

* 4.3.1 Thermal impedance. Thermal impedance $Z_{\theta JX}$ measurements shall be performed in accordance with method 3101 of MIL-STD-750. The maximum limit for $Z_{\theta JX}$ in screening (table IV of MIL-PRF-19500) shall be derived by each vendor by means of statistical process control and applied in screening of all subsequent lots. For mounting conditions see figure 7. The following conditions shall apply:

a. I_H = 5 A minimum.

b. t_H = 10 ms.

c. I_M = 1 mA to 10 mA.

d. t_{MD} = 100 μs maximum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

* 4.3.1.1 For initial qualification and requalification. Read and record data ($Z_{\theta JX}$) shall be supplied to the qualifying activity on one lot (random sample of 500 devices minimum) prior to shipment. Twenty-two samples shall be serialized and provided to the qualifying activity for test correlation.

4.3.2 Power burn-in conditions. Power burn-in conditions are as follows: method 1038 of MIL-STD-750, T_A = +25°C (minimum); V_{RWM} = rated V_{RWM} (see 1.3); I_O = rated I_{O1} (see 1.3); f $\geq$ 60 Hz.

* 4.3.3 Screening (JANHC). Screening of die shall be in accordance with appendix H of MIL-PRF-19500. As a minimum, die shall be 100-percent probed to ensure compliance with table I, subgroup 2. Burn-in duration for the JANHC follows JANTX requirements.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with MIL-PRF-19500 and table I herein.

* 4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VIb (JAN, JANTX, and JANTXV) of MIL-PRF-19500. Electrical measurements (end-points) and delta requirements shall be in accordance with the applicable steps of table III herein.

* 4.4.2.2 Group B inspection, table VIb (JAN, JANTX, and JANTXV of MIL-PRF-19500).

	Subgroup	Method	Condition
*	B2	1056	Thermal shock, 0°C to +100°C, 10 cycles.
*	B2	1051	Temperature cycling, -55°C to +175°C, 25 cycles.
	B2	4066	I_{FSM} = rated I_{FSM} (see 1.3); 10 surges of 8.3 ms each at 1 minute intervals, super-imposed on I_{O1} (see 1.3); V_{RWM} = rated V_{RWM} (see 1.3).
*	B3	1027	$I_{O1(min)}$ = rated I_{O1} (see col. 4 of 1.3); adjust I_O to achieve the required T_J apply V_R = rated V_{RWM} (see 1.3), f = 50-60 Hz (see 4.3.1.1). Mounting conditions (see 4.5.5.1 and 4.5.5.2).
	B5	4081	+25°C $\leq T_R \leq$ 35°C; $R_{\theta JL}$ at L = 0 inches, (see col. 8 of 1.3).

* 4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VII of MIL-PRF-19500. Electrical measurements (end-points) and delta requirements shall be in accordance with the applicable steps of table III herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

* 4.4.3.1 Group C inspection, table VII of MIL-PRF-19500.

	Subgroup	Method	Condition
*	C2	1056	Thermal shock, 0°C to +100°C, 15 cycles.
*	C2	1051	Temperature cycling, -55°C to +175°C, 25 cycles.
	C2	2036	Tension test condition A, t = 15s, for 1N6073 through 1N6075 weight = 10 lbs, for 1N6076 through 1N6081, weight = 20 lbs.
*	C5	4081	+25°C ≤ T_A ≤ +35°C (recorded before test is performed); $R_{\theta JL}$ (maximum) (see col. 8 of 1.3; L = .375 inch (9.53 mm).
*	C6	1027	$I_{O1(min)}$ = rated I_{O1} (see col. 4 of 1.3); adjust I_O to achieve the required T_J apply V_R = rated V_{RWM} (see 1.3), f = 50-60 Hz (see 4.3.1.1). Mounting conditions (see 4.5.5.1 and 4.5.5.2).

* 4.4.4 Group E inspection. Group E inspection shall be conducted in accordance with the tests and conditions specified for subgroup testing in appendix E, table IX of MIL-PRF-19500 and as specified herein.

4.5 Methods of inspection. Methods of inspection shall be specified in the appropriate tables and as follows.

4.5.1 Pulse measurements. Conditions for pulse measurement shall be as specified in section 4 of MIL-STD-750.

4.5.2 Inspection conditions. Unless otherwise specified, all inspections shall be conducted at an ambient temperature T_A of +25°C ±3°C.

4.5.3 Scope display evaluation. The reverse breakdown characteristics shall be viewed on an oscilloscope with display calibration factors of 20 μA/division and 10 to 50 V/division. Reverse current over the knee shall be at least 100 μA. Each device may exhibit a sharp knee characteristic and any discontinuity or dynamic instability of the trace shall be cause for rejection.

4.5.4 Reverse-recovery time. The reverse recovery time shall be measured in the circuit of figure 3 or an equivalent circuit. The recovery conditions shall be 0.5 A forward current to 1.0 A reverse current. The reverse recovery time is defined as the time the rectifier begins to conduct in the reverse direction (crosses I = zero) until the reverse current decays to - 0.25 A. The point of contact on the leads shall be no less than .375 inch (9.52 mm) from the diode body.

* 4.5.5 Steady-state operation life. This test shall be conducted with a half-sine waveform of the specified peak voltage impressed across the diode in the reverse direction, followed by a half-sine waveform of the specified average rectified current. The forward conduction angle of the rectified current shall be no greater than 180 degrees nor less than 150 degrees. Mounting conditions (see Figure 8).

* 4.5.5.1 Alternate mounting conditions. At the option of the manufacturer, other clip or heat-sink mounting configurations may be used provided the I_O is adjusted such that each device junction temperature +125°C ≤ T_J ≤ +155°C at an ambient temperature +25°C ≤ T_A ≤ +55°C.

* 4.5.6 Peak reverse power test. A 20 microsecond half-sine waveform of current shall be used and peak reverse power shall be determined by the product of peak reverse voltage and peak reverse current. A 20 microsecond square waveform may also be used with the approval of the qualifying activity.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

* 4.5.7 Burn-in and life tests. These tests shall be conducted with a half-sine waveform of the specified peak voltage impressed across the diode in the reverse direction followed by a half-sine waveform of the specified average rectified current. The forward conduction angle of the rectified current shall be neither greater than 180 degrees, nor less than 150 degrees.

* 4.5.7.1 Free air burn-in. Deliberate heat sinking, baffles to create an oven, forced air-cooling or heating is prohibited unless otherwise approved by the qualifying activity. The use of a current limiting or ballast resistor is permitted provided that each DUT still sees the full P_t (minimum) and that the minimum applied voltage, where applicable, is maintained through out the burn-in period. T_J = 135°C minimum for screening and T_J = 150°C for 4.4.2 and 4.4.3 life tests.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

* TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 1						
Visual and mechanical examination	2071					
Subgroup 2						
Thermal impedance 2/	3101	See 4.3.1	$Z_{\theta JX}$			°C/W
Forward voltage	4011	Pulse width ≤ 8.3 ms and duty cycle ≤ 2 percent.	V_{F1}			
1N6073 thru 1N6075		I_{FM} = 9.4 A dc			2.04	V dc
1N6076 thru 1N6078		I_{FM} = 18.8 A dc			1.76	V dc
1N6079 thru 1N6081		I_{FM} = 37.7 A dc			1.50	V dc
Reverse current leakage	4016	DC method; V_R = rated V_R (see 1.3).	I_{R1}			
1N6073 thru 1N6075					1.0	µA dc
1N6076 thru 1N6078					5.0	µA dc
1N6079 thru 1N6081					10.0	µA dc
Breakdown voltage	4021	I_R = 100 µA dc	$V_{(BR)R}$			
1N6073 thru 1N6075				60		V dc
1N6076 thru 1N6078				110		V dc
1N6079 thru 1N6081				160		V dc
Subgroup 3						
High temperature operation:		T_A = +100°C				
Reverse current leakage	4016	DC method; V_R = rated V_R (see 1.3).	I_{R2}			
1N6073 thru 1N6075					50	µA dc
1N6076 thru 1N6078					100	µA dc
1N6079 thru 1N6081					500	µA dc
Subgroup 4						
Reverse recovery time		See 4.5.4 and figure 3.	t_{rr}		30	ns

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection – Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 4 – Continued						
Capacitance	4001	V_R = 12 V; f ≥ 100 KHZ V_{SIG} ≤ 200 mV (pk)	C_J			
1N6073 thru 1N6075					24	pF
1N6076 thru 1N6078					58	pF
1N6079 thru 1N6081					230	pF
Scope display evaluation	4023	See 4.5.3, n = 116, c = o.				
Subgroup 5						
Not applicable						
* Subgroup 6						
Forward surge	4066	I_{FSM} = rated (see 1.3); 10 surges of 8.3 ms each at 1 minute intervals superimposed on $I_O = I_{O2}$ rated (see 1.3); V_{RWM} = rated (see 1.3); T_A = + 25°C.				
Electrical measurements		See table III, steps 1, 2, 3 and 5.				
Subgroup 7						
Not applicable						

1/ For sampling plan, see MIL-PRF-19500.
2/ Not applicable to JANHC devices.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

* TABLE II. Group E inspection (all quality levels) for qualification only.

Inspection	MIL-STD-750		Sampling plan
	Method	Conditions	
Subgroup 1			45 devices c = 0
Temperature cycling (air to air)	1051	-65°C to +175°C, 500 cycles.	
Hermetic seal	1071		
Electrical measurement		See table III, steps 1, 2, 3, 4, and 5.	
Subgroup 2			22 devices c = 0
Blocking life	1048	t = 1,000 hours; T_A = +150°C; V_R dc = 80 - 85 percent rated V_{RWM} (see 1.3.2)	
Electrical measurement		See table III, steps 1, 2, 3, 4, 5, and 6.	
Subgroup 4			N/A
Thermal impedance curves		Each supplier shall submit their qual-lot average and design thermal impedance curves to the qualifying activity. In addition, the optimal test conditions and $Z_{\theta JX}$ limit shall be provided to the qualifying activity in the qualification report.	
Subgroup 5			
Not applicable			
Subgroup 8			
Peak reverse power		See 4.5.6 and figure 8 herein. Peak reverse power, (P_{RM})= shall be characterized by the supplier and this data shall be available to the Government. Test shall be performed on each sublot.	
Electrical measurement		During the P_{RM} test, the voltage (V_{BR}) shall be monitored to verify it has not collapsed. Any collapse in V_{BR} during or after the P_{RM} test or rise in leakage current (I_R) after the test that exceeds I_{R1} in table I shall be considered a failure to that level of applied P_{RM}. Progressively higher levels of P_{RM} shall be applied until failure occurs on all devices within the chosen sample size to characterize each sublot.	
Subgroup 9			n = 45
Resistance to glass cracking	1057	Step stress to destruction by increasing cycles or up to a maximum of 25 cycles.	
Subgroup 10			22 devices c = 0
Forward surge	4066	Condition A, I_{FSM} = rated (see 1.3); 10 surges of 8.3 ms each at 1 minute intervals superimposed on I_O = I_{O2} rated (see 1.3); V_{RWM} = rated (see 1.3.2); T_A = + 25°C.	
Electrical measurement		See table III, steps 1, 2, 3, 4, and 5.	

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

* TABLE III. Groups A, B and C electrical measurements. 1/ 2/ 3/

Step	Inspection	MIL-STD-750		Symbol	Limits		Unit
		Method	Conditions		Min	Max	
1.	Forward voltage	4011	Pulse width ≤ 8.3 ms and duty cycle ≤ 2 percent.	V_F			
	1N6073 thru 1N6075		I_{FM} = 9.4 A dc			2.04	V dc
	1N6076 thru 1N6078		I_{FM} = 18.8 A dc			1.76	V dc
	1N6079 thru 1N6081		I_{FM} = 37.7 A dc			1.50	V dc
2.	Reverse current	4016	DC method, V_R = rated V_R (see 1.3).	I_R			
	1N6073 thru 1N6075					1.0	μA dc
	1N6076 thru 1N6078					5.0	μA dc
	1N6079 thru 1N6081					10.0	μA dc
3.	Reverse current	4016	DC method, V_R = rated V_R (see 1.3).	ΔI_R		4/	
	1N6073 thru 1N6075					.250	μA dc
	1N6076 thru 1N6078					1.0	μA dc
	1N6079 thru 1N6081					5.0	μA dc
4.	Breakdown voltage	4021	I_R = 100 μA dc	$V_{(BR)R}$			
	1N6073, 1N6076, 1N6079				60		V dc
	1N6074, 1N6077, 1N6080				110		V dc
	1N6075, 1N6078, 1N6081				160		V dc
5.	Forward voltage	4011	Pulse width ≤ 8.3 ms and duty cycle ≤ 2 percent.	ΔV_F			V dc
	1N6073 thru 1N6075		I_{FM} = 9.4 A dc			± 0.1 V dc maximum change from the previous measured value.	
	1N6076 thru 1N6078		I_{FM} = 18.8 A dc				
	1N6079 thru 1N6081		I_{FM} = 37.7 A dc				
6.	Thermal impedance	3101		$Z_{\theta JX}$		See 4.3.1	

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

* TABLE III. Groups A, B and C electrical measurements 1/ 2/ 3/ - Continued.


1/ The electrical measurements for table VIb (JAN, JANTX, and JANTXV) of MIL-PRF-19500 are as follows:
   a. Subgroup 2, see table II herein, steps 1 and 2.
   b. Subgroup 3, see table II herein, steps 1, 2, 3, and 5.
   c. Subgroup 6, see table II herein, steps 1, 2, 3, and 5.

2/ The electrical measurements for table VII of MIL-PRF-19500 are as follows:
   a. Subgroup 2, see table II herein, steps 1 and 2.
   b. Subgroup 3, see table II herein, steps 1 and 2.
   c. Subgroup 6, see table II herein, steps 1, 2, 3, and 5.


3/ electrical measurements for table IX of MIL-PRF-19500 are as follows:
   a. Subgroup 2, see table II herein, steps 1, 2, 3, 4, and 5.
   b. Subgroup 3, see table II herein, steps 1, 2, 3, 4, 5, and 6.
   c. Subgroup 6, see table II herein, steps 1, 2, 3, 4, and 5.

4/ Rated I_R or 100 percent, whichever is greater.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

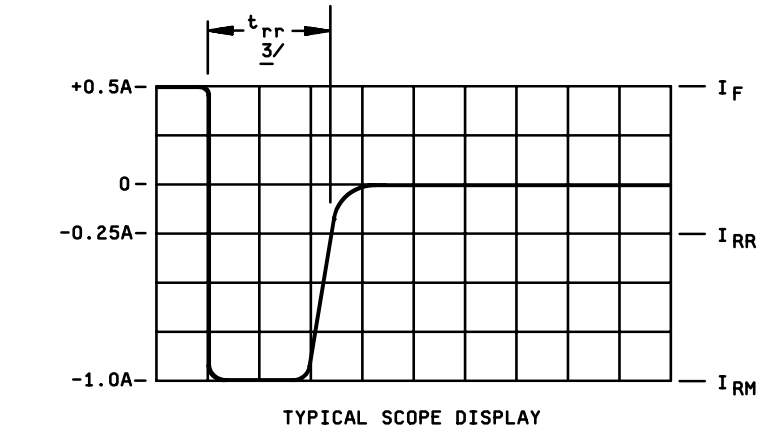

TYPICAL SCOPE DISPLAY

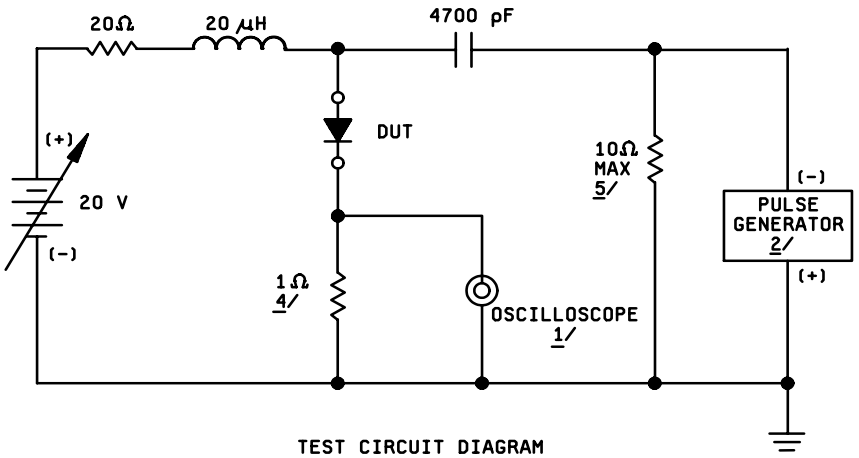


TEST CIRCUIT DIAGRAM

NOTES:

1/ Rise time ≤ 350 ps, input impedance 50 ohms, circuit impedance 50 ohms coaxial.
2/ Rise time ≤ 250 ps, source impedance = 8 ohms maximum, PRF ≈ 0.5 kHz, P_W ≥ 40 ns.
3/ Recovery conditions: 0.5 A forward current to 1.0 A reverse current. Recovery time measured when rectifier recovers to 0.25 A.
4/ Constructed from 10-10 ohm resistors 1/8 watt.
5/ Constructed from 10-100 ohm resistors 1/8 watt.

FIGURE 3. Reverse recovery time test circuit and characteristic waveform.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

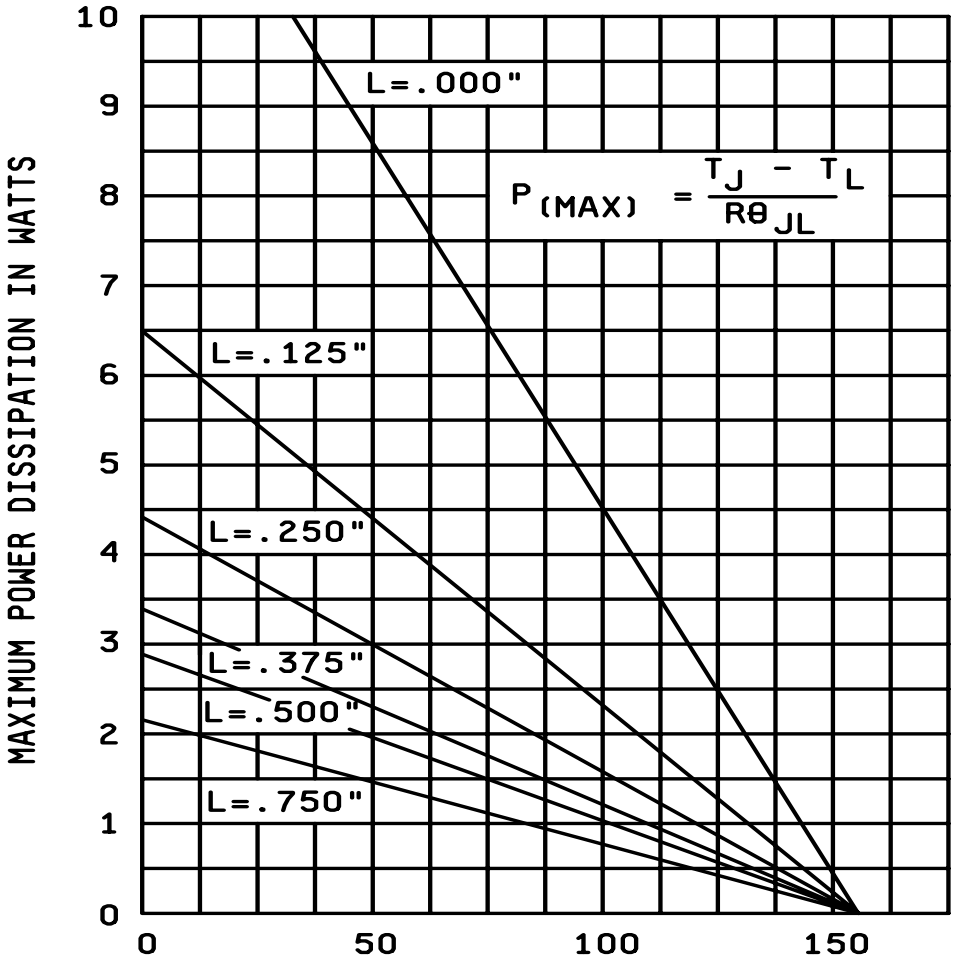


Maximum lead temperature in °C (T_L at point d from body (see table below).
For maximum operating junction temperature with equal two-lead conditions.

L	$R_{\theta J-L}$
Dimensions	°C/W
.000 (0.00 mm)	13
.125 (3.18 mm)	24
.250 (6.35 mm)	35
.375 (9.52 mm)	46
.500 (12.7 mm)	54
.750 (19.1 mm)	70

FIGURE 4. Power derating curves maximum power in watts vs lead temperature for 1N6073, 1N6074, and 1N6075.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

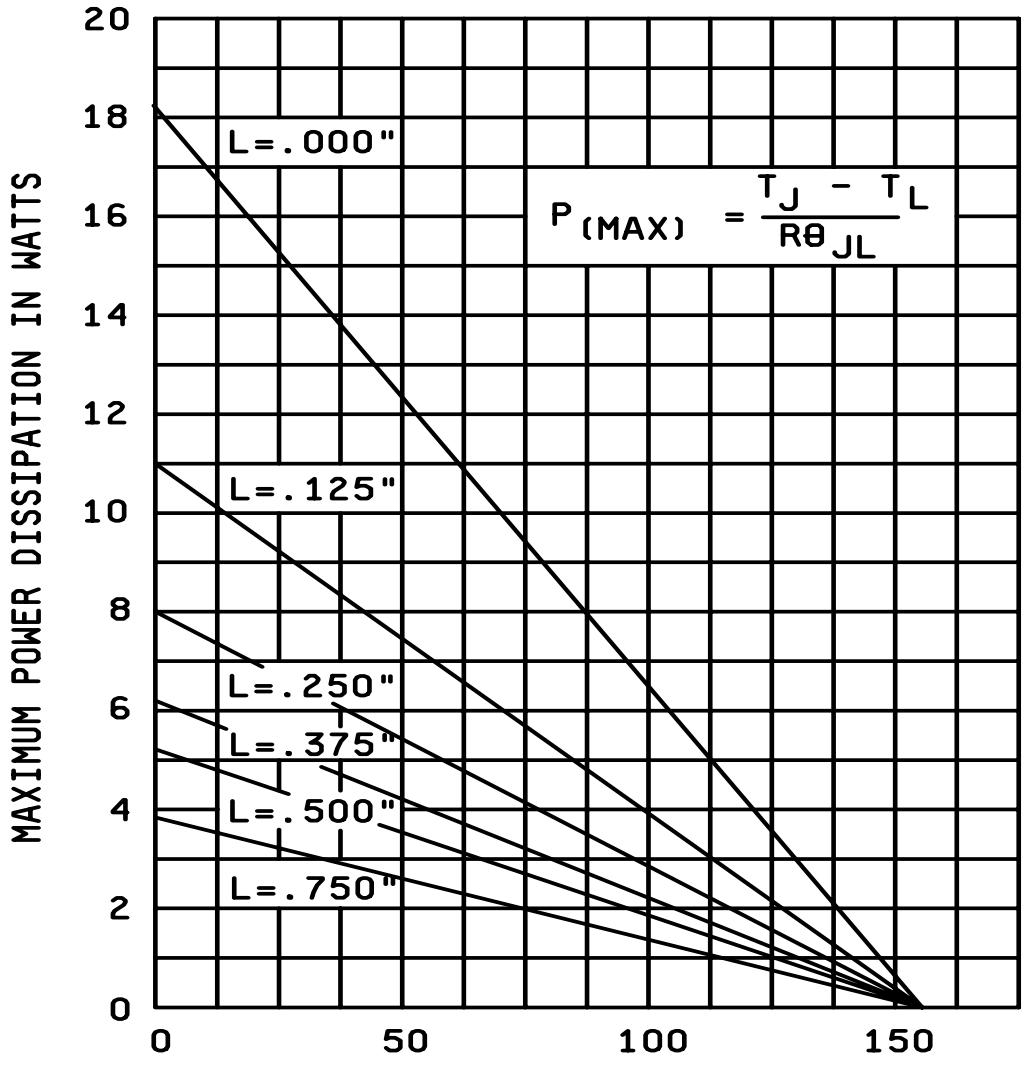


Maximum lead temperature in °C (T_L at point d from body (see table below).
For maximum operating junction temperature with equal two-lead conditions.

L	$R_{\theta J-L}$
Dimensions	°C/W
.000 (0.00 mm)	8.5
.125 (3.18 mm)	14.0
.250 (6.35 mm)	19.5
.375 (9.52 mm)	25.0
.500 (12.7 mm)	30.0
.750 (19.1 mm)	40.0

FIGURE 5. Power derating curves maximum power in watts vs lead temperature for 1N6076, 1N6077, and 1N6078.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

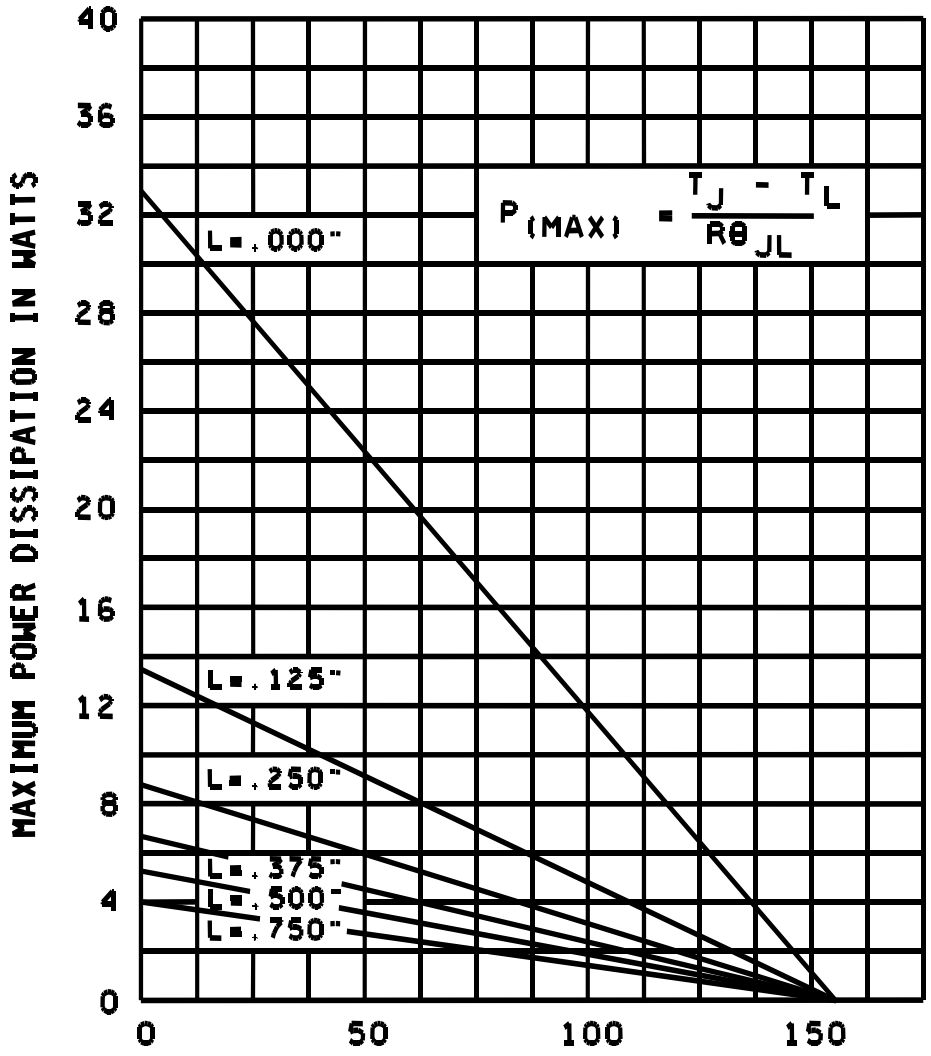


Maximum lead temperature in °C (T_L at point d from body (see table below).
For maximum operating junction temperature with equal two-lead conditions.

L	$R_{\theta J-L}$
Dimensions	°C/W
.000 (0.00 mm)	5.0
.125 (3.18 mm)	11.5
.250 (6.35 mm)	17.5
.375 (9.52 mm)	23.5
.500 (12.7 mm)	29.0
.750 (19.1 mm)	40.0


FIGURE 6. Power derating curves maximum power in watts vs lead temperature for 1N6079, 1N6080, and 1N6081.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

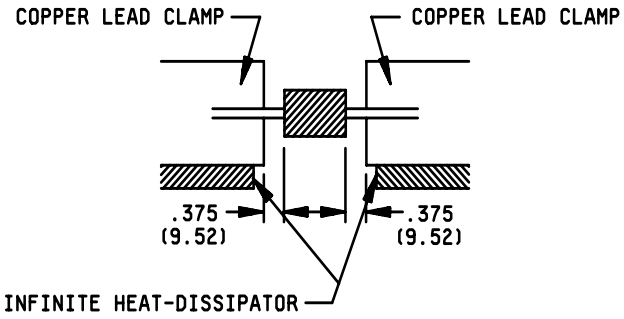


* FIGURE 7. Mounting arrangement.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

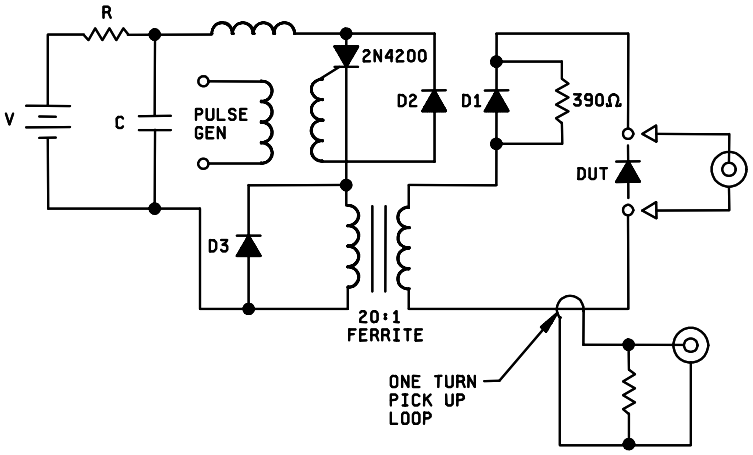

NOTES:
L = 13T H22 on 1 inch (25.4 mm) diameter form (air core).
C ≈ 1 to 10 μf to give 20 μs pulse width.
V - Adjustable to 200 volts for power desired in DUT.
D1 - 3 kV; 600 mA (1N3647 or equivalent).
D2, D3 - 600 V; 3A (1N5552 or equivalent).
* Values not stated are determined at the time of test.

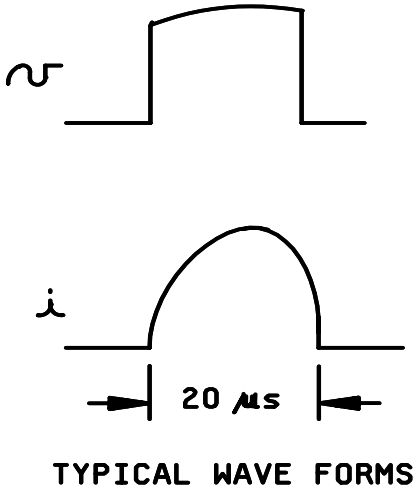

TYPICAL WAVE FORMS

FIGURE 8. Peak reverse power measurement circuit and waveform.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

5. PACKAGING

* 5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When actual packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the Military Service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The notes specified in MIL-PRF-19500 are applicable to this specification.

* 6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Packaging requirements (see 5.1).

c. Lead finish (see 3.4.1).

d. Product assurance level and type designator.

* 6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List (QML 19500) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Defense Supply Center, Columbus, ATTN: DSCC/VQE, P.O. Box 3990, Columbus, OH 43218-3990 or e-mail vqe.chief@dla.mil.

6.4 Thermal impedance. Device power capability with lead dissipators or body forced air cooling, may be determined from figures 3, 4, and 5, which shows maximum power dissipation in watts versus lead temperature in °C as a function of the distance "L" from the diode body at which lead temperature is measured.

6.5 Suppliers of JANHC die. The qualified JANHC suppliers with the applicable letter version (example, JANHCA1N6073) will be identified on the QPL.

JANHC ordering information	
PIN	Manufacturer
	33178
1N6073 through 1N6081	JANHCA1N6073 through JANHCA1N6081

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.

6.6 Changes from previous issue. The margins of this specification are marked with asterisks to indicate where changes from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

Custodians:
Army - CR
Navy - EC
Air Force - 11
DLA - CC

Preparing activity:
DLA - CC

(Project 5961-2887)

Review activities:
Air Force - 99

* NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at http://assist.daps.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T02:31Z
Check the source to verify that this is the current version before use.